

33132
33132
33132
33132

CLEARINGHOUSE FOR FEDERAL SCIENTIFIC AND TECHNICAL INFORMATION	
Hardcopy	Microfiche
\$ 2.00	\$ 0.50
52 pp	
ARCHIVE COPY	

Code 1

COPY NO. 13



TECHNICAL REPORT 3364

COMPARISON OF MECHANICALLY
BALLED MAGNESIUM WITH ATOMIZED
MAGNESIUM FOR USE IN
PYROTECHNIC COMPOSITIONS

JAMES A. CARRAZZA, JR.

DORIS E. MIDDLEBROOKS

SEYMOUR M. KAYE

SEPTEMBER 1966

DISTRIBUTION OF THIS DOCUMENT IS UNLIMITED

PICATINNY ARSENAL
DOVER, NEW JERSEY

Technical Report 3364

COMPARISON OF MECHANICALLY BALLED MAGNESIUM
WITH ATOMIZED MAGNESIUM FOR USE IN
PYROTECHNIC COMPOSITIONS

by

James A. Carrazza, Jr.
Doris E. Middlebrooks
Seymour M. Kaye

September 1966

AMCMS Code 5523.11.558
Dept of the Army Project 504-01-207

Distribution of this document is unlimited

Pyrotechnics Laboratory
Feltman Research Laboratories
Picatinny Arsenal
Dover, N. J.

The citation in this report of the trade names of commercially available products does not constitute official indorsement or approval of the use of such products.

TABLE OF CONTENTS

	Page
Object	1
Summary	1
Conclusions and Recommendations	1
Introduction	3
Results	4
Discussion of Results	5
Microscopic Examination	5
Particle Size Distribution	6
Average Particle Size	6
Apparent and Tapped Densities	6
Absolute Densities	7
Chemical Analysis	8
Moisture Content	8
Reactivity with Moisture	8
Surface Area Measurements	11
Thermochemical Analysis	12
Sensitivity	13
Performance Characteristics	13
Experimental Procedure	14
Testing	14
Materials	15
Preparation of Blends	15
Loading	15
Luminous Intensity Testing	16
References	16
Distribution List	44
Tables	
1	Sieve analysis of balled and atomized (30/50 mesh) magnesium as compared to specification requirement 18
2	Microscopic count particle size distribution of balled and atomized magnesium 19

		Page
Tables		
3	Average particle diameter of balled and atomized magnesium	20
4	Apparent and tapped densities of balled and atomized magnesium	20
5	Absolute density of balled and atomized magnesium after ambient and 70% relative humidity storage for 30 days	21
6	Chemical analysis (%) of balled and atomized magnesium as compared to specification requirements	21
7	Percentage moisture as determined by Electroynamics moisture analyzer	22
8	Percent weight gain of balled and atomized magnesium fractions after exposure to 30%, 50%, and 70% relative humidities	23
9	Reactivity with water	24
10	Vacuum stability of balled and atomized magnesium during thirty days storage	25
11	Effects of high relative humidity (70%) on specific surface area (cm^2/g) of balled and atomized magnesium	26
12	Performance characteristics of compositions containing balled and atomized magnesium, Test I	27
13	Performance characteristics of compositions containing balled and atomized magnesium, Test II	28
14	Performance characteristics of compositions containing balled and atomized magnesium, Test III	29
Figures		
1	Photomicrographs of powdered atomized magnesium at 35 \times magnification	30
2	Cross-sectional photomicrograph of typical balled and atomized magnesium particles at 75 \times magnification	32

		Page
Figures		
3	Photomicrograph of typical single balled and atomized magnesium particles at 75 × magnification	33
4	Photomicrographs of powdered balled magnesium at 35 × magnification	34
5	Percent weight gain at 70% relative humidity 30°C of balled and atomized magnesium	36
6	Reactivity with water at room temperature of balled and atomized magnesium	37
7	Reactivity with water at 76°C (167°F) of balled and atomized magnesium	38
8	Vacuum stability at 76°C of balled and atomized magnesium	39
9	Vacuum stability at 110°C of balled and atomized magnesium	40
10	Differential thermal analysis of pyrotechnic composition prepared with atomized magnesium	41
11	Differential thermal analysis of pyrotechnic composition prepared with balled magnesium	42
12	Typical luminous intensity vs time traces of compositions containing atomized and balled magnesium	43

OBJECT

To evaluate mechanically balled magnesium for use in pyrotechnic compositions as an alternate for the atomized magnesium currently required by Military Specification MIL-P-14067A, "Powders, Metals, Atomized (For Use in Ammunition)."

SUMMARY

Results of a variety of physical and chemical tests indicate that, with a few minor exceptions, Reade (balled) magnesium meets the requirements of Military Specification 14067-A for 30/50 mesh magnesium powder. The balled magnesium has been found to be less reactive than the currently prescribed atomized magnesium, both with water and as a result of exposure to high relative humidities, as determined by gas evolution, weight gain, and surface area measurements. Results of vacuum stability tests at 167°F and 230°F for thirty days indicate that the balled magnesium has greater stability than atomized magnesium; the thermochemical and sensitivity data for balled magnesium and atomized magnesium are comparable. In performance characteristics such as candlepower, burning rate, and luminous efficiency, similar results were obtained with the two materials. These results indicate that the Reade balled magnesium can be used as an alternate for Valley atomized 30/50 mesh magnesium in consolidated pyrotechnic compositions.

CONCLUSIONS AND RECOMMENDATIONS

Although the data derived in this study is based on an evaluation of samples from only one lot each of the balled and the atomized magnesium, the evaluation has resulted in the following conclusions. The balled magnesium essentially meets all the specification requirements for 30/50 mesh magnesium powder with the exception of the method of manufacture. The results of various reactivity tests indicate that it is less reactive than the atomized magnesium and has greater stability at elevated temperatures. No significant differences were found in the thermochemical analyses, heat of combustion determinations or reaction with water tests, and, according to Wilkaiets (Ref 4), the two types of magnesium have comparable sensitivity values when incorporated with an oxidant. Finally, the performance characteristics of a typical pyrotechnic flare composition containing the balled magnesium compare favorably with those of a like composition containing atomized magnesium.

Test results indicate that balled magnesium can be used as an alternate for 30/50 mesh atomized magnesium in consolidated pyrotechnic composition.

It is recommended that the current Military Specification (14067A, Ref 1) be amended to include the use of balled magnesium as an alternate for atomized in the 30/50 mesh size.

It is further recommended that a program be initiated to evaluate the effects of long term high temperature storage on consolidated pyrotechnic compositions employing both balled and atomized magnesium blended with sodium nitrate and with other oxidants used in colored flare formulations.

INTRODUCTION

The current military specification (Ref 1) prescribes the use of atomized magnesium powder in ordnance applications. The term "atomized" means that the molten magnesium is dispersed into a spray, the droplets of which are allowed to solidify into spheres in a helium atmosphere under the primary influence of surface tension and are then classified to the applicable granulation. This requirement for spherical material, dating back to June 1949 in earlier versions of the above specification, was based on results of previous investigations in which compositions containing atomized magnesium were compared with compositions containing ground magnesium (JAN-M-382, Ref 2). These findings, as reported by Hart (Ref 3), revealed that ground magnesium has greater sensitivity, lower ignition temperatures, and greater reactivity than the currently prescribed atomized magnesium. Atomized magnesium is currently being produced by only one manufacturer, and therefore the present supply is quite limited.

Another method exists for the production of powdered magnesium. It consists of mechanically ball-milling irregularly chipped pieces of magnesium ingots, under an inert atmosphere, into spheres which are then screened to the applicable granulation. This balled magnesium, is currently being produced in quantity only in a granulation comparable to 30/50 mesh (350 ± 50 microns) atomized magnesium.

Mechanically balled magnesium in this granulation currently costs approximately \$0.13 less per pound than atomized magnesium. The advantages of lower cost and also diversity in choice of manufacturers have made it mandatory that balled magnesium be evaluated as a possible alternate for atomized magnesium in pyrotechnic compositions.

Accordingly, a program was initiated to determine the physical and chemical properties of balled magnesium. This program was oriented to include comparisons of balled and atomized magnesium in terms of purity, moisture content, heat of combustion, vacuum stability, particle size distribution, particle shape and surface characteristics, density, surface area, and internal structure, as well as reactivity with moisture. Following these tests, a typical yellow flare composition was prepared and consolidated with both types of magnesium powder for evaluation of their performance characteristics.

Results of a study conducted by Olin Mathieson Chemical Corporation (Ref 4) indicated that both the atomized and the balled magnesium meet

the 30/50 mesh magnesium specification requirements for chemical analysis and distribution by sieve analysis. An investigation of the performance characteristics of a typical yellow composition in illuminant assemblies for the M301A2 81 mm illuminating projectile also gave comparable results for the two materials.

RESULTS

Photomicrographs of the various magnesium fractions at 35 x magnification and of single and cross sectioned particles at 75 x magnification are shown in Figures 1 through 4 (pp 30 through 35).

Results of sieve analyses of balled and atomized magnesium are compared to specification requirement in Table 1 (p 19) and the particle size distributions of the total samples and sieve fractions as determined by microscopic count, are shown in Table 2 (p 19).

The average particle size, as determined by air permeability, for the total samples and the sieve fractions of both the atomized and the balled magnesium are shown in Table 3 (p 20).

A comparison of the tapped and apparent densities of balled and atomized magnesium samples is made in Table 4 (p 20). Absolute density values for both types of magnesium samples, as determined before and after exposure to 70% relative humidity, are given in Table 5 (p 21).

Table 6 (p 21) compares the chemical analyses of the balled and atomized magnesiums with the specification requirement.

Moisture content data for the balled and atomized magnesium samples, as determined on the Electro-dynamics moisture analyzer, is shown in Table 7 (p 22).

Hygroscopicity values for the balled and atomized magnesium samples, as determined by percent weight gain at 30, 50, and 70% relative humidity, are shown in Table 8 (p 23). Figure 5 (p 36) shows the percent weight gain at 70% relative humidity.

Reactivity with water as determined by gas evolution as a function of time at room temperature (approximately 25°C) and 167°F (76°C) is indicated in Table 9 (p 24) and Figures 6 and 7 (pp 37 and 38). Gas evolution as

determined by the vacuum stability test for thirty days at 167°F (76°C) and 230°F (110°C) is shown in Table 10 (p 25) and Figures 8 and 8 (pp 39 and 40).

Table 11 (p 26) gives specific surface area measurements for the various magnesium fractions as determined by the MIC-103 Numinco-Orr surface area pore volume analyzer before and after exposure to an atmosphere of 70% relative humidity.

Tables 12, 13, and 14 (pp 27, 28, and 29) compare the performance characteristics of samples of a typical consolidated pyrotechnic composition containing balled and atomized magnesium.

Differential thermal analysis curves for compositions prepared with the balled and atomized magnesiums are shown in Figures 10 and 11 and typical time-intensity traces for the same compositions is given in Table 13.

DISCUSSION OF RESULTS

One drum of 30/50 mesh magnesium powder from each manufacturer was selected for test. The drums used were identified as (1) Reade Manufacturing Company, 30/50 mesh magnesium powder, RMC-305, Drum 32, and (2) Valley Metallurgical Processing Company, 30/50 mesh magnesium powder, atomized, Contract DA-28-017-A-5-08365A, Drum 14. The Reade material was mechanically balled magnesium powder, while the Valley magnesium was atomized in accordance with Military Specification MIL-P-14067A.

Microscopic Examination

Results of microscopic examination as presented in Figure 1 (p 30) show some degree of deviation from sphericity for the atomized magnesium. Indentations or cavities appear regularly in each of the fractions studied and are revealed in the cross sectional and single particle photomicrograph at 75 × magnification (Figs 2 and 3, pp 32 and 33). Deviations from the spheroidal shape normally exhibited by balled magnesium are also apparent. These deviations (see Fig 4, p 34) increase with decreasing particle size while particle elongation becomes more apparent. No cavities are evident in the cross sectional photomicrograph; however, an irregular roughness of the surface, which is probably due to the method of manufacture, is apparent (Figs 2 and 3).

Particle Size Distribution

The particle size distributions were determined by sieve analyses of thieved samples of both materials, in accordance with the procedure detailed in MIL-P-14057A (Ref 1). The results (Table 1) indicate that both materials meet the specification requirements, the atomized magnesium containing coarse and fine fractions which are substantially absent in the balled magnesium. The size distribution of the atomized material is thus significantly wider (10% at the coarse end and 15% at the fine end) than that of the balled magnesium.

Particle size distributions by microscopic count (Ref 5) were conducted on the original materials as well as on 20/30, 30/40, 40/50, and 50/60 sieve fractions to determine whether differences exist within these fractions which may effect the performance characteristics. The results (Table 2) show a fair similarity between the averages (geometric means) and the ranges for the two materials in the original (30/50) mesh size and the coarsest (20/30) fraction. This comparability becomes poorer with decreasing particle size, the balled magnesium being larger. This difference can be attributed to the elongated shape or the greater deviation from the spheroidal shape which increases with decreasing particle size, as the photomicrographs (Fig 4) of the balled magnesium particles indicate.

Average Particle Size

The average particle diameter of the original materials and of all of their fractions was determined using the Picatinny Arsenal particle sizer (Ref 5). The results indicate (Table 3) that the two types of magnesium have closely similar average particle diameters in all fractions tested. MIL-P-14067A requires that the 30/50 magnesium have an average particle size, determined by air permeability, falling within the 350 ± 50 -micron range. The original balled material exceeded the upper limit by 4 microns, which is not considered significant, as it falls within experimental error.

Apparent and Tapped Densities

Apparent and tapped density tests were performed on both the original magnesium samples and the fractions sieved from them. The apparent densities were determined in accordance with the procedure described in MIL-P-14067A (Ref 1), and the tapped densities by the procedure detailed in the Pyrotechnics Laboratory Handbook of Particle Size Procedures (Ref 5).

The results (Table 4) indicate that both the apparent and tapped density values for the atomized fractions are slightly higher than those obtained with the balled fractions. MIL-P-14067A specified a minimum apparent density of 1.0 g/ml for the 30/50 mesh material. The original balled 30/50 mesh magnesium is 0.98 g/ml, or 0.02 g/ml below the requirement, which may be due either to the elongated shape or to experimental error. Kristal (Ref 6) has reported that apparent density values as low as 0.95 g/ml should be considered acceptable.

Absolute Densities

Absolute densities were determined for all test samples both after storage under ambient conditions and after storage at high relative humidity (70% relative humidity for 30 days).

These measurements, not required by the specification, were made for two reasons: (1) to determine the amount of oxide or hydroxide coating on the original materials, and (2) to determine the reactivity of each sample with moisture in the air. Since the density of magnesium oxide (3.58 g/ml) and also that of magnesium hydroxide (2.38 g/ml) are greater than that of magnesium (1.74 g/ml), the absolute density values would be a true measure of the amount of oxide or hydroxide present. The absolute density measurements were made by pycnometer at 25°C using acetone, A.C.S. grade (Ref 7).

The results (Table 5) reveal that, after ambient storage, the balled and atomized magnesium samples have closely similar absolute density values, such slight differences as exist being attributable to experimental error. Since the values obtained are not above the absolute density value of magnesium (1.74 g/ml) the amount of oxide or hydroxide coating cannot be determined.

After storage at 70% relative humidity for 30 days, the balled magnesium showed essentially no change in absolute density, indicating that it does not react with moisture. The atomized magnesium, however, showed an increase, particularly marked in the 20/30 fraction, indicating greater reactivity with moisture than had been shown by the balled samples. This greater reactivity was also indicated by a less metallic appearance and by a grey discoloration evident in all sieve fractions but most marked in the 20/30 mesh fraction.

The greater reactivity of the atomized samples is attributed to the presence of cavities, which are evident in the photomicrographs (Figs 1, 2, and 3).

Although reactivity is evident in the atomized material after storage at 70% relative humidity, the true amount of oxide or hydroxide present could not be determined from the values obtained.

Chemical Analysis


A chemical analysis (Ref 8) was conducted on the original samples of balled and atomized magnesium powders in accordance with MIL-P-14067A. The results (Table 6) indicate that both the balled and the atomized powders are well within the specification requirement for 30/50 mesh. Since the method of production of the balled magnesium is mechanical, an analysis for grease and/or oil content was also conducted. No measurable quantity of grease or oil was found in either the balled or atomized samples (Table 6 and Ref 9).

Moisture Content

Both the balled and the atomized magnesium samples meet the specification requirement for total volatile content. However, moisture content was also determined electrolytically using the Consolidated Electroynamics moisture analyzer on the the original materials as received as well as on the 20/30, 30/40, 40/50, and 50/60 sieve fractions. The data obtained (Ref 10 and Table 7) indicates that the balled magnesium has a greater moisture content than the atomized magnesium. No correlation was found between this data and the data on total volatiles as determined in the chemical analysis (Table 6), which should include any moisture content.

Reactivity with Moisture

The reactivity of the magnesium with moisture is an important parameter since minute amounts of water are inadvertently incorporated in magnesium-fueled flares and signals because of moisture content or hygroscopicity of ingredients. This moisture can react with the magnesium on storage, both degrading the magnesium to its hydroxide and releasing gases which are capable of building up pressure sufficient to burst hermetically sealed containers, as is indicated by the work of H. Eppig (Ref 11) and the following equation:



Accordingly, a study was undertaken to determine the relative reactivity of balled and atomized magnesium with moisture.

The first phase of the study consisted of exposing the original 30/50 mesh materials and their respective sieve fractions to 30%, 50%, and 70% relative humidities at 30°C, and determining the percentage weight increase as a function of time for up to 31 days of exposure. The weight increases would be a result of magnesium hydroxide formation or a measure of reactivity. The data (see Table 8 and Ref 12) indicates that both the balled and the atomized samples are essentially nonreactive, with maximum weight increases of only 0.01% after 31 days at 30% relative humidity. Under 50% relative humidity conditions, the atomized samples showed increased reactivity, the weight increase being particularly marked for the 20/30 mesh fraction. Under 70% relative humidity conditions, all of the atomized fractions show marked weight increases compared with like balled fractions, the atomized 20/30 mesh fraction being particularly reactive.

A comparison of the percent weight gain of the different fractions at the various relative humidity levels after thirty-one days of 30°C exposure follows:

	Relative Humidity, %		
	30	50	70
Balled Magnesium			
Total samples (30/50 mesh)	0	*	0.04
20/30 mesh	0	0.01	0.01
30/40 mesh	0	*	0.02**
40/50 mesh	0	0.01	0.06
50/60 mesh	*	0	0.04
Atomized Magnesium			
Total samples (30/50 mesh)	0	0.01	0.16
20/30 mesh	0	0.07	0.60
30/40 mesh	0.01	0.01	0.12
40/50 mesh	*	*	0.07
50/60 mesh	0.01	0.01	0.07

* Loss in weight.

**25th day value.

It is interesting to note that the atomized 20/30 mesh fraction also had a density value of 1.99 g/ml after 31 days of conditioning at 70% relative humidity (see Table 5). This density value was far greater than those obtained for the other atomized or balled fractions stored under identical relative humidity conditions, and reflects increased formation of magnesium hydroxide, which is indicative of increased reactivity.

A second phase of this study was to determine the degree of reactivity of the magnesium fractions with water by measuring the amount of gas evolved. The results (Table 9, Figs 6 and 7, and Ref 13) indicate that the atomized magnesium is more reactive than the balled. At 167°F (76°C), all atomized samples exceeded the capacity of the apparatus (producing 11 ml of gas within a 2-hour interval). The balled magnesium samples did not reach this limit until after 16 hours had elapsed. At room temperature, all atomized magnesium samples yielded 11 ml of gas in the first 16 hours. The balled magnesium, however, required much longer periods ranging from 12 days for the 20/30 sieve fraction to 27 days for the 30/40 sieve fraction to produce 11 ml of gas. The total time required for each of the fractions to yield 11 ml of gas is shown in the following table:

	Reaction Time for Evolution of 11 ml of Gas, hr	
	Room Temperature (25°C)	76°C
Balled Magnesium		
Total samples (30/50 mesh)	480	16
20/30 mesh	288	16
30/40 mesh	648	16
40/50 mesh	472	16
50/60 mesh	480	16
Atomized Magnesium		
Total samples (30/50 mesh)	16	1
20/30 mesh	16	1
30/40 mesh	16	2
40/50 mesh	16	1.5
50/60 mesh	16	1.5

The third and final phase of the reactivity study consisted of gas evolution determinations for samples that had been stored at elevated temperatures. This was accomplished by using the standard vacuum stability apparatus and method as

described by Clear (Ref 14). The samples were kept under surveillance for thirty days at temperatures of 167°F and 230°F. The results, (Table 10, Figs 8 and 9, and Ref 13) indicate that the balled magnesium samples evolve significantly less gas than the atomized samples as a function of time at elevated temperatures. The gases evolved can be attributed to entrapment of gases during the manufacturing process, and/or to entrapment of moisture not removed by desiccant drying or decomposition of a hydroxide film on the surface of the magnesium. The results at the conclusion of the 30-day surveillance period were as follows:

30-Day Vacuum Stability Results
MI Gas at 165°F MI Gas at 230°F

Balled Magnesium

Total samples (30/50 mesh)	0.07	0.17
20/30 mesh	0.07	0.20
30/40 mesh	0.06	0.20
40/50 mesh	0.06	0.20
50/60 mesh	0.10	0.17

Atomized Magnesium

Total samples (30/50 mesh)	0.33	0.58
20/30 mesh	0.70	0.62
30/40 mesh	0.46	0.63
40/50 mesh	0.36	0.66
50/60 mesh	0.18	0.54

Surface Area Measurements

Surface area measurements were conducted on the total sample (30/50 mesh) and on 20/30, 30/40, 40/50, and 50/60 sieve fractions of both balled and atomized magnesium before and after exposure to 70% relative humidity for 30 days. The purpose of obtaining these measurements was to compare the specific surface areas of the two types of magnesium and to determine the effects of moisture on the surface areas. The results (Table 11 and Ref 15) indicate that the total (30/50 mesh) sample of atomized magnesium has a surface area approximately four times as great as that of the total (30/50 mesh) sample of balled magnesium. After exposure to an

atmosphere of 70% relative humidity for 30 days, the atomized total sample (30/50) increased in surface area twelve times (from 6,440 cm²/g to 77,900 cm²/g). The balled magnesium, however, only showed an eightfold increase (from 1,560 cm²/g to 12,500 cm²/g) after the same exposure. The increase in surface area after exposure to moisture is attributed to hydroxide formation and is considered a measure of reactivity.

The higher degree of reactivity shown by the Valley magnesium correlates with previous reactivity data which indicates that atomized magnesium is more reactive than balled magnesium. This greater reactivity may be a consequence of greater surface area.

The surface area measurements of the several sieve fractions all show the same trend. This is especially evident in the case of the 20/30 mesh atomized fraction, which reveals a 49-fold increase in surface area after exposure to 70% relative humidity for 30 days (from 8,820 cm²/g to 432,000 cm²/g).

The tendency of the surface area of these materials to increase with increasing particle size contradicts the normal expectation that the surface area will increase with decreasing particle size. These anomalous results are attributed to internal particle porosity, the porosity being more pronounced in larger particles. Evidence of the particle porosity is indicated by the photomicrographs (Fig 3).

Thermochemical Analysis

Differential thermal analyses by the method of Gordon and Campbell (Ref 16) were conducted on both the balled and atomized magnesium in a typical pyrotechnic blend (56/36.3/7.7 magnesium/sodium nitrate/Laminac). The results (see Figs 10 and 11) revealed no significant difference in either the ignition temperature (approximately 500°C) or the endotherms and exotherms obtained.

Heat of reaction determinations conducted on the above compositions failed to show any significant differences in calories per gram or volume of gas (ml/g) produced for either sample (Ref 17).

	Heat of Reaction, cal/g	Gas Volume, ml/g
Balled magnesium/sodium nitrate/Laminac	1444.0	80.1
Atomized magnesium/sodium nitrate/Laminac	1485.5	79.4

Heat of combustion determinations on both magnesium samples failed to reveal any significant difference in calories per gram (Ref 18).

	Heat of Combustion cal/g
Balled	5985.4
Atomized	6022.0

Sensitivity

Sensitivity experiments were conducted by the Olin Mathieson Chemical Corporation (Ref 4) on samples of both atomized and balled magnesium in a cured illuminant mix (not given) with oxidizer present. The following results were reported:

Impact Sensitivity – Bureau of Mines, 2 kg weight. Neither sample fired at a drop of 80 cm. This is the highest range of the equipment.

Electrostatic Sensitivity – Bureau of Mines, RI-403D. This test was conducted at .05 mfd and 5000 volts. No fires were observed for either sample in five (5) trials.

Ignition Temperature – Ignition time at 425°C was about five (5) seconds for both materials. Their ignition temperatures are considered equivalent.

Performance Characteristics

Performance characteristics of identical pressed pyrotechnic compositions containing balled and atomized magnesium were compared. Three separate tests were conducted with two different lots of atomized magnesium and one lot of balled magnesium.

The results (Tables 12, 13, and 14, pp 27, 28, and 29) fail to show any significant differences between the balled and the atomized magnesiums in luminous intensity, burning rate, or luminance efficiency values. The coefficients of variation, while not consistent from test to test, are small in all cases.

No differences were detected by visual observation of the burning flares; however, typical intensity-time traces (Fig 13) indicate that the balled magnesium composition burns with less fluctuation in the luminous intensity profile than the atomized magnesium composition.

EXPERIMENTAL PROCEDURE

Testing

Particle size distributions were determined by the method detailed in paragraph 4.4.6 of MIL-P-14067A (Ref 1) as well as by microscopic count as described in Chapter XV of the Pyrotechnics Handbook (Ref 5).

Average particle diameters were determined on the Picatinny Arsenal particle sizer by the air permeability method in accordance with Military Standard MIL-STD-1233, method 200 (Ref 19).

Apparent and tapped densities were determined by methods described in Chapter XV of the Pyrotechnics Handbook (Ref 5).

Absolute density determinations were carried out by using a pycnometer at 25°C with ACS grade acetone as the solvent (Ref 7).

The chemical analyses were performed in accordance with the method described in MIL-P-14067A and the moisture content was determined by the Electroynamics moisture analyzer in accordance with SOP-281-140.

Hygroscopicity determinations were conducted at 30%, 50%, and 70% relative humidity with 7-8 grams of material. Weight gain was recorded biweekly for a period of thirty days.

Reactivity with moisture tests were conducted on samples predried over phosphorus pentoxide. Equal amounts of water and magnesium (2.5 grams water/2.5 grams magnesium) were allowed to react in the standard vacuum stability apparatus (Ref 10) at room temperature (25°C) and at 167°F (76°C). Gas evolution was measured and recorded over a period of thirty days or till the sample evolved 11 ml of gas, the capacity of the apparatus.

Gas evolution was determined by vacuum stability with a 2.5-gram sample dried over phosphorus pentoxide. Determinations were made daily in accordance with a method described by A. J. Clear (Ref 14).

Surface area measurements were conducted by Edgewood Arsenal (Ref 15) using the Numinco-Orr MIC-103 surface area - pore volume analyzer.

Heats of combustion were determined in accordance with the procedure described in Parr Manual 130.

Heat of reaction tests were conducted in accordance with the procedure described in Report 62-VE6-25.

Materials

Magnesium, atomized, Drum 14, DA-28-017-A5-0836-5A, purchased from Valley Metallurgical Corporation as 30/50 mesh in accordance with Specification MIL-P-14067A. Average particle size as determined by Picatinny Arsenal particle size apparatus was 386.9 microns.

Magnesium, atomized, Drum 3, DA-28-019A-A-5-07291A, purchased from Valley Metallurgical Corporation as 30/50 mesh in accordance with Specification MIL-P-14067A. Average particle size as determined by Picatinny Arsenal particle size apparatus was 400 microns.

Magnesium, "balled," RMC-305, Drum 32, supplied by the Reade Manufacturing Company. Average particle size as determined by the Picatinny Arsenal particle size apparatus was 404.6 microns.

Sodium nitrate, double refined, Class 2, purchased from Davies Nitrate Company. Average particle size 34 microns, as determined by Fisher sub sieve sizer in accordance with Specification PA-PD-495.

Laminac 4116, in accordance with Specification PA-PD-2353, purchased from American Cyanamid Corporation.

Preparation of Blends

The illuminating compositions were prepared in a Lancaster LW Model blender in accordance with procedure described in SOP-PC-4.

Loading

Flares were consolidated using five increments of 50 grams each at a pressure of 5000 psi (3.47 ton dead load) into 1.33-inch-ID, paraffin wax coated, thin-walled (1/32 inch) kraft paper cases. The first increment contained an additional 5 grams of igniter composition FF-101-L and the last increment an additional 5 grams of Laminac-coated fireclay. Charge height was 6.2 inches (143 cc) and charge density was 1.75 cm/cc for the FY1230 and FY1230A compositions, while charge height was 6.4 inches (145 cc) and charge density 1.72 cm/cc for the FY-1231 composition.

Luminous Intensity Testing

The time-intensity characteristics of the flare compositions were determined statically under ambient pressure. The flares were burned in a face-up vertical position. All tests were conducted in the Pyrotechnics Laboratory's flare tunnel. Instrumentation consisting of a photocell-recorder combination was used to pick up the light emission and burning time.

REFERENCES

1. MIL-P-14067-A (MU), *Powders, Metal, Atomized (For Use in Ammunition)*, 16 May 1955
2. Jan-M-382, *Magnesium Powder (For Use in Ammunition)*, 28 August 1946
3. D. Hart and H. Eppig, *Long Range Research on Pyrotechnics: Burning Characteristics of Binary Mixtures. Report No. 1*, Picatinny Arsenal Technical Report 1669, 16 October 1947
4. N. J. Wilkaitis, *Mechanically Balled Magnesium for Reade Manufacturing Company*, Olin Mathieson Chemical Corporation, 15 February 1965
5. "Particle Size Procedures," *Pyrotechnics Handbook*, Chapter XV, The McGraw-Hill Technical Writing Service (In Press)
6. J. Kristal, *A Comparison Study of Apparent and Tapped Densities of Atomized Magnesium, Aluminum and Aluminum-Magnesium Alloy Metal Powders*, Pyrotechnics Laboratory Information Report 4, April 1963
7. *Operations and Maintenance Manual for the Sharples Micromerograph*, Chapter 3, Sharples Corporation Research Laboratories, Bridgeport, Penn.
8. Picatinny Arsenal Laboratory Report 65-VG1-103, Propellants Research Branch, 4 October 1965
9. Picatinny Arsenal Laboratory Report 66-VG1-8, Propellants Research Branch, 12 January 1966
10. Moisture Determination Results, Job Order 4067-01-004(370), Loading Branch, I. S. D., Picatinny Arsenal, 18 August 1965

11. H. Eppig, *Effects of Moisture on the Stability of Pyrotechnic Compositions, Report No. 1*, Picatinny Arsenal Technical Report 1661, 18 August 1947
12. Picatinny Arsenal Laboratory Report AL-P-223-65, Analytical Chemistry Branch, 4 August 1965
13. Picatinny Arsenal Laboratory Report AL-S-134-65, Analytical Chemistry Branch, 8 December 1965
14. Clear, A. J., Standard Laboratory Procedures for Sensitivity, Brisance and Stability of Explosives, Picatinny Arsenal Technical Report FRL-TR-25, January 1961; revised as PATR 3278, December 1965, same author.
15. Edgewood Arsenal Report *Surface Area Measurement of Magnesium Powders*, Letter dated 21 March 1966
16. S. Gordon and C. Campbell, "Differential Thermal Analysis of Inorganic Compounds," *Analytical Chemistry* 27: 1102 (July 1955)
17. Picatinny Arsenal Laboratory Report 63, Calorimetry Laboratory, 3 November 1965
18. Picatinny Arsenal Laboratory Report 56, Calorimetry Laboratory, 15 September 1965
19. MIL-STD-1233, Method 200, *Procedures for Determining Particle Size, Particle Size Distribution and Packed Density of Powdered Materials*, 21 March 1962

TABLE 1

Sieve analysis of balled and atomized (30/50 mesh) magnesium as compared to specification requirement

U. S. Standard Sieve	Percent Passing Through, by Weight						MIL-P-14067A Requirement
	Balled		Atomized		Run 2	Run 2	
	Run 1	Run 2	Run 1	Run 2			
20	100.0	100.0	99.5	99.5	99.5	99.5	95 min
30	99.4	99.5	88.1	87.5	87.5	87.5	85 min
50	1.2	1.2	11.3	7.9	7.9	7.9	40 max
60	0.3	0.3	8.5	5.5	5.5	5.5	25 max
100	0.0	0.0	1.2	0.3	0.3	0.3	5 max

TABLE 2

Microscopic count particle size distribution of balled and atomized magnesium

Magnesium Fractions	Nominal Particle Size, Range, in microns	Particle Size Data by Microscopic Count, microns			
		Balled		Atomized	
		Average, Geometric Mean	Range 16-84% Points	Average Geometric Mean	Range 16-84% Points
Original (30/50 mesh)	297-590	495	385-640	493	365-670
20/30 mesh	590-840	780	690-880	765	670-890
30/40 mesh	420-590	650	515-799	550	460-660
40/50 mesh	297-420	485	385-610	370	320-430
50/60 mesh	250-297	410	325-520	290	173-322

TABLE 3

Average particle diameter of balled and atomized magnesium *

Magnesium Fractions	Balled	Atomized
Original, 30/50 mesh	404.6	386.9
20/30 mesh	660.6	651.0
30/40 mesh	495.1	487.7
40/50 mesh	387.1	395.8
50/60 mesh	249.3	268.4

*As determined by air permeability.

TABLE 4

Apparent and tapped densities of balled and atomized magnesium

Magnesium Fractions	Balled, g/ml		Atomized, g/ml	
	Apparent	Tapped	Apparent	Tapped
Original, 30/50 mesh	0.98	1.08	1.06	1.12
20/30 mesh	1.02	1.09	1.03	1.08
30/40 mesh	0.98	1.08	1.03	1.09
40/50 mesh	0.96	1.08	1.01	1.08
50/60 mesh	0.94	1.05	1.03	1.09

TABLE 5

Absolute density of balled and atomized magnesium
after ambient and 70% relative humidity storage for 30 days

Magnesium Fractions	Balled, g/ml		Atomized, g/ml	
	Ambient Storage	Conditioned at 70% RH for 30 days	Ambient Storage	Conditioned at 70% RH for 30 days
Original, 30/50 mesh	1.70	1.73	1.70	1.73
20/30 mesh	1.71	1.73	1.70	1.99
30/40 mesh	1.72	1.74	1.70	1.76
40/50 mesh	1.73	1.73	1.70	1.78
50/60 mesh	1.73	1.72	1.70	1.73

TABLE 6

Chemical analysis (%) of balled and atomized magnesium
as compared to specification requirements

Determination	Balled	Atomized	MIL-P-14067A Requirements
Free metallic magnesium	99.6	100.7	98.0 min
Total magnesium	99.9	100.2	No requirement
Volatiles at 105°C	<0.01	<0.01	0.1 max
Carbides	<0.004	<0.004	0.004 max
Magnetic iron	0.017	<0.001	0.05 max
Alloy iron as Fe	<0.05	<0.05	0.05 max
Zinc	0.1	0.04	1.5 max
Other impurities	0.2	0.0	0.3 max
Grease and/or oil	0.0	0.0	No requirement

TABLE 7

Percentage moisture as determined by Electrodynamic moisture analyzer

Magnesium Fractions	Balled Magnesium	Atomized Magnesium
Original, 30/50 mesh	0.16	0.12
20/30 mesh	0.15	0.06
30/40 mesh	0.23	0.01
40/50 mesh	0.14	0.12
50/60 mesh	0.16	0.12

TABLE 8

Percent weight gain of balled and atomized magnesium fractions after exposure to 30%, 50%, and 70% relative humidities

Time, Days	Sample No.: Fraction:	Balled					Atomized				
		1 Total Sample	2 20/30	3 30/40	4 40/50	5 50/60	1 Total Sample	2 20/30	3 30/40	4 40/50	5 50/60
Hygroscopicity at 30% RH and 30°C											
1		0	0	0	0.01	*	*	*	*	*	
1		0.01	0	0.01	0.01	*	0	*	*	*	
8		0	0	0	0	*	*	*	*	0	
12		*	0.01	0.01	0.01	*	0	*	*	0	
15		0	0	0.01	0.01	*	0	*	*	0	
18		0	0.01	0	0	*	0	*	*	0	
21		0	0	0	0	*	0	*	*	0.01	
25		0.01	0.01	0.01	0.01	*	0	*	*	0.01	
31		0	0	0	0	*	0	0.01	*	0.01	
Hygroscopicity at 50% RH and 30°C											
1		0	0	0	0	*	0.01	0.03	0.01	0	0
4		0	0	0	0	0	0.01	0.06	0.01	0.01	0.01
8		0	0	0	0	*	0.01	0.06	0.01	0.01	0.01
12		0	0	0	0	0	0.01	0.06	0.01	0.01	0.01
15		0	0	0	0	0	0.01	0.13	0.01	0.01	0.01
18		*	0	*	0	0	0.01	0.09	0.01	0.01	0.01
21		*	0	*	0.01	0	0.01	0.09	0.01	*	0.01
25		*	0.01	*	0.01	0.01	0.01	0.06	0.01	*	0.01
31		*	0.01	*	0.01	0	0.01	0.07	0.01	*	0.01
Hygroscopicity at 70% and 30°C											
1		*	*	0.01	0	0	0.10	0.31	0.03	0.01	0.01
1		0.01	*	0	0.02	0.02	0.09	0.58	0.06	0.03	0.03
8		0.02	*	0.01	0.02	0.02	0.12	0.68	0.08	0.04	0.04
12		0.02	*	0.01	0.03	0.02	0.13	0.71	0.10	0.04	0.04
15		0.03	*	0.01	0.04	0.03	0.15	0.73	0.11	0.05	0.05
18		0.03	*	0.01	0.04	0.03	0.14	0.64	0.11	0.06	0.05
21		0.03	**	0.02	0.05	0.03	0.15	0.65	0.11	0.06	0.06
25		0.04	0.01	0.02	0.06	0.04	0.16	0.66	0.13	0.07	0.07
31		0.04	0.01	**	0.06	0.04	0.16	0.60	0.12	0.07	0.07

*Signifies a loss in weight.

**Means no data obtained.

TABLE 9

Reactivity with water (ml of gas produced as a function of time)

Total Sample	20/30 Mesh	30/40 Mesh	40/50 Mesh	50/60 Mesh
ATOMIZED MAGNESIUM AT ROOM TEMPERATURE (25°C)				
16 hours	11+	11+	11+	11+
ATOMIZED MAGNESIUM AT 76°C (167°F)				
1 hours	11+	11+	—*	—
1.5 hours	—	—	—	11+
2 hours	—	—	11+	—
BALLED MAGNESIUM AT ROOM TEMPERATURE				
1 day	3.6	5.2	3.7	4.0
2 days	4.7	7.0	4.8	—
4 days	—	—	—	5.9
5 days	5.8	8.5	5.8	6.4
6 days	6.1	8.9	6.2	6.9
7 days	6.5	9.6	6.5	7.5
8 days	7.0	10.3	7.0	7.9
9 days	7.3	10.4	7.3	—
11 days	—	—	—	9.1
12 days	8.3	11.0	8.0	9.4
13 days	8.4	—	8.2	9.8
14 days	8.5	—	8.7	10.2
15 days	9.5	—	9.0	10.2
16 days	9.1	—	9.2	—
19 days	10.1	—	—	11.2
20 days	10.3	—	10.1	—
21 days	—	—	10.3	—
22 days	—	—	10.5	—
23 days	—	—	10.2	—
26 days	—	—	10.9	—
27 days	—	—	11.1	—
BALLED MAGNESIUM AT 76°C				
16 hours	11+	11+	11+	11+

*—Means no data obtained.

TABLE 10

Vacuum stability of balled and atomized magnesium during thirty days storage (ml of gas)

Days	Balled Magnesium												Atomized Magnesium												
	76°C (167°F)				110°C (230°F)				76°C (167°F)				110°C (230°F)				76°C (167°F)				110°C (230°F)				
	Fractions:	20/30	30/40	40/50	50/60	Total Sample	20/30	30/40	40/50	50/60	Total Sample	20/30	30/40	40/50	50/60	Total Sample	20/30	30/40	40/50	50/60	Total Sample	20/30	30/40	40/50	50/60
1	0.11	0.11	0.10	0.11	0.15	0.15	0.19	0.18	0.16	0.16	0.27	0.05	0.15	0.47	0.26	0.20	0.11	0.11	0.14	0.14	0.16	0.11	0.15	0.18	0.16
2	-	-	-	-	0.23	0.16	0.17	0.13	0.19	0.17	-	-	-	0.49	0.27	0.21	0.15	0.18	0.18	0.18	0.18	0.21	0.15	0.18	0.18
3	-	-	-	-	0.12	0.14	0.15	0.17	0.17	0.15	-	-	-	0.46	0.25	0.25	0.15	0.19	0.19	0.21	0.21	0.25	0.15	0.19	0.21
4	0.08	0.06	0.04	0.08	0.11	0.13	0.14	0.17	0.17	0.15	0.33	0.21	0.19	0.38	0.21	0.21	0.19	0.18	0.19	0.19	0.21	0.19	0.18	0.19	0.17
5	0.09	0.08	0.06	0.10	-	-	-	-	-	-	0.31	0.20	0.20	-	-	-	-	-	-	-	-	-	-	-	-
6	0.08	0.10	0.06	0.09	-	-	-	-	-	-	0.32	0.29	0.25	-	-	-	-	-	-	-	-	-	-	-	-
7	0.07	0.06	0.04	0.07	0.13	0.11	0.13	0.14	0.17	0.11	0.30	0.25	0.22	0.40	0.25	0.11	0.21	0.26	0.27	0.27	0.26	0.21	0.26	0.27	0.26
8	0.08	0.06	0.03	0.08	0.12	0.13	0.11	0.15	0.13	0.12	0.29	0.19	0.19	0.40	0.25	0.39	0.28	0.32	0.33	0.33	0.32	0.28	0.32	0.33	0.32
9	-	-	-	-	0.10	0.13	0.11	0.15	0.15	0.12	-	-	-	0.42	0.25	0.10	0.29	0.32	0.31	0.31	0.33	0.10	0.29	0.32	0.31
10	-	-	-	-	0.11	0.15	0.18	0.18	0.15	0.12	-	-	-	0.41	0.25	0.46	0.33	0.38	0.40	0.41	0.41	0.33	0.38	0.40	0.41
11	0.07	0.06	0.05	0.08	0.09	0.16	0.18	0.18	0.18	0.18	0.29	0.25	0.20	0.43	0.26	0.12	0.28	0.33	0.35	0.35	0.33	0.28	0.33	0.35	0.33
12	0.06	0.06	0.05	0.08	-	-	-	-	-	-	0.29	0.25	0.20	-	-	-	-	-	-	-	-	-	-	-	-
13	0.06	0.06	0.02	0.08	-	-	-	-	-	-	0.29	0.25	0.21	-	-	-	-	-	-	-	-	-	-	-	-
14	0.06	0.07	0.05	0.08	0.09	0.13	0.17	0.17	0.18	0.13	0.31	0.30	0.27	0.40	0.23	0.40	0.27	0.12	0.31	0.33	0.27	0.12	0.31	0.33	
15	0.03	0.01	0.03	0.05	0.11	0.13	0.16	0.15	0.16	0.13	0.33	0.31	0.32	0.36	0.23	0.40	0.28	0.33	0.35	0.35	0.33	0.28	0.33	0.35	0.33
16	-	-	-	-	0.10	0.22	0.18	0.17	0.14	0.16	-	-	-	0.36	0.24	0.42	0.31	0.36	0.38	0.38	0.36	0.31	0.36	0.38	0.36
17	-	-	-	-	0.10	0.15	0.16	0.17	0.18	0.14	-	-	-	0.36	0.22	0.42	0.31	0.37	0.39	0.39	0.35	0.31	0.37	0.39	0.35
18	0.02	0.03	0.02	0.06	0.09	0.18	0.21	0.20	0.17	0.18	0.30	0.38	0.31	0.38	0.22	0.46	0.31	0.38	0.41	0.37	0.46	0.31	0.38	0.41	0.37
19	0.02	0.03	0.03	0.06	-	-	-	-	-	-	0.30	0.31	0.35	-	-	-	-	-	-	-	-	-	-	-	-
20	0.03	0.07	0.03	0.06	-	-	-	-	-	-	0.30	0.38	0.38	-	-	-	-	-	-	-	-	-	-	-	-
21	0.05	0.05	0.04	0.06	-	0.13	0.18	0.15	0.19	0.14	0.30	0.12	0.38	-	-	0.51	0.39	0.11	0.48	0.48	0.51	0.39	0.11	0.48	
22	0.06	0.03	0.01	0.06	0.09	0.15	0.17	0.16	0.15	0.13	0.31	0.52	0.39	0.35	0.18	0.51	0.38	0.12	0.48	0.48	0.51	0.38	0.12	0.48	
23	-	-	-	-	0.07	0.16	0.20	0.19	0.16	0.16	-	-	-	0.31	0.15	0.52	0.40	0.11	0.48	0.48	0.51	0.40	0.11	0.48	
24	-	-	-	-	0.10	0.18	0.20	0.21	0.19	0.17	-	-	-	0.35	0.15	0.53	0.13	0.46	0.51	0.51	0.46	0.13	0.46	0.51	
25	-	-	-	-	0.09	0.19	0.21	0.21	0.20	0.18	-	-	-	0.33	0.17	0.56	0.17	0.19	0.56	0.56	0.46	0.17	0.19	0.56	
26	0.03	0.03	0.03	0.05	-	-	-	-	-	-	0.30	0.59	0.40	-	-	-	-	-	-	-	-	-	-	-	-
27	0.03	0.03	0.03	0.04	-	-	-	-	-	-	0.28	0.60	0.42	-	-	-	-	-	-	-	-	-	-	-	-
28	0.03	0.05	0.04	0.08	0.14	0.17	0.21	0.19	0.19	0.18	0.30	0.68	0.41	0.36	0.22	0.52	0.52	0.51	0.59	0.51	0.52	0.51	0.59	0.51	
29	0.03	0.03	0.04	0.06	0.09	0.19	0.22	0.22	0.20	0.18	0.29	0.66	0.49	0.34	0.16	0.56	0.55	0.58	0.61	0.54	0.56	0.55	0.58	0.61	
30	-	-	-	-	0.10	0.17	0.20	0.20	0.20	0.17	0.33	0.70	0.46	0.36	0.18	0.58	0.62	0.63	0.66	0.51	0.58	0.62	0.63	0.66	
31	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
32	0.07	0.07	0.06	0.06	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-

*-Means no data obtained.

TABLE 11

Effects of high relative humidity (70%) on specific surface area (cm²/g) of
balled and atomized magnesium:

Sieve Fractions	Calculated Area*		Specific Surface Area of Unexposed Controls		Ratio		Specific Surface Area of Samples Exposed to 70% RH for 30 Days		Ratio	
	Balled	Atomized	Balled**	Atomized**	Atomized:Balled	Balled**	Atomized***	Atomized:Balled	Atomized: Balled	
Total (30/50)	85.0	89.5	1,560	6,440	4.1:1	12,500	77,900	6.2:1		
20/30 Mesh	34.4	52.9	3,570	8,820***	2.5:1	31,200	432,000	13.9:1		
30/40 Mesh	70.0	70.4	1,740	3,490	2.0:1	10,400	81,250	7.8:1		
40/50 Mesh	88.8	87.3	719	1,470	2.1:1	6,160	55,100	8.7:1		
50/60 Mesh	139.0	128.0	366	1,360	3.7:1	2,270	26,700	11.8:1		

*Calculated areas based on average particle diameter as determined by air permeability (Table 3, p 20) assuming all particles to be spherical.

**Surface areas determined using krypton as the adsorbing gas.

***Surface areas determined using nitrogen as the adsorbing gas.

TABLE 12

Performance characteristics of compositions containing balled and atomized magnesium, Test 1**

Item No.	Candlepower Average, 10 ³ Candles		Candlepower/sq. in., 10 ³ Candles		Burning Rate, in./min		Efficiency Candleseconds/g × 10 ³		Efficiency Candleseconds/cc × 10 ³	
	FY-1230A	FY-1231 B*	FY-1230A	FY-1231 B	FY-1230A	FY-1231 B	FY-1230A	FY-1231 B	FY-1230A	FY-1231 B
1	121.5	111.4	87.4	79.5	5.0	5.0	36.4	34.4	63.5	59.3
2	121.8	115.7	87.6	83.0	5.0	5.1	36.0	35.6	63.0	60.8
3	93.1	117.1	70.6	84.3	5.0	5.4	29.2	33.2	51.0	57.2
4	106.9	117.4	76.8	84.5	4.9	5.0	32.4	36.0	56.6	62.0
5	109.5	126.0	78.8	90.8	5.0	5.2	32.4	36.8	56.6	63.3
6	101.8	115.7	73.2	83.0	5.2	4.8	29.2	37.2	51.0	64.0
7	99.8	126.8	71.8	91.2	5.2	4.9	28.4	39.1	49.6	67.5
8	102.3	121.6	73.8	87.4	5.2	4.9	29.6	38.4	51.7	66.2
9	117.9	139.0	84.6	100.0	5.1	5.3	34.0	40.6	59.4	69.6
10	112.7	133.7	81.0	96.1	4.9	5.1	34.0	40.0	59.4	68.9
Average	109.2	122.7	78.6	88.0	5.1	5.1	32.2	37.1	56.2	63.9
Standard Deviation × 10 ³	9.1	8.8	9.3	6.5	.192	.13	2.9	2.4	5.1	4.1
Coefficient of Variation, %	8.3	7.3	11.8	7.4	3.8	2.6	9.0	6.4	9.1	6.4

*A = atomized, B = balled.

**Composition: Magnesium/sodium nitrate/Laminac 56/3r.3/7.7.
FY-1230, Atomized, Lot No. DA-28-017-A-5-0836-5A, Drum 14
FY-1230A, Atomized, Lot No. DA-28-019-A-5-0729-1A, Drum 3
FY-1231, Balled, Lot No. RMC-305, Drum 32.

TABLE 13

Performance characteristics of compositions containing balled and atomized magnesium, Test II***

Item No.	Candlepower Average, 10 ³ candelas				Candlepower/sq. in., 10 ³ candelas				Burning Rate, in./min				Efficiency Candleseconds/g × 10 ³				Efficiency Candleseconds/cc × 10 ³			
	FY-1230A		FY-1231		FY-1230A		FY-1231		FY-1230A		FY-1231		FY-1230A		FY-1231		FY-1230A		FY-1231	
	A*	A	B	A	A	A	B	A	A	A	B	A	A	A	B	A	A	A	A	B
1	127.1**	120.8	138.5**	91.4**	86.8	99.6**	4.7**	5.0	5.3**	40.8**	35.0	71.4**	63.0	69.0**						
2	126.0	141.7	151.8	70.6	101.8	109.0	5.0	5.0	5.0	37.6	42.4	65.8	74.2	80.0						
3	141.3	141.5	132.5	101.6	103.8	95.4	5.1	5.4	4.8	41.2	40.0	72.0	70.0	73.2						
4	131.6	145.6	134.6	94.8	105.4	96.8	4.9	5.1	4.6	38.2	40.0	67.0	70.0	77.8						
5	131.5	144.3	154.1	94.5	103.6	110.1	5.3	5.3	5.3	36.8	40.4	61.2	70.6	66.8						
6	148.1	128.1	157.1**	107.5	92.4	112.8**	5.3	5.1	5.9**	39.1	38.6	68.1	65.6	70.4**						
7	140.8	136.8	141.2	101.2	98.2	101.5	5.1	5.1	5.5	40.8	40.0	71.4	70.0	67.6						
8	131.4	147.0	146.5	94.5	105.6	105.2	4.9	5.3	5.3	40.0	42.4	70.0	74.2	72.4						
9	137.2	144.6	141.1	98.8	104.0	101.5	4.9	5.4	4.9	41.6	39.6	72.8	69.2	76.5						
10	143.5	146.9	135.4	103.2	105.5	97.5	5.4	5.4	5.0	39.6	40.0	69.2	70.0	71.0						
Average	136.7	140.1	142.2	98.3	100.7	102.1	5.1	5.2	5.1	39.4	39.9	68.9	69.7	73.1						
Standard Deviation × 10 ³	6.7	9.3	8.1	5.1	6.2	5.5	.19	.10	.31	1.7	1.8	2.9	3.4	4.5						
Coefficient of Variation, %	4.2	6.6	5.7	5.2	6.2	5.4	3.7	3.5	6.1	4.3	4.5	4.2	4.9	6.1						

*A = atomized; B = balled.

**Not included in averages, fell into pit and burned.

***Composition: Magnesium/sodium nitrate/Laminac 56/36.3/7.7.
FY-1230, Atomized, Lot No. DA-28-017-A-5-0836-SA, Drum 14
FY-1230A, Atomized, Lot No. DA-28-019-A-5-0729-1A, Drum 3
FY-1231, Balled, Lot No. RMC-305, Drum 32.

TABLE 14

Performance characteristics of compositions containing balled and atomized magnesium, Test III**


Item No.	Candlepower Average, 103 candelas		Candlepower/sq. in., 103 candelas		Burning Rate, in./min		Efficiency Candleseconds/g x 10 ³		Efficiency Candleseconds/cc x 10 ³			
	FY-1230 A*	FY-1230A A	FY-1230 A	FY-1230A A	FY-1230 A	FY-1230A A	FY-1230 A	FY-1230A A	FY-1230 A	FY-1230A A		
	FY-1231 B	FY-1230A B	FY-1231 B	FY-1230A B	FY-1231 B	FY-1230A B	FY-1231 B	FY-1230A B	FY-1231 B	FY-1230A B		
1	122.2	114.1	141.7	88.9	4.7	5.5	5.2	38.1	30.8	67.2	53.8	77.8
2	128.3	118.9	127.2	92.4	4.8	5.1	4.9	39.2	32.1	68.5	56.6	68.2
3	127.5	122.1	122.9	91.8	4.9	4.9	5.0	40.0	37.2	69.8	65.1	61.8
4	124.2	125.1	126.3	89.2	4.8	4.9	5.0	38.1	38.0	67.2	66.2	67.6
5	123.6	126.3	123.8	88.8	4.5	5.2	5.0	40.3	36.0	70.6	63.0	65.5
6	124.1	124.3	142.0	89.2	4.7	4.9	5.1	39.6	37.2	69.2	65.1	71.2
7	127.3	123.8	141.6	91.6	4.7	4.9	5.0	40.3	37.6	70.6	65.6	71.3
8	129.2	123.0	142.0	92.8	4.9	5.0	5.3	39.2	36.4	68.5	63.6	72.2
9	132.8	125.3	143.2	95.6	5.1	5.1	5.3	38.8	36.1	67.8	63.6	72.2
10	133.0	114.3	133.7	96.7	1.7	4.8	4.9	40.8	35.6	71.3	61.5	72.2
Average	127.2	121.8	131.6	91.5	4.8	5.1	5.1	39.5	35.8	69.1	62.1	70.6
Standard Deviation x 10 ³	3.8	4.1	9.2	2.8	.16	.21	.15	.83	2.3	1.5	4.1	1.0
Coefficient of Variation, %	3.0	3.6	6.8	3.1	3.3	4.7	2.9	2.1	6.4	2.2	6.6	5.7

*A = atomized; B = balled.

**Composition: Magnesium/sodium nitrate/Laminac 56/36.3/7.7.
 FY-1230, Atomized, Lot No. DA-28-017-A-5-0836-5A, Drum 14
 FY-1230A, Atomized, Lot No. DA-28-019-A-5-0729-1A, Drum 3
 FY-1231, Balled, Lot No. RMC-305, Drum 32.



20/30 mesh sieve fraction

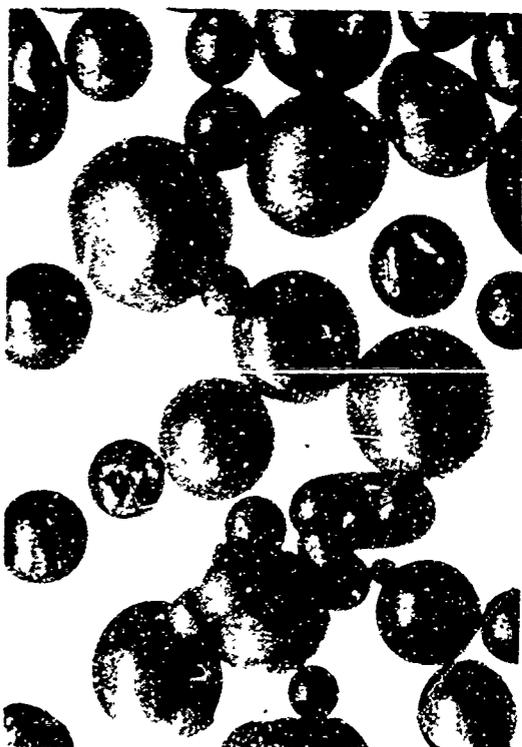


Total sample 30/50 mesh




30/40 mesh sieve fraction

Fig 1 Photomicrographs of powdered atomized magnesium at 35 x magnification

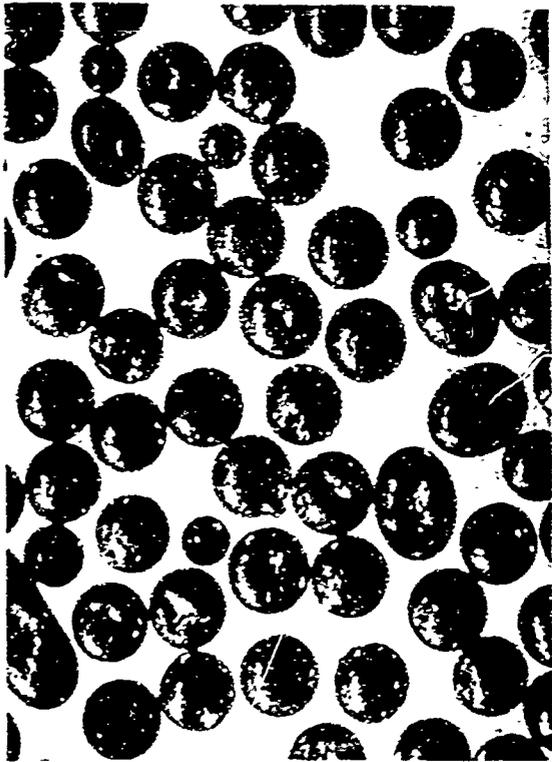


50/60 mesh sieve fraction

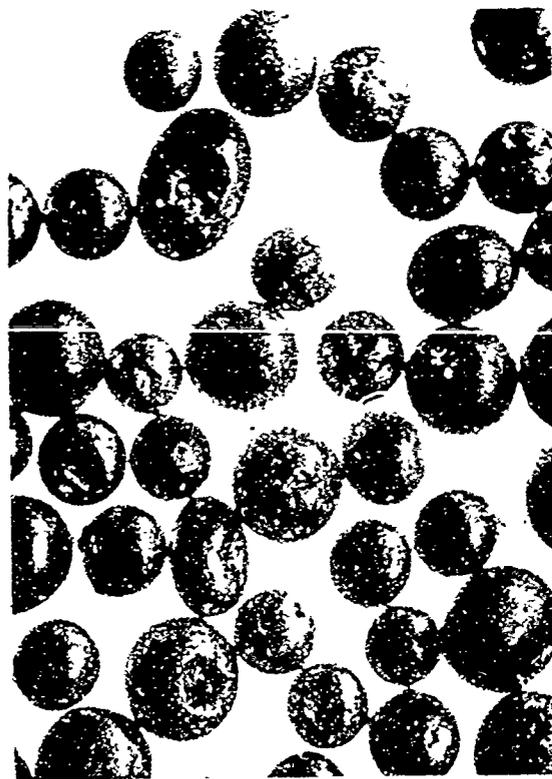


40/50 mesh sieve fraction

Fig 1 (cont)

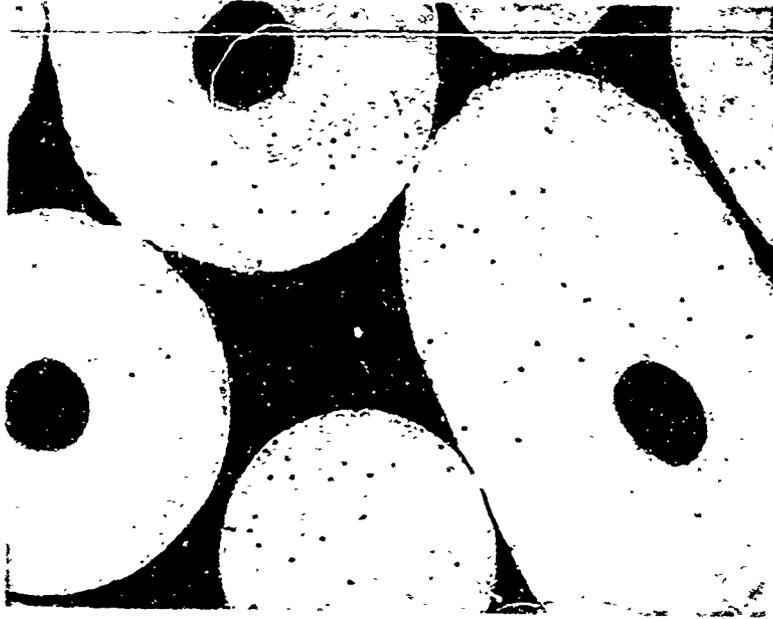


Atomized magnesium particles

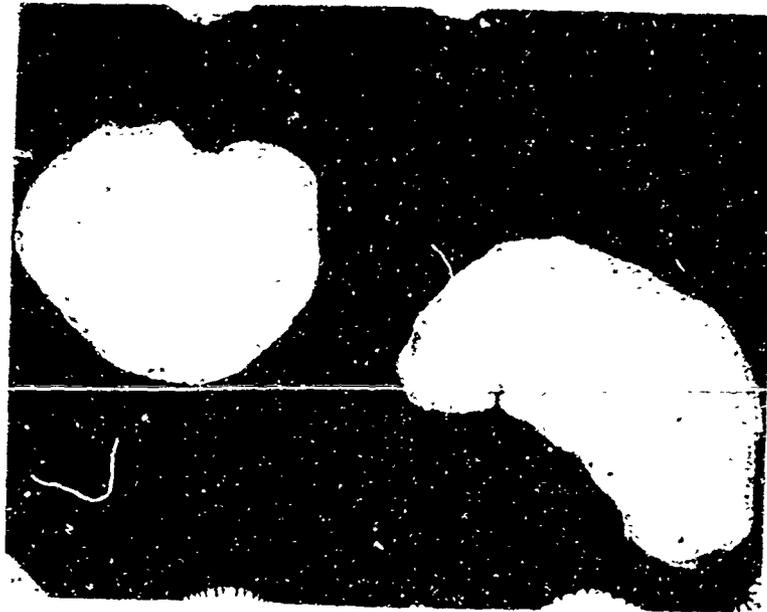


Balled magnesium particles

Fig 2 Cross-sectional photomicrograph of typical balled and atomized magnesium particles at 75 \times magnification

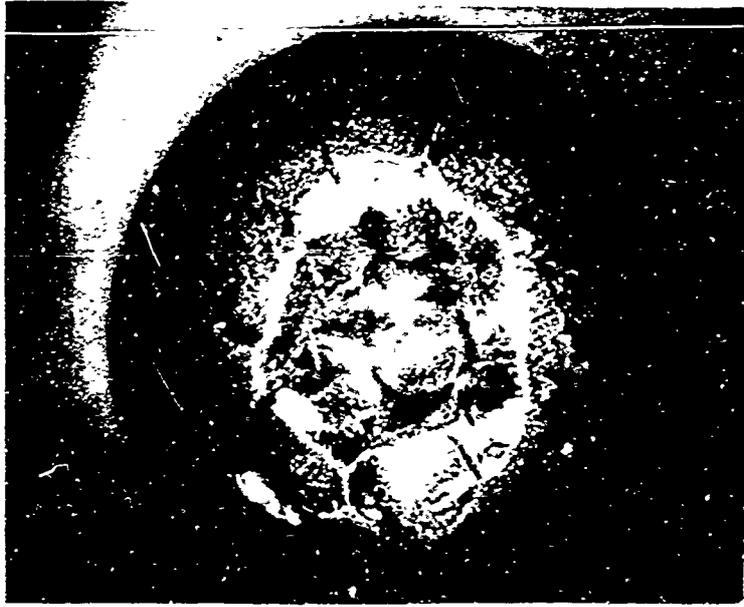

Atomized magnesium particle

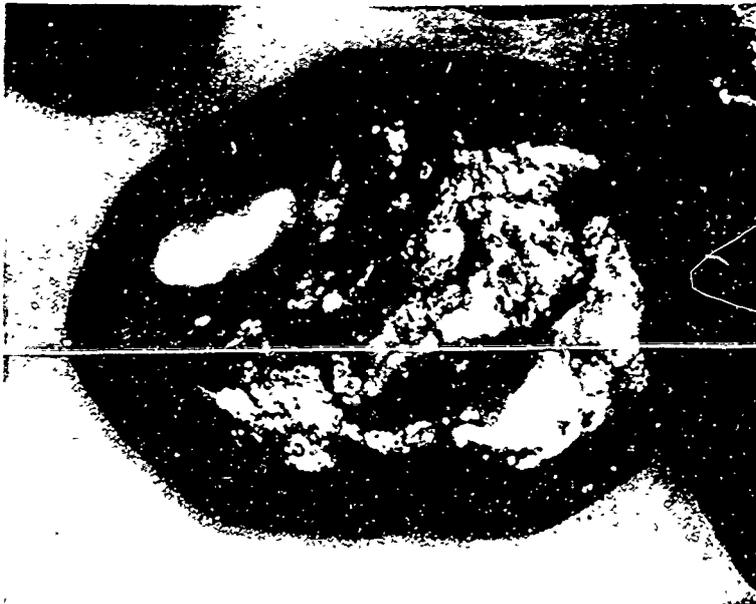

Balled magnesium particle

Fig 3 Photomicrograph of typical single balled and atomized magnesium particles at 75x magnification



20/30 mesh sieve fraction




Total sample 30/50 mesh



30/40 mesh sieve fraction

Fig 4 Photomicrographs of powdered balled magnesium at 35 x magnification

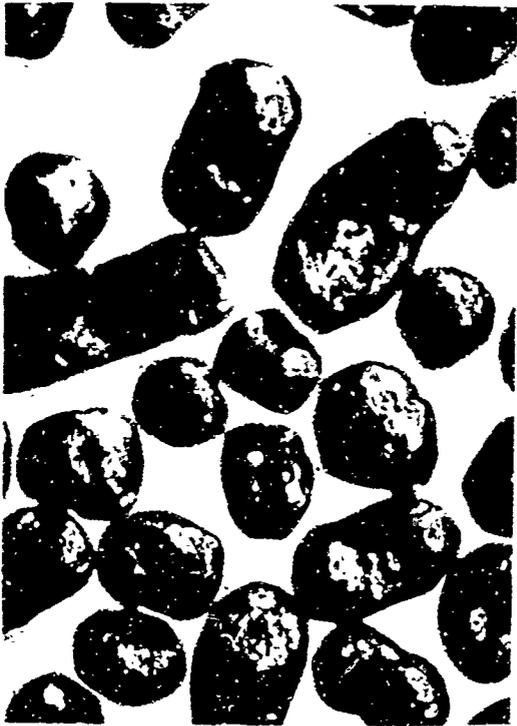

40/50 mesh sieve fraction



50/60 mesh sieve fraction

Fig 4 (cont)

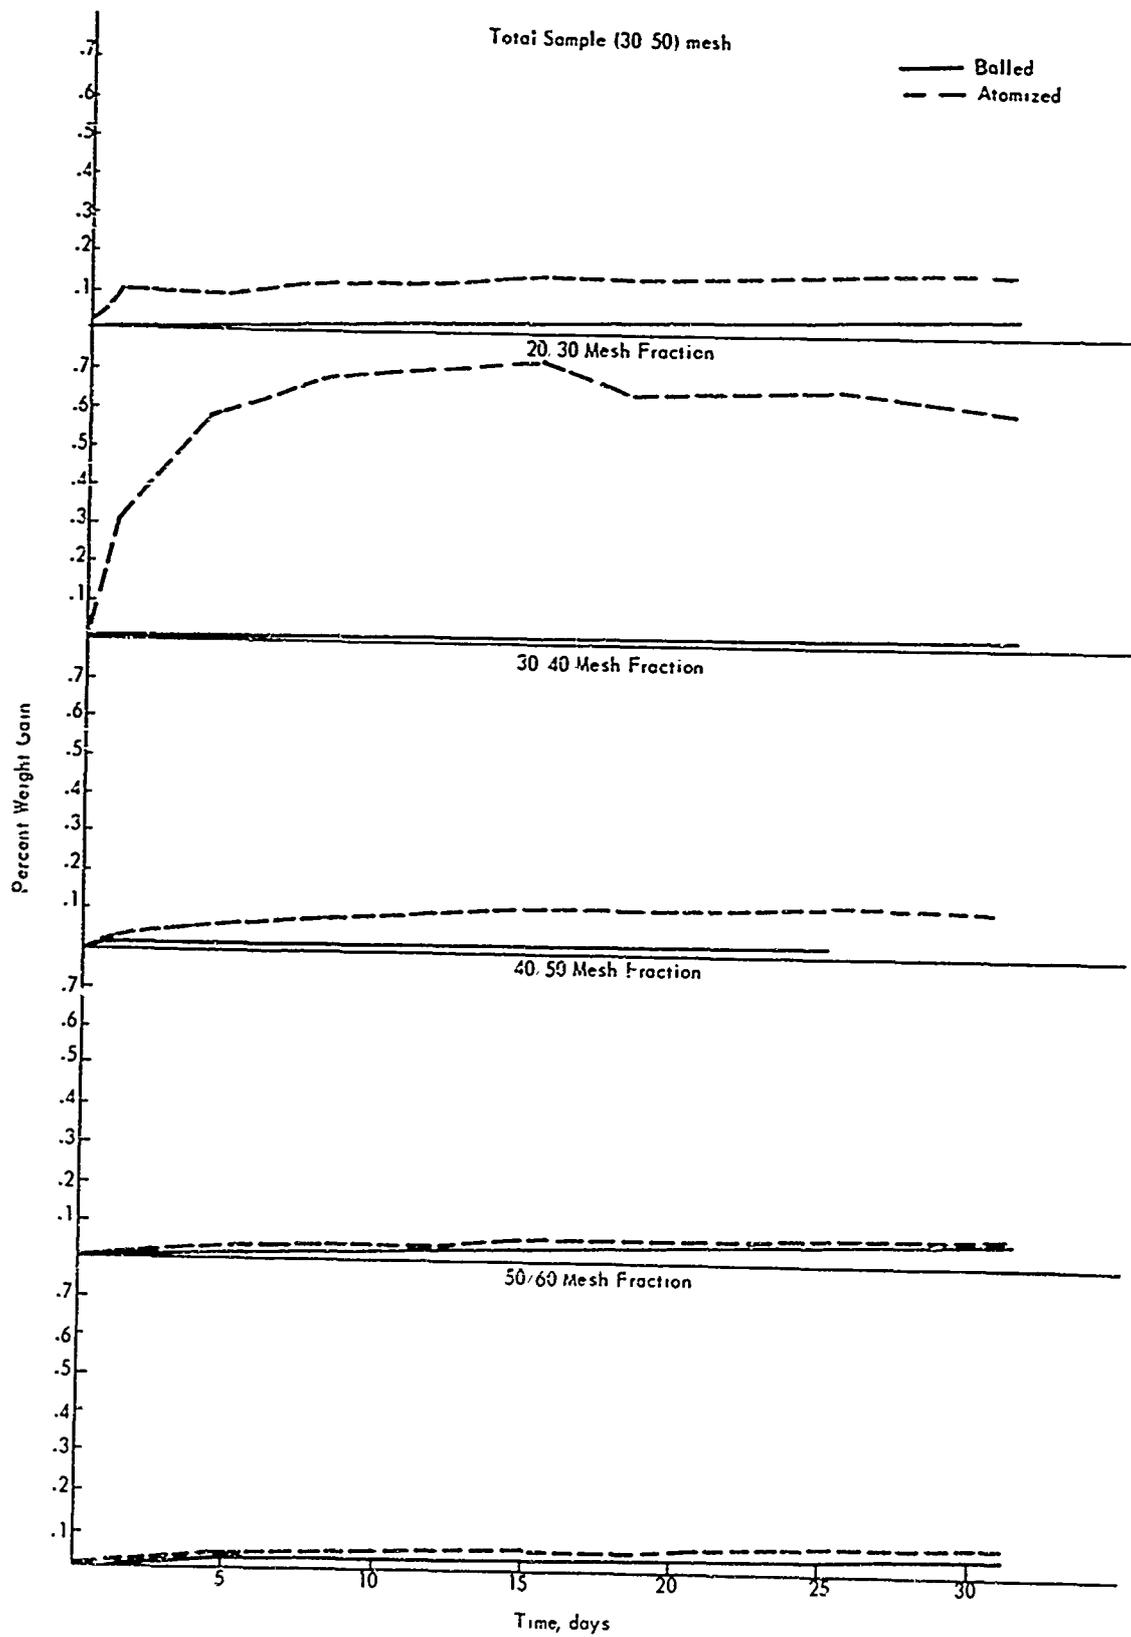


Fig 5 Percent weight gain at 70% relative humidity 30°C of balled and atomized magnesium

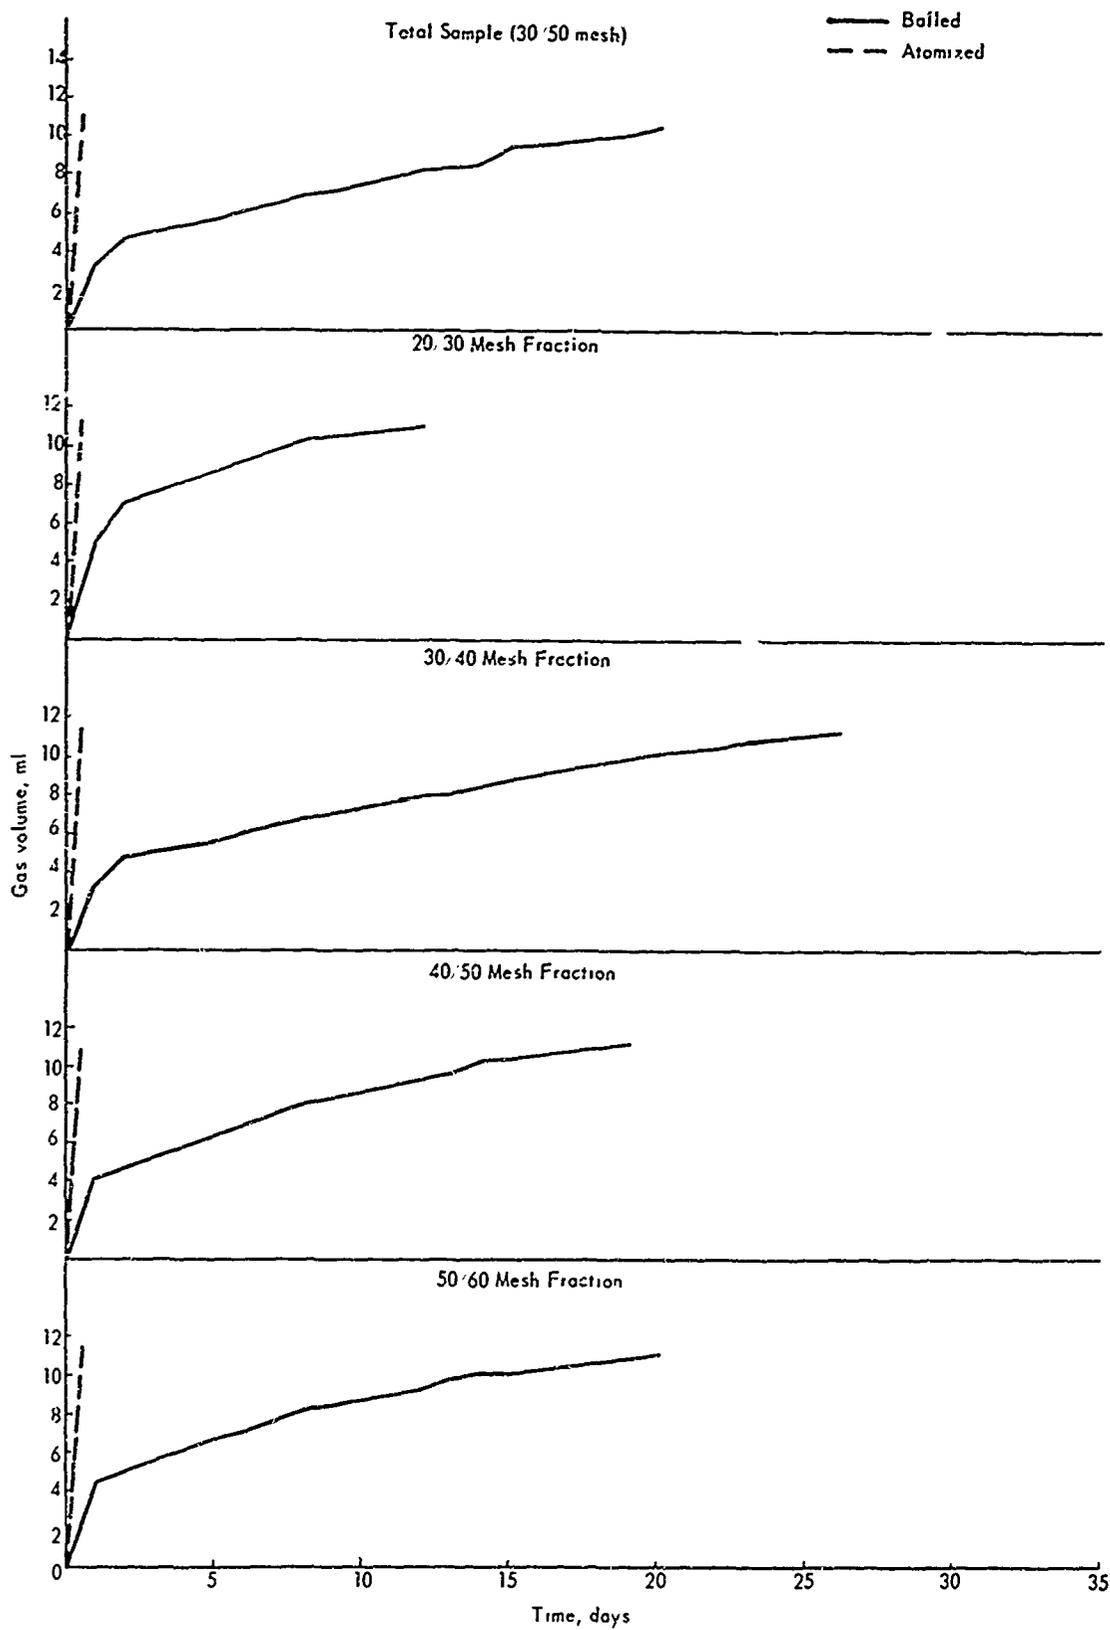


Fig 6 Reactivity with water at room temperature of balled and atomized magnesium

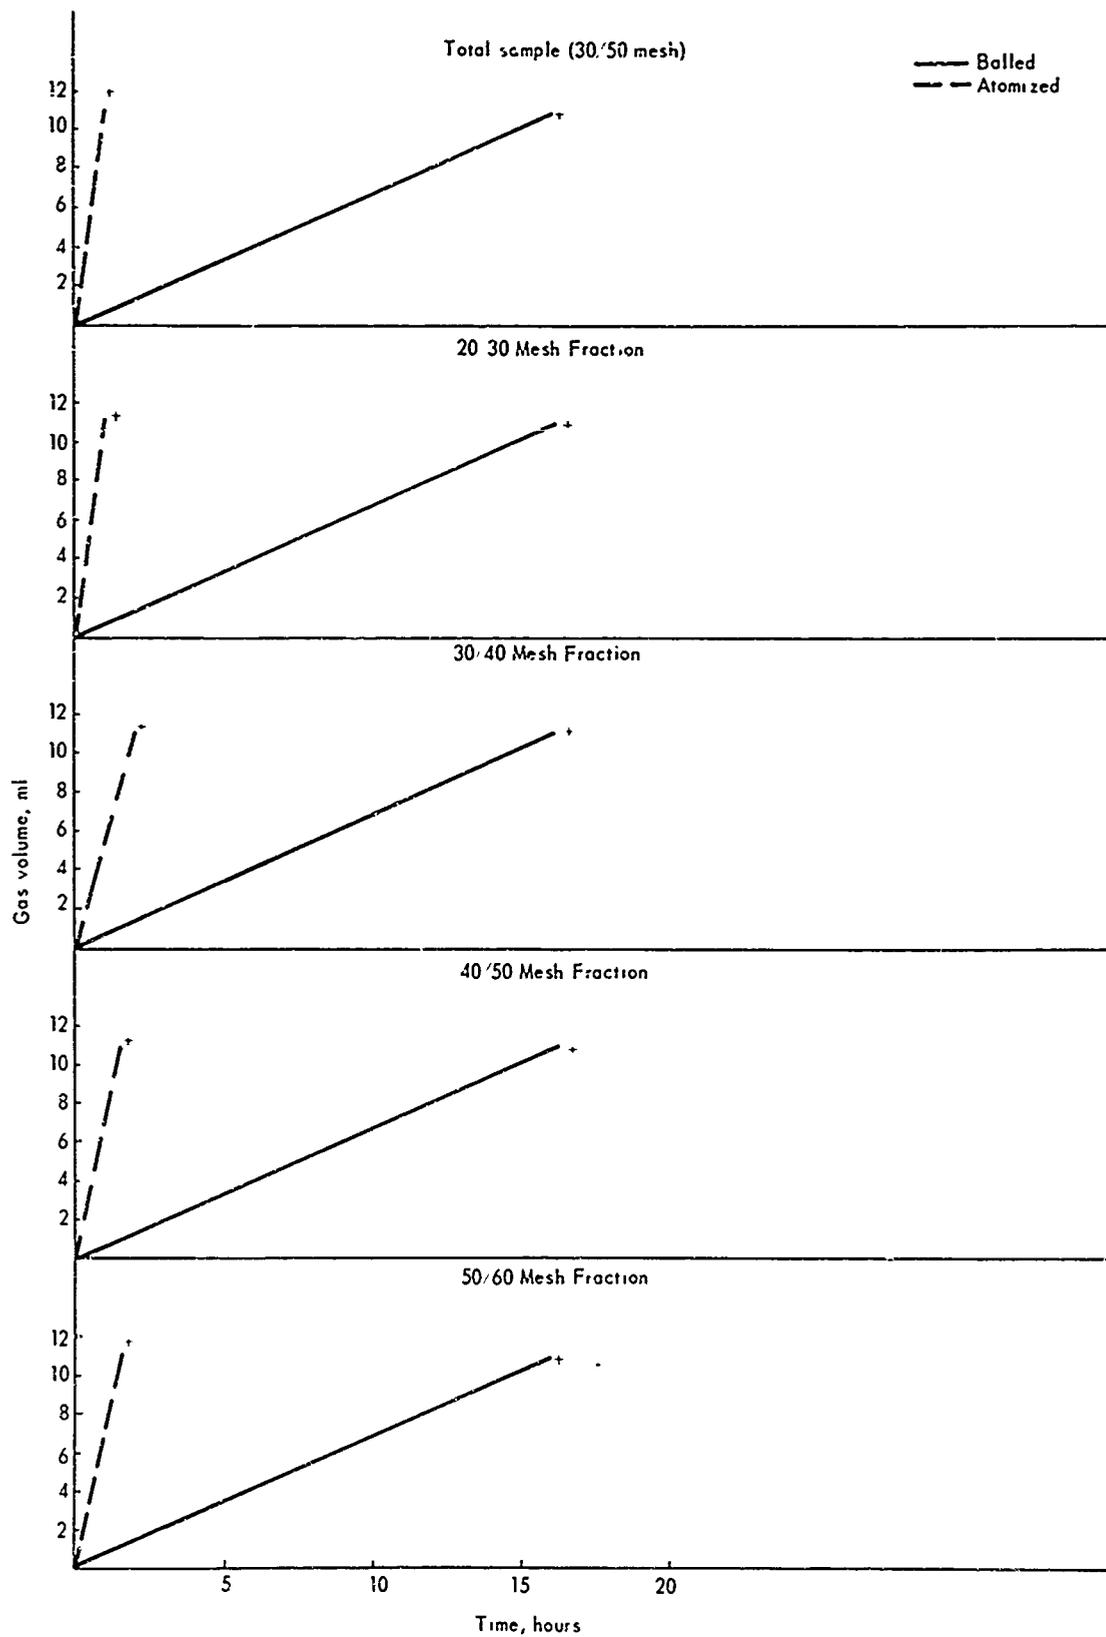


Fig 7 Reactivity with water at 76°C (167°F) of balled and atomized magnesium

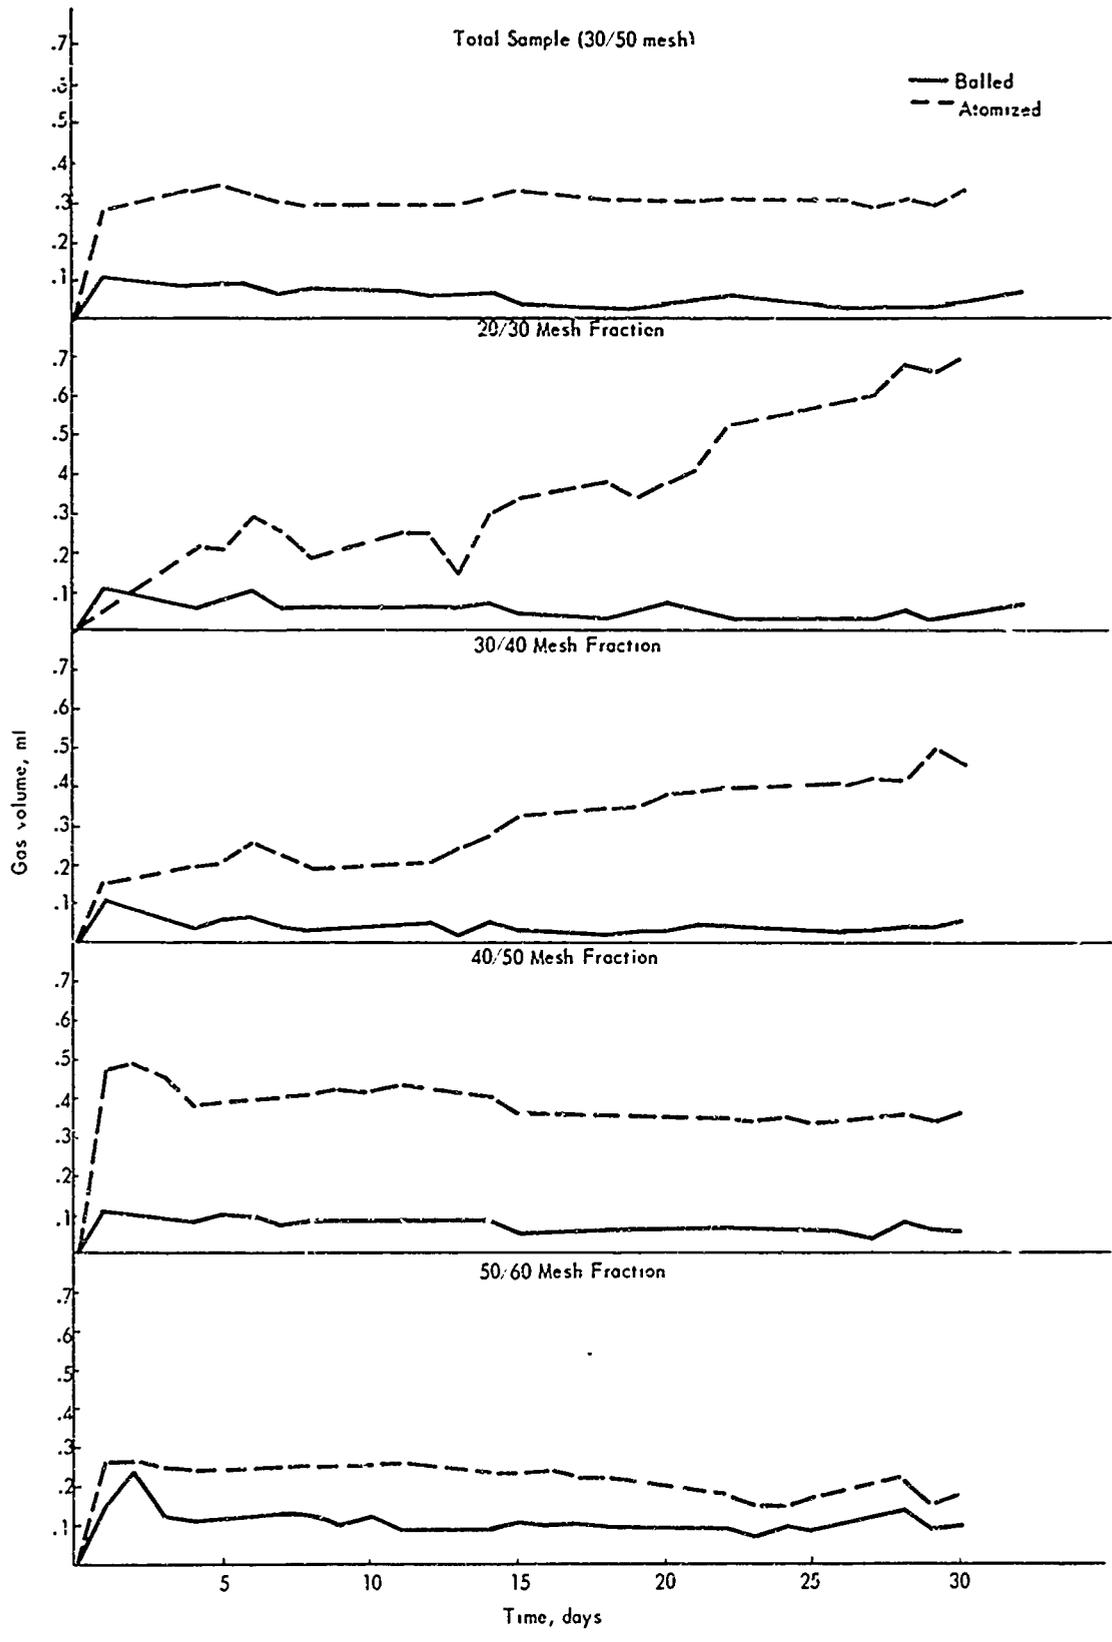


Fig 8 Vacuum stability at 76°C of balled and atomized magnesium

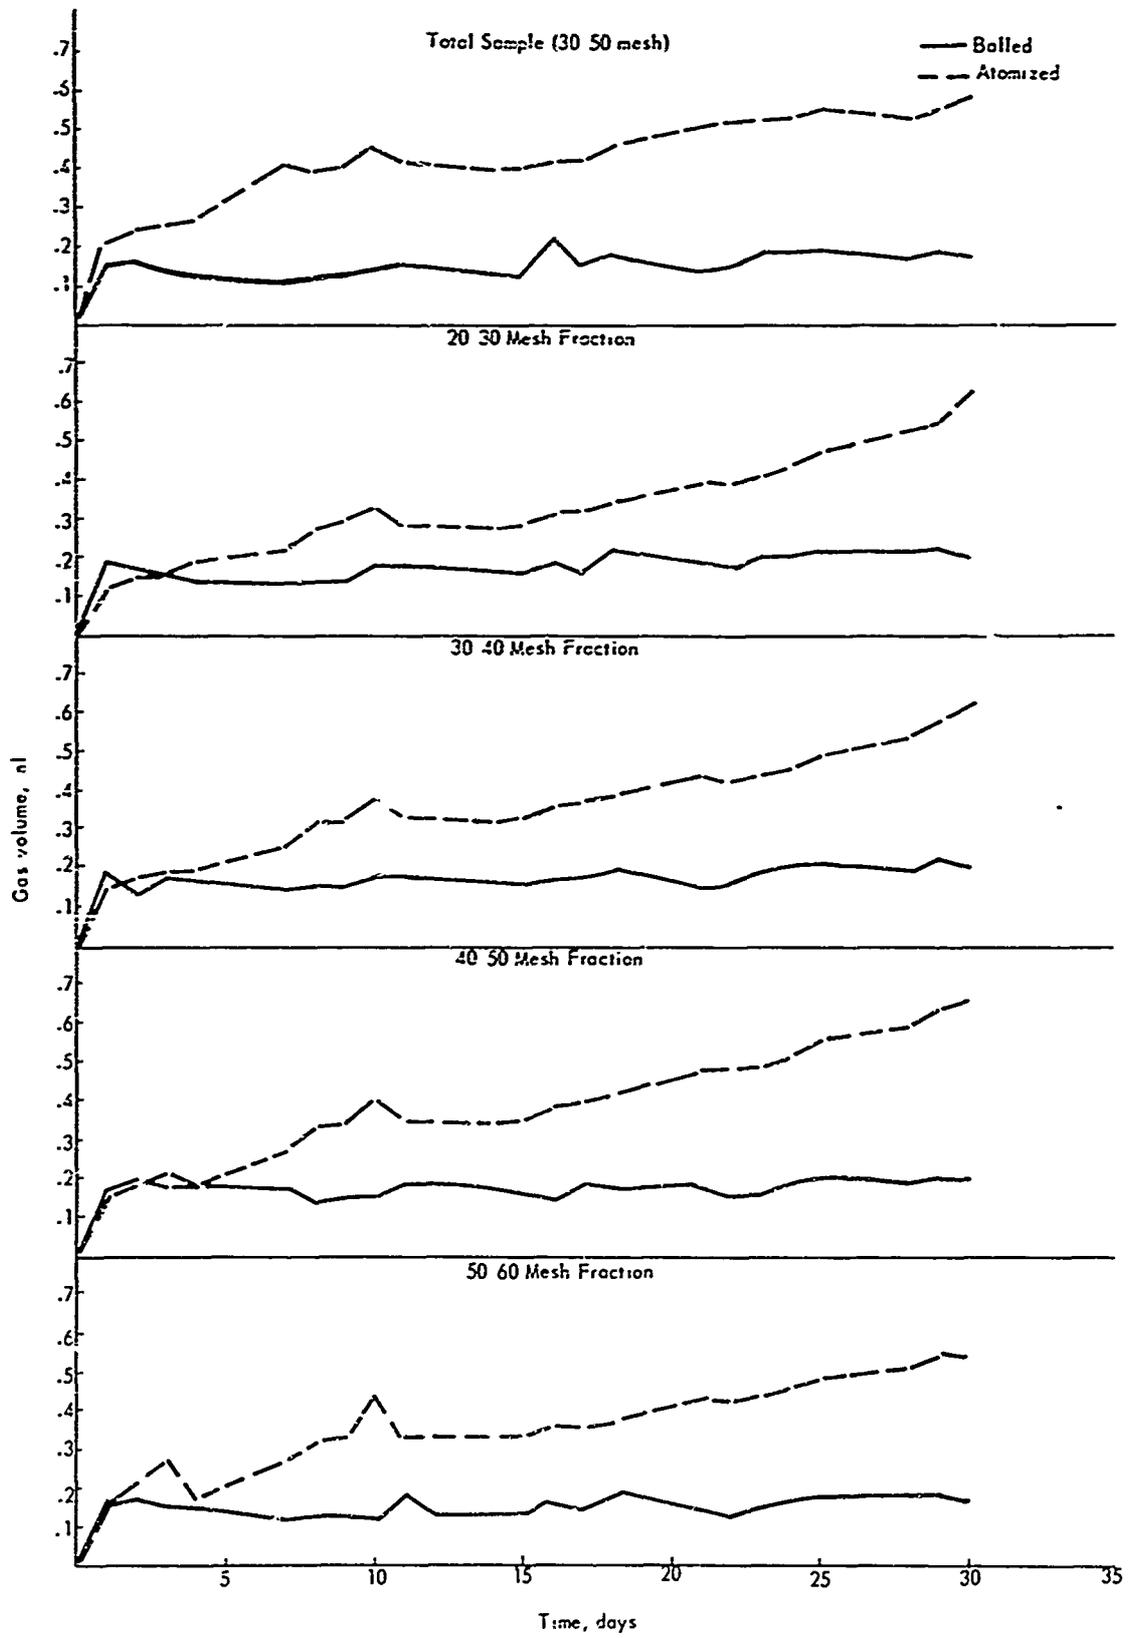


Fig 9 Vacuum stability at 110°C of balled and atomized magnesium

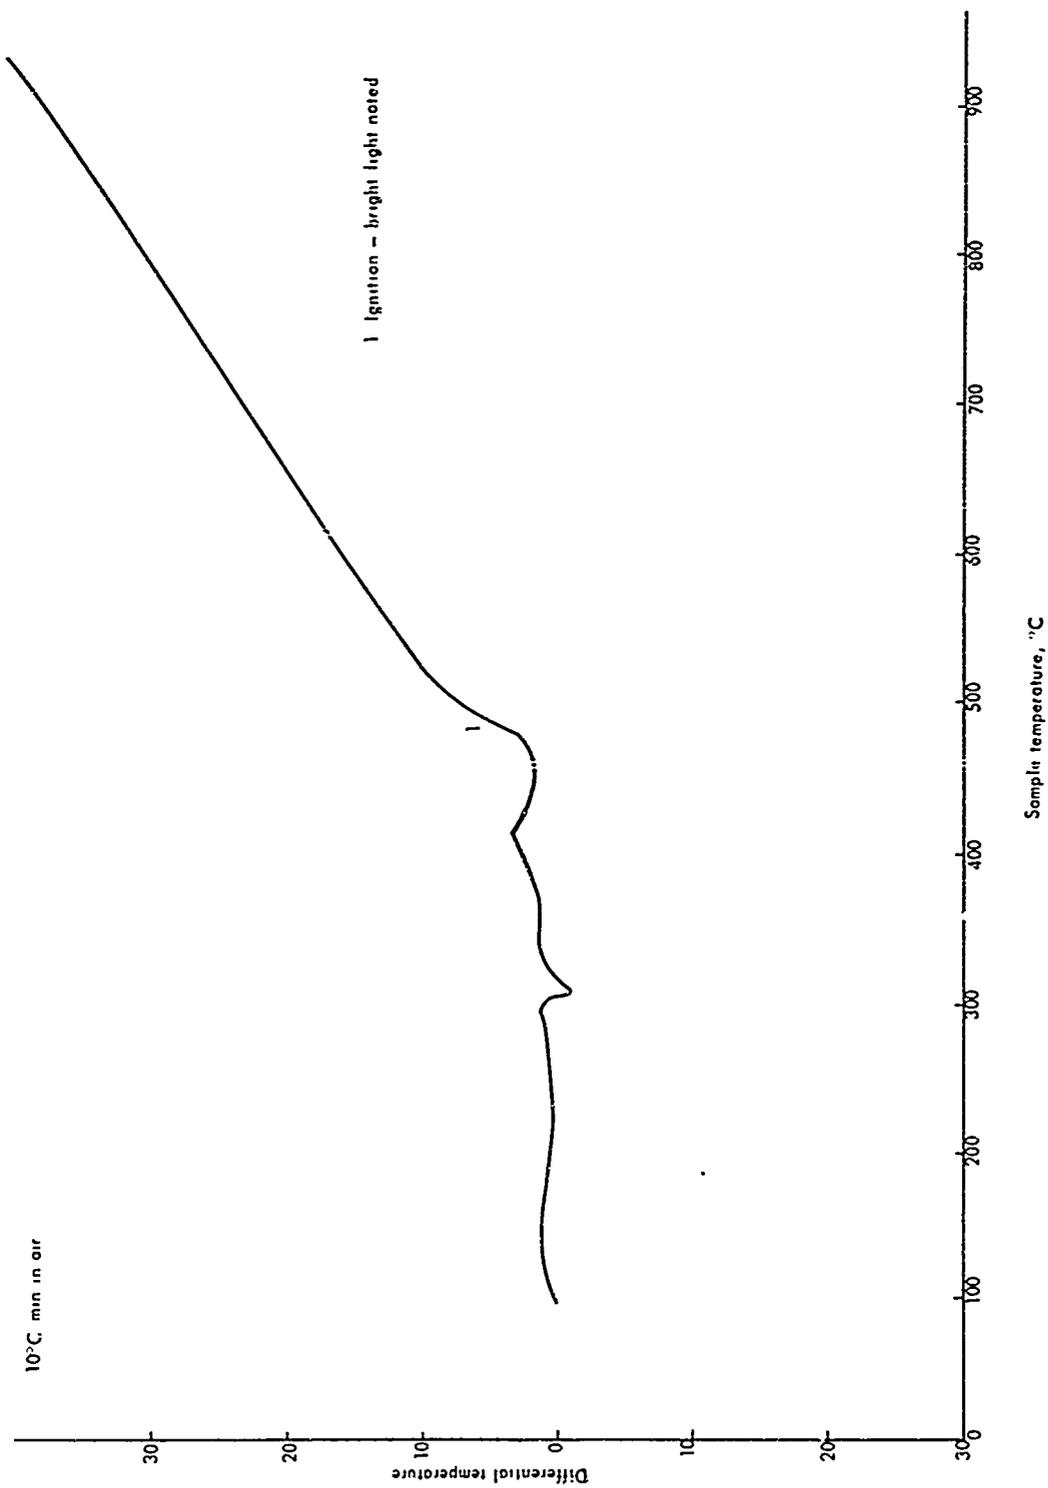


Fig 10 Differential thermal analysis of pyrotechnic composition* prepared with atomized magnesium
 *Composition: Mg, 30/50, atomized 56.0%
 Sodium nitrate, 34 microns 36.3%
 Laminac 4116 7.7%

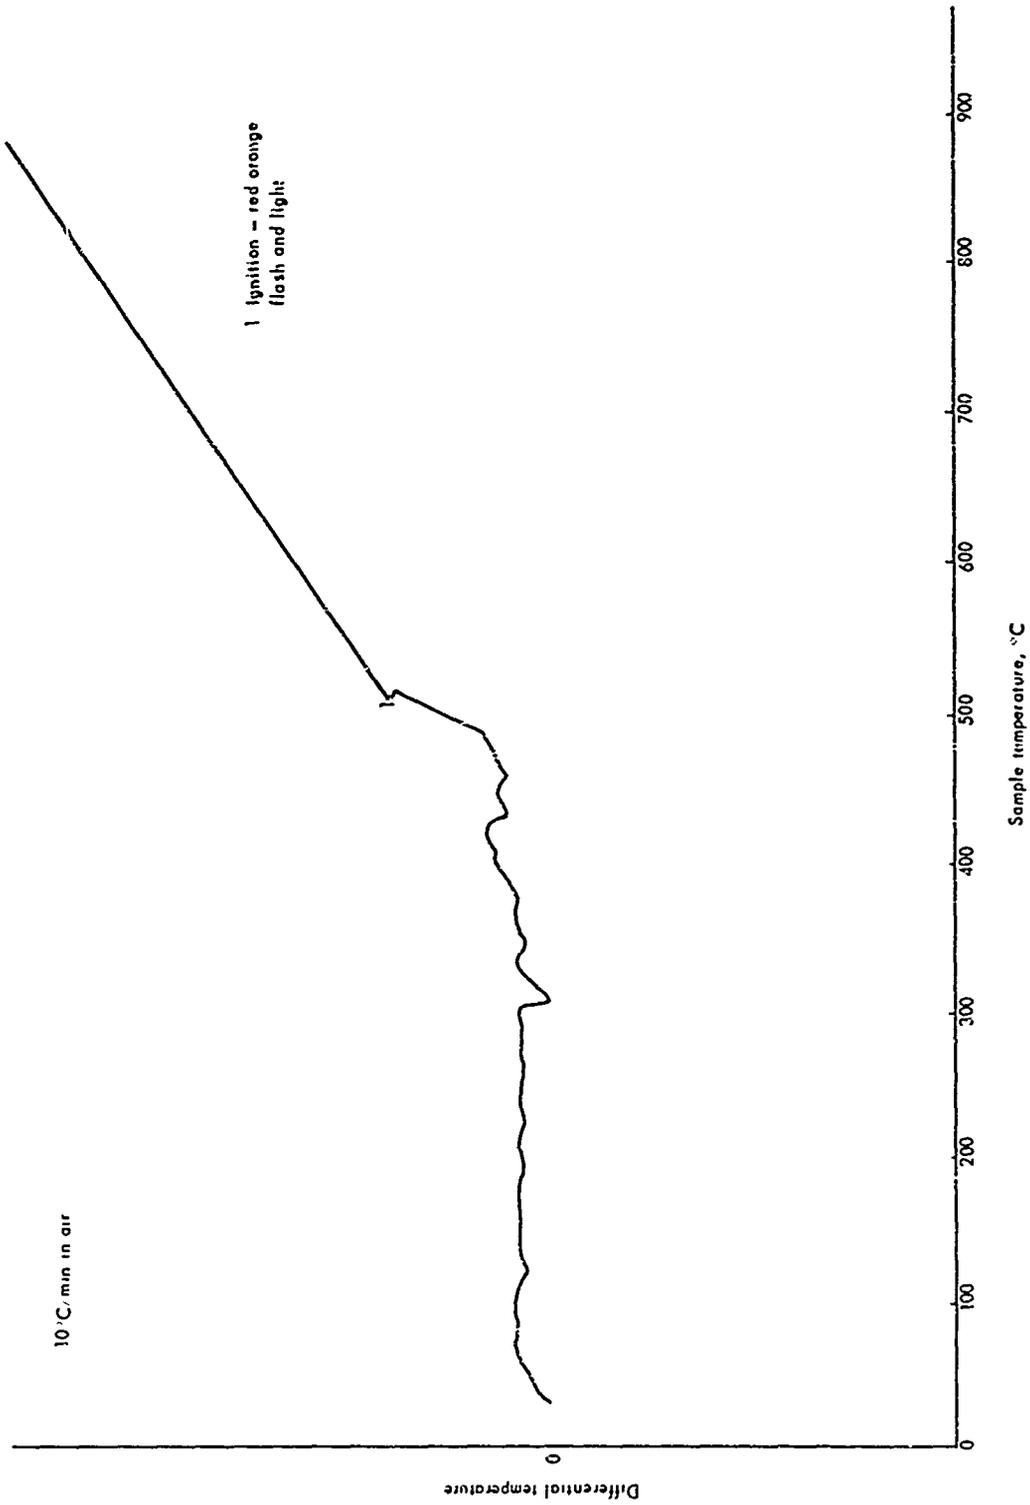


Fig 11 Differential thermal analysis of pyrotechnic composition* prepared with balled magnesium

*Composition: Mg, 30/50, balled 56.0%
 Sodium nitrate, 34 microns 36.3%
 Laminac 4116 7.7%

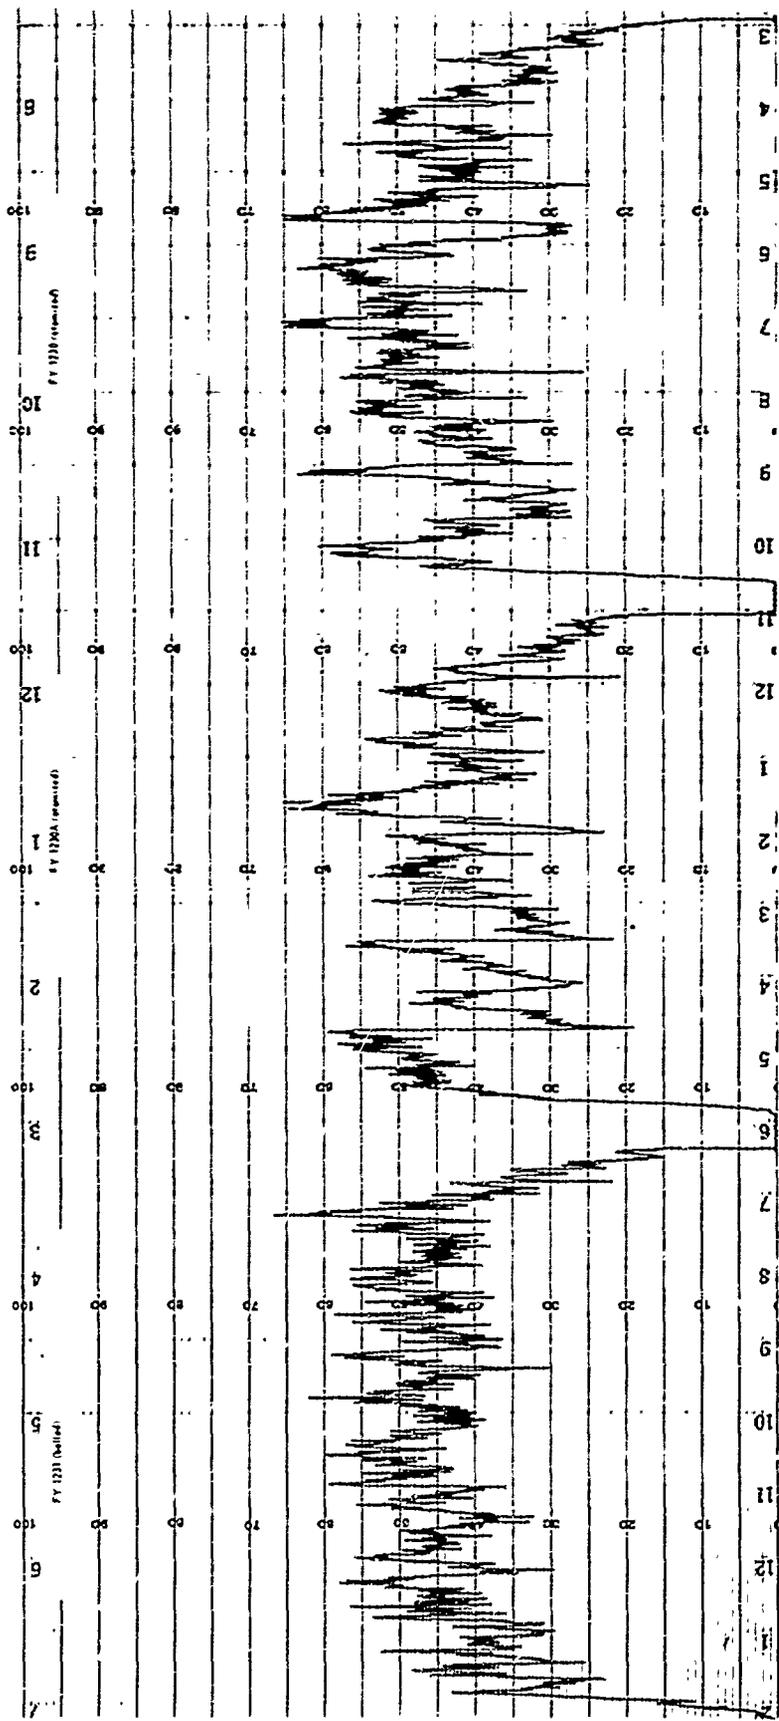


Fig 12 Typical luminous intensity vs time traces of compositions containing atomized and balled magnesium

UNCLASSIFIED
Security Classification

DOCUMENT CONTROL DATA - R&D		
<i>(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)</i>		
1. ORIGINATING ACTIVITY (Corporate author)		2a. REPORT SECURITY CLASSIFICATION
Picatinny Arsenal, Dover, N. J. 07801		Unclassified
		2b. GROUP
3. REPORT TITLE		
COMPARISON OF MECHANICALLY BALLED MAGNESIUM WITH ATOMIZED MAGNESIUM FOR USE IN PYROTECHNIC COMPOSITIONS		
4. DESCRIPTIVE NOTES (Type of report and inclusive dates)		
5. AUTHOR(S) (Last name, first name, initial)		
Carrazza, Jr., James A., Middlebrooks, Doris E., Kaye, Seymour M.		
6. REPORT DATE	7a. TOTAL NO. OF PAGES	7b. NO. OF REFS
September 1966	46	19
8a. CONTRACT OR GRANT NO.	9a. ORIGINATOR'S REPORT NUMBER(S)	
b. PROJECT NO. DA Project 504-01-207	TR 3364	
c. AMCMS Code 5523.11.558	9b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report)	
d.		
10. AVAILABILITY/LIMITATION NOTICES		
Distribution of this document is unlimited.		
11. SUPPLEMENTARY NOTES	12. SPONSORING MILITARY ACTIVITY	
13. ABSTRACT		
<p>Results of a variety of physical and chemical tests indicate that, with a few minor exceptions, Reade (balled) magnesium meets the requirements of Military Specification 14067-A for 30/50 mesh magnesium powder. The balled magnesium has been found to be less reactive than the currently prescribed atomized magnesium, both with water and as a result of exposure to high relative humidities, as determined by gas evolution, weight gain, and surface area measurements. Results of vacuum stability tests at 167°F and 230°F for thirty days indicate that the balled magnesium has greater stability than atomized magnesium; the thermochemical and sensitivity data for balled magnesium and atomized magnesium are comparable. In performance characteristics such as candlepower, burning rate, and luminous efficiency, similar results were obtained with the two materials. These results indicate that the Reade balled magnesium can be used as an alternate for Valley atomized 30/50 mesh magnesium in consolidated pyrotechnic compositions.</p>		

KEY WORDS	LINK A		LINK B		LINK C	
	ROLE	WT	ROLE	WT	ROLE	WT
Pyrotechnics Mechanically balled magnesium Atomized magnesium Vacuum stability tests Candlepower Burning rate Luminous efficiency Thermochemical data Particle size distribution Heat of combustion Sensitivity						

INSTRUCTIONS

1. ORIGINATING ACTIVITY: Enter the name and address of the contractor, subcontractor, grantee, Department of Defense activity or other organization (*corporate author*) issuing the report.

2a. REPORT SECURITY CLASSIFICATION: Enter the overall security classification of the report. Indicate whether "Restricted Data" is included. Marking is to be in accordance with appropriate security regulations.

2b. GROUP: Automatic downgrading is specified in DoD Directive 5200.10 and Armed Forces Industrial Manual. Enter the group number. Also, when applicable, show that optional markings have been used for Group 3 and Group 4 as authorized.

3. REPORT TITLE: Enter the complete report title in all capital letters. Titles in all cases should be unclassified. If a meaningful title cannot be selected without classification, show title classification in all capitals in parenthesis immediately following the title.

4. DESCRIPTIVE NOTES: If appropriate, enter the type of report, e.g., interim, progress, summary, annual, or final. Give the inclusive dates when a specific reporting period is covered.

5. AUTHOR(S). Enter the name(s) of author(s) as shown on or in the report. Enter last name, first name, middle initial. If military, show rank and branch of service. The name of the principal author is an absolute minimum requirement.

6. REPORT DATE: Enter the date of the report as day, month, year; or month, year. If more than one date appears on the report, use date of publication.

7a. TOTAL NUMBER OF PAGES: The total page count should follow normal pagination procedures, i.e., enter the number of pages containing information.

7b. NUMBER OF REFERENCES: Enter the total number of references cited in the report.

8a. CONTRACT OR GRANT NUMBER: If appropriate, enter the applicable number of the contract or grant under which the report was written.

8b, 8c, & 8d. PROJECT NUMBER: Enter the appropriate military department identification, such as project number, subject number, system numbers, task number, etc.

9a. ORIGINATOR'S REPORT NUMBER(S): Enter the official report number by which the document will be identified and controlled by the originating activity. This number must be unique to this report.

9b. OTHER REPORT NUMBER(S). If the report has been assigned any other report numbers (*either by the originator or by the sponsor*), also enter this number(s).

10. AVAILABILITY/LIMITATION NOTICES: Enter any limitations on further dissemination of the report, other than those imposed by security classification, using standard statements such as:

- (1) "Qualified requesters may obtain copies of this report from DDC."
- (2) "Foreign announcement and dissemination of this report by DDC is not authorized."
- (3) "U. S. Government agencies may obtain copies of this report directly from DDC. Other qualified DDC users shall request through _____."
- (4) "U. S. military agencies may obtain copies of this report directly from DDC. Other qualified users shall request through _____."
- (5) "All distribution of this report is controlled. Qualified DDC users shall request through _____."

If the report has been furnished to the Office of Technical Services, Department of Commerce, for sale to the public, indicate this fact and enter the price, if known.

11. SUPPLEMENTARY NOTES: Use for additional explanatory notes.

12. SPONSORING MILITARY ACTIVITY: Enter the name of the departmental project office or laboratory sponsoring (*paying for*) the research and development. Include address.

13. ABSTRACT: Enter an abstract giving a brief and factual summary of the document indicative of the report, even though it may also appear elsewhere in the body of the technical report. If additional space is required, a continuation sheet shall be attached.

It is highly desirable that the abstract of classified reports be unclassified. Each paragraph of the abstract shall end with an indication of the military security classification of the information in the paragraph, represented as (TS), (S), (C), or (U).

There is no limitation on the length of the abstract. However, the suggested length is from 150 to 225 words.

14. KEY WORDS: Key words are technically meaningful terms or short phrases that characterize a report and may be used as index entries for cataloging the report. Key words must be selected so that no security classification is required. Identifiers, such as equipment model designation, trade name, military project code name, geographic location, may be used as key words but will be followed by an indication of technical context. The assignment of links, rules, and weights is optional.