BRL
1342
c.2A

BRL R 1342

BRL

AD 644734

REPORT NO. 1342

A NUMERICAL SOLUTION TO AN ABLATION PROBLEM WITH POSSIBLE LASER APPLICATIONS

by

James G. Faller

October 1966

Distribution of this document is unlimited.

U. S. ARMY MATERIEL COMMAND
BALLISTIC RESEARCH LABORATORIES
ABERDEEN PROVING GROUND, MARYLAND

Destroy this report when it is no longer needed.
Do not return it to the originator.

The findings in this report are not to be construed as an official Department of the Army position, unless so designated by other authorized documents.

B A L L I S T I C R E S E A R C H L A B O R A T O R I E S

REPORT NO. 1342

OCTOBER 1966

Distribution of this document is unlimited.

A NUMERICAL SOLUTION TO AN ABLATION PROBLEM WITH POSSIBLE LASER APPLICATIONS

James G. Faller

PROPERTY OF U.S. ARMY
[illegible]
[illegible], [illegible], [illegible], [illegible]

Terminal Ballistics Laboratory

RDT&E Project No. 1P014501A31C

A B E R D E E N P R O V I N G G R O U N D, M A R Y L A N D

B A L L I S T I C R E S E A R C H L A B O R A T O R I E S

REPORT NO. 1342

JGFaller/sjw
Aberdeen Proving Ground, Md.
October 1966

A NUMERICAL SOLUTION TO AN ABLATION PROBLEM WITH POSSIBLE LASER APPLICATIONS

ABSTRACT

The problem of an ablating solid of limited extent under an applied non-uniform heat input is solved numerically, and the solution is compared in certain limiting cases with results from the exact analytical equations. Further, the usefulness of this model in predicting the depth of hole made in materials by a laser beam is explored.

TABLE OF CONTENTS

		Page
	ABSTRACT	3
1.	INTRODUCTION	7
2.	STATEMENT OF THE PROBLEM	7
3.	FINITE DIFFERENCES	10
4.	CALCULATING PROCEDURE	14
	4.1 General	14
	4.2 Detailed Procedure	15
5.	ERROR ANALYSIS	18
6.	AN EXAMPLE FOR LASER-INDUCED DAMAGE	22
7.	CONCLUSIONS	26
	REFERENCES	27
	DISTRIBUTION LIST	29

1. INTRODUCTION

The problem of an ablating* solid of limited extent under an applied non-uniform heat input is solved numerically, and the solution is compared in certain limiting cases with results from the exact analytical equations. Further, the usefulness of this model in predicting the depth of hole made in materials by a laser beam is explored.

Problems similar to the one considered have been formulated by numerous investigators,[1-8]** and some particular solutions exist. A numerical solution for this problem has been given by Landau[1] for the special case of a constant heat input to a semi-infinite solid. More recently Ready[4] reporting the effects of the absorption of laser radiation on metals introduced results from the ablation model for the case of a semi-infinite solid under a non-uniform heat input; but, he gave no details of the solution. In view of the very restrictive (specialized) treatment which this problem has received in the literature and because of its possible application to certain laser effects, we find sufficient justification in its reconsideration.

2. STATEMENT OF THE PROBLEM

A slab of thickness B initially at temperature $T_o g(x)$ is heated on one end with energy $Hf(t)$ over an area with dimensions large enough in relation to the final depth of heat penetration that heat flow becomes mathematically one-dimensional. The other end of the slab is insulated.

---

* *Ablation is generally associated with vaporization and sublimation, but the meaning has been extended to include liquefaction in which the liquid is removed as it is formed.*

** *Superscript numbers denote references which may be found on page 27.*

Given a pulse of sufficient power density and a long enough time, the surface of the slab will reach the phase-change temperature.* The material which has been transformed is removed immediately and the surface recedes into the solid. We are interested primarily in determining the thickness of material transformed with time.

We make the following definitions:

c = specific heat of material at constant pressure, (cal/g^{o}C)

ρ = density of material, (g/cm^3)

K = thermal conductivity of material, (cal/cm ^{o}C sec)

κ = thermal diffusivity of material, equal to $K/c\rho$, (cm^2/sec)

L = latent heat of transformation of material, (cal/g)

$T_o g(x)$ = initial temperature distribution of material, (^{o}C); for $g(x) = 1$ the temperature is initially uniform throughout the material.

T_L = transformation temperature of material, (^{o}C)

$y(t)$ = thickness of material transformed, (cm)

$Hf(t)$ = heat input as a function of time where H is a given constant, (cal/cm^{2}sec); $f(t) = 1$ for a uniform heat input

B = initial thickness of material, (cm)

The following equations describe the process:

$$T_t = \kappa T_{xx} \quad y(t) \le x < B, \; t > 0 \; , \tag{2.1}$$

$$T(x,0) = T_o g(x) < T_L \quad 0 \le x \le B \; , \tag{2.2}$$

$$T_x(B,t) = 0 \; , \tag{2.3}$$

$$Hf(t) = - KT_x \quad y(t) = 0 \; , \tag{2.4}$$

---

* *Whether the phase-change temperature is that for melting or vaporization will depend on the incident power density. At low densities only liquid will appear; whereas, at high densities the liquid formed prior to vaporization can be ignored because the latent heat of melting is much smaller than that of vaporization.*

$$Hf(t) = -KT_x + \rho L \frac{dy(t)}{dt} \quad , \tag{2.5}$$

$$\frac{dy(t)}{dt} \geq 0 \quad \text{for } T(y(t),t) = T_L \ , \tag{2.6}$$

$$\frac{dy(t)}{dt} = 0 \quad \text{for } T(y(t),t) < T_L \ . \tag{2.7}$$

Equation (2.1) may be recognized as the general parabolic relation of heat flow. The initial temperature distribution of the slab is given by (2.2), while (2.3) expresses the condition of no heat losses from the backface. Equation (2.5) is a statement relating the heat input to the rate of heat flow into the solid plus the rate of heat absorbed in the transformation. T_x is evaluated at the position of the boundary $y(t)$. Before the phase-change temperature is reached there is no boundary motion, (2.7), so that (2.5) reduces to (2.4). Equation (2.6) states that when the surface reaches the temperature T_L there may or may not occur boundary motion; this will depend on whether the energy required for the phase-change is or is not absorbed at the surface.

The equations can be manipulated more readily if the following transformations are made:

$$v(x,t) = \frac{T(x,t)}{T_L} \quad ,$$

$$\tau = Kt \ ,$$

$$N = \frac{L}{cT_L} \quad ,$$

$$p = \frac{H}{KT_L} \quad .$$

Equations (2.1) through (2.7) then become

$$v_\tau = v_{xx} \quad y(\tau) \leq x < B, \quad \tau > 0 \quad , \tag{2.8}$$

$$v(x,0) = v_o g(x) < 1 \quad 0 \leq x \leq B \ , \tag{2.9}$$

$$v_x(B,\tau) = 0 \quad , \tag{2.10}$$

$$pf(\tau) = - v_x \qquad y(\tau) = 0 \ , \tag{2.11}$$

$$pf(\tau) = - v_x + N \frac{dy(\tau)}{d\tau} \quad , \tag{2.12}$$

$$\frac{dy(\tau)}{d\tau} \geq 0 \quad \text{for } v(y(\tau),\tau) = 1 \ , \tag{2.13}$$

$$\frac{dy(\tau)}{d\tau} = 0 \quad \text{for } v(y(\tau),\tau) < 1 \ . \tag{2.14}$$

3. FINITE DIFFERENCES

We denote $v_{i,j}$ to be the value of v at the point i Δx at time j $\Delta\tau$ and $v_{i,j+1}$ the corresponding value at time (j+1) $\Delta\tau$. We further define according to practice $h = \Delta x$, $k = \Delta\tau$ and $r = \frac{k}{h^2}$. If the Crank-Nicholson differencing scheme[6] is selected, the time derivative can be approximated by

$$v_\tau = \frac{v_{i,j+1} - v_{i,j}}{k} + 0\left[k^2\right] \quad , \tag{3.1}$$

and the second order space derivative by

$$\begin{aligned} v_{xx} = \frac{1}{2h^2}\Big[\left(v_{i+1,j+1} + v_{i+1,j}\right) - 2\left(v_{i,j+1} + v_{i,j}\right) \\ + \left(v_{i-1,j+1} + v_{i-1,j}\right)\Big] + 0\left[kh^2\right] \ , \end{aligned} \tag{3.2}$$

where $0\left[\quad\right]$ is the truncation error. Substituting (3.1) and (3.2) in (2.8), introducing $r = \frac{k}{h^2}$ and rearranging we obtain

$$\begin{aligned} -\frac{r}{2} v_{i-1,j+1} + (1+r)v_{i,j+1} - \frac{r}{2} v_{i+1,j+1} = \\ \frac{r}{2} v_{i-1,j} + (1-r)v_{i,j} + \frac{r}{2} v_{i+1,j} \ . \end{aligned} \tag{3.3}$$

Equation (3.3) does not hold at the mathematical surface i = 0 since no account has been taken of the energy input to the material. This is dealt with by expanding $v_{i,j}$ in a Taylor series about the point (0, j+1) in both the space and the time directions. Thus

$$v_{1,j+1} = v_{0,j+1} + \left[\frac{\partial v}{\partial x}\right]_{0,j+1} \Delta x + (1/2) \left[\frac{\partial^2 v}{\partial x^2}\right]_{0,j+1} (\Delta x)^2 + 0\left[(\Delta x)^3\right] . \tag{3.4}$$

$$v_{0,j} = v_{0,j+1} - \left[\frac{\partial v}{\partial \tau}\right]_{0,j+1} \Delta\tau + \left[(\Delta\tau)^2\right] . \tag{3.5}$$

If $\left[\partial^2 v/\partial x^2\right]_{0,j+1}$ is replaced by $[\partial v/\partial \tau]_{0,j+1}$ in accordance with (2.8), then from (3.4), (3.5), and (2.11) the resulting equation becomes

$$(1+2r)v_{0,j+1} - 2rv_{1,j+1} = v_{0,j} + 2rhpf_{j+1} . \tag{3.6}$$

Equation (3.6) applies up to the time that the phase-change temperature is reached, i.e., so long as $y(\tau) = 0$.

Beyond this point account must be taken of the fact that the boundary no longer remains stationary. To avoid ambiguity in the use of the space coordinate i, a new coordinate w is defined such that the boundary will always lie at w or between w and w + 1. At the original surface w = 0. The index w, an integer, depends upon time, hence we denote this dependence by w_j. Initially, that is, at j = 0, $w_0 = 0$; however, at later times $0 \le w_j \le w_{j+1}$ and for each j the boundary lies between w_j and w_{j+1}. During boundary motion the temperature of the surface according to (2.13) is a known constant so that the first unknown temperature lies at the grid point w + 1 and is designated $v_{w+1,j+1}$. We expand about this point in both the time and space directions,

$$v_{w+s,j+1} = v_{w+1,j+1} - \left[\frac{\partial v}{\partial x}\right]_{w+1,j+1} (1-s)\,\Delta x + (1/2)\left[\frac{\partial^2 v}{\partial x^2}\right]_{w+1,j+1} (1-s)^2\Delta x^2 + 0\left[(\Delta x)^3\right] , \tag{3.7}$$

$$v_{w+1,j} = v_{w+1,j+1} - \left[\frac{\partial v}{\partial \tau}\right]_{w+1,j+1} \Delta\tau + 0\left[(\Delta\tau)^2\right] , \tag{3.8}$$

$$\begin{aligned} v_{w+2,j+1} = v_{w+1,j+1} &+ \left[\frac{\partial v}{\partial x}\right]_{w+1,j+1} \Delta x \\ &+ (1/2)\left[\frac{\partial^2 v}{\partial x^2}\right]_{w+1,j+1} \Delta x^2 + 0\left[(\Delta x)^3\right]. \end{aligned} \tag{3.9}$$

and where $0 \le s \le 1$. But at the surface we have $v_{w+s,j+1} = 1$. Further, if (3.7) and (3.9) are added after (3.9) has been multiplied through by (1-s) and (2.8) and (3.8) are substituted in that order in the resulting equation, we obtain

$$\begin{aligned} \left(2-s_{j+1}\right)\left(2r + 1-s_{j+1}\right) v_{w+1,j+1} - 2r\left(1-s_{j+1}\right) v_{w+2,j+1} = \\ \left(1-s_{j+1}\right)\left(2-s_{j+1}\right) v_{w+1,j} + 2r \cdot \end{aligned} \tag{3.10}$$

For clarity the subscript j+1 has been attached to s to show the exact time at which this quantity is evaluated.

Next the position of the boundary $y(\tau)$ must be determined. From the preceding discussion it is clear that y may be expressed in terms of an integer w and a fraction s by

$$y_j = \left(w_j + s_j\right) h , \tag{3.11a}$$

and

$$y_{j+1} = \left(w_{j+1} + s_{j+1}\right) h . \tag{3.11b}$$

Subtracting (3.11a) from (3.11b) we obtain

$$y_{j+1} - y_j = \Delta y = h\left[\left(w_{j+1} - w_j\right) + \left(s_{j+1} - s_j\right)\right]. \tag{3.12}$$

Since y_j, w_j and s_j are zero at the start of the transformation, there is no difficulty in keeping track of the boundary for subsequent times provided Δy can be calculated. This may be done from (2.12) which has the finite difference form

$$\frac{\Delta y}{k} = \left[\tilde{v}_x + pf_{j+1}\right] / N \quad , \tag{3.13}$$

where $\tilde{v}_x$ is the approximation of the space derivative v_x at the surface and may be evaluated by a three point Gregory-Newton forward difference approximation as

$$\begin{aligned} \tilde{v}_x = \Big[& -\left(5-2s_{j+1}\right) v_{w+1,j+1} \\ & + 4\left(2 - s_{j+1}\right) v_{w+2,j+1} \\ & -\left(3 - 2s_{j+1}\right) v_{w+3,j+1}\Big] / 2h \ . \end{aligned} \tag{3.14}$$

Equation (3.13) can be arranged more conveniently in terms of r giving

$$\frac{\Delta y}{h} = \frac{rh}{N}\left[\tilde{v}_x + pf_{j+1}\right] \ . \tag{3.15}$$

One is confronted in (3.15) with the evaluation of s_{j+1} from temperatures which are not known and which themselves cannot be calculated without knowing s_{j+1}. To circumvent this problem an iterative procedure must be used.

Finally, we note that at the back surface (3.3) must be modified to take into account the boundary condition (2.10). Formally, this is done by extending the mesh one unit past the back face,* where the latter is indexed by $i = M = B/\Delta x$. The existence of a zero temperature gradient requires that $v_{M-1} = v_{M+1}$ which reduces (3.3) at the back face to

$$-rv_{M-1,j+1} + (1 + r)v_{M,j+1} = (1 - r)v_{M,j} + rv_{M-1,j}. \tag{3.16}$$

* *Creating a false boundary.*

4. CALCULATING PROCEDURE

4.1 General

The difference equations of Section 3 from which the temperatures are computed have the tridiagonal appearance (for each mesh row)

$$
\begin{aligned}
B_0 v_0 + C_0 v_1 &= d_0 \\
A_1 v_0 + B_1 v_1 + C_1 v_2 &= d_1 \\
0 v_0 + A_2 v_1 + B_2 v_2 + C_2 v_3 &= d_2 \\
&\vdots \\
A_{M-1} v_{M-2} + B_{M-1} v_{M-1} + C_{M-1} v_M &= d_{M-1} \\
A_M v_{M-1} + B_M v_M &= d_M ,
\end{aligned}
\tag{4.1}
$$

with zeros everywhere except on the main diagonal and on the two diagonals parallel to it on either side.[9] In (4.1) all known quantities have been lumped in d thereby eliminating the necessity of the further use of j. Through a Gaussian elimination process this system can be solved explicity for the unknown v's. The method is credited to L. H. Thomas,[10] but received wide attention in published form in an article by Bruce, Peaceman, Rachford, and Rice.[11] Expressed in a less cumbersome way[11] the system (4.1) becomes

$$B_0 v_0 + C_0 v_1 = d_0 , \tag{a}$$

$$A_i v_{i-1} + B_i v_i + C_i v_{i+1} = d_i \qquad 1 \le i \le M - 1, \tag{4.2)(b}$$

$$A_M v_{M-1} + B_M v_M = d_M , \tag{c}$$

where the unknown temperatures corresponding to the $(j+1)^{st}$ step are given by

$$v_M = q_M$$

$$v_i = q_i - b_i v_{i+1} \qquad 0 \le i \le M - 1 ,$$

with

$$q_0 = \frac{d_0}{B_0}$$

$$q_i = \frac{d_i - A_i q_{i-1}}{B_i - A_i b_{i-1}} \qquad 1 \le i \le M \tag{4.3}$$

$$b_0 = \frac{C_0}{B_0}$$

$$b_i = \frac{C_i}{B_i - A_i b_{i-1}} \qquad 1 \le i \le M - 1 .$$

For convenience the calculations are carried out in two parts - Part I covering up to the time the phase-change temperature is reached and Part II beyond this point. In Part I (4.2) represents the system (3.6), (3.3) and (3.16); in Part II (4.2) represents the system (3.10), (3.3) and (3.16) with (3.15) and (3.12) being used in locating the boundary. Also in Part II, (4.2a) is more appropriately indexed as

$$B_{w+1} v_{w+1} + C_{w+1} v_{w+2} = d_{w+1} ,$$

with i being greater than or equal to w+2 in the remaining equations.

4.2 Detailed Procedure

Part I - Before Transformation

Using Equations (3.3), (3.6) and (3.16) computation continues until for some $j = j'$, $v_{0,j'+1} \ge 1$ and $v_{0,j'} < 1$.

To establish an accurate time for the beginning of the phase-change and as a baseline for Part II, the $(j'+1)$st = Jth row is re-determined using a smaller time step k' given by

$$k' = \left(\frac{1 - u_{0,j'}}{u_{0,j'+1} - u_{0,j'}}\right) k \quad ,$$

or equivalently

$$r' = \left(\frac{1 - u_{0,j'}}{u_{0,j'+1} - u_{0,j'}}\right) r \quad .$$

The time of the start of transformation is simply

$$\tau_m = j'k + k' \ .$$

Part II - Boundary Begins to Move

As first step in Part II the boundary must be located. Since the temperatures at time J + 1 are yet to be determined, (3.15) cannot be used directly. We, therefore, approximate Δy by

$$\frac{\Delta y^0_{J+1}}{h} = \frac{r}{2N}\left[\left(-1.5 + 2v_{1,J} - .5v_{2,J}\right) + \left(hpf_{J+1}\right)\right] \ . \qquad (4.4)$$

The first term inside the brackets may be recognized as the three-point Lagrange interpolation expanded in the neighborhood of the moving boundary with w = s = 0. Multiplying the brackets by 1/2 ensures the Δy is not over estimated. In the absence of any boundary displacement at time J the initial estimate of the position of the boundary is

$$y^0_{J+1} = \Delta y^0_{J+1} \ . \qquad (4.5)$$

where the superscript designates the number of the iteration n, taken to be zero initially.

Further y^0_{J+1} is decomposed into its whole and fractional components,

$$y^0_{J+1} = h\left(w^0_{J+1} + s^0_{J+1}\right) \quad . \tag{4.6}$$

At this point (3.10), (3.3) and (3.16) are solved for all $v_{i,J+1}$. It should be emphasized that temperatures $v_{i,J}$ are not replaced by those at $v_{i,J+1}$ until the iteration for the (J+1) step has been completed.

Using s^0_{J+1} and the appropriate $v_{i,J+1}$'s a new estimate of the boundary position is obtained from (3.15). This then becomes Δy^1_{J+1} from which y^1_{J+1} is derived. As an improved estimate of the boundary position the n and (n+1) iterative values of y_{J+1} are combined and a new s_{J+1} and w_{J+1} are found,

$$\frac{y^0_{J+1} + y^1_{J+1}}{2} = h\left(w^1_{J+1} + s^1_{J+1}\right) . \tag{4.7}$$

Then the system (4.2) is again solved and the process is repeated a fixed number of times or until some test is satisfied. We have chosen the test that the absolute value of the ratio of the difference between two successive values of y to their average be less than some constant ϕ and write

$$\left| \frac{y^n - y^{n-1}}{\left(y^n + y^{n-1}\right)/2} \right| \leq \phi \ , \tag{4.8}$$

where $0 < \phi << 1$.

For an approximation to y in the succeeding time step J + 2, a linear change of the boundary with time is assumed,

$$y^0_{J+2} = y_{J+1} + \Delta y_{J+1} \quad , \tag{4.9}$$

where y_{J+1} and Δy_{J+1} represent values of the quantities obtained in the final iteration of the (J+1)st step. The above procedure commencing with (4.6) is then repeated. Computation continues until $\tau \geq \tau_{max}$, where τ_{max} is the duration of the input pulse.

5. ERROR ANALYSIS

With assurance of stability for independent h's and k's, error analysis is one of the prime considerations of a numerical method. This subject is currently under extensive study, and most discussions found in the literature are of a qualitative nature.[9] Two main sources of error generally encountered are present here and are (a) the truncation error arising from the approximation of the analytical equations by finite differences, and (b) the round-off error due to use of only a finite number of decimal places in the arithmetic operations and due to the fact that the iterative solution is only continued until there is no change out to a certain decimal place. These errors are oppositely influenced by the interval size h. Decreasing h decreases the truncation error but in general increases the round-off error.

An example will best serve to check the accuracy of the present solution. For a semi-infinite slab and a constant heat input the time required for the surface to reach the phase-change temperature can be compared to the exact analytical solution.[12] These times are shown in Table I using physical data for aluminum undergoing a phase-change at the melting temperature. It is readily seen that with decreasing h at constant r the approximate time that the surface reaches the melting temperature more nearly approaches that of the exact solution. The error in the approximate solution is reduced by the square of the factor by which h is decreased. Thus if h is diminished by a factor of 8, e.g., in going from h = .01 to h = .00125, the error will decline by a factor of 64.

TABLE I

Time of the start of melting for a semi-infinite solid as determined by (a) the exact analytical solution* and (b) the approximate solution of this paper for varying h and constant r = 0.4. Based on physical data of Al.**

Exact Solution time, sec	Approximate Solution time, sec	h	% Error
$.2082 \times 10^{-3}$	$.2475 \times 10^{-3}$	.01	19
	$.2180 \times 10^{-3}$	.005	4.7
	$.2107 \times 10^{-3}$	.0025	1.2
	$.2088 \times 10^{-3}$	.00125	.3

* *See Reference 12.*

** $K = .480$, $c = .214$, $\rho = 2.70$, $L = 94.5$, $T_o = 20$, $T_L = 660$, $H = 2.07 \times 10^4$, $B = 1.0$, $f(\tau) = 1.0$.

In Figure 1 the results of Table I are extended into Part II involving the moving boundary. Here, however, it is no longer possible to calculate an exact solution and the approximate results must be compared to the steady state solution (1) given by

$$y = \frac{H\left(t - t_L\right)}{\rho\left[L + c\left(T_L - T_o\right)\right]} , \qquad (5.1)$$

where in addition to the quantities already defined t is the duration of the pulse and t_L is the time required to reach the transformation temperature.

Equation (5.1) gives an upper limit to the penetration of the boundary, which in the time $t = .24 \times 10^{-2}$ sec is 0.0725 cm. Even for the least favorable choice in h the solution is reasonable. Except in the very short time after transformation has begun, the boundary motion is essentially linear with time.

It is not clear from the preceding discussion how one, short of trial and error, goes about making an appropriate selection of h. Time and accuracy must be simultaneously considered and some optimum found between the two. Rather than select h first it is more meaningful to choose k first and then find the desired h by $h = (k/r)^{1/2}$.* This is necessary because any choice in h no matter how small might not be applicable due to the short duration of an input pulse. For a nanosecond long input pulse as encountered in the q-switched laser mode an h of say .00125 would yield a k of 0.625×10^{-6} for r = 0.4 which exceeds the entire length of the pulse. In choosing a k one may be guided by a rule of thumb in which the total time of the pulse is divided into about one thousand k's i.e., max j = 1000. Then a back calculation can be made to find an approximate h which can also be divided into B to give some whole number M.

* *In implicit methods stability is ensured for all $r > 0$.* [*Ref. 9, p.339*].

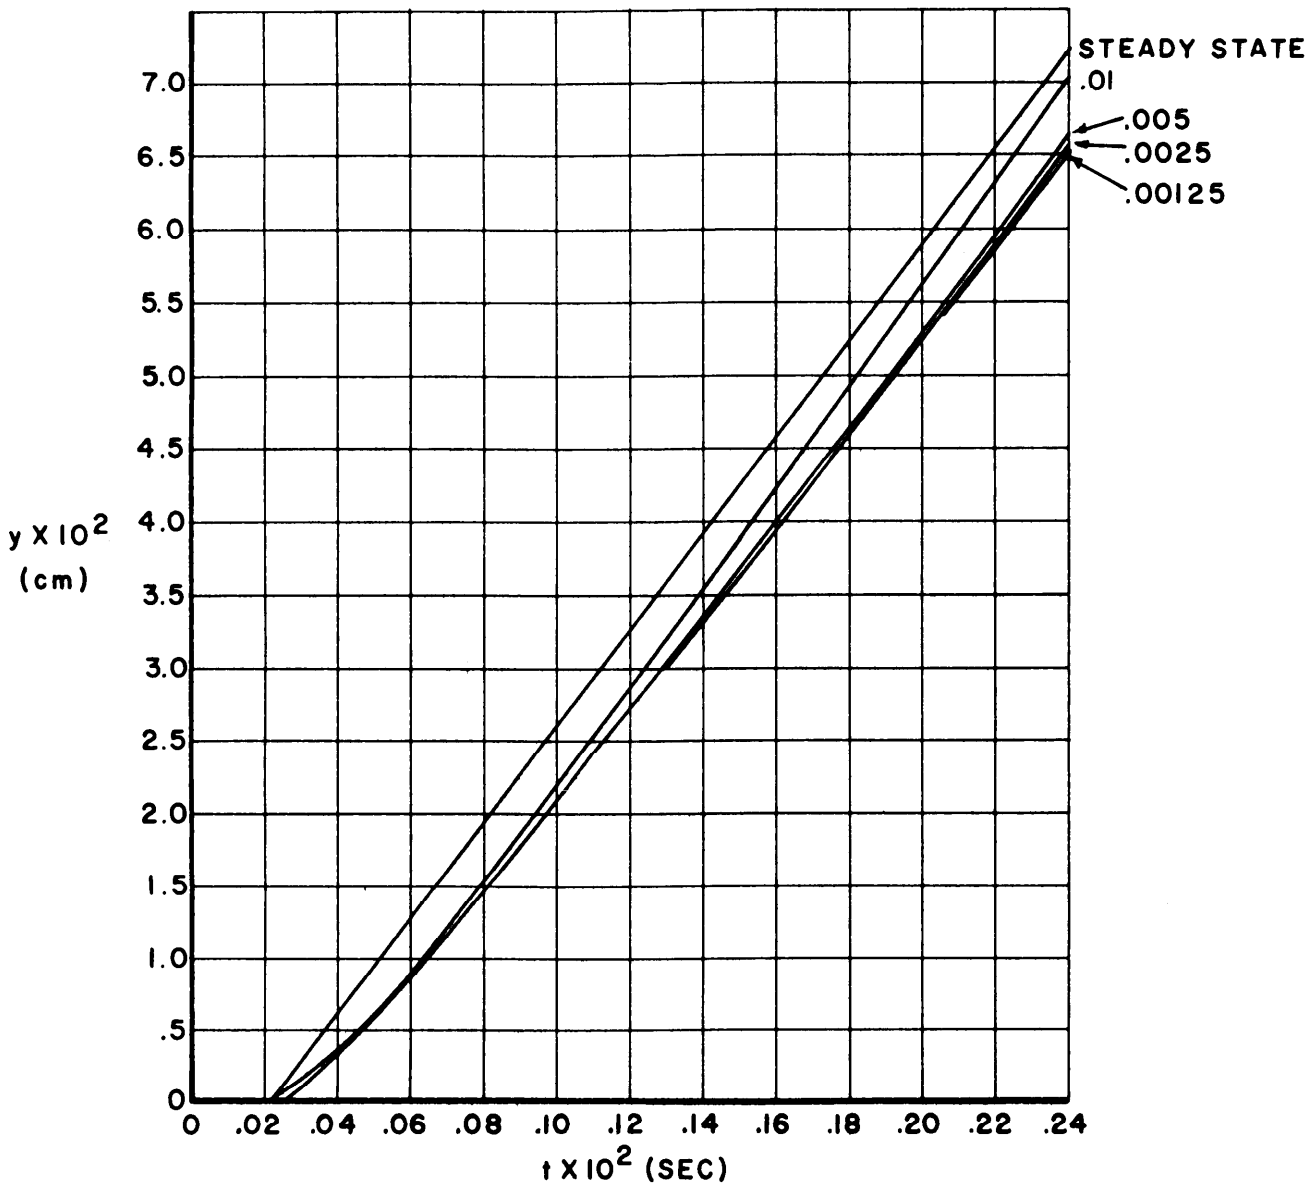

FIG. 1.-THE DEPENDENCE OF THE POSITION OF THE BOUNDARY y ON TIME t FOR CONSTANT r = .4 AND h OF .01, .005, .0025, .00125.

When the input energies are very large as in the case of the laser the time taken for the material to reach the transformation temperature is much shorter (sometimes by a factor of a thousand of more) than the duration of the entire pulse. It is, therefore, necessary to use different grid sizes for Parts I and II. If a single grid size is chosen say on the basis of the high resolution required in Part I the computational times required for Part II would become prohibitive. If on the other hand, the choice of grid sizes is made on the basis of the total pulse, the approximation of the time of the phase-change will contain a ridiculously large error. A rough idea for the onset time of the transformation may be obtained from an analytical solution of the heat equation. On this basis a reasonable selection of k and hence h may be made for Part I. The h selected in this manner may be so fine, however, that for the particular thickness of solid B, M will become an exceedingly large number. Insofar as the heat flow is concerned, only a small fraction of the total M points in the solid may register any change in temperature in the short times considered, the solid behaving as semi-infinite beyond a certain depth. Thus by either reducing B or equivalently reducing M by some arbitrary factor the times for calculation in Part I do not become prohibitive. When Part II is entered a much larger h may be used. To avoid the possibility of error the final temperature v_M may be printed as part of the output at the ends of Parts I and II. If v_M is the same as the initial temperature of the solid then the slab has remained semi-infinite throughout the length of the calculations.

6. AN EXAMPLE FOR LASER-INDUCED DAMAGE

In suggesting that the present problem may apply to laser-induced damage in materials we are cognizant of the pitfalls involved. The interaction of the laser with the target is a complex phenomenon. Several elements contribute to this complexity. It is not certain whether the plasma created in front of the target remains transparent to the beam throughout the duration of the pulse. It may be a safe

assumption to make at low incident power densities but not at high incident power densities such as those delivered by the laser in the q-switched mode. In addition to the plasma the target emits globules of transformed material which may further act to absorb the incoming beam. Another important consideration is the reflectance of the beam by the target which may be a strong function of the depth of hole, i.e., in the initial stages of heating and penetration highly reflecting materials such as aluminum may absorb only a small portion of the incoming radiation, while at a later stage or as the hole deepens, the entire incoming beam may be absorbed by being trapped in the hole. The model, furthermore, makes no allowance for the possibility of superheating or for the co-presence of vapor and liquid. Any attempt, however, to construct a mathematical model of laser damage which takes all the preceding factors into account would prove an enormously difficult task because a clear understanding of their relative significance is currently lacking.

In Table II and Figure 2, data are shown comparing the depth of hole predicted to that actually observed in Al of semi-infinite thickness. Case 1 in Table II is for a constant input energy, whereas Case 2 if for the variable pulse shown at the top of Figure 2. The lower portion of Figure 2 is a plot of the position of the boundary with time for this variable pulse with the maximum y being the entry in Table II.

In cases 1 and 2 the transformation is assumed to occur at the temperature of vaporization, the possibility of melting being totally ignored. Ignoring melting when vaporization is involved is not a serious error since the heat of vaporization and melting are so vastly different, the former being more than twenty-seven fold greater than the latter in Al.

The discrepancy, assuming full absorption of the energy of the beam by the target, is quite large. A second calculation has been done for each case at about half of this energy on the basis that much of the incident pulse is reflected. Specimens of Al treated with #300

TABLE II

DEPTH OF HOLE PRODUCED IN Al BY LASER PULSE

Case	Description of Pulse			
	Power Density joules/cm^2-sec	Duration sec	Calculated cm	Observed* cm
1	8.33×10^{6}	$.6 \times 10^{-3}$	1.43×10^{-1}	$.78 \times 10^{-1}$
	4.16×10^{6}	$.6 \times 10^{-3}$	$.695 \times 10^{-1}$	
2	1×10^{9} (peak)+	44×10^{-9}	6.05×10^{-4}	3.6×10^{-4}
	$.5 \times 10^{9}$	44×10^{-9}	2.87×10^{-4}	

* *See Reference 4.*

\+ *See Figure 2 for pulse shape.*

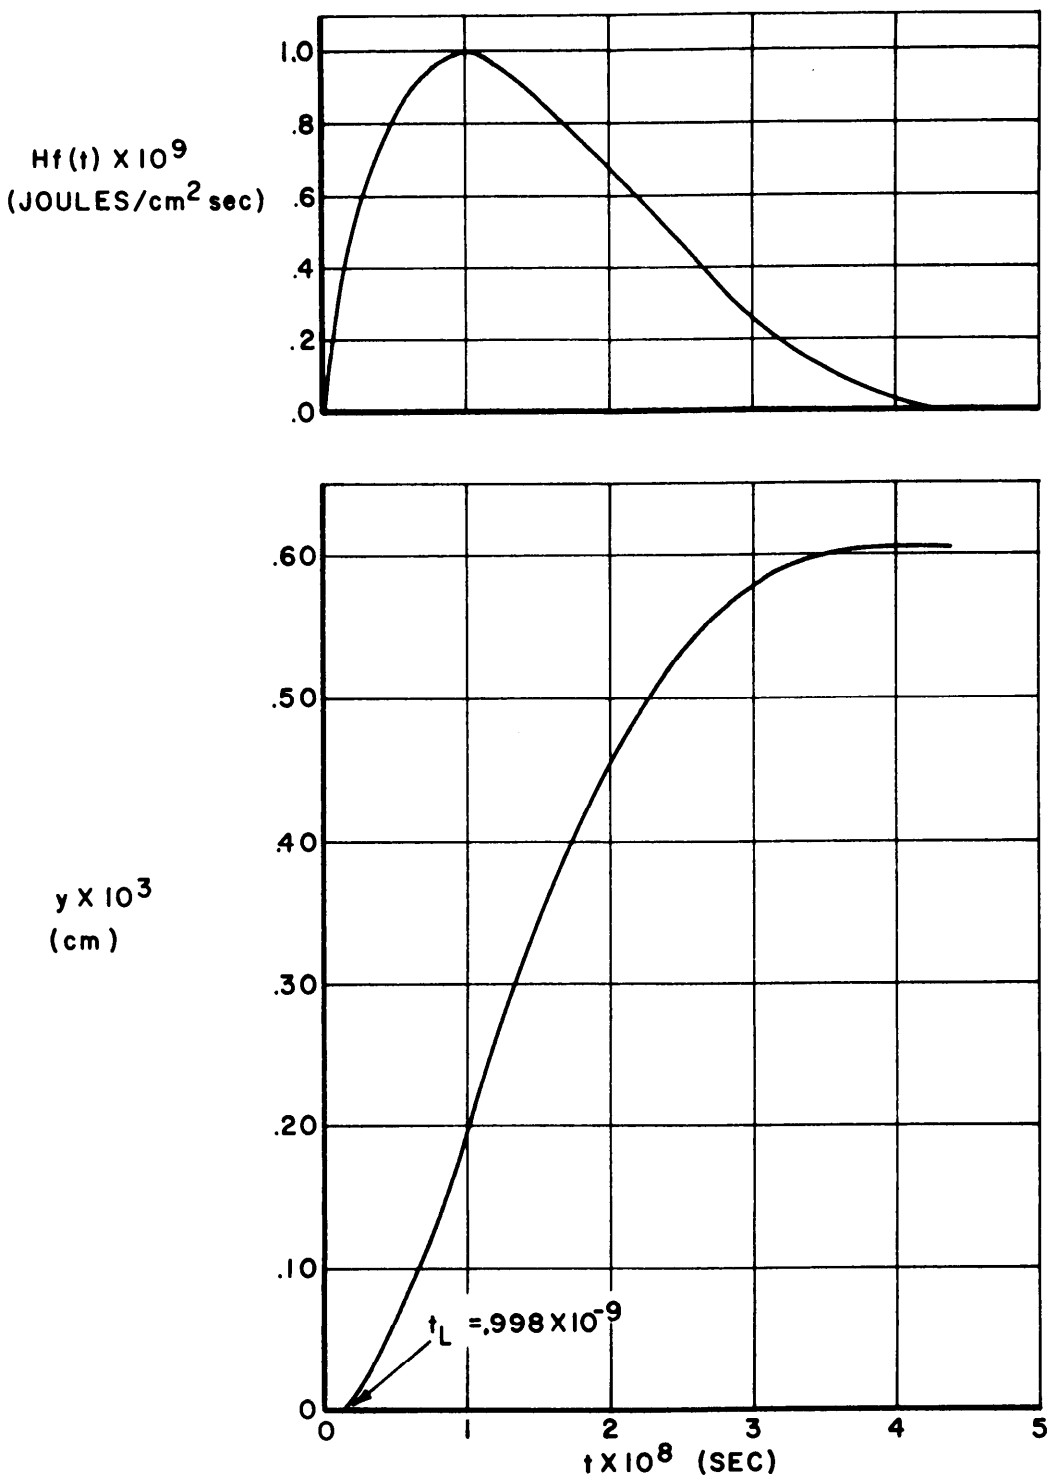

FIG. 2.- BOUNDARY MOTION y AS A FUNCTION OF THE TIME t FOR INPUT PULSE Hf(t) (SHOWN ON TOP GRAPH). MATERIAL IS Al AT VAPOR TEMPERATURE.

grit emery paper have been found in this laboratory to reflect up to 60 per cent of the incident light at room temperature. While large reflectance is a reasonable assumption during the heating-up, it is not known whether it will remain at or near the initial level for the entire length of the pulse. Better agreement with the experiment results when making the assumption of a constant reflectance throughout the pulse duration.

7. CONCLUSIONS

An implicit numerical scheme has been used successfully to solve the heat conduction problem for an ablating solid. The method introduces simplicity and accuracy in the calculations and allows for economic use of computer time. Further, the solution is valid for a variable input energy and sample thickness, features which make it especially suitable in applications related to the laser damage of materials.

In the example given for laser-induced damage to Aluminum we have purposely avoided manipulating our input energies etc., so as to obtain a better agreement with experimental observations. Published data of laser damage to targets is scarce and incomplete. Information concerning surface preparation, the spread in the measured input energies and depths, and the shape of the holes produced has never been set down for the same samples. In certain cases one cannot be certain whether a semi-infinite slab was used as reported or if the conditions for one-dimensional heat flow were truly satisfied. From the limited experimental observations considered, it is difficult to determine how widely the proposed model can be applied to predicting laser damage to targets.

ACKNOWLEDGEMENTS

I wish to thank Mr. Ralph Shear for his invaluable suggestions throughout the early stages of this project and Mrs. Alice Brown for writing the computer program.

JAMES G. FALLER

REFERENCES

1. H. G. Landau, "Heat Conduction in a Melting Solid," Q. Appl. Math. 8, 81 (1950).

2. L. W. Ehrlich, "A Numerical Method for Solving a Heat Flow Problem With a Moving Boundary," J. Assoc. Comp. Mach. 2, 161 (1958).

3. B. A. Boley, "Upper and Lower Bounds for the Solution of a Melting Problem," Q. Appl. Math. 21, 1 (1963).

4. J. F. Ready, "Effects Due to Absorption of Laser Radiation," J. Appl. Phys 36, 462 (1965).

5. J. Crank, "Two Methods for the Numerical Solution of Moving-Boundary Problems in Diffusion and Heat Flow, "Quart. J. Appl. Mech. and Appl. Math. 10, 220 (1957).

6. J. Crank and P. Nicholson, "A Practical Method for Numerical Evaluation of Solutions of Partial Differential Equations of the Heat-Conduction Type," Proc. Camb. Phil. Soc. 43, 50 (1947).

7. J. Douglas and T. M. Gallie, Jr., "On the Numerical Integration of a Parabolic Differential Equation Subject to a Moving Boundary Condition," Duke Math J. 22, 557 (1955).

8. F. P. Vasil ́ev, "The Method of Finite Differences for Solving Stephan's Single-Phase Problem for a Quasi-linear Equation," Soviet Math. 4, No. 5, 1393 (1963).

9. William F. Ames, Nonlinear Partial Differential Equations in Engineering (Academic Press, New York, 1965), Chap. 7, p. 341.

10. L. G. Thomas, "Elliptic Problems in Linear Difference Equation Over a Network," Rept. Watson Sci. Computing Lab. (Columbia University, New York, 1949).

11. G. H. Bruce, D. W. Peaceman, H. H. Rachford, Jr., and J. D. Rice, "Calculations of Unsteady-state Gas Flow Through Porous Media," Petroleum Trans., AIME 198, 79 (1953).

12. H. S. Carslaw and J. C. Jaeger, Conduction of Heat in Solids (Oxford University Press, London, 1959), 2nd ed., Chap. 2, p. 75.

DISTRIBUTION LIST

No. of Copies	Organization
20	Commander Defense Documentation Center ATTN: TIPCR Cameron Station Alexandria, Virginia 22314
1	Commanding General U.S. Army Materiel Command ATTN: AMCRD-ScT-M Washington, D.C. 20315
1	Commanding General U.S. Army Materiel Command ATTN: AMCRD-RP-P Mr. Blodgett Washington, D.C. 20315
1	Commanding General U.S. Army Materiel Command ATTN: AMCRD-DW, Mr. Darr Washington, D.C. 20315
1	Commanding General U.S. Army Materiel Command ATTN: AMCRD-SF Mr. Darracott Washington, D.C. 20315
1	Commanding General U.S. Army Materiel Command ATTN: AMCPM-AI, Mr. Cory Washington, D.C. 20315
3	Commanding General U.S. Army Electronics Command ATTN: AMSEL-RD-XE, Dr. Kedesdy AMSEL-RD-N, Dr. Bennett AMSEL-RD-PRG, Mr. Zinn Fort Monmouth, New Jersey 07703
4	Commanding General U.S. Army Electronics Command ATTN: AMSEL-RD-P, Mr. Louis Dr. Gerber AMSEL-RD-PF, Dr. Jacobs AMSEL-RD-PFM, Mr. Brand Fort Monmouth, New Jersey 07703
2	Commanding General U.S. Army Electronics Command ATTN: AMSEL-HL-CT-L, Dr. Merrill AMSEL-RD-HL, Dr. Tedo Fort Monmouth, New Jersey 07703
1	Commanding Officer U.S. Army Electronics Command ATTN: AMSEL-PP-E-P/IED Mr. Mogavero 225 S. 18th Street Philadelphia, Pa. 19103
1	Commanding Officer U.S. Army Electronics Research & Development Activity ATTN: SELHU-EE, Mr. R. Okada Fort Huachuca, Arizona 85613
1	Commanding Officer U.S. Army Electronics Research & Development Activity ATTN: Mr. R. Nelson White Sands Missile Range New Mexico 88002
3	Commanding General U.S. Army Missile Command ATTN: AMSMI-REP AMSMI-RFE, Mr. W. Davis AMSMI-RR Redstone Arsenal, Ala. 35809

DISTRIBUTION LIST

No. of Copies	Organization
1	Commanding General U.S. Army Mobility Command ATTN: AMSMO-RD, Mr. Renius Warren, Michigan 48090
1	Commanding General U.S. Army Tank-Automotive Center ATTN: SMOTA-RCS, Mr. McGregor Warren, Michigan 48090
2	Commanding Officer U.S. Army Engineer Research & Development Laboratories ATTN: SMOFB-EW, Dr. A. Hook STINFO Div Fort Belvoir, Virginia 22060
3	Commanding Officer U.S. Army Edgewood Arsenal ATTN: SMUEA-RB, Dr. Herget SMUEA-WGM Mr. Simonson SMUEA-DDW Mr. Tannenbaum Edgewood Arsenal, Md. 21010
1	Commanding Officer U.S. Army Frankford Arsenal ATTN: CC L6000-64, Dr. S. Ross Philadelphia, Pa. 19137
1	Commanding Officer U.S. Army Picatinny Arsenal ATTN: SMUPA-VL, Mr. Kisatsky Dover, New Jersey 07801
2	Commanding Officer U.S. Army Arctic Test Center APO Seattle 98733
1	President U.S. Army Armor Board ATTN: STEBB-CV Fort Knox, Kentucky 40121
1	President U.S. Army Artillery Board Fort Sill, Oklahoma 73504
1	President U.S. Army Aviation Test Board ATTN: STEBG-TP-V Fort Rucker, Ala. 36362
1	Commanding Officer U.S. Army Dugway Proving Ground ATTN: STEDP-TL Dugway, Utah 84022
2	Commanding General U.S. Army Electronic Proving Ground ATTN: STEEP-OC, COL Glover Fort Huachuca, Arizona 85613
1	Commanding Officer U.S. Army General Equipment Test Activity ATTN: Tech Lib, Bldg T-11000 Fort Lee, Virginia 23801
1	President U.S. Army Infantry Board ATTN: STEBC-SW Fort Benning, Georgia 31905
1	Commanding Officer U.S. Army Jefferson Proving Ground ATTN: STEJP-AAM Madison, Indiana 47251
2	Commanding Officer U.S. Army Tropic Test Center ATTN: STETC-PC APO New York 09827

DISTRIBUTION LIST

No. of Copies	Organization
1	Commanding General U.S. Army White Sands Missile Range ATTN: STEWS-RI-C, Mr. Miller White Sands Missile Range New Mexico 88002
2	Commanding Officer U.S. Army Yuma Proving Ground ATTN: STEYP-AD, Tech Lib Yuma, Arizona 85364
1	Commanding General U.S. Army Weapons Command ATTN: AMSWE-RDR, Mr. Reinsmith Rock Island, Illinois 61202
1	Commanding Officer U.S. Army Springfield Armory ATTN: SWESP-RER Mr. Shajenko Springfield, Massachusetts 01101
3	Commanding Officer U.S. Army Cold Regions Research & Engineering Laboratory ATTN: Mr. B. Hansen Dr. R. Gerdel Mr. W. Parrott Hanover, New Hampshire 03755
2	Commanding Officer U.S. Army Cold Regions Research & Engineering Laboratory ATTN: Lib AMXCR-PI, Dr. Rinker Hanover, New Hampshire 03755
1	Commanding Officer U.S. Army Foreign Science and Technology Center ATTN: AMXST-BS LT B. Chertok Munitions Building Washington, D.C. 20315
3	Commanding Officer U.S. Army Harry Diamond Laboratories ATTN: AMXDO-RCB Mr. Gibson Mr. Humphrey Mr. Harris Washington, D.C. 20438
2	Commanding Officer U.S. Army Materials Research Agency ATTN: AMXMR-ATL, Tech Lib AMXMR-EC, Mr. R. Farrow Watertown, Massachusetts 02172
1	Commanding General U.S. Army Natick Laboratories ATTN: AMXRE-PRD, Dr. Davies Natick, Massachusetts 01762
1	Commanding Officer U.S. Army Nuclear Defense Laboratory ATTN: AMXND-C, Ch Sc Edgewood Arsenal, Md. 21010
1	Commanding Officer U.S. Army Combat Developments Command Chemical-Biological-Radiological Agency ATTN: 1LT G. L. Jensen Fort McClellan, Ala. 36205
1	Commanding Officer U.S. Army Research Office ATTN: CRD/O, Dr. Watson Arlington, Virginia 22204
1	Commanding Officer U.S. Army Research Office (Durham) ATTN: Dr. Lontz Box CM, Duke Station Durham, North Carolina 27706

DISTRIBUTION LIST

No. of Copies	Organization
1	Advisory Group on Electron Devices ATTN: Secy, Sp Gp on Opt Masers 346 Broadway New York, New York 10013
	Aberdeen Proving Ground
	Ch, Tech Lib
	Air Force Ln Ofc Marine Corps Ln Ofc Navy Ln Ofc CDC Ln Ofc
	CG, USATECOM ATTN: AMSTE-TA-A, Mr. Somody (2 cys) Dir, D&PS ATTN: STEAP-DS-TS CO, USALWL ATTN: Mr. D. Samuels

Unclassified
Security Classification

DOCUMENT CONTROL DATA - R&D

(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)

1. ORIGINATING ACTIVITY *(Corporate author)*
U.S. Army Ballistic Research Laboratories
Aberdeen Proving Ground, Maryland

2a. REPORT SECURITY CLASSIFICATION
Unclassified

2b. GROUP

3. REPORT TITLE
A NUMERICAL SOLUTION TO AN ABLATION PROBLEM WITH POSSIBLE LASER APPLICATIONS

4. DESCRIPTIVE NOTES *(Type of report and inclusive dates)*

5. AUTHOR(S) *(Last name, first name, initial)*
Faller, James G.

6. REPORT DATE
October 1966

7a. TOTAL NO. OF PAGES
32

7b. NO. OF REFS
12

8a. CONTRACT OR GRANT NO.

b. PROJECT NO. RDT&E 1P014501A31C

c.

d.

9a. ORIGINATOR'S REPORT NUMBER(S)
Report No. 1342

9b. OTHER REPORT NO(S) *(Any other numbers that may be assigned this report)*

10. AVAILABILITY/LIMITATION NOTICES
Distribution of this document is unlimited.

11. SUPPLEMENTARY NOTES

12. SPONSORING MILITARY ACTIVITY
U.S. Army Materiel Command
Washington, D.C.

13. ABSTRACT
The problem of an ablating solid of limited extent under an applied non-uniform heat input is solved numerically, and the solution is compared in certain limiting cases with results from the exact analytical equations. Further, the usefulness of this model in predicting the depth of hole made in materials by a laser beam is explored.

DD FORM 1 JAN 64 1473

Unclassified
Security Classification

Unclassified
Security Classification

14. KEY WORDS	LINK A ROLE	LINK A WT	LINK B ROLE	LINK B WT	LINK C ROLE	LINK C WT
Laser						
Vaporization						
Liquefaction						
Sublimation						
Ablation						
Moving Boundary						
Heat Flow						
Stefan Problem						

INSTRUCTIONS

1. ORIGINATING ACTIVITY: Enter the name and address of the contractor, subcontractor, grantee, Department of Defense activity or other organization *(corporate author)* issuing the report.

2a. REPORT SECURITY CLASSIFICATION: Enter the overall security classification of the report. Indicate whether "Restricted Data" is included. Marking is to be in accordance with appropriate security regulations.

2b. GROUP: Automatic downgrading is specified in DoD Directive 5200.10 and Armed Forces Industrial Manual. Enter the group number. Also, when applicable, show that optional markings have been used for Group 3 and Group 4 as authorized.

3. REPORT TITLE: Enter the complete report title in all capital letters. Titles in all cases should be unclassified. If a meaningful title cannot be selected without classification, show title classification in all capitals in parenthesis immediately following the title.

4. DESCRIPTIVE NOTES: If appropriate, enter the type of report, e.g., interim, progress, summary, annual, or final. Give the inclusive dates when a specific reporting period is covered.

5. AUTHOR(S): Enter the name(s) of author(s) as shown on or in the report. Enter last name, first name, middle initial. If military, show rank and branch of service. The name of the principal author is an absolute minimum requirement.

6. REPORT DATE: Enter the date of the report as day, month, year; or month, year. If more than one date appears on the report, use date of publication.

7a. TOTAL NUMBER OF PAGES: The total page count should follow normal pagination procedures, i.e., enter the number of pages containing information.

7b. NUMBER OF REFERENCES: Enter the total number of references cited in the report.

8a. CONTRACT OR GRANT NUMBER: If appropriate, enter the applicable number of the contract or grant under which the report was written.

8b, 8c, & 8d. PROJECT NUMBER: Enter the appropriate military department identification, such as project number, subproject number, system numbers, task number, etc.

9a. ORIGINATOR'S REPORT NUMBER(S): Enter the official report number by which the document will be identified and controlled by the originating activity. This number must be unique to this report.

9b. OTHER REPORT NUMBER(S): If the report has been assigned any other report numbers *(either by the originator or by the sponsor)*, also enter this number(s).

10. AVAILABILITY/LIMITATION NOTICES: Enter any limitations on further dissemination of the report, other than those imposed by security classification, using standard statements such as:

(1) "Qualified requesters may obtain copies of this report from DDC."

(2) "Foreign announcement and dissemination of this report by DDC is not authorized."

(3) "U. S. Government agencies may obtain copies of this report directly from DDC. Other qualified DDC users shall request through _____."

(4) "U. S. military agencies may obtain copies of this report directly from DDC. Other qualified users shall request through _____."

(5) "All distribution of this report is controlled. Qualified DDC users shall request through _____."

If the report has been furnished to the Office of Technical Services, Department of Commerce, for sale to the public, indicate this fact and enter the price, if known.

11. SUPPLEMENTARY NOTES: Use for additional explanatory notes.

12. SPONSORING MILITARY ACTIVITY: Enter the name of the departmental project office or laboratory sponsoring *(paying for)* the research and development. Include address.

13. ABSTRACT: Enter an abstract giving a brief and factual summary of the document indicative of the report, even though it may also appear elsewhere in the body of the technical report. If additional space is required, a continuation sheet shall be attached.

It is highly desirable that the abstract of classified reports be unclassified. Each paragraph of the abstract shall end with an indication of the military security classification of the information in the paragraph, represented as *(TS)*, *(S)*, *(C)*, or *(U)*.

There is no limitation on the length of the abstract. However, the suggested length is from 150 to 225 words.

14. KEY WORDS: Key words are technically meaningful terms or short phrases that characterize a report and may be used as index entries for cataloging the report. Key words must be selected so that no security classification is required. Identifiers, such as equipment model designation, trade name, military project code name, geographic location, may be used as key words but will be followed by an indication of technical context. The assignment of links, rules, and weights is optional.

Unclassified
Security Classification