

AD-A145 836

DIRECT ANALYSIS OF HEAVILY LOADED CARBON BLACK FILLED
STYRENE-BUTADIENE R. (U) ARMY MATERIALS AND MECHANICS
RESEARCH CENTER WATERTOWN MA J M SLOAN ET AL JUN 84

1/1


UNCLASSIFIED

AMMRC-TR-84-25

F/G 11/10

NL



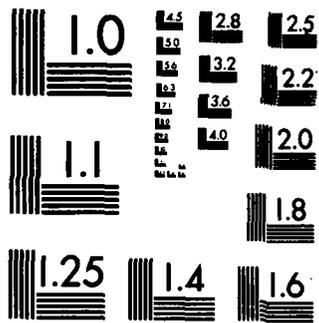

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A


12

AMMRC TR 84-25

AD

AD-A145 836

**DIRECT ANALYSIS OF HEAVILY LOADED
CARBON BLACK FILLED STYRENE-BUTADIENE
RUBBER USED IN TANK TRACK PADS BY FT-IR**



JAMES M. SLOAN and JOSEPH P. CLEMENTS
POLYMER RESEARCH DIVISION

June 1984

DTIC FILE COPY

Approved for public release; distribution unlimited.

DTIC
ELECTE
SEP 18 1984

S

B

ARMY MATERIALS AND MECHANICS RESEARCH CENTER
Watertown, Massachusetts 02172-0001

84 09 17 028

The findings in this report are not to be construed as an official Department of the Army position, unless so designated by other authorized documents.

Mention of any trade names or manufacturers in this report shall not be construed as advertising nor as an official indorsement or approval of such products or companies by the United States Government.

DISPOSITION INSTRUCTIONS

Destroy this report when it is no longer needed.
Do not return it to the originator.

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER AMMRC TR 84-25	2. GOVT ACCESSION NO. AD-A145836	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) DIRECT ANALYSIS OF HEAVILY LOADED CARBON BLACK FILLED STYRENE-BUTADIENE RUBBER USED IN TANK TRACK PADS BY FT-IR	5. TYPE OF REPORT & PERIOD COVERED Final Report	
	6. PERFORMING ORG. REPORT NUMBER	
7. AUTHOR(s) James M. Sloan and Joseph P. Clements	8. CONTRACT OR GRANT NUMBER(s)	
9. PERFORMING ORGANIZATION NAME AND ADDRESS Army Materials and Mechanics Research Center Watertown, Massachusetts 02172-0001 DRXMR-OP	10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS D/A Project: 1T161101A91A	
11. CONTROLLING OFFICE NAME AND ADDRESS U. S. Army Materiel Development and Readiness Command, Alexandria, Virginia 22333	12. REPORT DATE June 1984	
	13. NUMBER OF PAGES 11	
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)	15. SECURITY CLASS. (of this report) Unclassified	
	15a. DECLASSIFICATION/DOWNGRADING SCHEDULE	
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Elastomers Infrared spectroscopy		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) (SEE REVERSE SIDE)		

DD FORM 1473 1 JAN 73 EDITION OF 1 NOV 65 IS OBSOLETE

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

Block No. 20

(FT-IR.)

ABSTRACT

Infrared spectra have been obtained of a heavily loaded (50 per hundred) carbon black filled styrene-butadiene rubber using a Fourier transform infrared spectrometer. Attenuated total reflectance (ATR) spectroscopy sampling employing a germanium (Ge) internal reflectance element was found to yield quality infrared spectra where other techniques have failed. Subtle changes were observed between the spectra of the filled and unfilled styrene-butadiene rubber (SBR). These changes are attributed to the interaction between polymer and filler.

DTIC
ELECTE
SEP 18 1984
B

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution/	
Availability Codes	
Avail and/or	
Dist	Special
A-1	

DTIC
COPY
INSPECTED

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

INTRODUCTION

Carbon black is the most widely used reinforcement agent presently in use in the elastomer industry. The role of carbon black in the reinforcement of elastomers is an important one. Addition of carbon black to an elastomeric system improves the mechanical properties of the final vulcanizate. Considerable improvement in tensile strength, tear resistance, and abrasion resistance has already been realized.¹ Such variables as the size and shape of carbon black particles, their dispersability and the chemical nature of their surfaces^{1,2} contribute to the degree of reinforcement. Theories of reinforcement of elastomers by carbon black postulate the existence of a physical or chemical interaction at the polymer-filler interface.

Carbon black has also been found to increase the rate of vulcanization and improve reversion resistance.³ The degree of improvement in reversion resistance is largely dependent on the size of the carbon black particles.


Typical industrial rubber formulations include anywhere from 40 to 60 parts carbon black per hundred parts elastomer. Obtaining infrared spectra of materials with these high loadings of carbon black is not an easy matter. Corish⁴ obtained an IR spectrum of a heavily loaded carbon black filled styrene-butadiene rubber (SBR) using a microtomed (2-microns thick) slice aligned in the IR beam. Unfortunately, he used a grating spectrometer which allowed only a small fraction of radiation to reach the detector. This resulted in a spectrum of poor quality. A recent report⁵ used the above method in conjunction with a Fourier transform infrared spectrometer with greatly improved results. Hart et al.⁶ demonstrated the usefulness of using transmission sampling through dilution with KBr with an FT-IR spectrometer to obtain quality IR spectra of a 20 per hundred carbon black filled polybutadiene rubber.

The work presented in this paper demonstrates an easy method of sample preparation to obtain quality infrared spectra of heavily loaded (50 per hundred) carbon black filled SBR. The method utilizes an attenuated total reflectance (ATR) accessory employing Ge as the internal reflectance element (IRE). The quality of the IR spectrum is of sufficient quality to allow detection of small structural changes. These changes are thought to be a result of the interaction between the rubber and the carbon black filler.

EXPERIMENTAL

All spectra reported were recorded using a Harrick Model 4X-TBC-VA ATR accessory. The IRE was a rhombohedral-shaped Ge crystal with dimensions of 50 mm x 3 mm x 2 mm. This geometry allows multiple reflections of radiation to take place along the surface of the rubber. Figure 1 shows a schematic diagram of the ATR attachment.⁷

1. BLOW, C. M. *Rubber Technology and Manufacture*, The Butterworth Group, London, 1974.
2. DAVIDSON, H. W., WIGGS, K. C., CHURCHOUSE, A. H., MAGGS, F. A. P., and BRADLEY, R. D. *Manufactured Carbon*, MacLaren, London, 1968.
3. CHEN, C. H., KOENIG, J. L., SHELTON, J. R., and COLLINS, E. A. *The Influence of Carbon Black on the Reversion Process in Sulfur-Accelerated Vulcanization of Natural Rubber*. *Rubber Chem. and Technol.*, v. 55, 1982, p. 103.
4. CORISH, P. J., *J. Appl. Polym. Sci.*, v. 4, 1960, p. 86.
5. DEVLIN, E. F. *The Fourier Transform Infrared Spectrum of Cured, Black-Reinforced SBR*. *J. Polym. Sci., Poly. Lett. Ed.*, v. 19, April 1981, p. 189.
6. HART, W. W., PAINTER, P. C., KOENIG, J. L., and COLEMAN, M. M., *Appl. Spectrosc.*, v. 31, 1977, p. 220.
7. HARRICK, N. J. *Internal Reflection Spectroscopy*, Wiley-Interscience, New York, 1967.

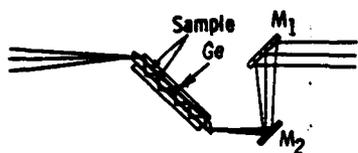

$$d_p = \frac{\lambda/n_{Ge}}{2\pi(\sin^2\theta - (n_{SAM}/n_{Ge})^2)^{1/2}}$$

- d_p - depth of penetration into sample
($n_{Ge} > n_{SAM}$)
- λ - wavelength of radiation in μm
- n_{Ge} - refractive index of germanium
- n_{SAM} - refractive index of sample
- θ - angle of incidence of radiation

Figure 1. Schematic outline of the internal reflectance accessory.

The IRE had an incident face angle of 60° . The depth of penetration varies as a function of frequency from approximately $1 \mu\text{m}$ at 4000 cm^{-1} to $1.2 \mu\text{m}$ at 400 cm^{-1} . Figure 2 shows a comparison of the depth of penetration for a germanium crystal and that of another often used internal reflectance crystal, KRS-5 (thallium bromide-iodide). This figure clearly shows the small penetration depth due to the use of the germanium crystal. Therefore, more IR radiation is permitted to reach the detector which was a severe problem previously encountered by other authors.^{4,6} By co-adding a large number of spectral scans and utilizing a scale expansion of the resultant IR spectrum, all spectral features of the heavily loaded carbon black filled rubber can be identified.

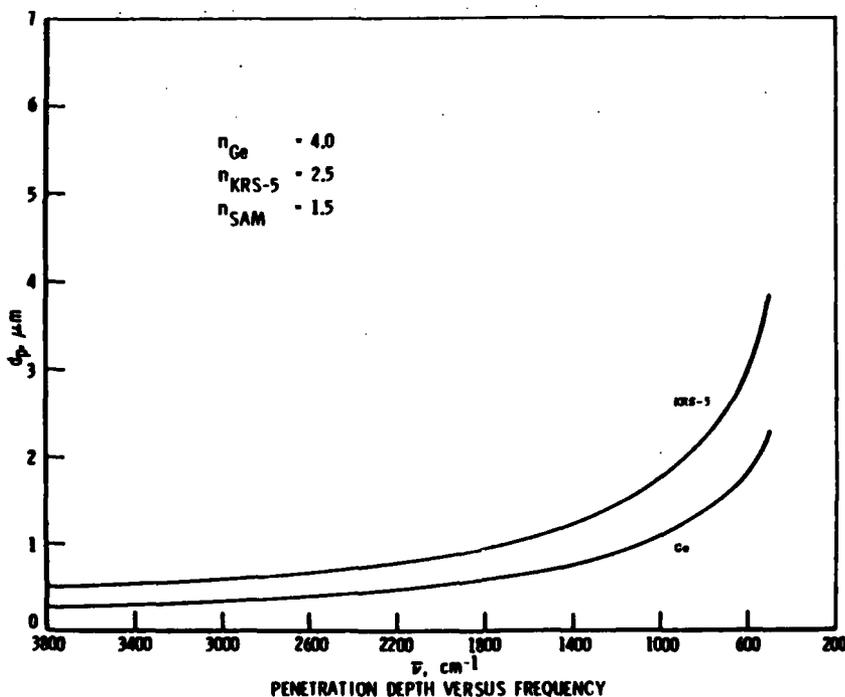


Figure 2. Depth of penetration profile of the infrared beam into the sample as a function of wave number.

All infrared spectra were measured on a Digilab FTS-10M Fourier transform infrared spectrometer. Spectra were recorded using 2048 co-added interferometric scans with a spectral resolution of 4 cm^{-1} .

Cured carbon black filled SBR samples were formulated by various rubber manufacturers and known to contain the same base SBR, containing approximately 24% bound styrene and processed with 50 per hundred carbon black. Samples were provided as bulk tensile sheets and cut to size. Sample formulations are given in Table 1.

Samples were prepared for IR analysis by soaking in acetone for one hour followed by soaking in methylene chloride for one hour. The samples were then allowed to dry in a vacuum oven at 100°C for one hour. This method of extraction serves to cleanse the elastomer surface of all additives and compounding ingredients while allowing the structural integrity of the elastomer to remain intact.

Table 1. SBR RUBBER FORMULATIONS IN PHR

	Control ??	Control	UOP 88	3 PLS POP 88	Styron 750
Styron 750	-	-	-	-	100
SBR-1500	100	100	100	100	
Zinc Oxide	3	3	3	3	3
Stearic Acid	2	2	2	2	2
Phenyl-b-naphthylamine	1	1	1	1	1
AgeRite Resin D	1	1	1	1	1
Carbon Black, HAF	50	50	50	50	-
N-cyclohexyl-2-benzothiazyl Sulfonamide	1	1	1	1	-
Sulphur	1.75	1.75	1.75	1.75	2
UOP 88	-	-	coated	3	-
Aromatic Oil	-	-	-	-	37.5

RESULTS AND DISCUSSION

ATR is a complex technique governed by many fundamental optical laws. Some key factors for obtaining quality ATR spectra are as follows:

1. The quality of the internal reflectance spectrum depends on the nature of the contact between the IRE and the sample. It is desirable to distribute the pressure uniformly along the surface of the IRE. This is accomplished by use of a torque wrench which allows reproducible and uniform pressure of the sample onto the IRE.
2. Approximate matching refractive indices of the sample and the IRE are required if good spectral contrast is to be obtained. In our case, the refractive index of carbon black filled rubber has not been determined. One can assume that this number is quite high. Thus, a germanium IRE with a refractive index of 4.0 would be a more appropriate IRE than a crystal with a refractive index of 2.5 (KRS-5).
3. Accurate knowledge of a good reference spectra. In double-beam grating instruments the sample spectrum is ratioed against air. In FT-IR systems the reference spectrum is a digitally stored spectrum of a free standing IRE, which allows a fully compensated IR spectrum to be obtained.

Spectra of Heavily Loaded Carbon Black Filled SBR

Figure 3 shows a spectrum of a heavily loaded carbon black filled rubber before and after baseline correction. The sloping baseline in the uncorrected spectrum is due to the wavelength dependence of the depth of penetration of the infrared beam into the sample. This can be easily compensated by using a baseline correction program available in the operating software. Due to the limited amount of radiation reaching the detector and the strong absorption of the carbon black throughout the infrared region, a scale expansion was necessary to detect the infrared bands of the SBR. The result of this operation is seen in the bottom spectrum in Figure 3.

Figure 4 shows a comparison between the corrected carbon black filled SBR spectrum and that of a nonfilled SBR. The absorption bands in the spectrum of the filled SBR can clearly be identified with that of the unfilled sample spectrum. Absorptions due to the butadiene portion (967 cm^{-1} , 910 cm^{-1}) of the copolymer can be seen, as can the absorptions due to the styrene portion (698 cm^{-1} , 1498 cm^{-1} , 1601 cm^{-1}). Clearly, absolute identification of the base elastomer can be made from the IR spectrum obtained by this technique. The band located at 1539 cm^{-1} has already been assigned to the presence of zinc stearate,⁸ which is formed during the curing process as a result of reaction between zinc oxide and stearic acid.

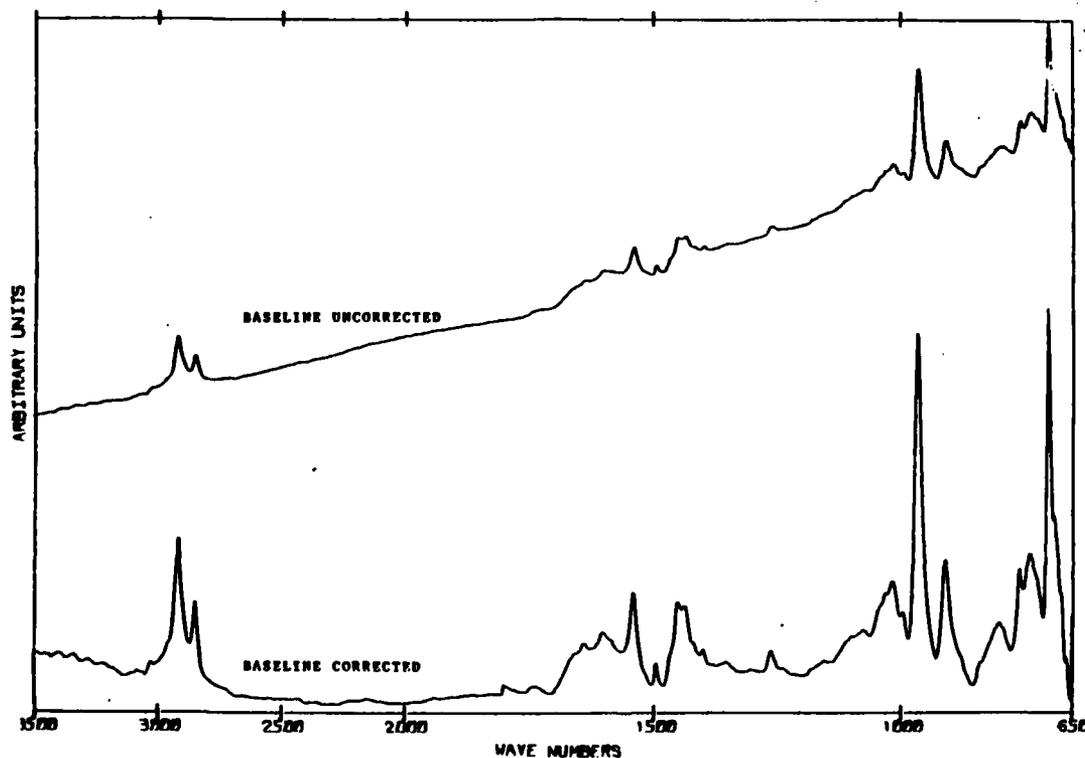


Figure 3. Top: uncorrected IR spectrum of carbon black filled SBR.
Bottom: baseline corrected IR spectrum of same SBR.

8. ANDRIES, J. C., ROSS, D. B., and DIEM, H. E. *Ozone Attack and Antiozonant Protection of Vulcanized Natural Rubber. A Surface Study by Attenuated Total Reflectance Spectroscopy.* Rubber Chem. Technol., v. 48, 1975, p. 41.

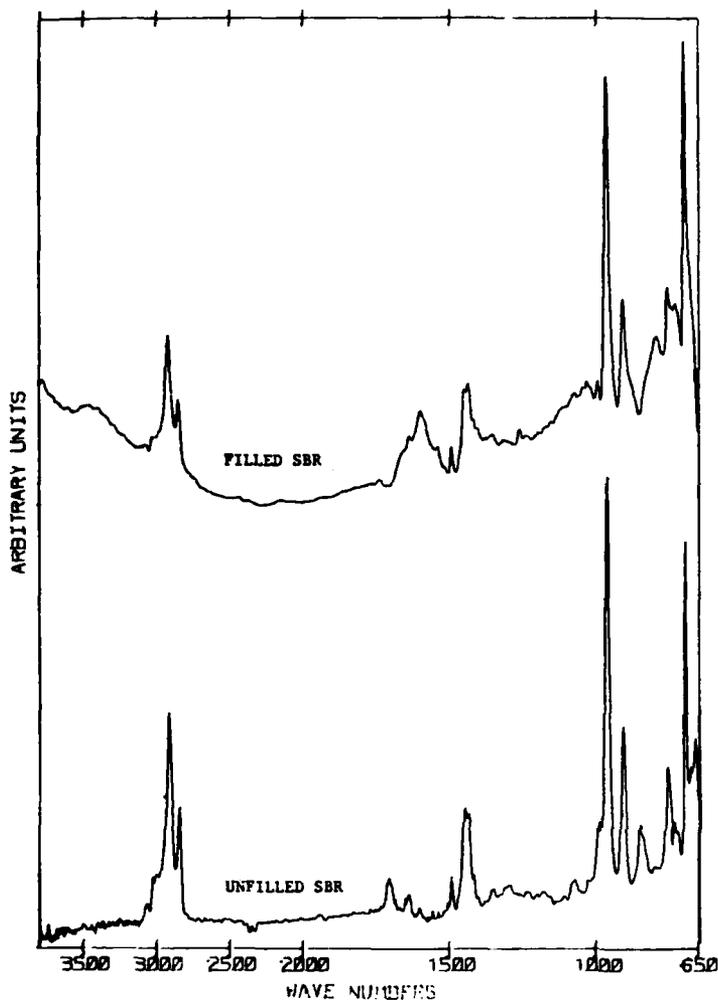


Figure 4. Comparison of two IR spectra.
 Top: carbon black filled SBR.
 Bottom: unfilled latex SBR.

Interaction Between Carbon Black and SBR

Figure 5 shows spectra of two different rubber formulations utilizing the same base SBR. The bottom spectrum is that of the unfilled SBR shown here for comparison. The top two spectra are spectroscopically identical as would be expected since the only differences between the two formulations are in the organic additives, which have been extracted out. This is an indication of the reproducibility that exists between different rubber formulations employing the same base rubber. Of particular interest in Figure 5 are the distortions of the various C-H bands along the polymer backbone. Absorbances at 698 cm^{-1} and 3065 cm^{-1} , attributed to various aromatic C-H motions, show changes in both their frequency maxima and their relative intensities. Similarly, absorbances at 2953 cm^{-1} , 2890 cm^{-1} , and 967 cm^{-1} attributed to the various C-H motions of the butadiene portion of the copolymer show intensity and positional shifts. These effects are thought to be due to the interaction between carbon black and the polymer. Although the exact nature of this interaction is beyond the scope of this report, it seems apparent that the polymer surface is strongly absorbed onto the carbon black.

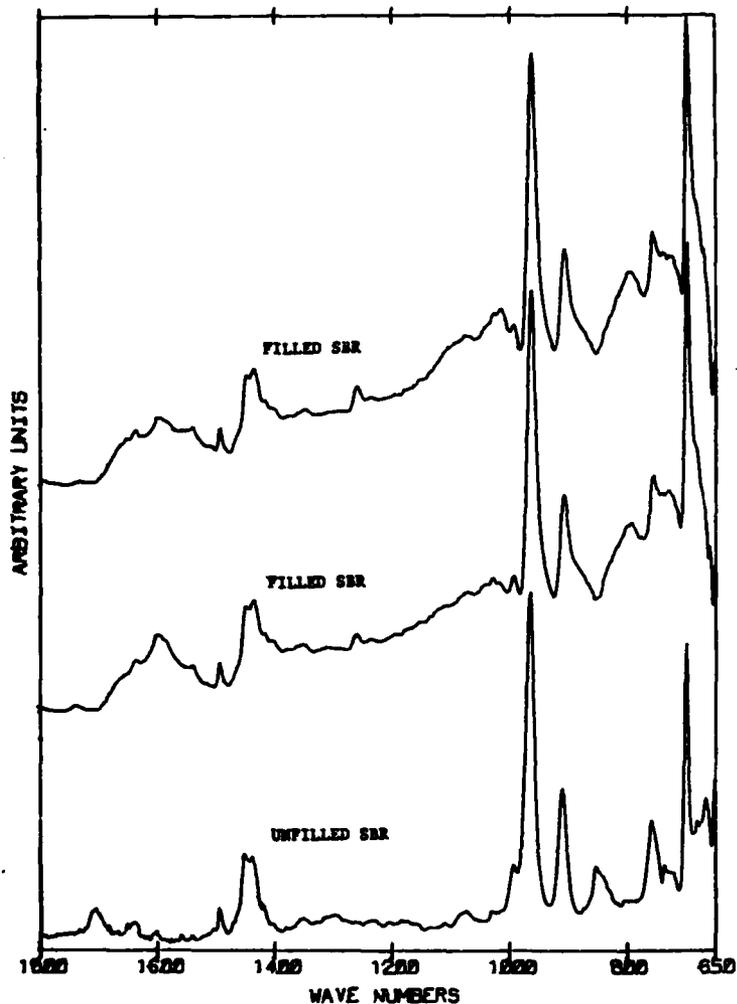


Figure 5. Spectral comparison between two differently formulated carbon black filled SBR and the raw unfilled SBR.

Figure 6 shows the expanded infrared region between 1350 cm^{-1} and 1480 cm^{-1} for the filled and unfilled elastomer. Clearly, the intensity of the 1433 cm^{-1} band increases with respect to the 1450 cm^{-1} band. These bands have previously been assigned to the CH_2 bending vibrations of the gauche and trans conformations, respectively,⁹ about the C-C bond. It is interesting to note that only one band is modified by the addition of carbon black, indicating a preferred loss of conformation from the trans conformer to the gauche conformer.

Quantitative Determination of Bound Styrene in SBR

The spectra obtained using this sampling technique are of sufficient enough quality to allow determination of the percent bound styrene in the copolymer, SBR. The method of determination is to use calibrated IR band intensity ratios for unknown samples and compare them to the IR band intensity ratios for a series of standards. In this case, the 698 cm^{-1} band of styrene was ratioed against the 967 cm^{-1} band of butadiene. A calibration graph was constructed for three known standards. Such a graph is shown in Figure 7.

9. CRAMPELLI, F., and MANOVICHI, I. Gazz. Chim. Ital., v. 91, 1961, p. 1045.

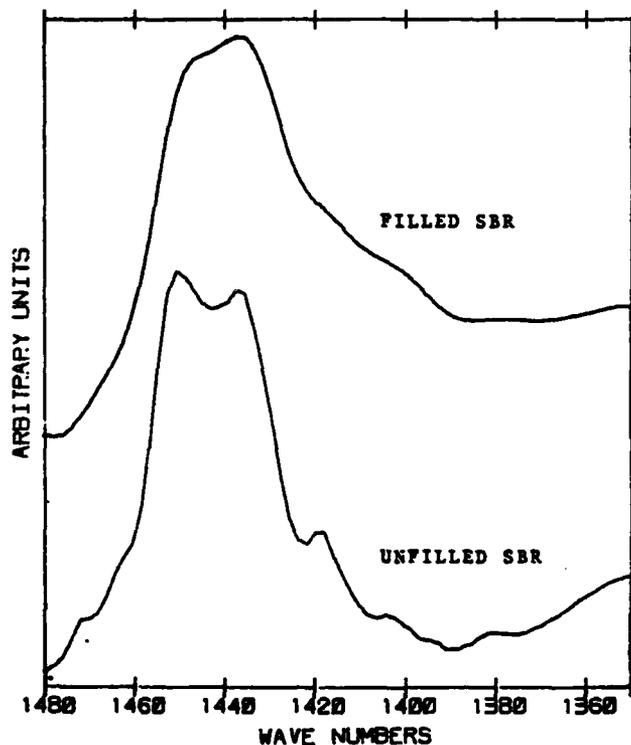


Figure 6. 1480 cm^{-1} - 1350 cm^{-1} region showing changes in band intensities upon addition of carbon black.

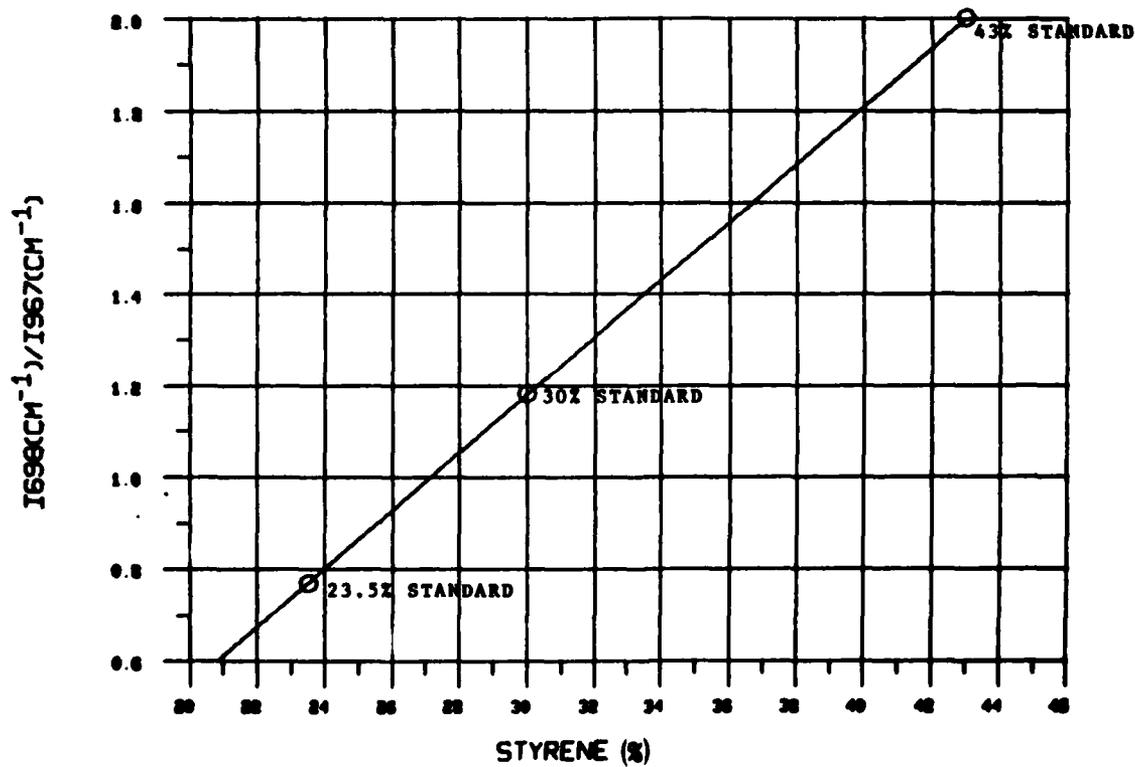


Figure 7. Typical calibration curve of IR band intensity ratios of $967\text{ cm}^{-1}/698\text{ cm}^{-1}$ versus percent-bound styrene in SBR.

Table 2 summarizes the results of a series of known cured carbon black filled samples analyzed in this way. As can be seen by this table, excellent agreement is shown between the known amount of styrene and the determined amount of styrene. These values show a maximum variation of between $\pm 2.5\%$.

Table 2. QUANTITATIVE ANALYSIS OF STYRENE-BUTADIENE COPOLYMERS

Sample	Known Styrene (%)	Determined Styrene (This Work) (%)
Control 22	23.5	24.7
UOP 88	23.5	24.5
3 PTS UOP 88	23.5	23.5
Control	23.5	24.5
TACOM L	23.5	22.8
Stereon 750	18.0	20.2

Identification of Antioxidants

For a complete analysis of a formulated elastomer system, it is useful to identify the antioxidant that has been used in processing. The small amount of antioxidant present (typically up to 3% by weight) in the formulation makes it necessary to extract the antioxidant as performed in the experimental section and concentrate it down. This extract contains various amounts of processing components, but is primarily composed of the antioxidant.

The solvent can be evaporated onto a KBr salt plate and an infrared spectrum taken. Figure 8 shows an example of the spectrum one obtains from this extracted residue. This material has been identified as an N,N^o substituted phenylene diamine antioxidant commonly used in elastomer formulations.

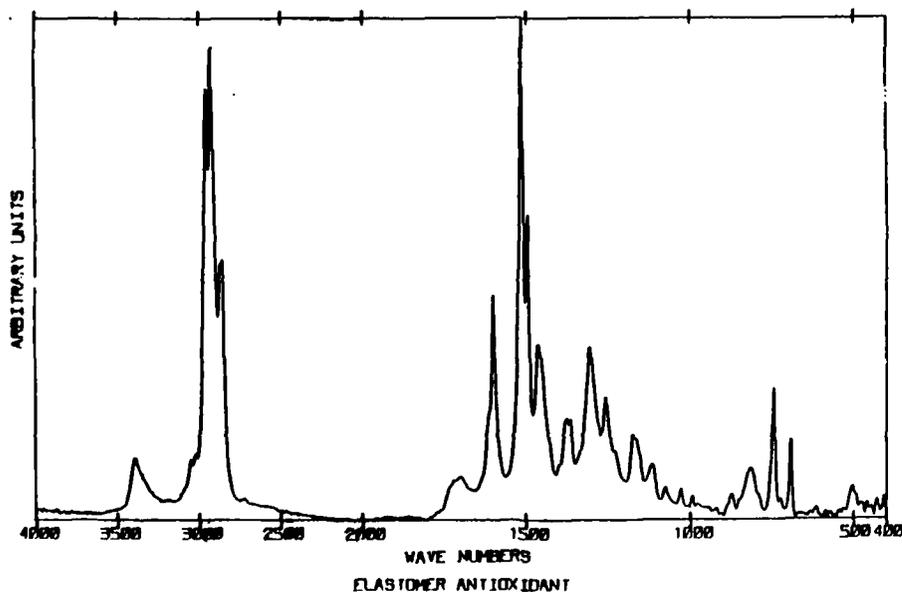


Figure 8. IR spectrum of rubber extract.

CONCLUSION

It has been shown that quality infrared spectra of heavily loaded (50 per hundred) carbon black filled styrene-butadiene rubbers can be measured by the use of a standard ATR sampling accessory. The utilization of Ge as the internal reflectance element allows more radiation to reach the detector. The resultant spectra yields absolute identification of an unknown elastomer.

The spectra obtained are of sufficient quality to allow subtle spectral changes of the elastomer to be detected. These changes are associated with the interaction of the polymer with the carbon black filler.

Additionally, FT-IR provides the advantage of a rapid and easy method for identification of quantitative differences in composition between standard and unknown styrene-butadiene rubbers by absorption band ratios. This has been shown to be accurate to $\pm 2.5\%$ bound styrene on samples tested.

DISTRIBUTION LIST

No. of Copies	To
1	Office of the Under Secretary of Defense for Research and Engineering, The Pentagon, Washington, DC 20301
12	Commander, Defense Technical Information Center, Cameron Station, Building 5, 5010 Duke Street, Alexandria, VA 22314
1	Commander, Army Research Office, P.O. Box 12211, Research Triangle Park, NC 27709 ATTN: Information Processing Office
1	Commander, U.S. Army Materiel Development and Readiness Command, 5001 Eisenhower Avenue, Alexandria, VA 22333 ATTN: DRCLD
1	Commander, U.S. Army Materiel Systems Analysis Activity, Aberdeen Proving Ground, MD 21005 ATTN: DRXSY-MP, H. Cohen
1	Commander, U.S. Army Electronics Research and Development Command, Fort Monmouth, NJ 07703 ATTN: DELSD-L
1	DELS-D-E
1	Commander, U.S. Army Missile Command, Redstone Arsenal, AL 35898 ATTN: DRSMI-RKP, J. Wright, Bldg. 7574
4	DRSMI-TB, Redstone Scientific Information Center
1	DRSMI-RLM
1	Technical Library
2	Commander, U.S. Army Armament, Munitions and Chemical Command, Dover, NJ 07801 ATTN: Technical Library
1	DRDAR-SCM, J. D. Corrie
1	DRDAR-QAC-E
1	DRDAR-LCA, Mr. Harry E. Peibly, Jr., PLASTECH, Director
1	Commander, U.S. Army Natick Research and Development Center, Natick, MA 01760 ATTN: Technical Library
1	Commander, U.S. Army Satellite Communications Agency, Fort Monmouth, NJ 07703 ATTN: Technical Document Center
1	Commander, U.S. Army Tank-Automotive Command, Warren, MI 48090 ATTN: DRSTA-ZSK
2	DRSTA-UL, Technical Library
1	Commander, White Sands Missile Range, NM 88002 ATTN: STEWS-WS-VT
1	President, Airborne, Electronics and Special Warfare Board, Fort Bragg, NC 28307 ATTN: Library

No. of
Copies

To

Director, U.S. Army Ballistic Research Laboratory, Aberdeen Proving Ground,
MD 21005

1 ATTN: DRDAR-TSB-S (STINFO)

Commander, Dugway Proving Ground, Dugway, UT 84022

1 ATTN: Technical Library, Technical Information Division

Commander, Harry Diamond Laboratories, 2800 Powder Mill Road, Adelphi, MD 20783

1 ATTN: Technical Information Office

Director, Benet Weapons Laboratory, LCWSL, USA ARRADCOM, Watervliet, NY 12189

1 ATTN: DRSMC-LCB-TL

1 DRSMC-LCB-R

1 DRSMC-LCB-RM

1 DRSMC-LCB-RP

Commander, U.S. Army Foreign Science and Technology Center, 220 7th Street, N.E.,
Charlottesville, VA 22901

1 ATTN: Military Tech, Mr. Marley

Commander, U.S. Army Aeromedical Research Unit, P.O. Box 577, Fort Rucker,
AL 36360

1 ATTN: Technical Library

Director, Eustis Directorate, U.S. Army Air Mobility Research and Development
Laboratory, Fort Eustis, VA 23604

1 ATTN: Mr. J. Robinson, DAVDL-E-MOS (AVRADCOM)

U.S. Army Aviation Training Library, Fort Rucker, AL 36360

1 ATTN: Building 5906-5907

Commander, U.S. Army Agency for Aviation Safety, Fort Rucker, AL 36362

1 ATTN: Technical Library

Commander, USACDC Air Defense Agency, Fort Bliss, TX 79916

1 ATTN: Technical Library

Commander, U.S. Army Engineer School, Fort Belvoir, VA 22060

1 ATTN: Library

Commander, U.S. Army Engineer Waterways Experiment Station, Vicksburg, MS 39180

1 ATTN: Research Center Library

Commander, U.S. Army Environmental Hygiene Agency, Edgewood Arsenal, MD 21010

1 ATTN: Chief, Library Branch

Technical Director, Human Engineering Laboratories, Aberdeen Proving
Ground, MD 21005

1 ATTN: Technical Reports Office

Commandant, U.S. Army Quartermaster School, Fort Lee, VA 23801

1 ATTN: Quartermaster School Library

No. of
Copies

To

Commander, U.S. Army Radio Propagation Agency, Fort Bragg, NC 28307
1 ATTN: SCCR-2

Naval Research Laboratory, Washington, DC 20375
1 ATTN: Dr. C. I. Chang - Code 5830
2 Dr. G. R. Yoder - Code 6384

Chief of Naval Research, Arlington, VA 22217
1 ATTN: Code 471

1 Edward J. Morrissey, AFWAL/MLTE, Wright-Patterson Air Force, Base, OH 45433

Commander, U.S. Air Force Wright Aeronautical Laboratories,
Wright-Patterson Air Force Base, OH 45433
1 ATTN: AFWAL/MLC
1 AFWAL/MLLP, M. Forney Jr.
1 AFWAL/MLBC, Mr. Stanley Schulman

Director, Army Materials and Mechanics Research Center, Watertown, MA 02172-0001
2 ATTN: DRXMR-PL
2 Authors

AD
Army Materials and Mechanics Research Center,
Watertown, Massachusetts 02172-0001
UNCLASSIFIED
UNLIMITED DISTRIBUTION
Key Words

AD
UNCLASSIFIED
UNLIMITED DISTRIBUTION
Key Words

Army Materials and Mechanics Research Center,
Watertown, Massachusetts 02172-0001
DIRECT ANALYSIS OF HEAVILY LOADED CARBON BLACK
FILLED STYRENE-BUTADIENE RUBBER USED IN TANK TRACK
PADS BY FT-IR -
James M. Sloan and Joseph P. Clements
Technical Report AMMRC TR 84-25, June 1984, 11 pp -
illus-tables, D/A Project 1161101A91A

Elastomers
Infrared spectroscopy

Infrared spectra have been obtained of a heavily loaded (50 per hundred) carbon black filled styrene-butadiene rubber using a Fourier transform infrared spectrometer. Attenuated total reflectance (ATR) spectroscopy sampling employing a germanium (Ge) internal reflectance element was found to yield quality infrared spectra where other techniques have failed. Subtle changes were observed between the spectra of the filled and unfilled styrene-butadiene rubber (SBR). These changes are attributed to the interaction between polymer and filler.

Army Materials and Mechanics Research Center,
Watertown, Massachusetts 02172-0001
DIRECT ANALYSIS OF HEAVILY LOADED CARBON BLACK
FILLED STYRENE-BUTADIENE RUBBER USED IN TANK TRACK
PADS BY FT-IR -
James M. Sloan and Joseph P. Clements
Technical Report AMMRC TR 84-25, June 1984, 11 pp -
illus-tables, D/A Project 1161101A91A

Elastomers
Infrared spectroscopy

Infrared spectra have been obtained of a heavily loaded (50 per hundred) carbon black filled styrene-butadiene rubber using a Fourier transform infrared spectrometer. Attenuated total reflectance (ATR) spectroscopy sampling employing a germanium (Ge) internal reflectance element was found to yield quality infrared spectra where other techniques have failed. Subtle changes were observed between the spectra of the filled and unfilled styrene-butadiene rubber (SBR). These changes are attributed to the interaction between polymer and filler.

AD
Army Materials and Mechanics Research Center,
Watertown, Massachusetts 02172-0001
UNCLASSIFIED
UNLIMITED DISTRIBUTION
Key Words

AD
UNCLASSIFIED
UNLIMITED DISTRIBUTION
Key Words

Army Materials and Mechanics Research Center,
Watertown, Massachusetts 02172-0001
DIRECT ANALYSIS OF HEAVILY LOADED CARBON BLACK
FILLED STYRENE-BUTADIENE RUBBER USED IN TANK TRACK
PADS BY FT-IR -
James M. Sloan and Joseph P. Clements
Technical Report AMMRC TR 84-25, June 1984, 11 pp -
illus-tables, D/A Project 1161101A91A

Elastomers
Infrared spectroscopy

Infrared spectra have been obtained of a heavily loaded (50 per hundred) carbon black filled styrene-butadiene rubber using a Fourier transform infrared spectrometer. Attenuated total reflectance (ATR) spectroscopy sampling employing a germanium (Ge) internal reflectance element was found to yield quality infrared spectra where other techniques have failed. Subtle changes were observed between the spectra of the filled and unfilled styrene-butadiene rubber (SBR). These changes are attributed to the interaction between polymer and filler.

Army Materials and Mechanics Research Center,
Watertown, Massachusetts 02172-0001
DIRECT ANALYSIS OF HEAVILY LOADED CARBON BLACK
FILLED STYRENE-BUTADIENE RUBBER USED IN TANK TRACK
PADS BY FT-IR -
James M. Sloan and Joseph P. Clements
Technical Report AMMRC TR 84-25, June 1984, 11 pp -
illus-tables, D/A Project 1161101A91A

Elastomers
Infrared spectroscopy

Infrared spectra have been obtained of a heavily loaded (50 per hundred) carbon black filled styrene-butadiene rubber using a Fourier transform infrared spectrometer. Attenuated total reflectance (ATR) spectroscopy sampling employing a germanium (Ge) internal reflectance element was found to yield quality infrared spectra where other techniques have failed. Subtle changes were observed between the spectra of the filled and unfilled styrene-butadiene rubber (SBR). These changes are attributed to the interaction between polymer and filler.

AD UNCLASSIFIED
UNLIMITED DISTRIBUTION
Key Words
Elastomers
Infrared spectroscopy

Army Materials and Mechanics Research Center,
Watertown, Massachusetts 02172-0001
DIRECT ANALYSIS OF HEAVILY LOADED CARBON BLACK
FILLED STYRENE-BUTADIENE RUBBER USED IN TANK TRACK
PADS BY FT-IR -
James M. Sloan and Joseph P. Clements
Technical Report AMMRC TR 84-25, June 1984, 11 pp -
illus-tables, D/A Project 11161101A91A

Infrared spectra have been obtained of a heavily loaded (50 per hundred) carbon black filled styrene-butadiene rubber using a Fourier transform infrared spectrometer. Attenuated total reflectance (ATR) spectroscopy sampling employing a germanium (Ge) internal reflectance element was found to yield quality infrared spectra where other techniques have failed. Subtle changes were observed between the spectra of the filled and unfilled styrene-butadiene rubber (SBR). These changes are attributed to the interaction between polymer and filler.

AD UNCLASSIFIED
UNLIMITED DISTRIBUTION
Key Words
Elastomers
Infrared spectroscopy

Army Materials and Mechanics Research Center,
Watertown, Massachusetts 02172-0001
DIRECT ANALYSIS OF HEAVILY LOADED CARBON BLACK
FILLED STYRENE-BUTADIENE RUBBER USED IN TANK TRACK
PADS BY FT-IR -
James M. Sloan and Joseph P. Clements
Technical Report AMMRC TR 84-25, June 1984, 11 pp -
illus-tables, D/A Project 11161101A91A

Infrared spectra have been obtained of a heavily loaded (50 per hundred) carbon black filled styrene-butadiene rubber using a Fourier transform infrared spectrometer. Attenuated total reflectance (ATR) spectroscopy sampling employing a germanium (Ge) internal reflectance element was found to yield quality infrared spectra where other techniques have failed. Subtle changes were observed between the spectra of the filled and unfilled styrene-butadiene rubber (SBR). These changes are attributed to the interaction between polymer and filler.

AD UNCLASSIFIED
UNLIMITED DISTRIBUTION
Key Words
Elastomers
Infrared spectroscopy

Army Materials and Mechanics Research Center,
Watertown, Massachusetts 02172-0001
DIRECT ANALYSIS OF HEAVILY LOADED CARBON BLACK
FILLED STYRENE-BUTADIENE RUBBER USED IN TANK TRACK
PADS BY FT-IR -
James M. Sloan and Joseph P. Clements
Technical Report AMMRC TR 84-25, June 1984, 11 pp -
illus-tables, D/A Project 11161101A91A

Infrared spectra have been obtained of a heavily loaded (50 per hundred) carbon black filled styrene-butadiene rubber using a Fourier transform infrared spectrometer. Attenuated total reflectance (ATR) spectroscopy sampling employing a germanium (Ge) internal reflectance element was found to yield quality infrared spectra where other techniques have failed. Subtle changes were observed between the spectra of the filled and unfilled styrene-butadiene rubber (SBR). These changes are attributed to the interaction between polymer and filler.

AD UNCLASSIFIED
UNLIMITED DISTRIBUTION
Key Words
Elastomers
Infrared spectroscopy

Army Materials and Mechanics Research Center,
Watertown, Massachusetts 02172-0001
DIRECT ANALYSIS OF HEAVILY LOADED CARBON BLACK
FILLED STYRENE-BUTADIENE RUBBER USED IN TANK TRACK
PADS BY FT-IR -
James M. Sloan and Joseph P. Clements
Technical Report AMMRC TR 84-25, June 1984, 11 pp -
illus-tables, D/A Project 11161101A91A

Infrared spectra have been obtained of a heavily loaded (50 per hundred) carbon black filled styrene-butadiene rubber using a Fourier transform infrared spectrometer. Attenuated total reflectance (ATR) spectroscopy sampling employing a germanium (Ge) internal reflectance element was found to yield quality infrared spectra where other techniques have failed. Subtle changes were observed between the spectra of the filled and unfilled styrene-butadiene rubber (SBR). These changes are attributed to the interaction between polymer and filler.

1

END

FILMED

10-84

DTIC