

AD-A146 508

PREPARATION AND ELECTRONIC PROPERTIES OF MOS(2) AND
WS(2) SINGLE CRYSTALS. (U) BROWN UNIV PROVIDENCE RI
DEPT OF CHEMISTRY D H D'AMBRA ET AL. 21 SEP 84 TR-30
N00014-77-C-0387


1/1

UNCLASSIFIED

F/G 20/2

NL



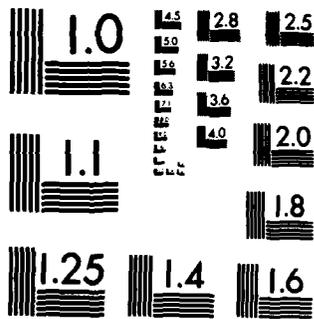

COPY RESOLUTION TEST CHART

12

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER 30	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Preparation and Electronic Properties of MoS ₂ and WS ₂ Single Crystals Grown in the Presence of Cobalt	5. TYPE OF REPORT & PERIOD COVERED	
	6. PERFORMING ORG. REPORT NUMBER 30	
7. AUTHOR(s) D.M.D'Ambra, J.V.Marzik, R.Kershaw, J.Baglio K.Dwight and A.Wold	9. CONTRACT OR GRANT NUMBER(s) N00014-77-C-0387	
PERFORMING ORGANIZATION NAME AND ADDRESS Aaron Wold Department of Chemistry Brown University, Providence, RI 02912	10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR 359-653	
CONTROLLING OFFICE NAME AND ADDRESS Dr. David Nelson Office of Naval Research - Code 472 Arlington, Virginia 22217	12. REPORT DATE September 21, 1984	
	13. NUMBER OF PAGES 17	
MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)	15. SECURITY CLASS. (of this report)	
	15a. DECLASSIFICATION/DOWNGRADING SCHEDULE	
16. DISTRIBUTION STATEMENT (of this Report) APPROVED FOR PUBLIC RELEASE: DISTRIBUTION UNLIMITED		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES SUBMITTED TO JOURNAL OF SOLID STATE CHEMISTRY		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Layered dichalcogenides; Hall measurements; Surface phase		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Single crystals of MoS ₂ and WS ₂ were grown by chemical vapor transport both in the presence and absence of cobalt. Hall measurements indicate that cobalt cannot diffuse appreciably into the bulk of MoS ₂ or WS ₂ and, therefore, can be present only on the surface. Similar results were obtained for as-grown crystals annealed or sulfided in contact with CogSg or sulfided after being dipped in a 0.1M CoSO ₄ /methanol solution.		

AD-A146 508

DTIC FILE COPY

DTIC
EXTRACTED
OCT 10 1984

OFFICE OF NAVAL RESEARCH

Contract N00014-77-C-0387

Task No. NR 359-653

TECHNICAL REPORT NO. 30

Preparation and Electronic Properties of MoS₂ and WS₂ Single Crystals
Grown in the Presence of Cobalt

by

D. M. D'Ambra, J. V. Marzik, R. Kershaw, J. Baglio

K. Dwight and A. Wold

Prepared for Publication

in the

Journal of Solid State Chemistry

Brown University
Department of Chemistry
Providence, Rhode Island 02912

and

¹GTE Laboratories
Waltham, Massachusetts 02554

September 24, 1984

Reproduction in whole or in part is permitted for
any purpose of the United States Government

This document has been approved for public release and sale;
its distribution is unlimited

PREPARATION AND ELECTRONIC PROPERTIES OF MoS₂ AND WS₂ SINGLE CRYSTALS

GROWN IN THE PRESENCE OF COBALT

by

D. M. D'Ambra, J. V. Marzik, R. Kershaw, J. Baglio*,

K. Dwight and A. Wold*

Department of Chemistry, Brown University

Providence, Rhode Island 02912

*GTE Laboratories, Inc., Sylvan Road, Waltham, Massachusetts 02254

Accession For		
NTIS	GRA&I	<input checked="" type="checkbox"/>
DTIC	TAB	<input type="checkbox"/>
Unannounced		<input type="checkbox"/>
Justification		
By		
Distribution/		
Availability Codes		
Availability/		
Initials		
A-1		

*To whom all correspondence should be addressed.

ABSTRACT

Single crystals of MoS_2 and WS_2 were grown by chemical vapor transport both in the presence and absence of cobalt. Hall measurements indicate that cobalt cannot diffuse appreciably into the bulk of MoS_2 or WS_2 and, therefore, can be present only on the surface. Similar results were obtained for as-grown crystals annealed or sulfided in contact with Co_9S_8 or sulfided after being dipped in a 0.1M CoSO_4 /methanol solution.

INTRODUCTION

Recently, extended x-ray absorption fine structure (EXAFS) of cobalt promoted MoS₂ hydrodesulfurization catalysts has demonstrated that they contain a sulfided molybdenum phase which is structurally similar to crystalline MoS₂ (1, 2, 3). However, within a S-Mo-S sheet the average coordination number for the Mo-Mo coordination shell appeared to be reduced relative to that of bulk MoS₂. Additionally, Huntley et al. (2) and Parham et al. (3) indicated that a reduced coordination number was found for the first coordination shell of sulfur about molybdenum. These results suggest that the molybdenum is present in the form of very small crystallites ($\sim 10-15\text{\AA}$) of MoS₂.

The nature as well as the promotional effect of the cobalt associated with these MoS₂ crystallites is less clear. Schrader and Cheng (4) have indicated that the function of cobalt was to facilitate the reduction of oxysulfide phases during the sulfiding of the oxide precursor and also to prevent formation of well-crystallized MoS₂. However, they were unable to identify by Raman spectroscopy what cobalt phase(s) were present. Topsøe, using a number of techniques including Mössbauer emission spectroscopy, has proposed the existence of a distinct Co-Mo-S phase (5, 6). When dispersed on alumina, this MoS₂-like phase consists of single S-Mo-S sheets with cobalt atoms located on surface positions. Furthermore, for both bulk (7) and supported (8) Co-Mo sulfide catalysts, the catalytic activity appears to be related to the amount of cobalt associated with this Co-Mo-S phase.

Other models have been proposed to explain the promotional effect of cobalt. Delmon (9) has proposed a synergistic effect resulting from intimate contact between Co₉S₈ and MoS₂ (contact synergy model). Voorhoeve and Stuver (10) introduced the intercalation model in which nickel was partially intercalated

into the van der Waals gap (between sulfur-sulfur layers) of WS_2 . The model was extended to cobalt promoted MoS_2 hydrodesulfurization catalysts by Farragher and Cossee (11). This pseudo-intercalation model restricted the intercalation of cobalt to the edges of MoS_2 .

If any appreciable quantity of cobalt were to diffuse into bulk MoS_2 or WS_2 , then there should be a measurable change in the number of carriers as obtained from Hall measurements. However, if the cobalt remains primarily associated with the surface, then there would be no significant change. In this study a number of different methods were used to prepare single crystals of cobalt promoted MoS_2 and WS_2 . Hall measurements were made on crystals grown both in the presence and absence of cobalt.

EXPERIMENTAL

Crystal Growth

Single crystals of MoS_2 and WS_2 were grown by chemical vapor transport both in the presence and absence of Co_9S_8 . Chlorine was used as the transport agent. Molybdenum (Gallard-Schlesinger, 99.99%) and tungsten (Gallard-Schlesinger, 99.995%) were both reduced at $800^\circ C$ for 8 hrs in a dry 85%/15% Ar/H_2 atmosphere to remove oxygen. Sulfur (Gallard-Schlesinger, 99.999%) was resublimed in vacuum at $80^\circ C$ before use. Co_9S_8 powder was prepared at $450^\circ C$ as described previously (12).

For crystals grown in the absence of cobalt, large single crystals of MoS_2 and WS_2 were prepared as described in an earlier publication (13). For crystals grown in the presence of cobalt, 1 wt% Co_9S_8 was added to the charge. Growth conditions identical to those for undoped crystals were followed. A chlorine concentration of 3 mg/ml was used. The effect of slow cooling or annealing the as-grown crystals was determined. At the end of the growth process, some

transport tubes were cooled at a rate of $10^{\circ}/\text{hr}$ to room temperature; others were cooled to a temperature of 450°C and the crystals annealed for one week at that temperature. All crystals grown in the presence of cobalt were washed and dried with acetone to remove surface cobalt halide.

Some crystals of MoS_2 and WS_2 , grown in the absence of cobalt, were placed in silica tubes and totally covered with Co_9S_8 powder. The tubes were evacuated and the samples annealed at 450°C for one week.

Other crystals covered with Co_9S_8 were placed in a vertical silica reactor and sulfided for 4 hrs with $\text{H}_2/\text{H}_2\text{S}$ (40:1 v/v) at 450°C . The reactor tube was then air quenched to room temperature. Further details of this sulfiding procedure have recently been reported (12).

Still other crystals were divided into two parts. One of the pieces was dipped into a freshly prepared 0.1 M CoSO_4 /methanol solution and air dried. The dipped portions were then placed in the vertical reactor and sulfided as described above.

Electrical Measurements

Prior to performing any measurements, crystals grown in the absence of cobalt were peeled with Scotch tape to remove surface silicon and oxygen impurities (13). Crystals grown in the presence of cobalt were also peeled, but in addition, a comparison was made with unpeeled samples. Crystals treated in intimate contact with Co_9S_8 were initially measured unpeeled. Surface peeling and remeasurement of the same sample followed subsequently. The electrical properties of crystal portions that were dipped in CoSO_4 and sulfided were compared with those of the undipped sections.

Room temperature resistivity and DC Hall effect were measured on the single crystals using the van der Pauw technique (14). Contacts were made by the

ultrasonic soldering of indium directly onto the samples, and ohmic behavior was established by measuring current-voltage characteristics.

RESULTS

The electrical properties obtained for the undoped MoS₂ and WS₂ crystals (Table I) agree well with those values reported in the literature (13, 15). Hall data for crystals grown in the presence of cobalt are shown in Table II. There appears to be no variation in the sign of the carrier and little in the number of carriers for both MoS₂ and WS₂ crystals grown either in the presence or absence of cobalt. Surface peeling of crystals grown in the presence of cobalt has no significant effect on their electrical properties. Furthermore, for crystals grown by chemical vapor transport in which the tube was either slow-cooled or annealed, little change in the Hall measurements was observed.

The Hall data are summarized in Table III for as-grown crystals treated with either Co₉S₈ or CoSO₄. The MoS₂ and WS₂ crystals annealed in Co₉S₈ show no significant change in the number of carriers let alone in their sign. Surface peeling also had no effect. Similar results were obtained for crystals covered with Co₉S₈ and sulfided. Portions of the crystals dipped in a cobalt sulfate/alcohol solution, removed, dried and sulfided in a H₂/H₂S atmosphere showed no meaningful change in the number of carriers compared to undipped portions.

Sulfiding of cobalt sulfate under the conditions specified would be expected to produce Co₉S₈ (12). Visual examination of these crystals revealed the presence of a black phase on the crystal surface. Identification of this phase was obtained by repeatedly placing drops of CoSO₄ solution onto an undoped crystal, followed by drying. This produced a sufficiently thick CoSO₄ coating

which, after sulfiding, could be removed and characterized. X-ray powder diffraction of this phase indicated the presence of single-phase Co_9S_8 . Despite the presence of Co_9S_8 on the surface, no variation in the electrical properties could be determined.

DISCUSSION

Hall measurements provide a sensitive method for detecting the presence of impurity atoms within the bulk. If cobalt atoms were to diffuse appreciably into the bulk of MoS_2 or WS_2 , a change in the number of carriers would be expected. The results presented in this study suggest that no appreciable change occurs regardless of the method used to try to introduce cobalt.

Wentrcek and Wise (16) have reported that when cobalt is diffused into the bulk of naturally occurring MoS_2 crystals, a change from n to p-type behavior is observed. This observation could not be reproduced on the pure synthetic dichalcogenides prepared in this study.

Recently, Chianelli et al. (17) have examined the chemistry of single crystal edge planes in MoS_2 . Results obtained using Auger spectroscopy, indicated that crystals grown in the presence of cobalt tended to show a segregation of cobalt at the surface edges of MoS_2 . Furthermore, Chianelli et al. indicated that oxidation occurred preferentially along these edge planes. Previously, Bahl, et al. (18) reported similar findings for surface oxidation of naturally occurring MoS_2 crystals. Surface oxidation of synthetic WS_2 crystals in a CO_2 atmosphere has also been found to give preferential edge plane oxidation (Figure 1). It does appear that cobalt impurities accumulate at the edges and reactions, e.g. hydrodesulfurization, could occur along these edge planes.

Hall measurements indicate that cobalt can be present only on the surface of MoS_2 and has not diffused appreciably into the bulk. Topsøe has indicated that for cobalt promoted molybdenum hydrodesulfurization catalysts the cobalt occupies surface positions in an MoS_2 -like structure which he identifies as a Co-Mo-S phase (6). The lack in variation of the number of carriers found in MoS_2 and WS_2 single crystals containing small quantities of surface cobalt sulfides are consistent with this "surface phase".

ACKNOWLEDGMENTS

Acknowledgment is made to the National Science Foundation (DMR-82-03667) for the support of D. M. D'Ambra and K. Dwight and the Office of Naval Research for the support of J. V. Marzik. The authors would also like to express their appreciation for the use of Brown University's Materials Research Laboratory which is supported by the National Science Foundation. Special thanks go to M. Sosnowski and J. Fogarty for their assistance with the microscopic analysis.

REFERENCES

1. B. S. Clausen, H. Topsøe, R. Candia, J. Villadsen, B. Lengeler, J. Als-Nielsen, and F. Christensen, *J. Phys. Chem.* 85, 3868 (1981).
2. D. R. Huntley, T. G. Parham, R. P. Merrill, and M. J. Sienko, *Inorg. Chem.* 22, 4144 (1983).
3. T. G. Parham and R. P. Merrill, *J. Catal.* 85, 295 (1984).
4. G. L. Schrader and C. P. Cheng, *J. Catal.* 85, 488 (1984).
5. H. Topsøe, "Advances in Catalytic Chemistry II" Salt Lake City, May 18-21, 1982.
6. H. Topsøe, B. S. Clausen, R. Candia, C. Wivel and S. Mørup, *J. Catal.* 68, 433 (1981).
7. R. Candia, B. S. Clausen, and H. Topsøe, *J. Catal.* 77, 564 (1982).
8. C. Wivel, R. Candia, B. S. Clausen, S. Mørup, and H. Topsøe, *J. Catal.* 68, 453 (1981).
9. B. Delmon, in "Proceedings of the Climax Third International Conference on Chemistry and Uses of Molybdenum." (H. F. Barry and P. C. H. Mitchell, Eds.), p.73. Climax Molybdenum Co., Ann Arbor, Michigan, 1979.
10. R. J. H. Voorhoeve and J. C. M. Stuiiver, *J. Catal.* 23, 243 (1971).
11. A. L. Farragher and P. Cossee, in "Proceedings, 5th International Congress on Catalysis, Palm Beach, 1972." (J. W. Hightower, Ed.) p. 1301. North-Holland, Amsterdam, 1973.
12. D. M. Pasquariello, R. Kershaw, J. D. Passaretti, K. Dwight, and A. Wold, *Inorg. Chem.* 23, 872 (1984).
13. J. Baglio, E. Kamieniecki, N. DeCola, C. Struck, J. Marzik, K. Dwight, and A. Wold, *J. Solid State Chem.* 49, 166 (1983).

14. L. J. van der Pauw, Philips Res. Rep. 13, 1 (1958).
15. J. A. Wilson, A. D. Yoffe, Adv. Phys. 18(73), 193 (1969).
16. P. R. Wentrcek and H. Wise, J. Catal. 51, 80 (1978).
17. R. R. Chianelli, A. F. Ruppert, S. K. Behal, B. H. Kear, A. Wold,
and R. Kershaw, Submitted for publication.
18. O. P. Bahl, E. L. Evans, and J. M. Thomas, Surface Sci. 8, 473
(1967); Proc. Roy. Soc. A 306, 53 (1968).

FIGURE CAPTIONS

Figure 1. Scanning Electron Micrographs of a WS_2 crystal edge plane before and after oxidation: (a) Unoxidized-- magnification = 2000x; (b) Oxidized-- magnification = 500x; (c) Oxidized-- magnification = 2000x.

TABLE I
Room Temperature Hall Measurements of MoS₂ and WS₂ Crystals
Grown in Absence of Cobalt

Compound	Carrier Type	No. Carriers (/cm ³)
MoS ₂	n	.8(1) x 10 ¹⁶
	n	1.3(1) x 10 ¹⁶
WS ₂	n	1.6(1) x 10 ¹⁵
	n	1.5(1) x 10 ¹⁵

TABLE II
Hall Measurements of MoS₂ and WS₂ Crystals
Grown in Presence of Cobalt

Compound	Preparation	Treatment	Carrier Type	No. Carriers (/cm ³)
MoS ₂	(a)	Unpeeled	n	2.1(2) x 10 ¹⁶
		Peeled	n	1.9(3) x 10 ¹⁶
	(b)	Unpeeled	n	1.5(2) x 10 ¹⁶
		Peeled	n	.7(1) x 10 ¹⁶
	(c)	Unpeeled	n	1.1(1) x 10 ¹⁶
		Peeled	n	1.1(1) x 10 ¹⁶
WS ₂	(a)	Unpeeled	n	3.1(3) x 10 ¹⁵
		Peeled	n	3.9(4) x 10 ¹⁵
	(b)	Unpeeled	n	1.6(2) x 10 ¹⁵
		Peeled	n	2.9(4) x 10 ¹⁵
	(c)	Unpeeled	n	2.1(1) x 10 ¹⁵
		Peeled	n	2.9(2) x 10 ¹⁵

(a) Allowed to cool in furnace overnight

(b) Slow-cooled @ 10°C/hr to room temperature

(c) Annealed @ 450°C for 1 week

TABLE III


Hall Measurements of MoS₂ and WS₂ Crystals
Treated in CogSg or Dipped/Sulfided with CoSO₄

Compound	Preparation	Treatment	Carrier Type	No. Carriers (/cm ³)
MoS ₂	(a)	Unpeeled	n	2.8(2) x 10 ¹⁶
		Peeled and remeasured	n	2.8(4) x 10 ¹⁶
	(b)	Unpeeled	n	.7(1) x 10 ¹⁶
		Peeled and remeasured	n	1.3(1) x 10 ¹⁶
	(c)	Undipped	n	2.9(4) x 10 ¹⁶
		Dipped	n	1.9(2) x 10 ¹⁶
WS ₂	(a)	Unpeeled	n	1.7(1) x 10 ¹⁵
		Peeled and remeasured	n	1.8(1) x 10 ¹⁵
	(b)	Unpeeled	n	2.1(1) x 10 ¹⁵
		Peeled and remeasured	n	4.4(1) x 10 ¹⁵
	(c)	Undipped	n	2.0(2) x 10 ¹⁵
		Dipped	n	2.1(1) x 10 ¹⁵

(a) Annealed in CogSg at 450°C

(b) Sulfided in CogSg at 450°C

(c) CoSO₄ dipped and sulfided at 450°C



WS2
2K X



WO₃/WS₂
500X



WO₃/WS₂
2K X

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	<u>No. Copies</u>		<u>No. Copies</u>
Office of Naval Research Attn: Code 413 800 N. Quincy Street Arlington, Virginia 22217	2	Naval Ocean Systems Center Attn: Technical Library San Diego, California 92152	1
ONR Pasadena Detachment Attn: Dr. R. J. Marcus 1030 East Green Street Pasadena, California 91106	1	Naval Weapons Center Attn: Dr. A. B. Amster Chemistry Division China Lake, California 93555	1
Commander, Naval Air Systems Command Attn: Code 310C (H. Rosenwasser) Washington, D.C. 20360	1	Scientific Advisor Commandant of the Marine Corps Code RD-1 Washington, D.C. 20380	1
Naval Civil Engineering Laboratory Attn: Dr. R. W. Drisko Port Hueneme, California 93401	1	Dean William Tolles Naval Postgraduate School Monterey, California 93940	1
Superintendent Chemistry Division, Code 6100 Naval Research Laboratory Washington, D.C. 20375	1	U.S. Army Research Office Attn: CRD-AA-IP P.O. Box 12211 Research Triangle Park, NC 27709	1
Defense Technical Information Center Building 5, Cameron Station Alexandria, Virginia 22314	12	Mr Vincent Schaper DTNSRDC Code 2830 Annapolis, Maryland 21402	1
DTNSRDC Attn: Dr. G. Bosmajian Applied Chemistry Division Annapolis, Maryland 21401	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, Pennsylvania 19112	1
Naval Ocean Systems Center Attn: Dr. S. Yamamoto Marine Sciences Division San Diego, California 91232	1	Mr. A. M. Anzalone Administrative Librarian PLASTE/ARRADCOM Bldg 3401 Dover, New Jersey 07801	1

DL/413/83/01
359/413-2

TECHNICAL REPORT DISTRIBUTION LIST, 359

Dr. Paul Delahay
Department of Chemistry
New York University
New York, New York 10003

Dr. P. J. Hendra
Department of Chemistry
University of Southampton
Southampton SO9 5NH
United Kingdom

Dr. T. Katan
Lockheed Missiles and
Space Co., Inc.
P.O. Box 504
Sunnyvale, California 94088

Dr. D. N. Bennion
Department of Chemical Engineering
Brigama Young University
Provo, Utah 84602

Dr. R. A. Marcus
Department of Chemistry
California Institute of Technology
Pasadena, California 91125

Mr. Joseph McCartney
Code 7121
Naval Ocean Systems Center
San Diego, California 92152

Dr. J. J. Auburn
Bell Laboratories
Murray Hill, New Jersey 07974

Dr. Joseph Singer, Code 302-1
NASA-Lewis
21000 Brookpark Road
Cleveland, Ohio 44135

Dr. P. P. Schmidt
Department of Chemistry
Oakland University
Rochester, Michigan 48063

Dr. H. Richtol
Chemistry Department
Rensselaer Polytechnic Institute
Troy, New York 12181

Dr. E. Yeager
Department of Chemistry
Case Western Reserve University
Cleveland, Ohio 44106

Dr. C. E. Mueller
The Electrochemistry Branch
Naval Surface Weapons Center
White Oak Laboratory
Silver Spring, Maryland 20910

Dr. Sam Perone
Chemistry & Materials
Science Department
Lawrence Livermore National Lab.
Livermore, California 94550

Dr. Royce W. Murray
Department of Chemistry
University of North Carolina
Chapel Hill, North Carolina 27514

Dr. G. Goodman
Johnson Controls
5757 North Green Bay Avenue
Milwaukee, Wisconsin 53201

Dr. B. Brummer
EIC Incorporated
111 Chapel Street
Newton, Massachusetts 02158

Dr. Adam Heller
Bell Laboratories
Murray Hill, New Jersey 07974

Electrochimica Corporation
Attn: Technical Library
2485 Charleston Road
Mountain View, California 94040

Library
Duracell, Inc.
Burlington, Massachusetts 01803

Dr. A. B. Ellis
Chemistry Department
University of Wisconsin
Madison, Wisconsin 53706

TECHNICAL REPORT DISTRIBUTION LIST, 359

Dr. M. Wrighton
Chemistry Department
Massachusetts Institute
of Technology
Cambridge, Massachusetts 02139

Dr. B. Stanley Pons
Department of Chemistry
University of Utah
Salt Lake City, Utah 84112

Donald E. Mains
Naval Weapons Support Center
Electrochemical Power Sources Division
Crane, Indiana 47522

S. Ruby
DOE (STOR)
M.S. 6B025 Forrestal Bldg.
Washington, D.C. 20595

Dr. A. J. Bard
Department of Chemistry
University of Texas
Austin, Texas 78712

Dr. Janet Osteryoung
Department of Chemistry
State University of New York
Buffalo, New York 14214

Dr. Donald W. Ernst
Naval Surface Weapons Center
Code R-33
White Oak Laboratory
Silver Spring, Maryland 20910

Mr. James R. Moden
Naval Underwater Systems Center
Code 3632
Newport, Rhode Island 02840

Dr. Bernard Spielvogel
U.S. Army Research Office
P.O. Box 12211
Research Triangle Park, NC 27709

Dr. William Ayers
ECD Inc.
P.O. Box 5357
North Branch, New Jersey 08876

Dr. M. M. Nicholson
Electronics Research Center
Rockwell International
3370 Miraloma Avenue
Anaheim, California

Dr. Michael J. Weaver
Department of Chemistry
Purdue University
West Lafayette, Indiana 47907

Dr. R. David Rauh
EIC Corporation
111 Chapel Street
Newton, Massachusetts 02158

Dr. Aaron Wold
Department of Chemistry
Brown University
Providence, Rhode Island 02192

Dr. Martin Fleischmann
Department of Chemistry
University of Southampton
Southampton SO9 5NH ENGLAND

Dr. R. A. Osteryoung
Department of Chemistry
State University of New York
Buffalo, New York 14214

Dr. Denton Elliott
Air Force Office of Scientific
Research
Bolling AFB
Washington, D.C. 20332

Dr. R. Nowak
Naval Research Laboratory
Code 6130
Washington, D.C. 20375

Dr. D. F. Shriver
Department of Chemistry
Northwestern University
Evanston, Illinois 60201

Dr. Aaron Fletcher
Naval Weapons Center
Code 3852
China Lake, California 93555

TECHNICAL REPORT DISTRIBUTION LIST, 359

Dr. David Aikens
Chemistry Department
Rensselaer Polytechnic Institute
Troy, New York 12181

Dr. A. P. B. Lever
Chemistry Department
York University
Downsview, Ontario M3J1P3

Dr. Stanislaw Szpak
Naval Ocean Systems Center
Code 6343, Bayside
San Diego, California 95152

Dr. Gregory Farrington
Department of Materials Science
and Engineering
University of Pennsylvania
Philadelphia, Pennsylvania 19104

M. L. Robertson
Manager, Electrochemical
and Power Sources Division
Naval Weapons Support Center
Crane, Indiana 47522

Dr. T. Marks
Department of Chemistry
Northwestern University
Evanston, Illinois 60201

Dr. Micha Tomkiewicz
Department of Physics
Brooklyn College
Brooklyn, New York 11210

Dr. Lesser Blum
Department of Physics
University of Puerto Rico
Rio Piedras, Puerto Rico 00931

Dr. Joseph Gordon, II
IBM Corporation
K33/281
5600 Cottle Road
San Jose, California 95193

Dr. D. H. Whitmore
Department of Materials Science
Northwestern University
Evanston, Illinois 60201

Dr. Alan Bewick
Department of Chemistry
The University of Southampton
Southampton, SO9 5NH ENGLAND

Dr. E. Anderson
NAVSEA-56Z33 NC #4
2541 Jefferson Davis Highway
Arlington, Virginia 20362

Dr. Bruce Dunn
Department of Engineering &
Applied Science
University of California
Los Angeles, California 90024

Dr. Elton Cairns
Energy & Environment Division
Lawrence Berkeley Laboratory
University of California
Berkeley, California 94720

Dr. D. Cipris
Allied Corporation
P.O. Box 3000R
Morristown, New Jersey 07960

Dr. M. Philpott
IBM Corporation
5600 Cottle Road
San Jose, California 95193

Dr. Donald Sandstrom
Department of Physics
Washington State University
Pullman, Washington 99164

Dr. Carl Kannewurf
Department of Electrical Engineering
and Computer Science
Northwestern University
Evanston, Illinois 60201

TECHNICAL REPORT DISTRIBUTION LIST, 359

Dr. Robert Somoano
Jet Propulsion Laboratory
California Institute of Technology
Pasadena, California 91103

Dr. Johann A. Joebstl
USA Mobility Equipment R&D Command
DRDME-EC
Fort Belvoir, Virginia 22060

Dr. Judith H. Ambrus
NASA Headquarters
M.S. RTS-6
Washington, D.C. 20546

Dr. Albert R. Landgrebe
U.S. Department of Energy
M.S. 6B025 Forrestal Building
Washington, D.C. 20595

Dr. J. J. Brophy
Department of Physics
University of Utah
Salt Lake City, Utah 84112

Dr. Charles Martin
Department of Chemistry
Texas A&M University
College Station, Texas 77843

Dr. H. Tachikawa
Department of Chemistry
Jackson State University
Jackson, Mississippi 39217

Dr. Theodore Beck
Electrochemical Technology Corp.
3935 Leary Way N.W.
Seattle, Washington 98107

Dr. Farrell Lytle
Boeing Engineering and
Construction Engineers
P.O. Box 3707
Seattle, Washington 98124

Dr. Robert Gotscholl
U.S. Department of Energy
MS G-226
Washington, D.C. 20545

Dr. Edward Fletcher
Department of Mechanical Engineering
University of Minnesota
Minneapolis, Minnesota 55455

Dr. John Fontanella
Department of Physics
U.S. Naval Academy
Annapolis, Maryland 21402

Dr. Martha Greenblatt
Department of Chemistry
Rutgers University
New Brunswick, New Jersey 08903

Dr. John Wasson
Syntheco, Inc.
Rte 6 - Industrial Pike Road
Gastonia, North Carolina 28052

Dr. Walter Roth
Department of Physics
State University of New York
Albany, New York 12222

Dr. Anthony Sammells
Eltron Research Inc.
710 E. Ogden Avenue #108
Naperville, Illinois 60540

Dr. W. M. Risen
Department of Chemistry
Brown University
Providence, Rhode Island 02192

Dr. C. A. Angell
Department of Chemistry
Purdue University
West Lafayette, Indiana 47907

Dr. Thomas Davis
Polymer Science and Standards
Division
National Bureau of Standards
Washington, D.C. 20234

END

FILMED

DTIC