

AD-A150 270


RAPID SOLIDIFICATION PROCESSING OF MAGNESIUM ALLOYS(U)  
MASSACHUSETTS INST OF TECH CAMBRIDGE DEPT OF MATERIALS  
SCIENC. M C FLEMINGS ET AL. SEP 84 AMMRC-TR-84-37  
DAG46-82-K-0051

1/1


UNCLASSIFIED

F/G 13/8

NL





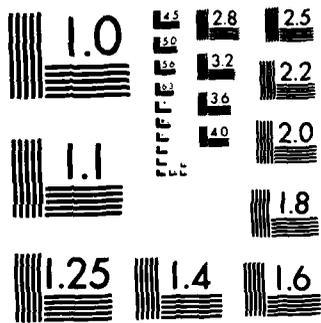

MICROCOPY RESOLUTION TEST CHART  
NATIONAL BUREAU OF STANDARDS-1963-A

AD-A150 270

12



AD

AMMRC TR 84-37

RAPID SOLIDIFICATION PROCESSING OF  
MAGNESIUM ALLOYS

September 1984

M. C. FLEMINGS and A. MORTENSEN  
Department of Materials Science & Engineering  
Massachusetts Institute of Technology  
Cambridge, Massachusetts 02139

FINAL REPORT

DAAG46-82-K-0051

DTIC  
ELECTE  
FEB 11 1985

B

Approved for public release; distribution unlimited

DTIC FILE COPY

Prepared for

ARMY MATERIALS AND MECHANICS RESEARCH CENTER  
Watertown, Massachusetts 02172-0001

85 01 30 010

The findings in this report are not to be construed as an official Department of the Army position, unless so designated by other authorized documents.

Mention of any trade names or manufacturers in this report shall not be construed as advertising nor as an official indorsement or approval of such products or companies by the United States Government.

**DISPOSITION INSTRUCTIONS**

Destroy this report when it is no longer needed.  
Do not return it to the originator

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER AMMRC TR 84-37	2. GOVT ACCESSION NO. <b>AD-A150 270</b>	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) RAPID SOLIDIFICATION PROCESSING OF MAGNESIUM ALLOYS		5. TYPE OF REPORT & PERIOD COVERED Final Report 1 Aug 82 - 31 Jul 83
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) M. C. Flemings and A. Mortensen		8. CONTRACT OR GRANT NUMBER(s) DAAG46-82-K-0051
9. PERFORMING ORGANIZATION NAME AND ADDRESS Department of Materials Science & Engineering Massachusetts Institute of Technology Cambridge, Massachusetts 02139		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS AMCMS Code: 612105-H84001
11. CONTROLLING OFFICE NAME AND ADDRESS Army Materials & Mechanics Research Center ATTN: AMXMR-K Watertown, Massachusetts 02172-0001		12. REPORT DATE September 1984
		13. NUMBER OF PAGES 47
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		15. SECURITY CLASS (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report)  Approved for public release; distribution unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Rapid solidification, Mechanical properties Processing, Magnesium alloys Extrusion, Powder metallurgy;		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number)  (SEE REVERSE)		

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

Block No. 20

## ABSTRACT

This report comprises the second year of a two year program on Rapid Solidification, extrusion processing and mechanical property measurement of Magnesium alloys.

During the first year, the Rapid Solidification of various Mg alloys and the resultant structures were investigated in two stages. The first involved the study of the Mg-Zn system processed by chill casting and melt spinning. It was observed that the amount of second phase decreased with decreasing distance from the chill surface to eventually become completely suppressed in a featureless zone. The second stage dealt with the splat quenching and melt spinning of Mg-5%Zn, Mg-8%Al, EZ33, AZ91, and QE22. In all the alloys, the presence of a featureless zone was observed that was shown in the Mg-Zn system to consist of a homogeneous solid solution having the initial alloy composition. For the Mg-5%Zn, EZ33, and ZE41 alloys, melt spun ribbons were almost completely featureless throughout a 70  $\mu$ m average ribbon thickness. Microhardness measurements were taken for alloys EZ33 and ZE41, and the rapidly solidified featureless regions were found to have a greater hardness than both the as-received (primary phase) alloys and the rapidly solidified dendritic structures.

During the second year, samples were cast using a controlled atmosphere (He gas), and vertical wheel melt-spinning apparatus constructed at MIT. Casting conditions were thus perfected, to obtain larger quantities of ribbons of consistent quality. Extrusion procedures were investigated on rapidly solidified magnesium alloys. A gradual lowering of the extrusion temperature from 470°C to 210°C yielded improved mechanical properties on alloys ZK60, EZ33, and Mg-5.3%Zn. Optimal conditions were: a reduction in area ratio of about 1/30, and an extrusion temperature of about 200-250°C. Results on alloy ZK60, extruded under these conditions, displayed interesting mechanical properties, and made it comparable in specific properties to R.S.P. aluminum alloys.

Tensile properties in the as extruded condition were: Y.S. 53.0 ksi, and U.T.S. 56.3 ksi. The ductility in particular was significantly higher than that of wrought ZK60 alloy: 19.6% (typical mechanical properties of the conventional extruded material are: Y.S. 41 ksi, U.T.S. 51 ksi, elongation, 11%).

*Originator furnished...*

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

FOREWORD

This final technical report covers the activity performed under the U.S. Army Contract DAAG-46-82-K-0051 for "Rapid Solidification Processing of Magnesium Alloys" during the period of August 1, 1982 - July 31, 1983 with Professor Merton C. Flemings, Department of Materials Science & Engineering, Massachusetts Institute of Technology as principal investigator. The contract was administered under the direction of the Army Materials & Mechanics Research Center, Watertown, MA 02172, with Dr. Judith J. Kohatsu as Program Technical Monitor.

**S** DTIC  
 ELECTE **D**  
 FEB 11 1985  
 B

Accession For	
NTIS	<input checked="" type="checkbox"/>
DTIC	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution	
Availability Codes	
Dist	Special
A-1	



## FIGURES

1. From Ref. 9 Properties of Mg-1 Zn-Si Extrusions (pg. 10)
2. From Ref. 16 (pg. 10)
3. Processing Steps (pg. 14)
4. Schematic Illustration of Strip Casting Apparatus, Side View (pg. 17)
5. Schematic Illustration of Strip Casting Apparatus, Front View (pg. 18)
6. Strip Casting Apparatus (pg. 19)
7. Strip Casting Apparatus, Wheel and Crucible Assembly (pg. 19)
- 8a. Uncoated Crucible (pg. 21)
- 8b. Coated Crucible (pg. 21)
- 8a. Conical Extrusion Die Geometry (pg. 21)
- 9b. Straight Extrusion Die Geometry (pg. 21)
10. (Scale 1) Extrusion Tooling (pg. 23)
11. Extruded EZ33 Microstructure (x 1000) (pg. 27)
12. Extruded EZ33 Fracture Surface (x 25, x 1000) (pg. 27)
13. Mg. 5.3% Zn, extruded at 450°C (pg. 28)
14. Effect of Aluminum and Zinc Additions on the Strength and Ductility of Rolled Magnesium. % Elongation Scale on Right (After McDonald) (pg. 28)
15. Mg-5.3% Zn, Extruded at 450°C (pg. 31)
16. Mg-5.3% Zn, Extruded at 310°C (pg. 32)
17. Melt-Spun ZK60 (pg. 33)
18. Splatter of ZK60 (pg. 34)
19. Melt-Spun ZK60 - A Thick Ribbon (pg. 34)
20. ZK60 Extruded at 470°C (pg. 37)
21. ZK60 - First Extrusion at 210°C (pg. 38)
22. ZK60 - Second Extrusion at 210°C (pg. 40)
23. ZK60 Double Extrusion at 210°C - Fracture Surface (pg. 41)

## TABLES

- I Properties of Magnesium Powder Extrusions From Ref 6 and 11 (pg. 8)
- II Properties of Extruded Mg Alloys From Ref. 14 (pg. 9)
- III Properties of Microquenched ZK60 From Ref. 13 (pg. 9)
- IV Typical Heat Treatment Schedules for Casting Alloys From Ref. 6 (pg. 12)
- V Binary Mg-Zn Alloys Cast at MIT (pg.16)
- VI Pure Magnesium Extrusion (pg. 26)
- VII EZ33 Extrusion (pg. 26)
- VIII Magnesium-Zinc Extrusion (pg.30)
- IX ZK60 Extrusions (pg. 36)

## Abstract

This report comprises the second year of a two year program on Rapid Solidification, extrusion processing and mechanical property measurement of Magnesium alloys.

During the first year, the Rapid Solidification of various Mg alloys and the resultant structures were investigated in two stages. The first involved the study of the Mg-Zn system processed by chill casting and melt spinning. It was observed that the amount of second phase decreased with decreasing distance from the chill surface to eventually become completely suppressed in a featureless zone. The second stage dealt with the splat quenching and melt spinning of Mg-5%Zn, Mg-8%Al, EZ33, AZ91, and QE22. In all the alloys, the presence of a featureless zone was observed that was shown in the Mg-Zn system to consist of a homogeneous solid solution having the initial alloy composition. For the Mg-5%Zn, EZ33, and ZE41 alloys, melt spun ribbons were almost completely featureless throughout a 70 um average ribbon thickness. Microhardness measurements were taken for alloys EZ33 and ZE41, and the rapidly solidified featureless regions were found to have a greater hardness than both the as-received (primary phase) alloys and the rapidly solidified dendritic structures.

During the second year, samples were cast using a controlled atmosphere (He gas), and vertical wheel melt-spinning apparatus constructed at MIT. Casting conditions were thus perfected, to obtain larger quantities of ribbons of consistent quality. Extrusion procedures were investigated on rapidly solidified magnesium alloys. A gradual lowering of the extrusion temperature from 470°C to 210°C yielded improved mechanical properties on alloys ZK60, EZ33, and Mg-5.3%Zn. Optimal conditions were: a reduction in area ratio of about 1/30, and an extrusion temperature of about 200-250°C. Results on alloy ZK60,

extruded under these conditions, displayed interesting mechanical properties, and made it comparable in specific properties to R.S.P. aluminum alloys.

Tensile properties in the as extruded condition were: Y.S. 53.0 ksi, and U.T.S. 56.3 ksi. The ductility in particular was significantly higher than that of wrought ZK60 alloy: 19.6% (typical mechanical properties of the conventional extruded material are: Y.S. 41 ksi, U.T.S. 51 ksi, elongation, 11%).

## I. INTRODUCTION

Rapid Solidification Processing (R.S.P.), the subject of numerous research projects in Materials Science and Engineering for the past 20 years, has led to the obtention of considerable mechanical property improvements in a number of alloys. Possible, or existing applications of R.S.P. metals are many, ranging from turbine blades<sup>2</sup> to magnetic recording heads<sup>3</sup>. Alloys of aluminum have received considerable attention, and research on those has yielded numerous payoffs in terms of improved mechanical properties, as was exposed in our previous report<sup>1</sup>.

Magnesium alloys, on the other hand, have so far barely been explored in that light. It is the ambition of this project to help fill in that gap, and explore the processing and the engineering properties of R.S.P. magnesium alloys.

Published articles dealing with the subject are relatively few. In one article, the nature and the mixing enthalpies of intermediate and Al-rich phases of the Al-Mg system were investigated using a rapid solidification technique<sup>4</sup>. Metastable solid solutions or intermetallic compounds were found to exist. In another article<sup>5</sup>, the increase in solubility in magnesium of

1. Rapid Solidification Processing, Final Technical Report, 1981-1982, Contract Number DAAG 46-81-K-0051.
2. Rapid Solidification Processing: Principles and Technologies II, Ed., R. Mehrabian, B.H. Kear, and M. Cohen, Claitor's Publishing Division, Baton Rouge, 1980, page 1.
3. T. Masumoto, Proc. 4th Int. Conf. on Rapidly Quenched Metals, Sendai 1981, page 5.
4. B. Predel and K. Hulse, Z. fur Metallkunde, 69, page 690, 1978.
5. N.J. Varich and B.N. Litvin, The Physics of Metals and Metallography, 16, No. 4, 1968, page 29.

Mn or Zr after splat cooling was explored using lattice parameter measurements obtained by X-ray diffraction. The thermal stability of the supersaturated Mg-Mn phases was also explored. In particular, an increase in the solubility of Zr in Mg to a value of 1.2 wt % is claimed by splat quenching "small portions of the melt (at above 800 C° onto a copper chill)". However, this seems to contradict data given by Emley<sup>6</sup> on an already confused issue.

The Mg-Zn system has been found to form metallic glasses by melt-spinning alloys in the range from Mg<sub>80</sub>Zn<sub>20</sub> to Mg<sub>60</sub>Zn<sub>40</sub><sup>7</sup>. Crystallization and recrystallization kinetics of amorphous alloys in that range were studied. Electron transport properties have also been investigated on these metallic glasses<sup>8</sup>.

Work on densified products emanates mainly from the closely related powder metallurgy field. Although in one instance, the standard compaction-sintering path was used<sup>9</sup>, most often extrusion was preferred as a means of densification. The advantage is to be found in the far greater amounts of shear deformation involved in the latter process, an aspect of importance in breaking off the oxide layer surrounding the magnesium particles, to promote metal-metal bonding. Magnesium powder extrusions, alloy extrusions, or powder mixture extrusions

6. E.F. Emley, Principles of Magnesium Technology, Pergamon Press, 1966, page 254.
7. Z. Altounian, et al., J. of Materials Science 17, 1982, page 3268.
8. T. Matsuda and U. Mizutani, J. Phys F: Met. Phys., 12, 1982, page 1877.
9. S. Storchheim, Int. J. of Powder Metallurgy, 8, (3), 1982, page 115.

have been reported by Emley<sup>10</sup>, Foerster<sup>11</sup>, Fischer<sup>12</sup>, and Isserow and Rizzitano<sup>13</sup>. Pure Mg metal powders have been extruded, to investigate to what extent the oxide could produce properties similar to those in S.A.P. aluminum. Some results are given in Table I. A variety of processes such as interference hardening, first described by Busk and Leontis<sup>14</sup> were invented and explored. Work on pre-alloyed quenched powders is relatively rare, however. Busk and Leontis hot extruded atomized ZK60 powders, as well as alloys AZ31, M1 and AMZ111, the three first alloys being commercial. ZK60 gave the best results, as shown in Table II and was even produced on a commercial basis<sup>10</sup> as (P) ZK60B. Isserow and Rizzitano<sup>13</sup> also extruded ZK60, starting with powders obtained by the rotating electrode process. Here the powders were sealed in an aluminum container, and evacuated prior to extrusion. Extrusion temperatures varied from ambient to 370°C (700°F). Results are given in Table II and display excellent mechanical properties. But fracture surfaces show that the products delaminated and care must be exerted in judging the observed longitudinal properties, as they may be highly inferior in directions orthogonally to the extrusion direction. Extrusion reduction in area ratios were 1/10. Also, Storchheim extruded atomized Mg-1% Zn-Si powders, with the results shown in Figure 1.

Magnesium alloys are generally not quite as strong as those of aluminum, on an equal volume basis, but are on the other hand, much lighter. If we compare the specific properties of the two metal alloys, that is the ratio strength/density; to achieve the same specific strength as a typical R.S.P. aluminum alloy with a yield strength of 90 ksi (a reasonable value, as can be seen in

10. E.F. Emley, *Supra* note 2, page 531.
11. G.S. Foerster, *Metals Eng. Quarterly*, 12, (1), page 22.
12. P.A. Fisher, *Int. Metals Reviews*, 1978, No. 6, page 269.
13. S. Isserow and F.J. Rizzitano, *Int. J. of Powder Metallurgy*, 10, (3), July 1974, page 217.
14. R.S. Busk and T.E. Leontis, *Trans. AIME*, Vol. 188, Feb. 1950, *J. of Metals*, page 297.

TYPICAL SCREEN ANALYSIS AND PACKING DENSITIES OF POWDERS USED

Grade	Packing density g cm <sup>3</sup>	Approx. B.S. screen analysis (%)				Remarks
		44-100	72-100	100-240	Passing 240	
Grade 2A	0.4	71	—	2.8	0.3	Ball milled to increase density
3	0.7	—	0.2	98	2	
4	0.4	—	3	89	8	Fines obtained by sieving through 240 BS
4F	—	—	—	—	100	

COMPARATIVE PROPERTIES OF CONVENTIONAL AND POWDER EXTRUSIONS IN PURE MAGNESIUM (3/8 in. ROD FROM 3 in. CONTAINER)

Material extruded	Extrusion conditions		Tensile properties of extrusion		
	Temp. (°C)	Speed (ft. min)	0.1 P.S. (tsi)	U.T.S. (tsi)	El. (%)
Cast billet	420	15	4.6	12.4	9 (on 1 in.)
4	420	30	15.2	22.7	3 1/2
Powder 4F	450	75	17.9	20.6	4 (on 4 1/2 area)
4F - Be	455	120	21.0	22.6	5 1/2

From Ref 6 .

Properties of Dispersion-Hardened Magnesium Extrusions

Composition	Fabrication Data	Extrusion*			Elongation, Pct	Yield Strength, psi		Stress
		Shape	Temperature, °F	Speed, fpm		Tension	Compression	
Mg	<1 μ powder	1/8 in. diam.	1100	<1	1	35,000	36,000	4
ZK10 + 2MgO	Screw extruded	3/8 by 3/8 in.	820	4	7	35,000	22,000	4
Mg-1 Zn-1.6 Si	Atomized, 35/65 mesh	1/16 by 3/8 in.	600	5	3	43,000	36,000	5
Mg-1 Zn-1.6 Si	Atomized, 35/65 mesh	1/16 by 3/8 in.	600	100	7	34,000	22,000	4
Mg-1 Zn-1.6 Si	Atomized, -100 mesh	1/16 by 3/8 in.	600	100	4	45,000	29,000	4
AK11	Interference hardened†	1/16 by 3/8 in.	600	100	8	44,000	45,000	5
AK11	Interference hardened†	1/16 by 3/8 in.	900	70	10	48,000	36,000	5

\* 1/8 in. diam. wire was extruded from 3/8 in. container, others, from 3 in. container.

† Atomized magnesium-zirconium pellets were coated with aluminum flake powder, compacted at 650°F and heat treated 16 hr at 780°F.

From Ref 11 .

TABLE I . Properties of Magnesium Powder Extrusions .

Comparison of As Extruded Properties of Alloys  
Extruded from Powder and from Permanent Mold Billets

Shape	Extrusion Conditions		Powder				Billet			
	Temp. °F	Speed Fpm	1000 psi				1000 psi			
			Pct E	YS	CS	TS	Pct E	YS	CS	TS
AZ31 Rod	600	5	15	39	40	47	16	34	30	44
	700	5	15	36	36	45	15	34	25	45
	800	5	15	35	30	45	14	34	22	44
Strip	650	5	12	29	29	43	18	23	18	39
	650	15	12	25	18	39	16	25	15	38
	650	30	11	25	15	37	15	25	15	38
M1 Rod	600	5	14	44	38	48	25	27	23	39
	700	5	11	43	35	47	23	30	24	40
	800	5	13	43	28	47	14	33	19	43
Strip	650	5	6	34	33	43	23	16	16	33
	650	15	9	30	26	40	19	18	14	35
	650	30	8	28	19	40	18	18	14	35
AMZ111 Rod	600	5	12	40	41	48	19	37	31	45
	700	5	15	40	37	46	13	33	30	42
	800	5	12	38	34	46	11	32	18	40
Strip	650	5	5	37	36	45	10	29	19	40
	650	20	9	33	31	42	8	29	13	38
	650	40	8	32	24	39	9	28	13	38
ZK60 Rod	600	5	16	44	48	53	17	41	41	54
	700	5	17	41	43	51	14	40	34	51
	800	5	15	37	38	48	15	39	27	48
Strip	650	5	10	43	43	52	10	40	40	52
	650	20	8	37	37	47	13	38	38	49
	650	40	7	35	30	45				Hot Short

TABLE II - Properties of extruded Mg Alloys . Ref 14 .

Mechanical Properties of Magnesium ZK60A Rods from Microquenched Powders

Identification	Ext. temp °F	Aging temp °F (24 hr)	0.2 Y.S. ksi	U.T.S. ksi	El. %	RA %	Charpy V-notch ft.-lb.
Commercial	700	300	40.5	49.1	21.0	44.6	5.7
Microquenched K-1*	250	none	48.0		25		
		250	51.4		23		30
K-2**	RT	none	56.5		6		
		250	61.4		17		20; 29
D**	RT	none	54.0	58.5	4.0	5.0	
		250	53.1	57.9	19.0	41.0	
		300	57.2	61.2	4.0	2.6	
E**	150	none	54.5	56.5	17.0	28.1	
		250	57.5	61.0	14.0	32.2	18.5
		300	53.5	59.5	14.0	35.4	15.8

\* Air-cooled after extrusion.

\*\* Water-quenched after extrusion.

Table III - Properties of Microquenched ZK 60 . Ref 13 .


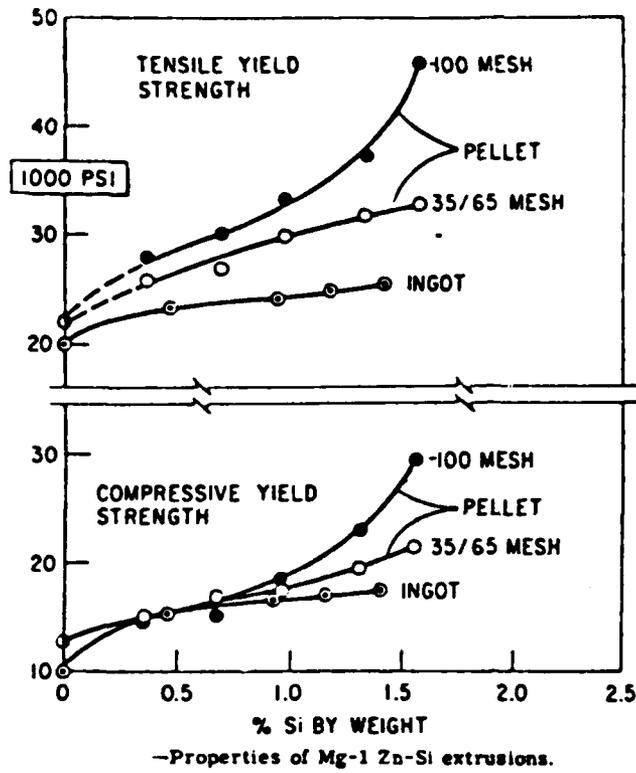


Figure 1 - From Ref 9 .

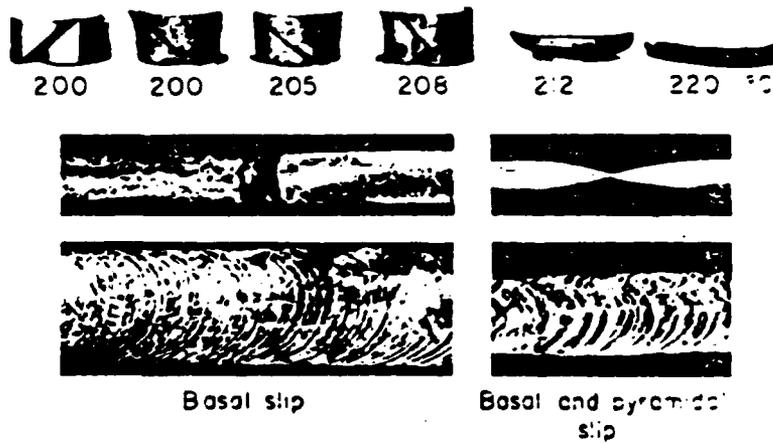

(a) Sudden change in the plastic properties of a magnesium alloy, AZM, with increasing temperature.  
 (b) Slip bands in cold and hot stretched magnesium crystals.

Figure 2 - From Ref 16 .

our previous report), an R.S.P. magnesium alloy must attain a yield strength of about  $(90 \times 108/166) = 58.5$  ksi. Such mechanical properties seem perfectly feasible in magnesium alloys by R.S.P., and are indeed approached on one sample in this project. Such alloys could be of definite interest in aerospace applications, where specific properties are important.

Magnesium has a hexagonal crystal structure, as do most of its solid solutions. An exception is obtained when more than 10% Lithium is alloyed to magnesium, where the structure becomes cubic<sup>15</sup>. At room temperature, only one slip system, operating on the basal (0001) planes is active, together with twinning, to allow plastic deformation of the metal. Formability is therefore poor at room temperature. For each alloy, however, there is a temperature slightly above 200°C, at which pyramidal slip planes become active, with drastic increases in formability<sup>16</sup>. That temperature is 225°C in pure magnesium, and the change is illustrated in Figure 2.

Heat treating temperatures lie usually in the range 150-250°C for aging, see Table IV. Moreover, melt-spun ribbons of EZ33 and ZE41 showed no decrease in hardness properties when treated to the T5 condition at 180°C, for 12 and 16 hours respectively<sup>1</sup>.

In this work, magnesium alloys have been rapidly solidified by melt spinning small quantities onto a rotating copper wheel. The ribbons were subsequently consolidated by first compacting them, and then extruding the green compact. For this last step, there is a compromise to be obtained, between the need for a high temperature, above 220-225°C for improved formability, and a low temperature necessary to retain the quenched-in structures, or interesting modifications thereof, below about 250 C, as was

15. E.F. Emley, Supra note 2, page 299.

16. E.F. Emley, Supra note 2, page 483.

Table IV - From Ref .6  
TYPICAL HEAT TREATMENT SCHEDULES FOR CASTING ALLOYS

Type of treatment	Alloy	Conditions		Typical Tensile Properties †						US Treatment (where difference appreciable)		Remarks
				As cast			Heat treated			Time (hr)	Temp. (°C)	
		Time (hr)	Temp. (°C)	0.1% P.S.	U.T.S.	% El.	0.1% P.S.	U.T.S.	% El.			
Annealing	ZRE1	10-16	170-180	5½	10	4	5½	10	4	{ 2 6	343 215	§
	ZT1	16	315	4½	13½	13	5½	15	7			
Precipitation	Z5Z	10-16±	170-180	7½	15	10	9½	17	7			
	RZ5	(a) { 2 10-16	330 170-180	6	11½	5	8½	14	4			
		(b) 24	250									
TZ6	{ 2 10-16	330 170-180	7½	17	17	10	17½	10				
Solution	A8	{ 8 16	380-390 410-420	5	10	4	4½	16	13	(a) 18 (b)†= { 6 2 10	410 410 350 410	++
Full, with air cooling	AZ91	{ 8 16 10	380-390 410-420 200	5½	10	2	5½	15	7 (ST)	†= { 18 16 6 2 10	410 170 410 350 410	++
							7½	15½	2 (FHT)			
	AZ92	(a) { 18 16	405 170	((14))	(24)	-	((22))	(40)	-			++
		(b)†= { 6 2 10 16	405 350 405 270									
	AZG (AZ63)	{ 12 5	385 220	((14))	(29)	-	((19))	(40)	-			++
	HK31	{ 2 16	565 200	4½	9	5	6½	14	7			=
Z6Z (ZK61)	{ 2 48	500 130	((22))	(38)	-	((28))	(43)	-				
Full, with liquid quenching	MSR	{ 4-8 Quench 8-16	520-530 200	6½	11½	7½	12	16½	5			§§

§ The 2-stage treatment is not recommended since heating at 343°C (650°F) reduces creep resistance.

† Tensile properties not enclosed in parentheses are expressed in tsi; these figures relate to British D.T.D. test bars. ( ) denotes figures expressed in kpsi; these results relate to ASTM bars. (( )) denotes 0.2 per cent PS values expressed in kpsi; these results relate to ASTM bars. Multi-stage treatments are bracketed; alternative treatments are marked (a), (b) etc.

± Castings to be loaded in furnace at operating temperature.

±± Optionally preceded by 2 hr at 330°C; this effects stress relief.

†† U.S. practice is to load castings into furnace at about 250°C and raise furnace to operating temperature over about 2 hr.

ST = Solution heat treated. FHT = Fully heat treated.

§§ Few per cent SO<sub>2</sub> in furnace atmosphere necessary to minimize formation of RE and Zr hydrides with reduction in tensiles.

†: Alternative treatment designed to prevent grain growth.

explained above. Usual extrusion temperatures for magnesium lie in the range 300-450°C<sup>17,18</sup>.

In what follows, three alloys are examined: EZ33, a zirconium grain-refined cast alloy containing zinc and rare earth; ZK60, a high strength wrought alloy containing 5.5% zinc, also grain-refined with zirconium, and a binary 5.3% zinc alloy, cast at MIT. The processing steps named above are summarized in Figure 3, the double extrusion procedure having been used on one sample, of alloy ZK60.

17. E.F. Emley, Supra note 2, page 544.

18. "Extrusion," by K. Laue, H. Stenger; American Society for Metals, 1981.

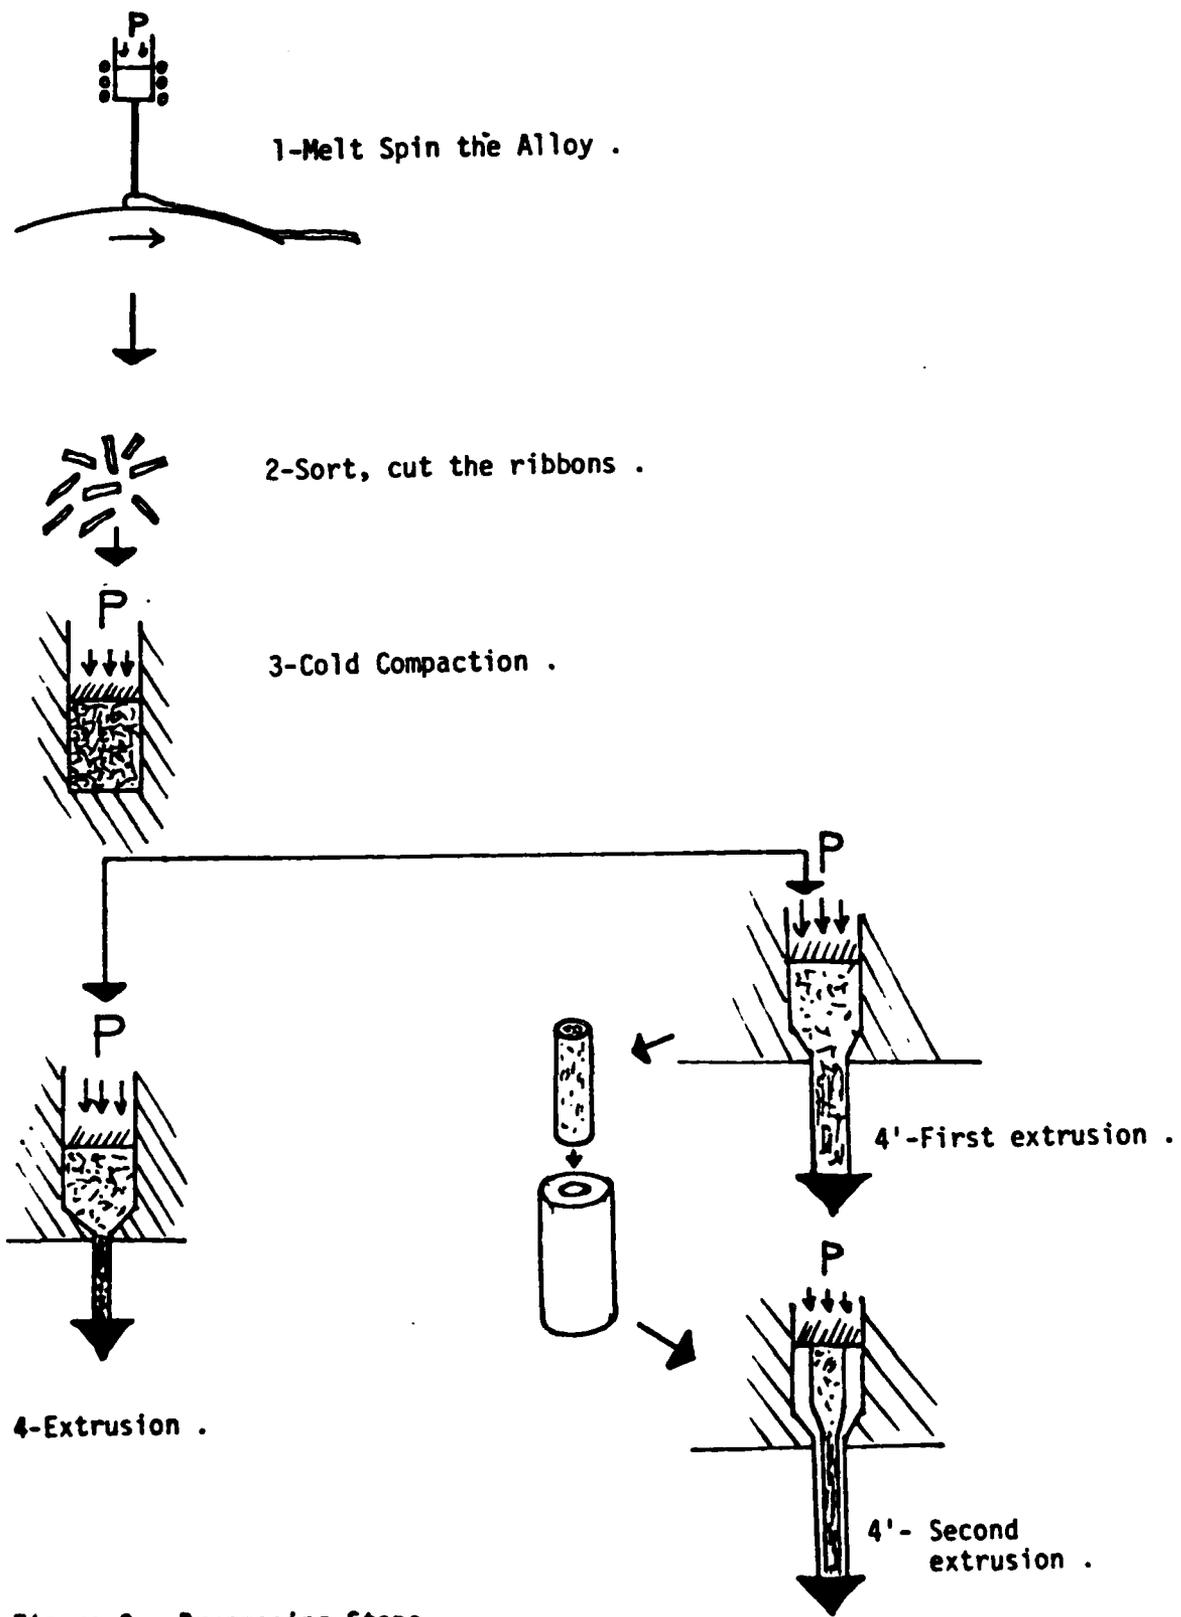


Figure 3 - Processing Steps .

## II. EXPERIMENTAL PROCEDURES

A. Alloying - Alloys EZ33 and ZK60 were both purchased as such. Mg-Zn binary alloys were prepared at MIT, in a gas furnace, using a steel crucible and standard melting and alloying procedures with Dow flux #310<sup>6</sup>. All castings were analyzed for Zn by atomic absorption, and results are given in Table V. Nominal compositions were selected to be close to those of the commercial Zn-Zr containing wrought alloys ZK60 and ZK20, and otherwise scan by increments of 2% the low Zn containing compositions. Ingots cast were about 1.5 kg in mass. Initial metals were 99.9% pure Mg and analytical Zn.

B. Melt-Spinning Procedures - Two melt-spinning apparatus were used. The first is described in the previous report, and was used until a more performant apparatus was built within the Solidification Processing Group at MIT. Alloy EZ33, and pure magnesium were cast on this first melt-spinner.

The second wheel casting apparatus (Figures 4, 5, 6, and 7) allows for single roll strip casting on the outside edge of a rotating wheel; the entire melt spinner is housed inside a vacuum-tight enclosed chamber. This permits strip casting experiments to be conducted in vacuum or under controlled atmospheres (He gas). The casting substrate is a wheel of 14 cm diameter and 3.8 cm width made of OFHC copper. The wheel is mounted on the shaft of a "Ferromatic" rotary vacuum feedthrough. The wheel has been precisely balanced on the shaft to insure smooth rotation at high speeds. The wheel is driven by a 1/7 H.P. variable speed, series wound motor capable of 10,000 rpm, which gives a substrate speed of up to 73 m/sec. The shaft of the motor is linked by a flexible coupling to the rotary feedthrough shaft. This minimizes the motor vibrations transmitted to the wheel via the drive shafts.

TABLE V

Binary Mg-Zn Alloys Cast at MIT.

Ingot #53	2.5% Zn.
Ingot #62	4.3% Zn.
Ingot #38	5.3% Zn.
Ingot #41	5.3% Zn.
Ingot #61	6.4% Zn.

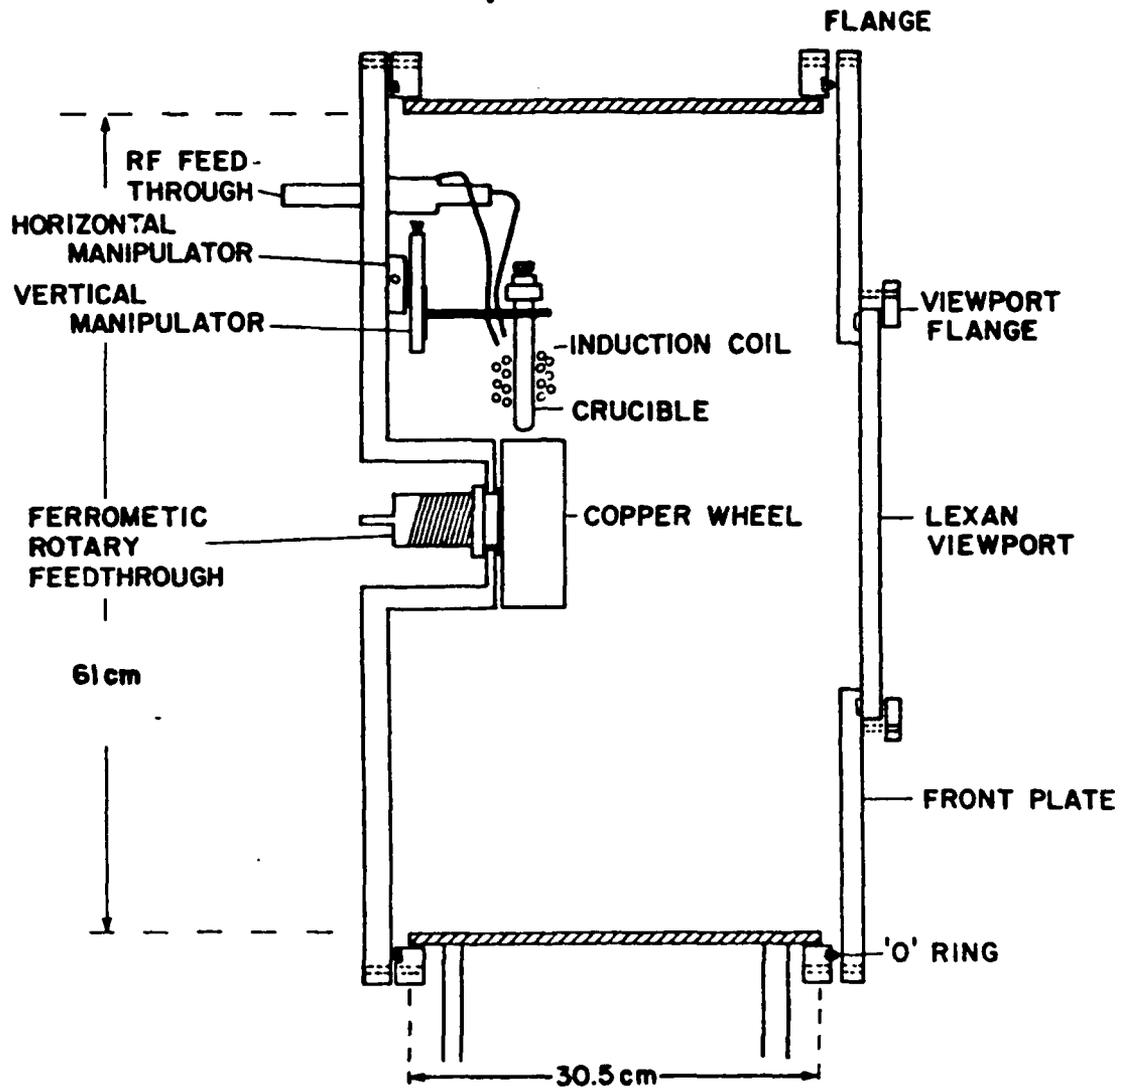


Figure 4 - Schematic illustration of strip casting apparatus, side view.

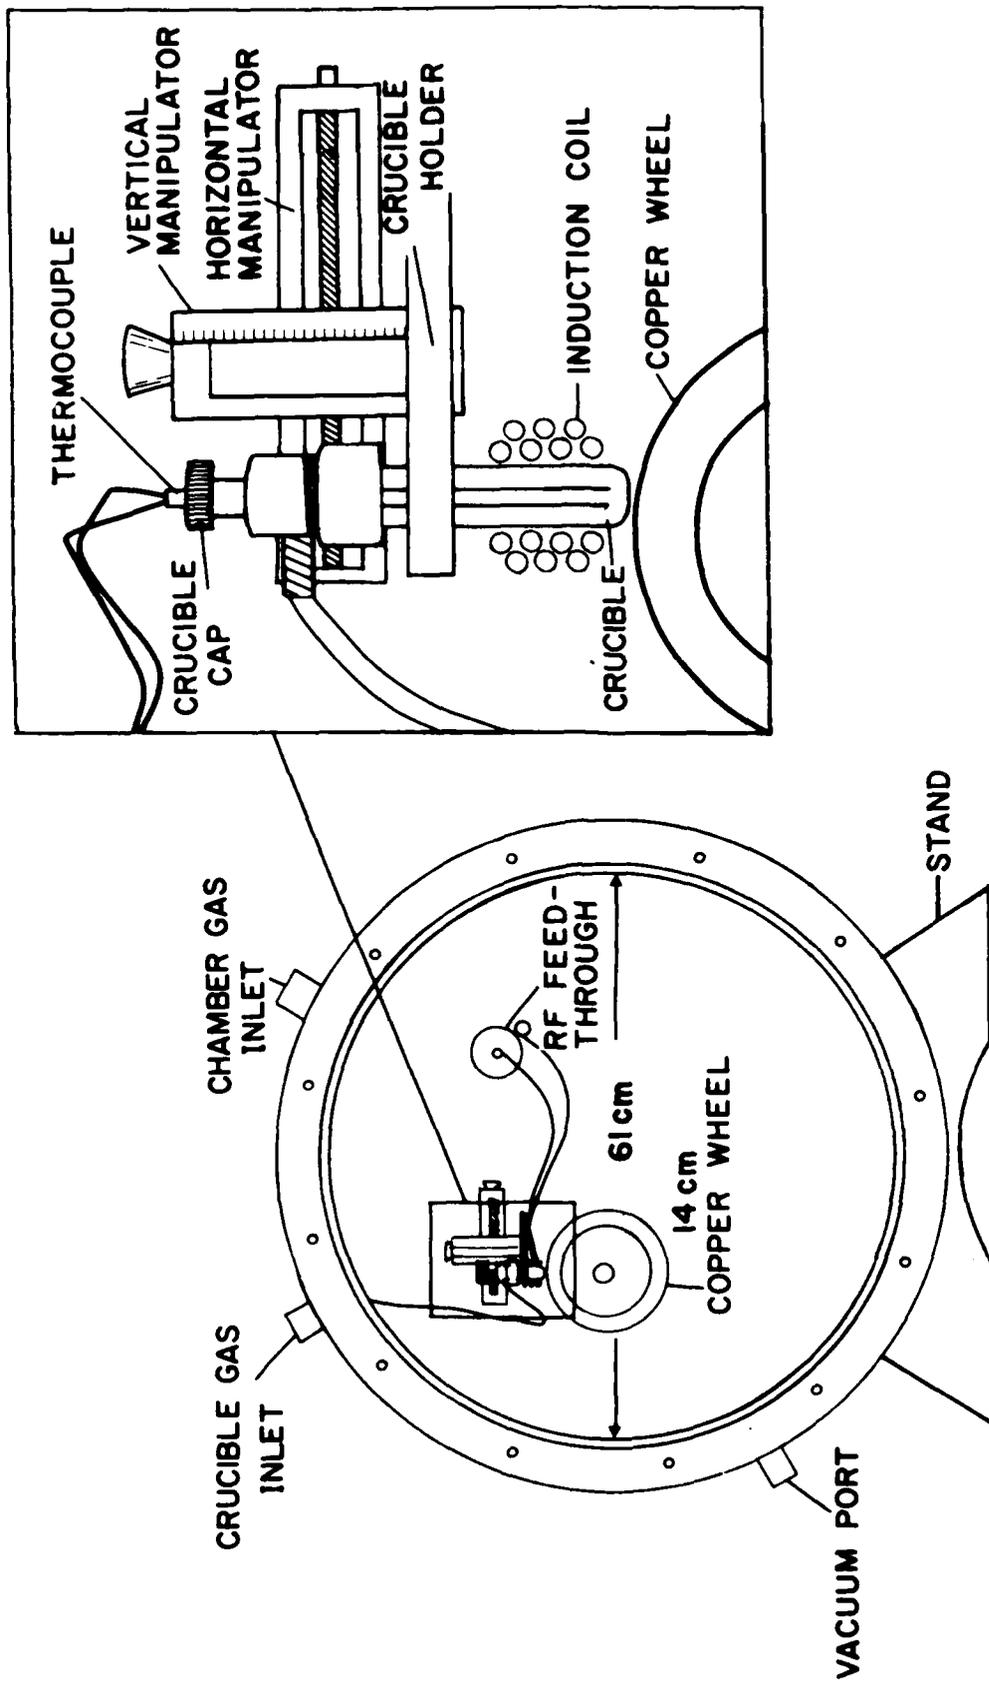


Figure 5. Schematic illustration of strip casting apparatus, front view.

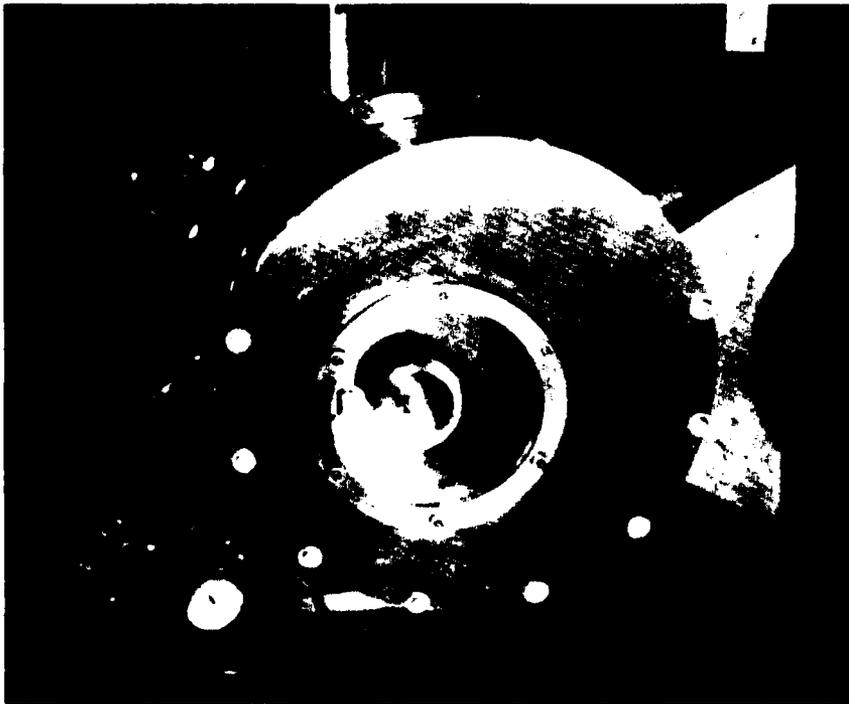


Figure 6. Strip casting apparatus.



Figure 7. Strip casting apparatus, wheel and crucible assembly.

The charges are induction heated by a 10KHZ, 20KW inverter power supply. The mild steel crucible is surrounded by an alumina holder, onto which a brass cap is attached. The brass cap allows a pressurized gas to be fed over the molten charge to force it over the moving copper wheel.

The cap also has a feedthrough, allowing a thermocouple covered by a mild steel sheath to measure the temperature of the melt. Runs in this apparatus were conducted under a helium atmosphere, thus suppressing any burning of the molten magnesium, and also minimizing boundary layer effects at the wheel<sup>19</sup>.

The alloys were cast at 700°C, and to minimize metal evaporation, heat-up times were short, around 3 minutes. The gas ejection pressure was 40 KPa, and substrate velocities around 35 m/sec. The ejection hole diameter was about 0.5 mm (drill #74). The ribbons produced had a thickness that varied around 50 um and a width of about 3 mm.

One considerable source of problems was the fact that zinc containing alloys wet iron extremely well - which makes sense when remembering that zinc wets iron so well that it is used in plating. This fact caused the molten metal jet to be very unstable, and to form large droplets that would stick to the crucible's outer side, as depicted in Figure 8a. To solve this problem, a coating of MgO mold wash was applied to the tip of the crucible, and nice ribbons were obtained, Figure 8b.

Ribbon formation was always accompanied by some splatter, that was reduced, but never suppressed. Two available set-ups were used, one able to cast samples of about 4 grams, the other casting about 20 grams at a time, thus reducing the number of runs necessary for one extrusion from 5-10 to one or two.

19. H. Liebermann, "Rapidly Quenched Metals III," 1978, Ed., B.Cantor, The Metals Society.

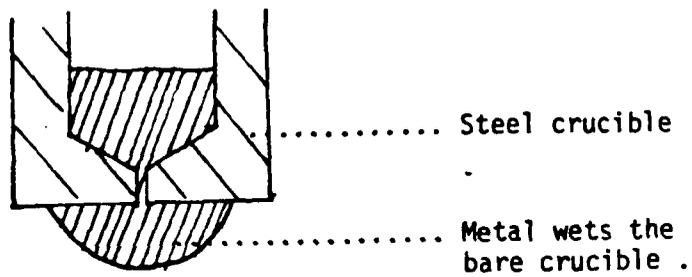


Figure 8-a . Uncoated crucible .

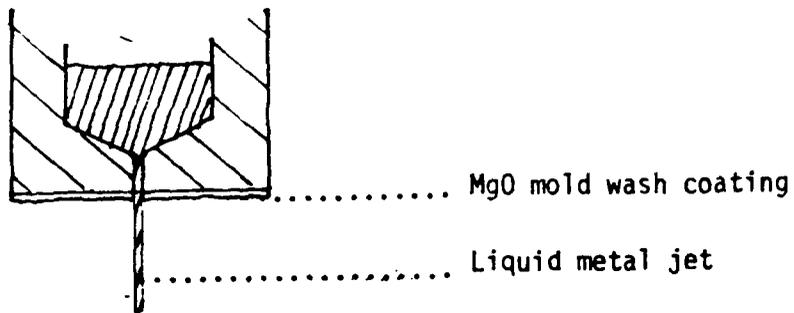


Figure 8-b , Coated crucible .

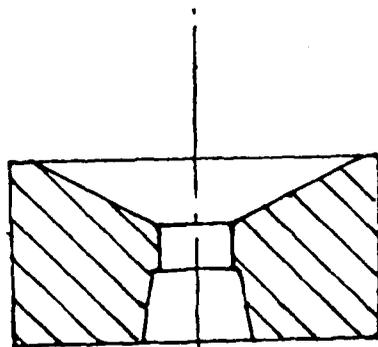


Figure 9-a . Conical Extrusion Die Geometry .

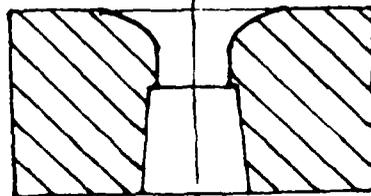


Figure 9-b . Straight Extrusion Die Geometry .

C. Densification - The apparatus was a small scale extrusion set up, built and used at MIT under a 10 ton press at first, and a 20 ton press when the need for higher loads became apparent.


A sketch describes the set up in Figure 10. All parts were machined from stainless steel, except where otherwise indicated. Dies are easily interchangeable, and two different geometries were employed. One consists of a 120° conical die (Figure 9A), the other of a flat die with a rounded off edge (Figure 9b). The former was used to minimize losses in the extrusion butt, the second is the standard shape used in hot extruding magnesium<sup>18</sup>.

No substantial difference in the performance of the two geometries was noticed, and they therefore were both used. The graphite dummy block was included to avoid damaging the piston on the die at the end of the extrusion runs, as well as to minimize the risk of piston seizure in the container by back extruded metal. A new dummy block was used for each run.

As described in the introduction, the densification of the ribbons involved two steps:

1. A cold compaction in the extrusion set up, under a pressure of 10,000 psi to 20,000 psi.
2. A hot extrusion of the compact, usually using the maximum load of the press, to keep the temperature at a minimum. No container was used at this stage of the project, at the risk of some gas entrapment. It should be noted, however, that successful hot extrusions were obtained by Busk and Leontis<sup>14</sup> without any such canning or evacuation.

The main problem to be overcome in densifying powders of metals such as magnesium or aluminum, is the necessity to shear off the oxide layer covering each particle. If this condition has not been fulfilled, the extruded product will delaminate, and produce fracture surfaces where each individual particle is quite visible and separated from its neighbor. A simple test for an

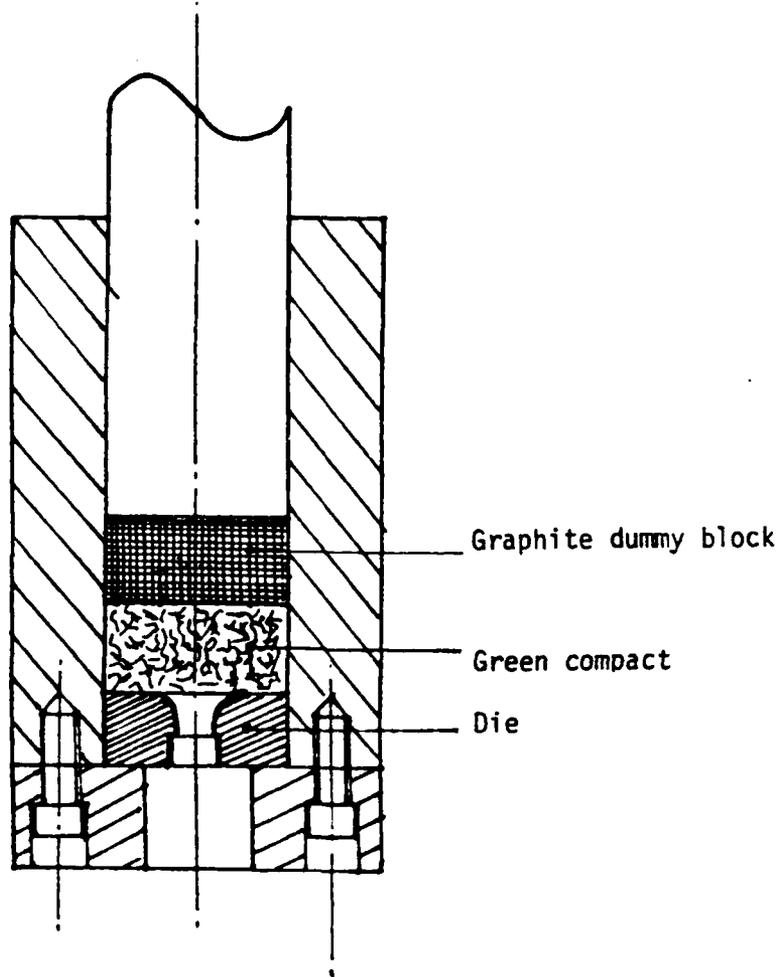

Scale 1 .

Figure 10 - Extrusion Tooling .

extruded bar consists therefore of breaking it by hand and looking at the fracture surface. It was thus found that an extrusion ratio of about 1/30 is sufficient to avoid delamination of the densified melt-spun ribbons. Reduction in area ratios of the order of 1/5 to 1/10 were on the other hand insufficient.

Again, the pressure was fixed by the capacity of the press, so the temperature varied from sample to sample. The extrusion speed was not controlled, but was low because the temperature was kept at a minimum. The surface finish of the samples was smooth and regular. As is standard practice for hot extruding magnesium, graphite was used for lubrication<sup>18</sup>.

The initial green compact was 1 inch in diameter, and the final extruded R.S.P. alloy 3/16 of an inch in diameter, unless otherwise noted. This corresponds to a reduction in area of  $(3/16)^2 = 1/28.4$ . Extruded rod lengths varied between 15 and 40 centimeters.

D. Metallography - Standard techniques were used, involving alumina powder polishing, and an optical microscope. A glycol etch was used on all samples.

#### E. Tensile Property Evaluation

Tensile specimens were machined from the extruded rods according to ASTM specifications. Gage lengths were four times the gage diameter. The latter was 0.125 inches when allowed, less when necessary. Given the small grain size of the extrusions, this is an amply sufficient diameter. The gage length was polished smooth with a 0.3  $\mu\text{m}$   $\text{Al}_2\text{O}_3$  powder suspension. The specimens were gripped in an Instron testing machine, and tested at cross head speeds of 0.02 inches/min.

### III. RESULTS - DISCUSSION

A. Pure Magnesium - One sample of compacted and extruded melt-spun ribbons of pure magnesium was produced to obtain a reference point against which the reinforcing action of alloying elements can be compared, at an equal level of oxide inclusion. Oxide inclusions are of importance in that they can modify the mechanical properties of the consolidated product, as can be seen in Table I. A similar effect is obtained on S.A.P. aluminum parts. Properties obtained are given in Table VI, together with extrusion conditions. As can be seen, by comparing with data in Table I, the reinforcing effect of the oxide is slight with these relatively coarse ribbons.

B. EZ33 - Alloy EZ33 was hot extruded and tested. The extrusion temperature was high: 470°C. The microstructure of the ribbons was similar to those given in the previous report<sup>1</sup>. White "Featureless" zones are apparent. Hardness properties were promising, which conditioned the choice of this alloy as a first test. The microstructure of the extruded sample is given in Figure 11. As can be seen, thanks to the slightly shifting focus range, the grain size is small, and many small precipitates are present and evenly distributed. The fracture surface, given in Figure 12, is typically ductile, and no trace of delamination is present. Thus, the extrusion ratio of 1/28.4 is clearly adequate for densification.

C. Magnesium-Zinc Alloys - Samples were cast from #41 (see Table V), and thus have a zinc content close to that of AK60. In this way, the effect of zirconium additions can be judged, as will be done in the next section.

Microstructures can be seen in Figure 13. Ribbons were thin, and abundantly display the "Featureless" zone mentioned in the previous report.

TABLE VI


Pure Magnesium Extrusion

Extrusion Ratio	1/28.4
Extrusion Pressure	20 ksi
Extrusion Temperature	45°C 10°C
Yield Strength	22.8 ksi
U.T.S.	32.9 ksi
Elongation	11.7%

TABLE VII

EZ33 Extrusion

		Nominal (as cast)
Extrusion Ratio	1/28.4	
Extrusion Pressure	20 ksi	
Extrusion Temperature	470°C 20°C	
Yield Strength	32.9 ksi	16 ksi
U.T.S.	41.3 ksi	23 ksi
Elongation	14%	3%

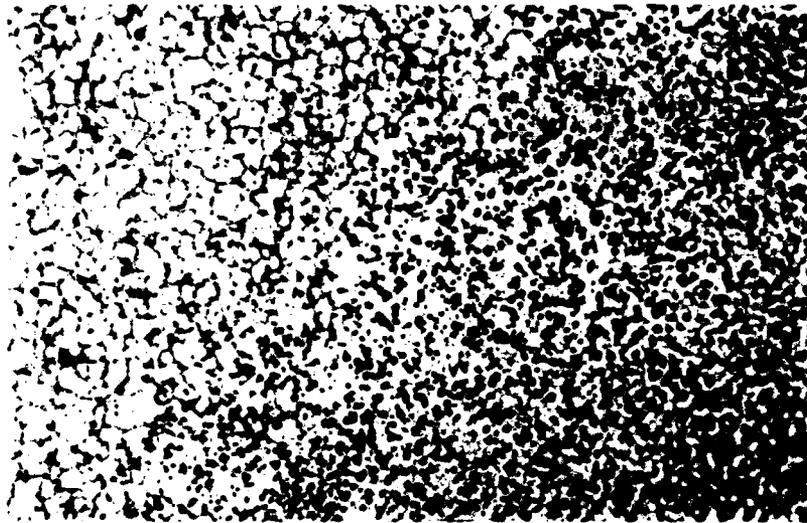


x 1000

Figure 11. Extruded EZ33 Microstructure




x 25

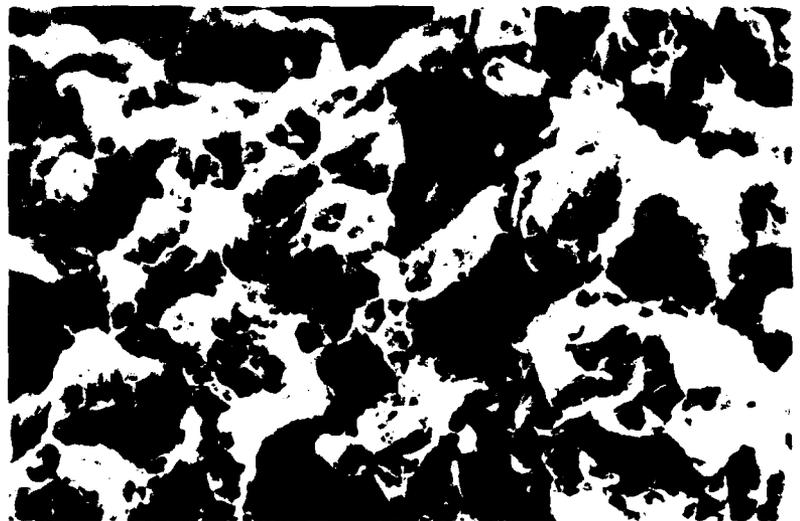


x 1000

Figure 12. Extruded EZ33 - Fracture Surface

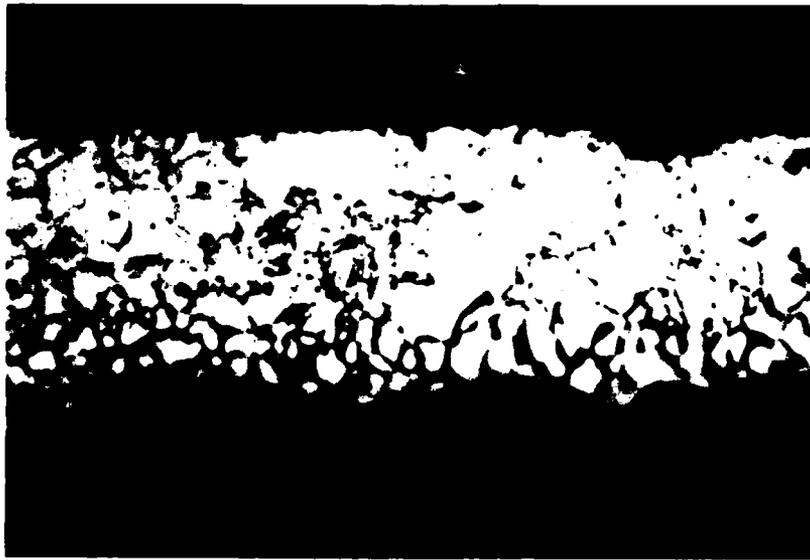

x 1000

Figure 13. Mg 5.3% Zn Melt-Spun Ribbon

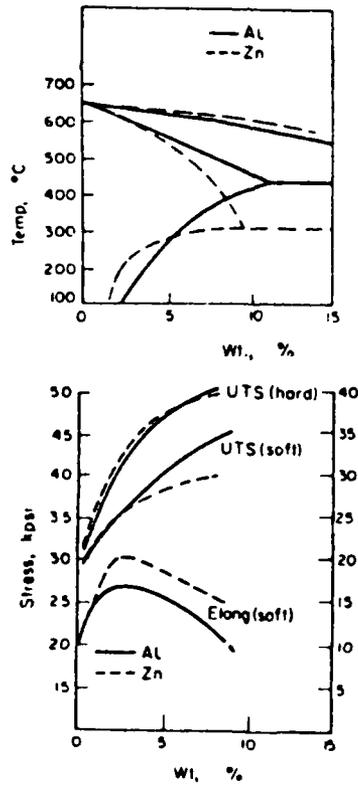

Effect of aluminum and zinc additions on the strength and ductility of rolled magnesium. Percentage elongation scale on right (after McDonald)

Figure 14.

Two extrusions were obtained and mechanically tested. Results are given in Table VIII. A reduction of the extrusion temperature from 450 to 310°C was obtained by using a more powerful press on the same die. The microstructure of the first extrusion, given Figure 15, displays a fine second phase distribution, but also the presence of intensive grain growth after recrystallization. Mechanical properties are therefore poor (Table VIII).

The second sample's microstructure, given in Figure 16, shows that the temperature was low enough to avoid grain growth, but not for recrystallization not to take place. A fine equiaxed grain structure is visible in both transverse and longitudinal directions. A comparison of mechanical properties given in Table VIII with those of rolled binary run R.S.P. samples given in Figure 14 show no marked improvement in the R.S.P. sample. 310°C is therefore still too high an extrusion temperature.

#### D. ZK60


This alloy is a standard commercial grain refined wrought alloy. It is also one that has been investigated before, using R.S.P. techniques and extrusion procedures.

Microstructures of the melt-spun ribbons are given in Figure 17. As can be seen, no grain refinement is visible close to the chill, and throughout most of the 50  $\mu\text{m}$  ribbon thickness. Comparison with a piece of splatter (a 1-2 mm droplet) from the crucible during one of the melt-spinning runs, Figure 18, shows, however, that the grain refining action of the Zr addition had not disappeared during meltdown. Also, a thicker ribbon does display such a microstructure far from the chill, Figure 19. There is, therefore, a critical cooling rate, over which zirconium isn't active as a grain refiner in magnesium, and must, therefore, be either in solid solution, or in a very finely distributed precipitate.

TABLE VIII

Magnesium-Zinc Extrusion

Extrusion Ratio	1/28.4	1/28.4
Extrusion Pressure	22 ksi	50 ksi
Extrusion Temperature	450°C 20°C	310°C 10°C
Yield Strength	27.3 ksi	35.2 ksi
U.T.S.	40 ksi	46 ksi
Elongation	11%	25.4%



Longitudinal Cut


x 500



Transverse Cut

x 500

Figure 15 - W-5.5% Zn, extruded at 450°C.

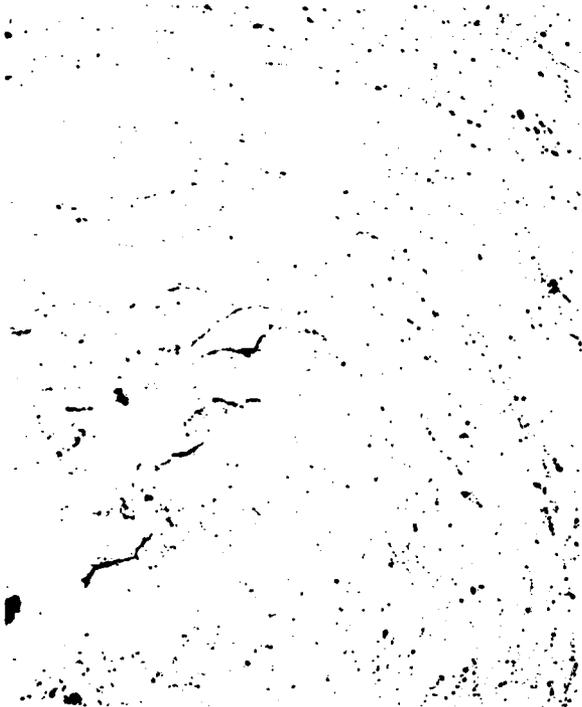

x 50



x 50



Transverse Cuts x 1000




Longitudinal Cuts x 1000

Figure 16. Mg-5.3% Zn, Extruded at 310°C



x 1000


Longitudinal Cut

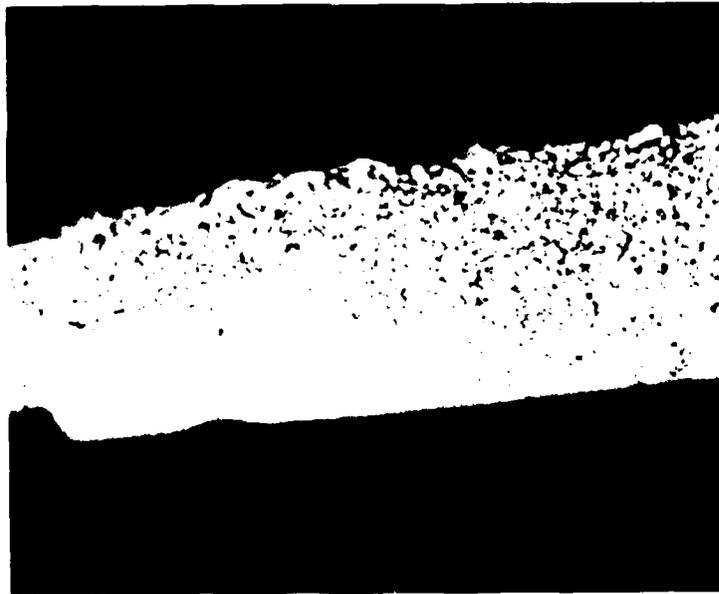

x 1000

Transverse Cut

Figure 17. Melt-spun SK60

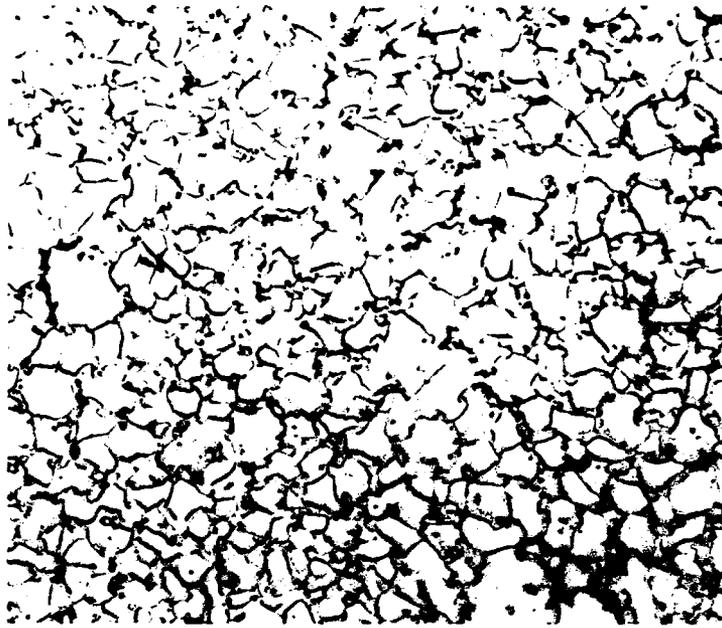

x 200

Figure 13. Splatter of EK60



x 200

Figure 14. Splatter of EK60 - Aerial View

Two extrusions were obtained from these ribbons. One was extruded using the 10 ton press, and a 3/16 inch die. Properties are given in Table IX, and microstructures in Figure 20. The grain size is small, and although recrystallization has apparently taken place, grain growth was inhibited by the zirconium addition, as is usually the case<sup>20</sup>. The second phase distribution is not uniform, and on the same scale as the ribbon thickness, probably due to the lack of uniformity within the ribbons themselves.

Mechanical properties were slightly, but not very much, better than those of the commercial as received alloy, given in Table IX. Therefore, the extrusion temperature was substantially lowered, by means of a double extrusion procedure in the second sample.

A die, 0.41 inches in diameter was machined, and the green compact extruded once under the 20 ton press. The temperature was 210°C. The extruded sample was then cut, inserted into a pure magnesium sleeve, and the resulting composite was re-extruded at a similar temperature, using the same die. The total reduction in area ratio was therefore 1/35.4. The procedure is described in Figure 3. The resulting sample was machined down to a tensile specimen 0.100 inches in diameter, and was thus free of the surrounding Mg sheath over the gage length.

Mechanical properties are given in Table IX. The sample displayed a nearly perfect textbook elastic-plastic curve and properties compare well with those obtained by Isserow and Rizzitano<sup>13</sup>.

Microstructures are given in Figure 21 and 22. After the first extrusion, Figure 21, a banded structure can be discerned,

20. E.F. Emley, Supra note 2, page 506.

TABLE IX

ZK60 Extrusions

ZK60A-T5 Extruded Rods (Metals Handbook)		First Extrusion	Second Extrusion
Extrusion Ratio	1/27.4	1/6	1/6
Extrusion Pressure	22 ksi	50 ksi	25 ksi
Extrusion Temperature	470°C 20°C	210°C 15°C	210°C 20'
Yield Strength	41 ksi	32.6 ksi	53.0 ksi
U.T.S.	51 ksi	47.3 ksi	56.3 ksi
Elongation	11%	21.1%	19.6%



x 100

Longitudinal Cuts




x 1000



x 100

Transverse Cuts

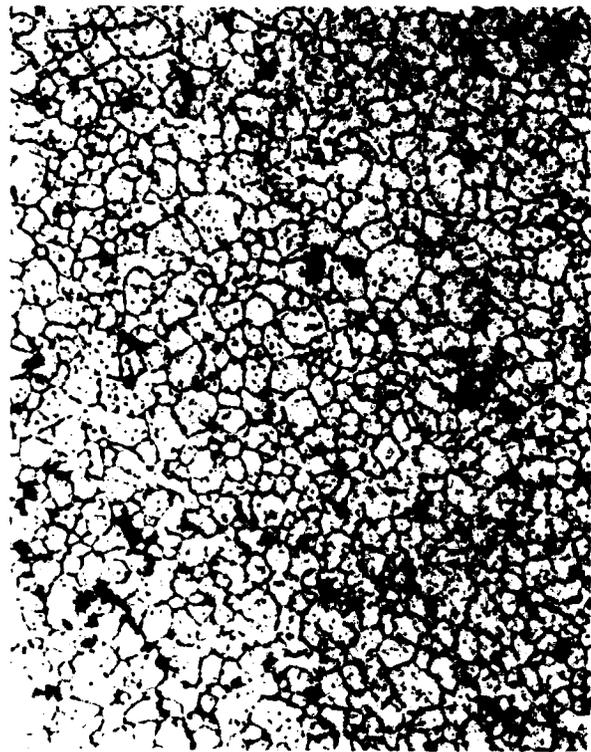

x 1000


Figure 20. ZK60 Extruded at 470°C



x 100



x 100

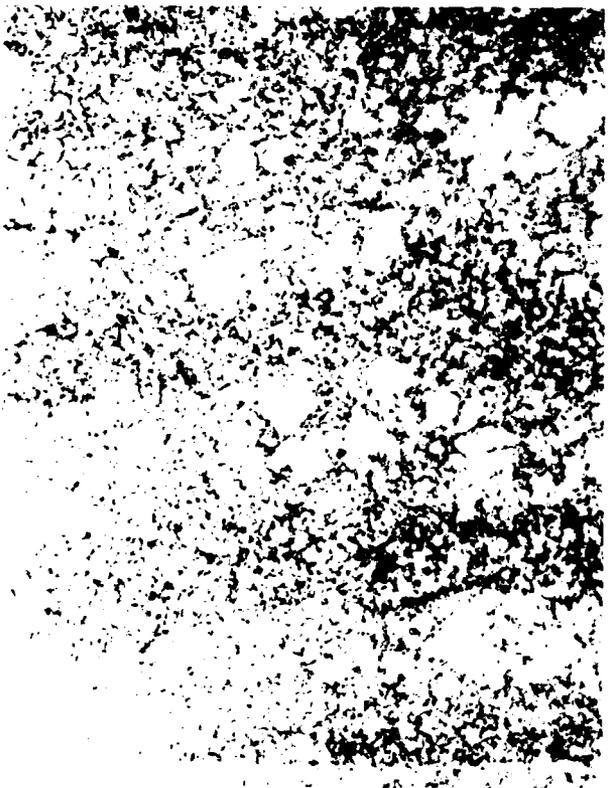

Transverse Cuts x 1000



Longitudinal Cuts x 1000

Figure 11. PE60 - First Extrusion at 210°C

on the scale of the extruded ribbons. The white grains, therefore probably correspond to the white "Featureless" zones displayed by the ribbons. Oxide films are clearly visible, and this sample displayed some delamination at the tip when re-extruded. The reduction in area ratio of 1/6 was not sufficient for full densification.

The re-extruded microstructure, Figure 22, is finer still, and the white bands less easily discernable, but still present. Throughout both extrusions, no noticeable amounts of recrystallization are apparent.


The fracture surfaces are given in Figure 23. A very slight delamination is still discernable to a critical eye, but the fracture surface is ductile, and is completely different from that observed by Isserow and Rizzitano<sup>13</sup>. It is therefore believed that this product would have superior transverse properties.

#### IV. CONCLUSIONS


1. A melt spinning apparatus was constructed at MIT, with a relatively large crucible to allow for rapid obtention of ribbons for consolidation purposes.
2. Casting under a controlled atmosphere is advantageous in avoiding the risk of burning inherent to molten and finely divided magnesium.
3. Zinc containing magnesium alloys wet iron very well. This may lead to instabilities in the metal stream if no precautions are taken.
4. The existence of a "featureless" zone in the ribbons is



x 100

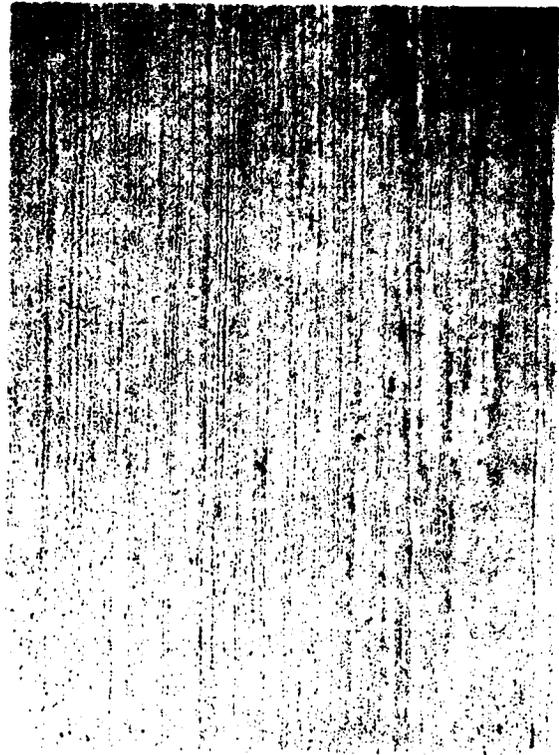

x 100

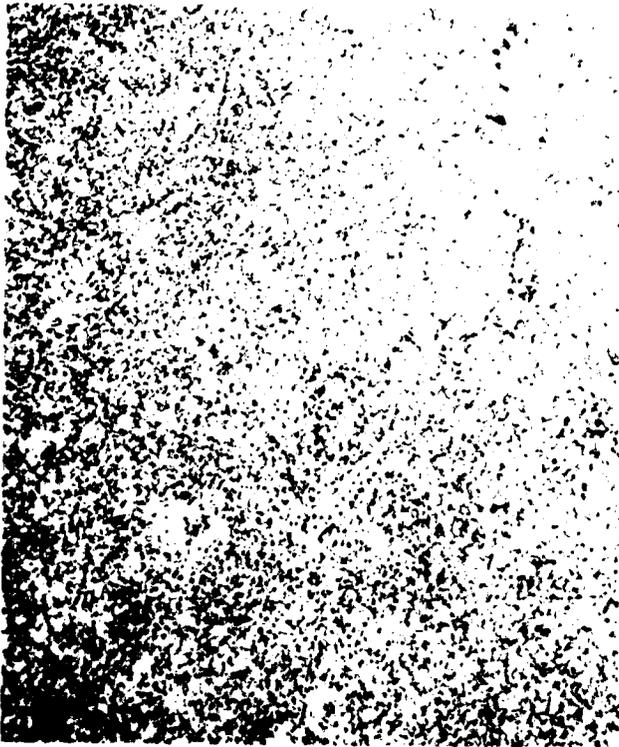

Transverse Cuts x 1000



Longitudinal Cuts x 1000

Figure 22. ZK60 - Second Extrusion at 210°C

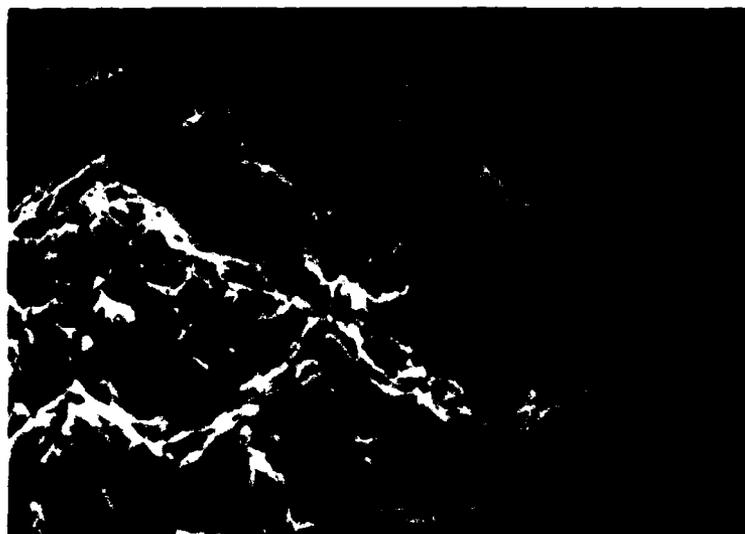
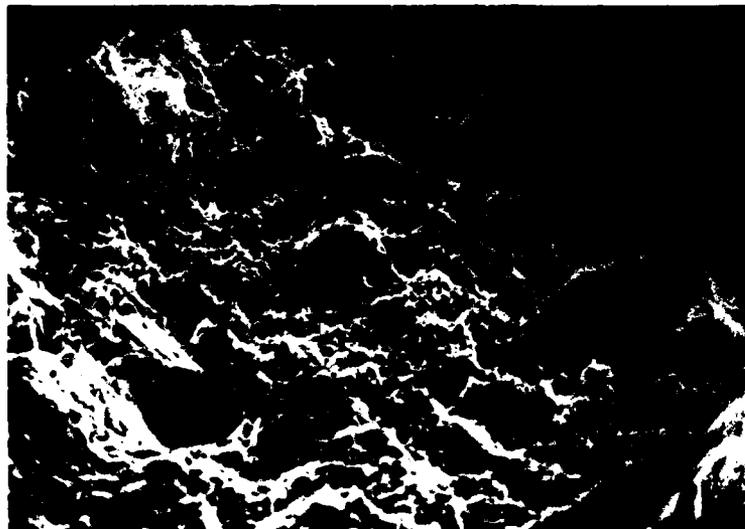
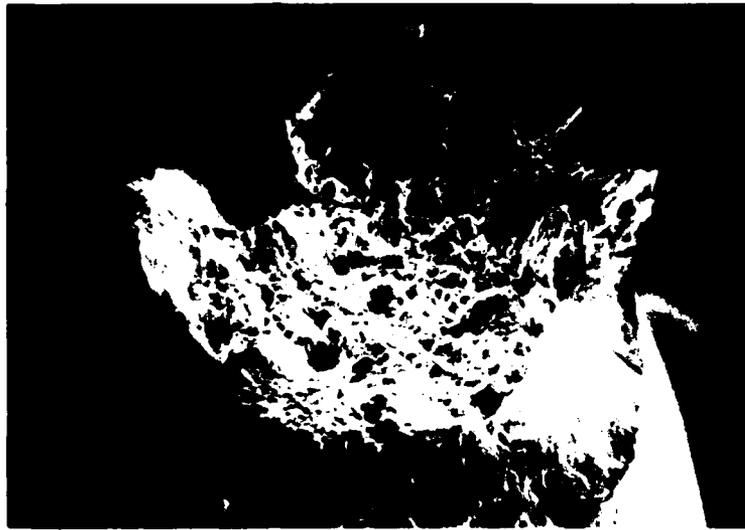


Figure 23. ZK60 Double Extrusion at 210°C - Fracture Surface

proved. It is located along the chill face, and its fraction increases as the ribbon thickness decreases. In particular, the grain refining action of zirconium is suppressed in that zone.

5. Hot extrusion conditions have been studied in a laboratory bench scale for these R.S.P. magnesium alloys.

6. Full, delamination free, densification is obtained with a reduction in area ratio of about 1/30.

7. The extrusion temperature is of paramount importance in obtaining the remarkable properties of rapidly solidification materials for magnesium alloys. Samples of Mg-5.3%Zn, EZ33, ZK60 extruded above 300°C gave non-exceptional properties. The metal recrystallizes, and in non-zirconium containing alloys, grain growth occurs at higher temperatures. Also, the second phase can precipitate out, as occurred in EZ33.

8. To produce interesting properties in the extruded R.S.P. sample, temperatures lower than about 250°C are necessary. This correlates well with previous data, as exposed in the introduction.

9. A double extrusion procedure was designed to extrude ZK60 at these temperatures.

10. Using these apparatus, techniques, and conditions, the following properties were obtained in ZK60: Y.S. 53.0 ksi

U.T.S. 56.3 ksi

Elongation: 19.6%

Y.S. 41 ksi

U.T.S. 51 ksi

Elongation: 11%

for conventionally extruded ZK60. The fracture surface proved that a fully dense, delamination free sample was obtained.

It is thus proved that Rapid Solidification can yield remarkable materials when applied to magnesium alloys. This sample was not heat treated, was not canned, and the whole process has, still, margin for improvement. The alloy compositions can be varied, and the materials further characterized. This should give an idea of the potential lying in this barely explored field, the Rapid Solidification Processing of magnesium alloys.

## DISTRIBUTION LIST

No. of Copies	To
	Defense Advanced Research Projects Agency; Materials Science Division, 1400 Wilson Boulevard, Arlington, VA 22209
1	ATTN: Dr. S. Fishman
1	Dr. Ben A. Wilcox
12	Commander, Defense Technical Information Center, Cameron Station, Building 5, 5010 Duke Street, Alexandria, VA 22314
1	Mr. Jerome Persh, Office of the Under Secretary of Defense for Research and Engineering (Engineering Technology), The Pentagon, Room 3D 1089, Washington, DC 20301
1	Dr. Lewis Schmidt, Office of the Under Secretary for Defense, Research and Engineering, OFAN (R.E.S.), Department of the Navy, Washington, DC 20350
	Commander, Army Research Office, P.O. Box 12211, Research Triangle Park, NC 27709
1	ATTN: Information Processing Office
1	Dr. P. A. Parrish
	Commander, U.S. Air Force Wright Aeronautical Laboratories, Wright-Patterson Air Force Base, OH 45433
1	ATTN: AFWAL/MLLM, Mr. A. M. Adair
1	AFWAL/MLLM, Mr. Wm. Kerr
	Department of Metallurgy & Materials Science, Carnegie-Mellon University, Pittsburgh, PA 15213
1	ATTN: Prof. James C. Williams
	Mr. Patrick L. Martin
1	Dr. Robert Mehrabian, Chief, Metallurgy Division, National Bureau of Standards, Washington, DC 20234
1	Mr. R. V. Miner, Jr., Mail Stop 49-3, Lewis Research Center, NASA, 21000 Brookpark Road, Cleveland, OH 44135
	Office of Naval Research, 800 N. Quincy Street, Arlington, VA 22217
1	ATTN: Dr. Bruce MacDonald, Code 471
1	Dr. Donald Polk, Code 431
1	Mr. Joe Collins, Naval Air Systems Command, 5163C1, Washington, DC 20361
1	Dr. M. A. Greenfield, Manager, Metallic Materials Program, NASA, Washington, DC 20546
	Air Force Office of Scientific Research, Bolling Air Force Base, DC 20332
1	ATTN: Dr. Alan Rosenstein, Bldg. 410
1	Mr. Joe Glatz, NAP Center, Box 7176, Trenton, NJ 08628

No. of Copies	To
1	Mr. B. B. Rath, Naval Research Laboratory, Code 6300, 455 Overlook Ave., SW, Washington, DC 20375
1	Prof. H. L. Fraser, Department of Metallurgy, University of Illinois, 1304 W. Green, Urbana, IL 61801
1	Mr. O. J. Remson, Naval Materials Command (O8T22), Washington, DC 20360
	National Materials Advisory Board, National Research Council, 2101 Constitution Avenue, Washington, DC 20418
1	ATTN: Dr. Joseph R. Lane
1	National Science Foundation, Division of Materials Research, 1800 G Street, NW, Washington, DC 20550
	Department of Materials Science and Engineering, Room 13-5046, M.I.T., Cambridge, MA 02139
1	ATTN: Prof. M. Cohen
1	Prof. N. Grant
1	Dr. L. A. Davis, Allied Corporation, P.O. Box 1021R, Morristown, NJ 07960
1	Dr. B. H. Kear, Exxon Research and Engineering Co., P.O. Box 45, Linden, NJ 07036
1	Mr. J. B. Moore, Pratt & Whitney Aircraft, P.O. Box 2691, West Palm Beach, FL 33402
1	Dr. Earl Thompson, United Technologies Research Center, Silver Lane, East Hartford, CT 06108
1	Dr. Hans Vanderveldt, Naval Sea Systems Command, Washington, DC 20350
1	Dr. R. A. Sprague, Materials and Process Technology Laboratories, General Electric Company, Mail Drop M82, Neumann Way, Cincinnati, OH 45215
1	Mr. T. F. Kearns, Institute for Defense Analyses, 1801 N. Beauregard Street, Alexandria, VA 22311
1	Mr. Marshall Thomas, Naval Air Development Center, Code 60634, Warminster, PA 18974
	U.S. Army Research and Technology Lab (AVSCOM), Applied Technology Labs, Fort Eustis, VA 23604
1	ATTN: DAVDL-ATL-ATP, Mr. Jan Lane
1	Prof. Bill C. Giessen, Materials Science Division, Northeastern University, Rm 341, 360 Huntington Avenue, Boston, MA 02115
1	Allan H. Clauer, Assistant Manager, Adv. Materials Processing, Battelle Columbus Laboratories, 505 King Avenue, Columbus, OH 43201

No. of Copies	To
1	Chi Law, Material Engineering and Research Laboratory, Bldg. 140, Pratt & Whitney Aircraft Company, Middletown, CT 06457
	Department of the Army, U.S. Army Aviation Systems Command, 4300 Goodfellow Boulevard, St. Louis, MO 63120
1	ATTN: AMDAV-EGX, Dan Haugan
	Commander, Headquarters, U.S. Army Tank-Automotive Command, Warren, MI 48090
1	ATTN: AMSTA/RCKM, Dr. Brij Roopchand
	Director, Benet Weapons Laboratory, Physical Science Section, Watervliet Arsenal, Watervliet, NY 12189
1	ATTN: AMSMC-LCB-PS, Dr. I. Ahmad
	Commander, U.S. Army Armament, Munitions and Chemical Command, Dover, NJ 07801
1	ATTN: FC & SC, Dr. E. Bloore
1	FC & SC, Dr. S. J. Cytron
	Commander, U. S. Army Mobility Equipment, Research and Development Command, Materials Technology Laboratory, Ft. Belvoir, VA 22060
1	ATTN: AMDME-VL, Mr. F. L. Harris
1	Mr. John Dunning, Bureau of Mines, Albany Metallurgy Research Center, P.O. Box 70, Albany, OR 87321
1	Bruce A. Ewing, Detroit Diesel Allison, Division of General Motors Corporation, P.O. Box 894 T-27, Indianapolis, IN 46206
1	Dr. Subhash C. Singhal, Manager, High Temperature Metallurgy Research & Development Center, Westinghouse Electric Corporation, 1310 Beulah Road, Pittsburgh, PA 15235
1	Dr. Shih C. Hsu, Precision Material Technology, GTE Laboratories Incorporated, 40 Sylvan Road, Waltham, MA 02154
1	Ms. Mary Ellen Hadricky, Aluminum Company of America, 1200 Ring Building, Washington, DC 20036
1	AMAX-Magnesium 230 North 2200, West Salt Lake City, UT 84116
2	Dow Chemical USA Dr. S. F. Spangenberg, Laboratory Director, 1776 Building, Midland, Michigan 48640
1	International Magnesium Association 1406 Third National Building., Dayton, OH 45402
2	Thomas Tietz, Lockheed Palo Alto Research Lab, Organ. 52-30 3251 Hanover Street, Palo Alto, CA 94304

---

No. of  
Copies

To

---

Director, Army Materials and Mechanics Research Center, Watertown, MA 02172

2	ATTN: AMXMR-PL
1	AMXMR-PR
1	AMXMR-K
2	AMXMR-MD, Dr. S. Isserow
2	AMXMR-MMP, Dr. J. Kohatsu

**END**

**FILMED**

**3-85**

**DTIC**



