

AD-A200 389

DTIC FILE COPY ②

OFFICE OF NAVAL RESEARCH

Contract N00014-83-K-0470-P0003

R&T Code NR 33359-718

Technical Report No. 107

A Conducting Polymer Electrochemically Generated Via  
Anodic Oxidation of Toluene

by

K. Ashley, D.B. Parry, J.M. Harris and S. Pons

Prepared for publication in J. Chem. Soc. Chem. Comm.

Department of Chemistry  
University of Utah  
Salt Lake City, UT 84112

July 15, 1988

DTIC  
SELECTED  
NOV 14 1988  
S E

Reproduction in whole, or in part, is permitted for  
any purpose of the United States Government

This document has been approved  
for release and sale by the  
Department of Defense

88 11 10 085

**REPORT DOCUMENTATION PAGE**

1a. REPORT SECURITY CLASSIFICATION Unclassified		1b. RESTRICTIVE MARKINGS	
2a. SECURITY CLASSIFICATION AUTHORITY		3. DISTRIBUTION / AVAILABILITY OF REPORT Approved for public release and sale. Distribution unlimited.	
2b. DECLASSIFICATION / DOWNGRADING SCHEDULE		4. PERFORMING ORGANIZATION REPORT NUMBER(S) ONR Technical Report No. 107	
5. MONITORING ORGANIZATION REPORT NUMBER(S)		6a. NAME OF PERFORMING ORGANIZATION University of Utah	
6b. OFFICE SYMBOL (if applicable)		7a. NAME OF MONITORING ORGANIZATION	
6c. ADDRESS (City, State, and ZIP Code) Department of Chemistry Henry Eyring Building Salt Lake City, UT 84112		7b. ADDRESS (City, State, and ZIP Code)	
8a. NAME OF FUNDING / SPONSORING ORGANIZATION Office of Naval Research		8b. OFFICE SYMBOL (if applicable)	
9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER N00014-83-K-0470-P00003		10. SOURCE OF FUNDING NUMBERS	
8c. ADDRESS (City, State, and ZIP Code) Chemistry Program, Code 1113 800 N. Quincy Street Arlington, VA 22217		PROGRAM ELEMENT NO.	PROJECT NO.
11. TITLE (Include Security Classification) A Conducting Polymer Electrochemically Generated Via Anodic Oxidation of Toluene		TASK NO.	WORK UNIT ACCESSION NO.
12. PERSONAL AUTHOR(S) K. Ashley, D.B. Parry, J.M. Harris and S. Pons			
13a. TYPE OF REPORT Technical	13b. TIME COVERED FROM 9/87 TO 7/88	14. DATE OF REPORT (Year, Month, Day) July 13, 1988	15. PAGE COUNT 24
16. SUPPLEMENTARY NOTATION			
17. COSATI CODES		18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)	
FIELD	GROUP	SUB-GROUP	conducting polymers, toluene
19. ABSTRACT (Continue on reverse if necessary and identify by block number)  Attached.			
20. DISTRIBUTION / AVAILABILITY OF ABSTRACT <input checked="" type="checkbox"/> UNCLASSIFIED/UNLIMITED <input type="checkbox"/> SAME AS RPT <input type="checkbox"/> DTC USERS		21. ABSTRACT SECURITY CLASSIFICATION Unclassified	
22a. NAME OF RESPONSIBLE INDIVIDUAL Stanley Pons		22b. TELEPHONE (Include Area Code) (801)581-4760	22c. OFFICE SYMBOL

**A Conducting Polymer Formed from the Anodic Oxidation of Toluene in Acetonitrile.**  
Kevin Ashley, Department of Chemistry, San Jose State University, San Jose, CA, USA 95192,  
Diane B. Parry, Joel M. Harris, and Stanley Pons, Department of Chemistry, University of Utah,  
Salt Lake City, UT, USA 84112.

As opposed to the much harsher conditions demanded in homogeneous solutions, a conducting polymer of toluene is readily formed by anodic oxidation of acetonitrile solutions containing the precursor.

The fabrication of new conductive polymers is of interest due to the potential practical applications of these materials. We report here the electrochemical polymerization of a conducting polymer from toluene precursor. Anodic oxidation of concentrated solutions (0.5 M) toluene in anhydrous acetonitrile solution containing 0.15 M  $\text{Bu}_4\text{N}^+\text{BF}_4^-$  leads to the formation of a highly conductive poly[methylphenylene] polymer film on the surface of a platinum mirror electrode (bulk metal). The polymer can also be formed in solutions of lower toluene concentrations (1-10 mM), but only after successive pulsing or sweeping techniques at high positive potentials ( $\geq 1.8$  V vs  $\text{Ag}/\text{Ag}^+$ ) for long periods of time.

Preliminary electrochemical experiments for the formation and characterization of the film were carried out in dry acetonitrile (nominal water content  $< 0.005\%$ ) with  $\text{Bu}_4\text{N}^+\text{BF}_4^-$  electrolyte, which had been freshly recrystallized twice from methylene chloride-diethyl ether and dried in vacuo at  $75^\circ\text{C}$  for 24 h. Solutions were degassed with and carried out under Ar. Films were formed in the range of thicknesses 0.5-5 microns. (A.C.)

Figure 1 shows the cyclic voltammetry of a typical solution. The irreversible wave is similar to those observed in the anodic oxidation of pyrrole to polypyrrole<sup>1</sup>, or biphenyl to poly[p-phenylene]<sup>2</sup> in similar electrolytes. At high positive potentials, a brassy film is rapidly formed on the surface of the electrode, and streaming of unprecipitated solid product away from the surface is observed. Continued growth of the film is observed on subsequent potential scans as evidenced by the behavior of the current on the anodic excursion and darkening of the surface film. Slight attenuation of the current after several scans is similar to that observed in polypyrrole formation.

As has been observed and reported previously, these films are doped during the oxidation with the  $\text{BF}_4^-$  anion<sup>2,4</sup>; infrared spectra confirm the presence of the electrolyte within the film.

Figure 2 shows the transient spectroelectrochemistry at 420 nm for the formation of the polymer film at a platinum mirror electrode upon application of a +2.2 V (vs Ag/Ag<sup>+</sup>) potential step from 1.0 V. We note that the shape of the forward transient is linear in time. If the potential is then returned to 0.0 V, the absorbance falls only slowly. This is typical behavior for an irreversibly formed adherent polymer film at the surface. At high concentrations of the precursor, the reaction is virtually first order with respect to the coupling of the hydrocarbon free radicals, and the total amount of product formed is linear over this time interval. An increase in the solution acidity, as evidenced by the appearance of a proton reduction wave at -0.2 V, is direct evidence for the formation of the toluene free radical species from the initially formed toluene cation radical<sup>5,6</sup>.

Figure 3 shows the voltammetry of a typical polymer film electrode which has been removed from the synthetic cell to a cell containing only the electrolyte solution. Again, the film behaves similarly to other conducting polymer films<sup>4,7,8</sup>. In the present case, the film is oxidized at about +1.8V, and a significant capacitive component to the current is observed (notice sudden decrease in current at the positive potential switching potential). The oxidation of the film also results in the coupled chemical formation of other insoluble polymeric forms in the matrix; continued proton loss from the initially formed polymer film is observed at potentials where the film is oxidized. This indicates that the polymer anions formed under these conditions are still unstable with respect to further cross-linking or to the formation of multiple pi bonded polymer products. The voltammetry of the film changes only slowly over continued scanning, indicating the sluggishness of the oxidation of the total film. The film is reduced at about -1.0 V, and breaks down rapidly after sweeps to higher negative potentials. Preliminary measurements of the conductivity give a value of approximately 0.1 S/cm.

The film demonstrates an electrochromic effect. Figure 4 shows the change in absorbance at 420 nm of the film upon anodic oxidation. Unlike poly(p-phenylene) the effect is irreversible (note the constant value of the absorbance when the potential is switched back to 0.0 V). This corroborates the assumption of chemical irreversibility of the film oxidation under these conditions. This result together with the voltammetric results and the previous spectroelectrochemical results (Figure 2) indicates that the product of the oxidation is also conductive, and that electron transfer to the outer layers of the initially formed film is slow.

Raman scattering studies from the film shows bands at 1338, 1362, 1395, and 1610  $\text{cm}^{-1}$ ; strong fluorescence from the film may obscure other bands. The Raman shifts are similar to those observed for poly(phenylene)<sup>9</sup>. The conductivity of the polymer film is lower than that of poly(p-phenylene); conductivity values as a function of type of electrolyte dopant and a full characterization of the system will be reported elsewhere. It may be that poly(o-phenylene) type products are formed; these types of polymers are the primary products in the homogeneous solution oxidation of toluene<sup>10</sup>.

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input checked="" type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By _____	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	



**ACKNOWLEDGEMENTS**

**We thank the Office of Naval Research for support of this work. K.A. thanks the San Jose State University Foundation for a starter grant.**

## REFERENCES

1. M. L. Marcos, I. Rodriguez, and J. Gonzalez-Velasco, *Electrochim. Acta* 1987, 32, 1453.
2. J. F. McAleer, K. Ashley, J. J. Smith, S. Bandyopadhyay, J. Ghoroghchian, E. M. Eyring, S. Pons, H. B. Mark, Jr., and G. Dunmore, *J. Mol. Electron.* 1986, 2, 183.
3. S. Aeiych, J. E. Dubois, and P. C. Lacaze, *J. Chem. Soc. Chem. Commun.* 1986 1668.
4. M. Satoh, M. Tabata, K. Kaneto, and K. Yoshino, *J. Electroanal. Chem.*, 1985, 195, 203.
5. E. M. Genies, G. Bidan, and A. F. Diaz, *J. Electroanal. Chem.*, 1983, 149, 101.
6. A. Bewick, G. J. Edwards, J. M. Mellor, and S. Pons, *J. Chem. Soc., Perkin II Trans.* 1977, 1952.
7. T. A. Skotheim, S. W. Feldberg, and M. B. Armand, *J. Phys. (Paris)* 1983, C3, 270.
8. K. Ashley, PhD Thesis, University of Utah (1987).
9. K. Ashley, D. B. Parry, J. M. Harris, S. Pons, D. N. Bennion, R. Lafollette, J. Jones, and E. J. King, *Electrochim. Acta*, submitted.
10. P. Kovacic and J. S. Ramsey, *J. Polym. Sci., Part A-1*, 1969, 7, 111.

**FIGURE LEGENDS**

1. **Voltammetry of toluene (0.5M) in 0.15M tetra-n-butylammonium tetrafluoroborate in acetonitrile at a platinum mirror disk electrode. Sweep rate is  $50\text{mV s}^{-1}$ .**
2. **Absorbance transient at 430nm following a potential step from +1.0 to +2.2V to the system described in Figure 1. The transient is the average of 10 experiments.**
3. **Voltammetry of an approximately 1 micron thick polymer film electrode in the pure electrolyte solution. Sweep rate is  $100\text{ mV s}^{-1}$ .**
4. **Absorbance transient at 420nm following a potential step from +1.0 to +2.0V on a polymer film formed from the system described in Figure 1. The transient is a single scan.**

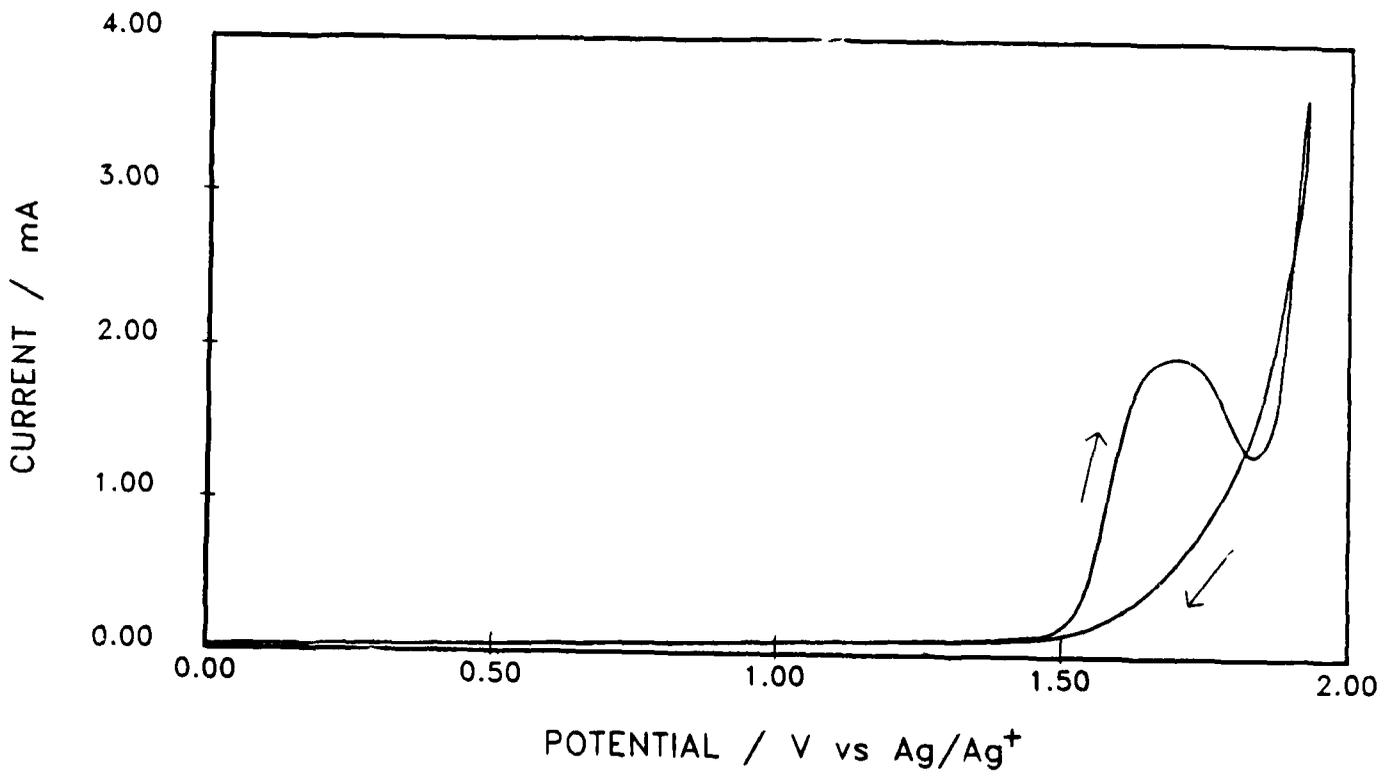


Fig 1

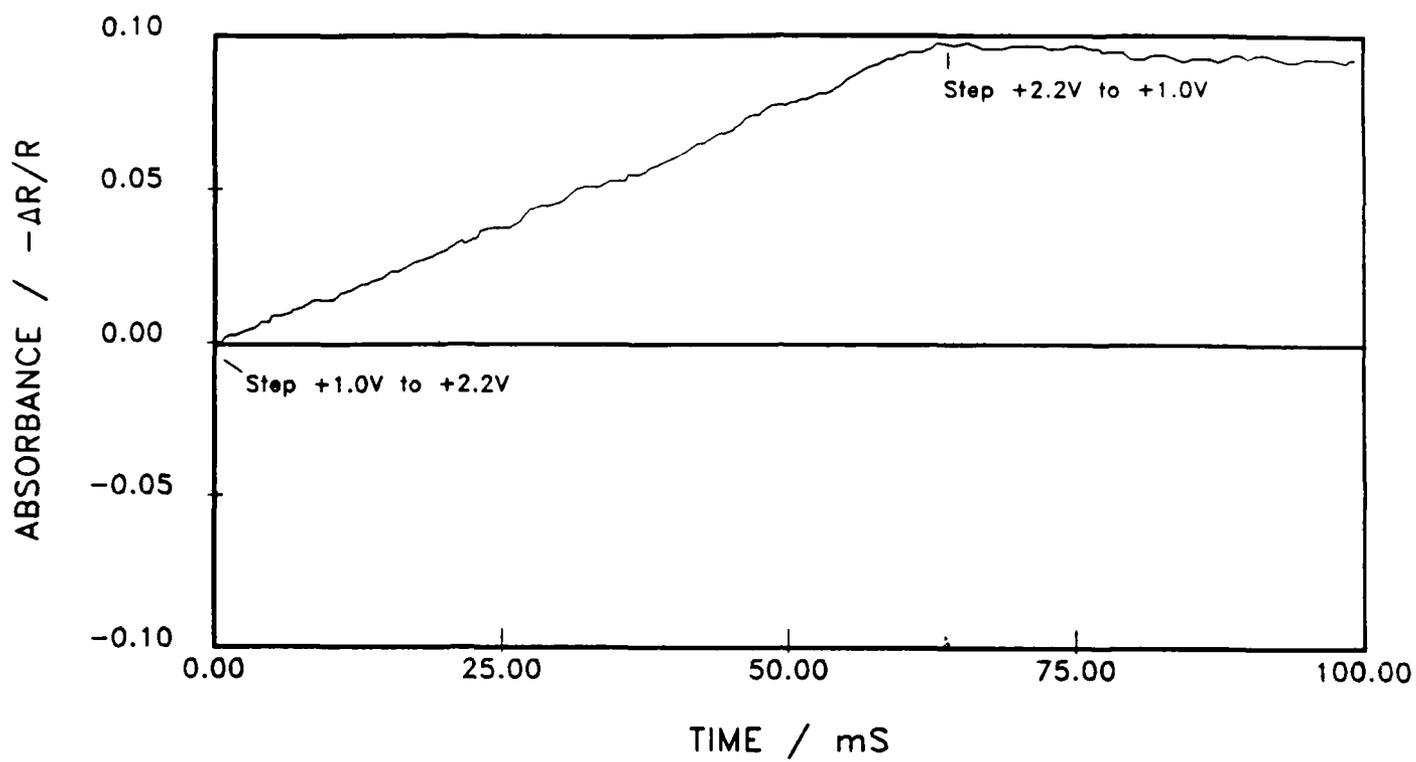


Fig 2

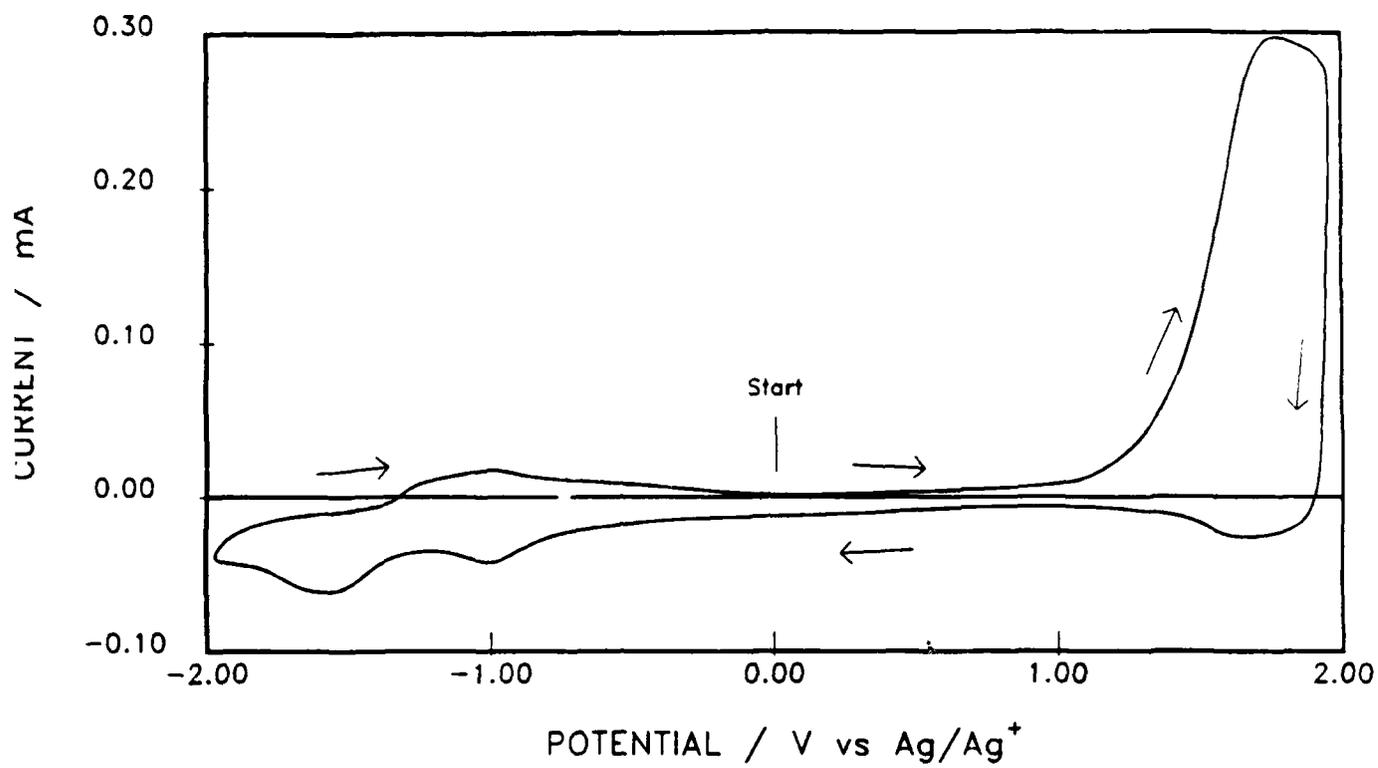


Fig 3

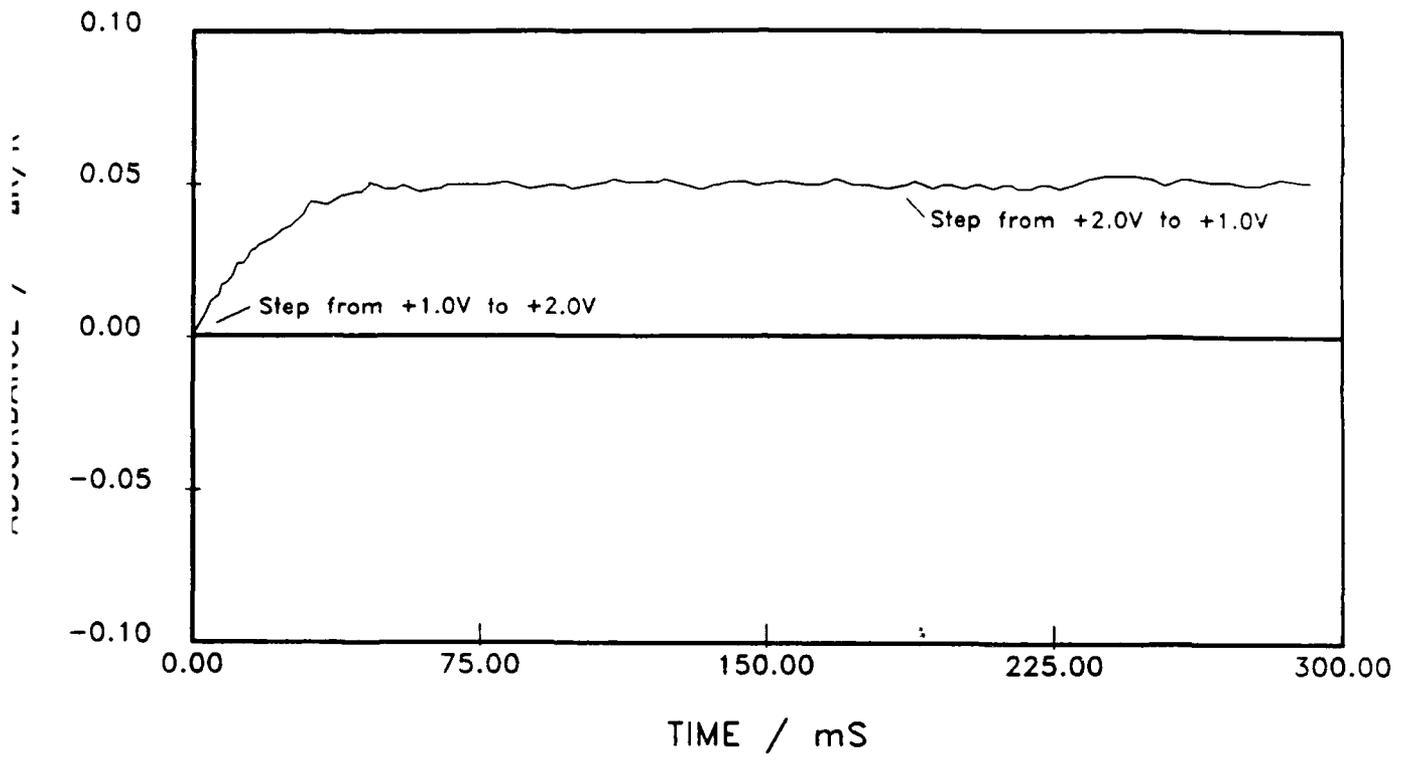


Fig 4

DL/1113/87/2

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	<u>No. Copies</u>		<u>No. Copies</u>
Office of Naval Research Attn: Code 1113 800 N. Quincy Street Arlington, Virginia 22217-5000	2	Dr. David Young Code 334 NORDA NSTL, Mississippi 39529	1
Dr. Bernard Douda Naval Weapons Support Center Code 50C Crane, Indiana 47522-5050	1	Naval Weapons Center Attn: Dr. Ron Atkins Chemistry Division China Lake, California 93555	1
Naval Civil Engineering Laboratory Attn: Dr. R. W. Drisko, Code L52 Port Hueneme, California 93401	1	Scientific Advisor Commandant of the Marine Corps Code RD-1 Washington, D.C. 20380	1
Defense Technical Information Center Building 5, Cameron Station Alexandria, Virginia 22314	12 high quality	U.S. Army Research Office Attn: CRD-AA-IP P.O. Box 12211 Research Triangle Park, NC 27709	1
DTNSRDC Attn: Dr. H. Singerman Applied Chemistry Division Annapolis, Maryland 21401	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, Pennsylvania 19112	1
Dr. William Tolles Superintendent Chemistry Division, Code 6100 Naval Research Laboratory Washington, D.C. 20375-5000	1	Naval Ocean Systems Center Attn: Dr. S. Yamamoto Marine Sciences Division San Diego, California 91232	1

ABSTRACTS DISTRIBUTION LIST, SDIO/IST

Dr. Robert A. Osteryoung  
Department of Chemistry  
State University of New York  
Buffalo, NY 14214

Dr. Douglas N. Bennion  
Department of Chemical Engineering  
Brigham Young University  
Provo, UT 84602

Dr. Stanley Pons  
~~Department of Chemistry~~  
University of Utah  
Salt Lake City, UT 84112

Dr. H. V. Venkatesetty  
Honeywell, Inc.  
10701 Lyndale Avenue South  
Bloomington, MN 55420

Dr. J. Foos  
EIC Labs Inc.  
111 Downey St.  
Norwood, MA 02062

Dr. Neill Weber  
Ceramatec, Inc.  
163 West 1700 South  
Salt Lake City, UT 84115

Dr. Subhash C. Narang  
SRI International  
333 Ravenswood Ave.  
Menlo Park, CA 94025

Dr. J. Paul Pemsler  
Castle Technology Corporation  
52 Dragon Ct.  
Woburn, MA 01801

Dr. R. David Rauh  
EIC Laboratory Inc.  
111 Downey Street  
Norwood, MA 02062

Dr. Joseph S. Foos  
EIC Laboratories, Inc.  
111 Downey Street  
Norwood, Massachusetts 02062

Dr. Donald M. Schleich  
Department of Chemistry  
Polytechnic Institute of New York  
333 Jay Street  
Brooklyn, New York 01

Dr. Stan Szpak  
Code 633  
Naval Ocean Systems Center  
San Diego, CA 92152-5000

Dr. George Blomgren  
Battery Products Division  
Union Carbide Corporation  
25225 Detroit Rd.  
Westlake, OH 44145

Dr. Ernest Yeager  
Case Center for Electrochemical  
Science  
Case Western Reserve University  
Cleveland, OH 44106

Dr. Mel Miles  
Code 3852  
Naval Weapons Center  
China Lake, CA 93555

Dr. Ashok V. Joshi  
Ceramatec, Inc.  
2425 South 900 West  
Salt Lake City, Utah 84119

Dr. W. Anderson  
Department of Electrical &  
Computer Engineering  
SUNY - Buffalo  
Amherst, Massachusetts 14260

Dr. M. L. Gopikanth  
Chemtech Systems, Inc.  
P.O. Box 1067  
Burlington, MA 01803

Dr. H. F. Gibbard  
Power Conversion, Inc.  
495 Boulevard  
Elmwood Park, New Jersey 07407

DL/1113/87/2

ABSTRACTS DISTRIBUTION LIST, SDIO/IST

Dr. V. R. Koch  
Covalent Associates  
52 Dragon Court  
Woburn, MA 01801

Dr. Randall B. Olsen  
Chronos Research Laboratories, Inc.  
4186 Sorrento Valley Blvd.  
Suite H  
San Diego, CA 92121

Dr. Alan Hooper  
Applied Electrochemistry Centre  
Harwell Laboratory  
Oxfordshire, OX11 0RA UK

Dr. John S. Wilkes  
Department of the Air Force  
The Frank J. Seiler Research Lab.  
United States Air Force Academy  
Colorado Springs, CO 80840-6528

Dr. Gary Bullard  
Pinnacle Research Institute, Inc.  
10432 N. Tantan Avenue  
Cupertino, CA 95014

Dr. J. O'M. Bockris  
Ementech, Inc.  
Route 5, Box 946  
College Station, TX 77840

Dr. Michael Binder  
Electrochemical Research Branch  
Power Sources Division  
U.S. Army Laboratory Command  
Fort Monmouth, New Jersey 07703-5000

Professor\* Martin Fleischmann  
Department of Chemistry  
University of Southampton  
Southampton, Hants, SO9 5NH UK