

2

SECURITY CLASSIFICATION OF THIS PAGE

REPORT DOCUMENTATION PAGE

1a. REPORT SECURITY CLASSIFICATION Unclassified		1b. RESTRICTIVE MARKINGS None	
2a. SECURITY CLASSIFICATION AUTHORITY		3. DISTRIBUTION/AVAILABILITY OF REPORT Unlimited	
2b. DECLASSIFICATION/DOWNGRADING SCHEDULE			
4. PERFORMING ORGANIZATION REPORT NUMBER(S) interim technical report #40		5. MONITOR <b>AD-A222 026</b>	
6a. NAME OF PERFORMING ORGANIZATION Department of Chemistry	6b. OFFICE SYMBOL (if applicable)	7a. NAME Office of Naval Research	
6c. ADDRESS (City, State, and ZIP Code) Massachusetts Institute of Technology 77 Mass. Avenue, Bldg. 6-335 Cambridge, MA 02139		7b. ADDRESS (City, State, and ZIP Code) Chemistry Division 800 N. Quincy Street Arlington, VA 22217	
8a. NAME OF FUNDING/SPONSORING ORGANIZATION Office of Naval Research	8b. OFFICE SYMBOL (if applicable)	9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER N00014-84-K-0553	
8c. ADDRESS (City, State, and ZIP Code) Chemistry division 800 N. Quincy Street Arlington, VA 22217		10. SOURCE OF FUNDING NUMBERS	
		PROGRAM ELEMENT NO.	PROJECT NO.
		TASK NO.	WORK UNIT ACCESSION NO.
			051-579
11. TITLE (Include Security Classification) Use of Microelectrode Arrays to Directly Measure Diffusion of Ions in Solid Electrolytes			
12. PERSONAL AUTHOR(S) V. Cammarata, D.R. Talham, R.M. Crooks and M.S. Wrighton			
13a. TYPE OF REPORT technical interim	13b. TIME COVERED FROM 5/89 TO 5/90	14. DATE OF REPORT (Year, Month, Day) 5/16/90	15. PAGE COUNT 32
16. SUPPLEMENTARY NOTATION Prepared for publication in Journal of Physical Chemistry			
17. COSATI CODES		18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)	
FIELD	GROUP	SUB-GROUP	
		Ag ion diffusion, microelectrodes, solid polymer electrolytes	
19. ABSTRACT (Continue on reverse if necessary and identify by block number)  See Attached Sheet			
20. DISTRIBUTION/AVAILABILITY OF ABSTRACT <input type="checkbox"/> UNCLASSIFIED/UNLIMITED <input type="checkbox"/> SAME AS RPT. <input type="checkbox"/> OTIC USERS		21. ABSTRACT SECURITY CLASSIFICATION Unlimited	
22a. NAME OF RESPONSIBLE INDIVIDUAL Mark S. Wrighton		22b. TELEPHONE (Include Area Code) 617-253-1597	22c. OFFICE SYMBOL

OTIC  
MAY 23 1990  
D

**ABSTRACT**

We report experiments which demonstrate direct measurement of diffusion of molecular or ionic species in solid electrolyte media. A microelectrode array of closely spaced (1.4  $\mu\text{m}$ ) Pt microelectrodes ( $\sim 70 \mu\text{m}$  long x 2.7  $\mu\text{m}$  wide x 0.1  $\mu\text{m}$  high) allows direct measurement of the movement of  $\text{Ag}^+$  in aqueous electrolyte and in the solid polymer electrolytes,  $\text{LiCF}_3\text{SO}_3/\text{MEEP}$  (MEEP = poly[bis(2-(2-methoxyethoxy)ethoxy)phosphazene]) at 298 K with a molar ratio of  $\text{LiCF}_3\text{SO}_3$  to polymer repeat unit of 1 to 4 and  $\text{LiCF}_3\text{SO}_3/\text{PEO}$  (PEO = poly[ethylene oxide]) at 352 K and a molar ratio of  $\text{LiCF}_3\text{SO}_3$  to polymer repeat unit of 1 to 8. The crucial experiments involve anodically stripping Ag from a Ag-coated Pt microelectrode (generator) and electrochemically detecting the resulting  $\text{Ag}^+$  at nearby (1.4 to 23.4  $\mu\text{m}$ ) Pt electrodes (collectors) by reducing the  $\text{Ag}^+$  back to Ag. The time dependence of the collector current corresponding to  $\text{Ag}^+$  to Ag reduction after the generation step allows evaluation of the diffusion coefficient,  $D$ , for the  $\text{Ag}^+$  in the various media and conditions used:  $D = 5 \pm 2 \times 10^{-9} \text{ cm}^2/\text{s}$  at 298 K in  $\text{LiCF}_3\text{SO}_3/\text{MEEP}$ ,  $2.3 \pm 0.3 \times 10^{-5} \text{ cm}^2/\text{s}$  in aqueous 0.1 M  $\text{LiClO}_4$  and  $7 \pm 1 \times 10^{-8} \text{ cm}^2/\text{s}$  at 352 K in  $\text{LiCF}_3\text{SO}_3/\text{PEO}$ . For the arrays used  $D = 0.22d^2/t_{\text{mt}}$  where  $d$  is the separation between the generator and the collector and  $t_{\text{mt}}$  is the time of the maximum collector current.



Office of Naval Research  
 Contract NOOO14-84-K-0553  
 Task No. 051-597  
 Technical Report #40

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By _____	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	

Use of Microelectrode Arrays to Directly Measure Diffusion  
 of Ions in Solid Electrolytes: Physical Diffusion of Ag<sup>+</sup> in  
 a Solid Polymer Electrolyte

by

Vince Cammarata, Daniel R. Talham, Richard M. Crooks,  
 and Mark S. Wrighton

Prepared for Publication

in

Journal of Physical Chemistry

Massachusetts Institute of Technology  
 Department of Chemistry  
 Cambridge, MA 02139

Reproduction in whole or in part is permitted for any purpose of the  
 United States Government.

This document has been approved for public release and sale; its  
 distribution is unlimited.

[Prepared for publication in the Journal of Physical  
Chemistry]

**Use of Microelectrode Arrays to Directly Measure Diffusion  
of Ions in Solid Electrolytes: Physical Diffusion of  $\text{Ag}^+$  in  
a Solid Polymer Electrolyte**

Vince Cammarata, Daniel R. Talham, Richard M. Crooks,  
and Mark S. Wrighton\*

Department of Chemistry  
Massachusetts Institute of Technology  
Cambridge, Massachusetts 02139

\*Address correspondence to this author.

**ABSTRACT**

We report experiments which demonstrate direct measurement of diffusion of molecular or ionic species in solid electrolyte media. A microelectrode array of closely spaced (1.4  $\mu\text{m}$ ) Pt microelectrodes ( $\sim 70$   $\mu\text{m}$  long x 2.7  $\mu\text{m}$  wide x 0.1  $\mu\text{m}$  high) allows direct measurement of the movement of  $\text{Ag}^+$  in aqueous electrolyte and in the solid polymer electrolytes,  $\text{LiCF}_3\text{SO}_3/\text{MEEP}$  (MEEP = poly[bis(2-(2-methoxyethoxy)ethoxy)phosphazene]) at 298 K with a molar ratio of  $\text{LiCF}_3\text{SO}_3$  to polymer repeat unit of 1 to 4 and  $\text{LiCF}_3\text{SO}_3/\text{PEO}$  (PEO = poly(ethylene oxide)) at 352 K and a molar ratio of  $\text{LiCF}_3\text{SO}_3$  to polymer repeat unit of 1 to 8. The crucial experiments involve anodically stripping Ag from a Ag-coated Pt microelectrode (generator) and electrochemically detecting the resulting  $\text{Ag}^+$  at nearby (1.4 to 23.4  $\mu\text{m}$ ) Pt electrodes (collectors) by reducing the  $\text{Ag}^+$  back to Ag. The time dependence of the collector current corresponding to  $\text{Ag}^+$  to Ag reduction after the generation step allows evaluation of the diffusion coefficient,  $D$ , for the  $\text{Ag}^+$  in the various media and conditions used:  $D = 5 \pm 2 \times 10^{-9}$   $\text{cm}^2/\text{s}$  at 298 K in  $\text{LiCF}_3\text{SO}_3/\text{MEEP}$ ,  $2.3 \pm 0.3 \times 10^{-5}$   $\text{cm}^2/\text{s}$  in aqueous 0.1 M  $\text{LiClO}_4$  and  $7 \pm 1 \times 10^{-8}$   $\text{cm}^2/\text{s}$  at 352 K in  $\text{LiCF}_3\text{SO}_3/\text{PEO}$ . For the arrays used  $D = 0.22d^2/t_{\text{mt}}$  where  $d$  is the separation between the generator and the collector and  $t_{\text{mt}}$  is the time of the maximum collector current.

## INTRODUCTION

We have recently communicated a technique which allows the electrochemical determination of the diffusion coefficient,  $D$ , of a redox active species by monitoring the time required for a species to move from a "generator" electrode, through an electrolyte medium to a separate "collector" electrode, Scheme I.<sup>1</sup> The critical measurement is to determine the time dependence of the collector current associated with the redox chemistry of the species created at the generator. Equation (1) has been shown to apply to a

$$D = 0.22d^2/t_{mt} \quad (1)$$

geometry of generator/collector electrodes consisting of parallel microelectrodes where  $D$  is the diffusion coefficient of the species created at the generator,  $d$  is the distance from the center of the generator to the nearest edge of the collector and  $t_{mt}$  is the time associated with the maximum in the collector current.<sup>1</sup>

In this report we demonstrate the utility of microelectrode generation/collection techniques to directly measure the movement of ions in solid polymer electrolyte media and to determine their diffusion coefficients. The experimental strategy is summarized in Scheme II. The critical measurement is the time dependence of the collector current corresponding to the reduction of  $Ag^+$  after the pulsed generation of  $Ag^+$  from a Ag-coated generator

electrode, a distance  $d$  from the collector. For simplicity we assume  $\text{Ag}^+$  movement, however, the actual species moving may be  $\text{Ag}^+$ ,  $\text{Ag}^+\text{CF}_3\text{SO}_3^-$ ,  $\text{Ag}^+(\text{S})$ , or  $\text{Ag}^+\text{CF}_3\text{SO}_3^-(\text{S})$  where  $\text{S}$  is one or more solvent molecules. In any case, we detect the movement of some  $\text{Ag}^+$  species from one point in space to another.

Our new measurement techniques complement studies of ionic conductivity by AC impedance, pulsed-field gradient NMR and radiotracer methods.<sup>2,3</sup> Measurements of solid-state ionic conductivity from AC impedance are not always easily interpreted,<sup>4</sup> however the measurements here directly provide data concerning diffusivity. Electrochemical studies to determine  $D$  based on steady-state currents of codissolved electroactive species have been made in solvent swollen solid electrolytes.<sup>5</sup> Measurements of the effective diffusion coefficient for charge-transport in a redox polymer have been made using a microelectrode array coated with a polymer.<sup>6,7</sup> In the redox polymer studies, the movement of charge is a diffusion process that occurs via electron-hopping, driven by a concentration gradient between oxidized and reduced sites. Our extension of this methodology relates to a situation where net physical movement of an ion occurs in a non-electronic conductive media. A significant point regarding our method for determining  $D$  for  $\text{Ag}^+$  is that the measurement is unambiguous in terms of the movement of the  $\text{Ag}^+$ , because all  $\text{Ag}$  is initially confined to the generator and the current measured

is due to the reduction only at the collectors. Transit time techniques can determine diffusion coefficients without knowledge of the concentration of the diffusing species.<sup>6</sup>

Solid electrolytes show great promise in battery technology, in solar energy systems, and in solid-state gas sensors.<sup>8</sup> Solid polymer electrolytes differ from the classical solid electrolytes in that generally they are conductive in the elastomeric phase as opposed to in a crystalline or polycrystalline phase. Since they are generally glasses at operating temperature, embrittlement and delamination do not limit long term durability. Processing of these materials for the construction of odd shapes or sizes is facilitated by their plasticity. Many ionic conducting polymers behave as solvents for ions which have, on a microscopic scale, liquid-like degrees of freedom. Our primary illustration of the direct dynamic movement of ions through a solid concerns the solid electrolyte, MEEP/LiCF<sub>3</sub>SO<sub>3</sub> at a 1 to 4 molar ratio of LiCF<sub>3</sub>SO<sub>3</sub> to polymer repeat unit.<sup>9</sup> MEEP, shown in Scheme III, is known to have good ionic conductivity for many monovalent salts at 298 K.<sup>10</sup> We have also studied PEO/LiCF<sub>3</sub>SO<sub>3</sub> at a 8 to 1 molar ratio of polymer repeat unit to LiCF<sub>3</sub>SO<sub>3</sub>.<sup>11</sup> PEO, also shown in Scheme III, has good ionic conductivity above the melting point of the crystalline phase (~67 °C) and is the most well-studied of the organic polymer solid electrolytes.<sup>2,12</sup> The structure of both of these polymers include ether linkages separated

by  $-\text{CH}_2\text{CH}_2-$  groups analogous to crown ethers and their linear analogues. The affinity of this class of molecules for alkali metal cations is well documented.<sup>2,4</sup> The mechanism of conduction (diffusion) is assumed to be ion hopping from Lewis base site to Lewis base site in which chain motion is a significant factor.<sup>13</sup> This is inferred from discontinuities in the conductivity-temperature plots near the melting point of these polymers. Our studies provide some of the first data on direct measurement of diffusivity of ions in solid polymer electrolytes. The methodology can be applied to studies to investigate the factors governing ionic conductivity.

## EXPERIMENTAL

MATERIALS. The polymers PEO and MEEP were deposited from 1-2% stock solutions based on  $\text{CH}_3\text{CN}$  and tetrahydrofuran (THF), respectively (i.e. 100 mg MEEP/10 ml THF). PEO (Aldrich, MW  $5 \times 10^6$ ) was dried under 1 mm vacuum at 50 °C for 24 h. then stored in a Vacuum Atmospheres dry box for use.  $\text{LiCF}_3\text{SO}_3$  (Aldrich) was dried at 100 °C for 24 h. under vacuum. MEEP<sup>9,10</sup> was a generous gift from Professor H. R. Alicock at the Pennsylvania State University. The polymers were dissolved in  $\text{CH}_3\text{CN}$  or THF with 4:1 and 8:1 molar ratios of polymer repeat unit to electrolyte for MEEP and PEO, respectively. Solvents used were reagent grade and distilled from  $\text{CaH}_2$  before use.

MICROELECTRODE MODIFICATION. The Pt microelectrode arrays used have been described previously<sup>14</sup> and consist of eight, individually addressable Pt microelectrodes each 70  $\mu\text{m}$  long  $\times$  2.7  $\mu\text{m}$  wide  $\times$  0.1  $\mu\text{m}$  high with an interelectrode spacing of 1.4  $\mu\text{m}$ . A small area of Ag epoxy was placed 300-500  $\mu\text{m}$  from the array to be used as a counterelectrode in these experiments. Ag metal was then deposited on the characterized array. At least one electrode typically #1 or #8 was plated with Ag metal to act as a reference electrode under the solid electrolyte. Ag metal was selectively deposited by pulsing the desired electrodes from 0 V to -0.5 V vs. Ag wire in a commercial Ag cyanide plating bath (Transene Co.) for 1 to 2 s. The remaining electrodes were held at +0.2 V vs. Ag wire. Typical plating currents were

50-200 nA per electrode ( $\sim 10$  mA/cm<sup>2</sup>). The Ag-coated microelectrode array devices were brought into the dry box, and 1 or 2 drops of polymer solution placed on the electrode surface. The devices were then placed in the antechamber of the drybox and dried by slowly evacuating the antechamber to an ultimate vacuum of 0.1 mm of Hg over 15 min. The devices were left under vacuum for an additional 1.5 h. The device was then brought back into the dry box, and fitted through a rubber septum into a round bottom flask in order to maintain an inert atmosphere above the device throughout the experiment. 20  $\mu$ l of THF per 50 ml of N<sub>2</sub> atmosphere was injected as a "plasticizer" to increase ionic conductivity<sup>2,4,5</sup> and to insure a reproducible atmosphere. PEO experiments were done at elevated temperatures above the melting point ( $\sim 67$  °C) of the polymer while the MEEP experiments were done at room temperature ( $\sim 23$  °C).

CHARACTERIZATION TECHNIQUES. Auger electron spectra were obtained on a Physical Electronics 660 Scanning Auger Microprobe. Scanning electron micrographs were obtained on a Hitachi 5 800 instrument. Optical photography was taken on a Bausch and Lomb MicroZoom microscope.

ELECTROCHEMICAL MEASUREMENTS. Electrochemical equipment consisted of a Pine Instruments, RDE4 bipotentiostat specially modified to include a 100 nA/V scale and with leads prior to the first stage amplifier shielded to the chassis ground. The electrochemical cell was enclosed by a Faraday shield or in the high temperature experiments

enclosed in a Will lab oven to stabilize the operating temperature. Signals were recorded on Kipp and Zonen BD 91 X-Y-Y' dual pen chart recorder or dual channel Nicolet 4904 Digital Collection Oscilloscope. Pulses were generated from a Princeton Applied Research, PAR 175 Universal Programmer. The  $\text{Ag}^+$  solution experiment was performed in an aqueous 0.1 M  $\text{LiClO}_4$  solution at 23 °C.

## RESULTS AND DISCUSSION

### DIFFUSION IN LIQUID ELECTROLYTES

Figure 1 illustrates microelectrode transit time data recorded in aqueous 0.1 M LiClO<sub>4</sub> at 298 K. With reference to Scheme I, collection current vs. time is shown for two values of  $d$ , 9.6  $\mu\text{m}$  and 17.8  $\mu\text{m}$ , giving values of  $t_{\text{mt}}$  of 11.5 ms and 32.3 ms, respectively, for the Ag<sup>+</sup> experiment. Consistent with a diffusion process, the value of  $t_{\text{mt}}$  is found experimentally to be proportional to  $d^2$  as illustrated in the inset of Figure 1. The inset of Figure 1 also gives  $t_{\text{mt}}$  vs.  $d^2$  for experiments involving the diffusion of Ru(NH<sub>3</sub>)<sub>6</sub><sup>2+</sup> where the Ru(NH<sub>3</sub>)<sub>6</sub><sup>2+</sup> is generated by reduction of Ru(NH<sub>3</sub>)<sub>6</sub><sup>3+</sup> at the generator.<sup>1</sup> The ratio of slopes of the plots of  $t_{\text{mt}}$  vs.  $d^2$  for the Ag<sup>+</sup> and Ru(NH<sub>3</sub>)<sub>6</sub><sup>2+</sup> gives the ratio of  $D$  for these two species, and equation (1) can be used to determine  $D$ . Our measurements give  $D = 2.3 \times 10^{-5}$  cm<sup>2</sup>/s and  $7.8 \times 10^{-6}$  cm<sup>2</sup>/s for Ag<sup>+</sup> and Ru(NH<sub>3</sub>)<sub>6</sub><sup>2+</sup> respectively,<sup>15,16</sup> results which agree well with previous measurements. The Ag<sup>+</sup> transit time experiment is somewhat different than the solution species experiment since the generation step involves stripping of confined redox material instead of generation from a solution species. In addition, the collection step truly collects the material at the electrode as opposed to collection being a change in redox state of a solution species. The Ag<sup>+</sup> experiments show that despite the differences in the nature of the redox

process, the diffusion of the solution species determines the transit time and the shape of the collection curve.

#### SURFACE ANALYSIS

In earlier work on monitoring the diffusion of solution species, it was determined that the best fit of the distance dependence to transit time used a center to edge distance on the microelectrode array.<sup>1</sup> Since the generator and collector electrodes have a finite width relative to the gap, it was unclear how far the majority of the species had to travel. Although this empirical formula worked well in the cases considered, direct experimental evidence justifying its use was lacking. Optical microscopy of an array after a  $\text{Ag}^+$  microelectrode transit time experiment in aqueous solution or in MEEP/ $\text{LiCF}_3\text{SO}_3$  (*vide infra*) shows a dark precipitate on the collector electrodes on the nearest edge to the generator. This is diagrammed in Scheme II. Figure 2 shows a scanning electron micrograph (SEM) of a Pt array on which  $5 \times 10^{-8}$  C of Ag was deposited on electrode #4 then anodically stripped by pulsing from -0.6 V to 1.2 V vs. SCE in an aqueous 0.1 M  $\text{LiClO}_4$  solution. The collector electrodes, #2 and #6 (the second electrodes away) are held at -0.6 V vs. SCE. In the SEM the deposition of the dark precipitate is confirmed and the extent of the localization on the collector electrode is shown. Auger analyses confirm that the black precipitate on the collector electrodes and the generator is indeed Ag. The Auger analysis also confirms that Ag is deposited only on the edge of the

collector electrode nearest the generator, and not on the center or far edge or at electrodes not used as collectors. Since Ag is initially confined to the generator electrode and after the experiment localized on the closest edge of the collector electrodes, therefore Ag travels from generator to collector.

#### DIFFUSION IN SOLID ELECTROLYTES

The top portion of Figure 3 shows the generation-collection voltammograms for  $\text{Ag}^+$  in MEEP/ $\text{LiCF}_3\text{SO}_3$ . The anodic curve represents the stripping voltammogram for Ag by scanning the Ag-coated Pt electrode from -0.5 V to 1.4 V vs. Ag electrode at 50 mV/s. The cathodic curve is the current for  $\text{Ag}^+$  reduction monitored concurrently at two collector electrodes, symmetrically disposed 1.4  $\mu\text{m}$  from the generator and held at -0.5 V vs. Ag quasi-reference electrode. Subsequent stripping analysis of the collector electrode confirms that the product deposited there is Ag. This result shows that  $\text{Ag}^+$  indeed travels from the generator to the collector electrodes in the polymer electrolyte.

The lower portion of Figure 3 shows the microelectrode transit time experiment in MEEP/ $\text{LiCF}_3\text{SO}_3$ . The collector current peak of 2.2 nA occurs at 3.15 s for the generation conditions used. Comparing the time for the maximum in collector current in aqueous 0.1 M  $\text{LiClO}_4$  and  $\text{LiCF}_3\text{SO}_3/\text{MEEP}$  shows that the peak occurs ~3000 times later in the solid electrolyte, and  $D = 5 \times 10^{-9} \text{ cm}^2/\text{s}$ . The shape of the collector current vs. time plot (adjusted for height and

width) is similar in both solid and liquid experiments to measure the diffusivity of  $\text{Ag}^+$ .

Transit time experiments have also been done in PEO/ $\text{LiCF}_3\text{SO}_3$  media at 352 K. From experiments similar to those described above, we find  $t_{\text{mt}} = 240$  ms. Using equation (1),  $D = 7 \times 10^{-8}$   $\text{cm}^2/\text{s}$  in this system.

#### COMPUTER SIMULATIONS

Earlier work on redox active ions in solution included simulating the microelectrode transit time experiment.<sup>1</sup> In those cases a semi-infinite boundary condition could be applied since the solution volume dimensions were greater than the critical diffusion lengths. We estimate polymer thickness to exceed 10  $\mu\text{m}$ , but our studies lack accurate information on polymer thicknesses. Surface profilometry yields little information (the stylus cuts through the polymer) and the lack of density information on MEEP (solvent swollen or dry) and the irregularity of the area over which the polymer is spread also contribute to this information gap. To get a better perspective on the dependency of transit time on polymer thickness, digital simulations of such experiments were performed. The simulation is similar to that of the solution case with two exceptions.<sup>1</sup> First, the spatial resolution of the basis grid is more sensitive (i.e. 0.685  $\mu\text{m}$  vs. 1.37  $\mu\text{m}$  spacing for our 1.37  $\mu\text{m}$  gap devices). Second, the boundary conditions are changed such that a reflective boundary is placed at a given distance from the array surface. This

replaces the semi-infinite boundary of the solution simulation. The boundary is intended to model the interface of the polymer with the atmosphere. This boundary is adjustable so that the collector response as a function of time can be simulated as a function of film thickness. The diffusing species is given a simulated diffusion coefficient of  $1 \times 10^{-8} \text{ cm}^2/\text{s}$ .

The plot of the flux of collected species as a function of time is relevant to the observed experimental results (collector current vs. time) in the transit time experiments. Figure 4 shows the flux of collected species as a function of time for a number of simulated polymer thicknesses at a microelectrode array with symmetric, adjacent collectors. The top portion of this figure shows the flux profiles as a function of time for thicknesses of  $27.4 \mu\text{m}$ ,  $10.96 \mu\text{m}$ ,  $6.85 \mu\text{m}$  and  $4.11 \mu\text{m}$ . For  $27.4 \mu\text{m}$  and  $10.96 \mu\text{m}$  thicknesses the collection vs. time curves are identical. In the  $6.85 \mu\text{m}$  case the flux profile shows increased collection around 15 s but the peak flux remains unchanged. At the  $4.11 \mu\text{m}$  thickness the peak starts to broaden and below this limit the simulation shows significant differences from the semi-infinite case. This seems reasonable since the species would have to reach the boundary and return to the collector before the information relating to the thickness would be transmitted to the collector. Only when the thickness is on the order of the interelectrode spacing does the boundary condition affect

the microelectrode transit time results. The lower portion of Figure 4 shows the collection fluxes vs. time for boundary conditions of 2.055 and 2.74  $\mu\text{m}$  as well as 4.11  $\mu\text{m}$  for reference. The peak in the collection flux for the two conditions is severely distorted, though transit time measurements only change ~50% at most. This shows that only measurements with very thin films (less than the interelectrode spacing) would be subject to errors in our analysis of D.

## CONCLUSION

Our results support the conclusion that microelectrochemical techniques can be useful in studies of physical diffusion in solid electrolytes. Results for the movement of  $\text{Ag}^+$  in MEEP and PEO establish a methodology, but do not yet provide unambiguous conclusions regarding the actual diffusing species. Additional research will be required to establish details of the diffusion mechanism in solid polymer electrolytes using microelectrochemical methods. For a given system it is clear that meaningful information will result from measurements of  $t_{\text{mt}}$  as a function of temperature, electrolyte and its concentration, and the actual polymer used. The values of  $D$  reported herein show, as expected, that diffusion of  $\text{Ag}^+$  is much slower ( $\sim 10^3$ ) in MEEP or PEO than in aqueous solution. Additional microelectrochemical studies are in progress to investigate the factors influencing the diffusion of metal cations and new experimental methods are being developed for the study of both anionic and neutral species.

## ACKNOWLEDGMENTS

We thank Professor H. R. Allcock of the Pennsylvania State University for providing a sample of MEEP. We thank Mr. J. J. Hickman for obtaining the Auger analysis and Mr. T. J. Gardner for obtaining the Scanning Electron micrographs. We would like to acknowledge Lockheed Missile and Space Company, Inc. and the Office of Naval Research and

the Defense Advanced Research Projects Agency for partial financial support of this research.

## REFERENCES

1. Licht, S.; Cammarata, V.; Wrighton, M. S. *Science*, **1989**, **243**, 1176; Licht, S.; Cammarata, V.; Wrighton, M. S. to be submitted to *J. Phys. Chem.*
2. Vincent, C. A. *Prog. Solid St. Chem.*, **1987**, **17**, 145.
3. Macdonald, J. R. *Impedance Spectroscopy*, Wiley-Interscience: New York, **1987**.
4. Shriver, D. F.; Ratner, M. A. *Chem. Rev.*, **1988**, **88**, 109.
5. Reed, R. A.; Geng, L.; Murray, R. W. *J. Electroanal. Chem.*, **1986**, **208**, 185; Geng, L.; Reed, R. A.; Longmire, M.; Murray, R. W. *J. Phys. Chem.*, **1987**, **91**, 2908; Geng, L.; Longmire, M. L.; Reed, R. A.; Parcher, J. F.; Barbour, C. J.; Murray, R. W. *Chemistry of Materials*, **1989**, **1**, 58; Geng, L.; Reed, R. A.; Kim, M. -H.; Wooster, T. T.; Oliver, B. N.; Egekeze, J.; Kennedy, R. T.; Jorgenson, J. W.; Parcher, J. F.; Murray, R. W. *J. Am. Chem. Soc.*, **1989**, **111**, 1614.
6. Feldman, B. J.; Feldberg, S. W.; Murray, R. *J. Phys. Chem.*, **1987**, **91**, 6558.
7. Kittlesen, G. P.; White, H. S.; Wrighton, M. S. *J. Am. Chem. Soc.*, **1985**, **107**, 7373; Smith, D. K.; Lane, G. A.; Wrighton, M. S. *J. Am. Chem. Soc.*, **1986**, **108**, 3522; Belanger, D.; Wrighton, M. S. *Anal. Chem.*, **1987**, **59**, 1426.
8. Chiang, C. K. *Polymer*, **1981**, **22**, 1454; Skotheim, T. A.; Lundstrom, I. *J. Electrochem. Soc.*, **1982**, **129**, 894; Chao, S.; Wrighton, M. S. *J. Am. Chem. Soc.*, **1987**, **109**, 8.
9. Allcock, H. R.; Austin, P. E.; Neenan, T. X.; Sisko, J. T.; Blonsky, P. M.; Shriver, D. F. *Macromolecules*, **1986**, **19**,

- 1508; Austin, P. E.; Riding, G. H.; Allcock, H. R. *Macromolecules*, **1983**, **16**, 719.
10. Blonsky, P. M.; Shriver, D. F.; Austin, P. E.; Allcock, H. R. *J. Am. Chem. Soc.*, **1984**, **106**, 6854; Blonsky, P. M.; Shriver, D. F.; Austin, P. E.; Allcock, H. R. *Solid State Ionics*, **1986**, **18**, 258.
11. Weston, J. E.; Steele, B. C. H. *Solid State Ionics*, **1981**, **2**, 347.
12. Armand, M. B.; Chabagno, J. M.; Duclot, M. J. In *Fast Ion Transport in Solids*, Vashishta, P; Mundy, J. N.; Shenoy, G. K., Ed. North Holland: Amsterdam, **1979**, 131.
13. Ratner, M. A. In *Polymer Electrolyte Reviews*, MacCallum, J. R.; Vincent, C. A., Ed. Elsevier: New York, **1987**, 173.
14. Thackeray, J. W.; White, H. S.; Wrighton, M. S. *J. Phys. Chem.*, **1986**, **89**, 5133.
15. von Stackelberg, M.; Pilgram, M.; Toome, W. Z. *Elektrochem.*, **1953**, **57**, 342.
16.  $D$  for  $\text{Ru}(\text{NH}_3)_6^{2+}$  has been independently measured at a 25  $\mu\text{m}$  microdisk electrode from the limiting steady-state currents.

**FIGURE CAPTIONS**




**Figure 1.** Microelectrode transit time measurements of  $\text{Ag}^+$  in 0.1 M  $\text{LiClO}_4$  solution. (A) Collector current vs. time associated with the reduction of  $\text{Ag}^+$  generated by a 2 ms pulse from 0.0 V to 1.4 V returning to 0.0 V vs. SCE at a Pt generator microelectrode coated with  $2 \times 10^{-12}$  moles of Ag metal separated from the collector by 9.6  $\mu\text{m}$ . The Pt collector microelectrode is held at 0.0 V vs. SCE. (B) Collector current vs. time associated with a 10 ms anodic pulse under the same conditions as in (A) with the exception that the interelectrode separation is 17.8  $\mu\text{m}$ . The inset shows the distance dependence of the time of the peak collection current at different collector electrodes for  $\text{Ag}^+$  in 0.1 M  $\text{LiClO}_4$  and also for 2.5 mM  $\text{Ru}(\text{NH}_3)_6^{2+}$  in 0.1 M  $\text{NaClO}_4$ .

**Figure 2.** Scanning electron micrographs of a Pt microelectrode array consisting of eight electrodes (each 70  $\mu\text{m}$  long x 2.7  $\mu\text{m}$  wide x 0.1  $\mu\text{m}$  high with an interelectrode spacing of 1.4  $\mu\text{m}$ ).  $5 \times 10^{-8}$  C of Ag was deposited on electrode #4 (electrodes are numbered 1-8, left to right, see **EXPERIMENTAL**) and then stripped by pulsing from -0.6 V to 1.2 V vs. SCE three times for 10 ms each in an aqueous 0.1 M  $\text{LiClO}_4$ . The collector electrodes, #2 and #6, were held at -0.6 V. The rest of the microelectrode array was left "floating" (i.e. not under potentiostatic or


amperometric control). (Upper) Electrodes #2-8 are shown. (Lower) Electrodes #5 and #6 are shown closeup.

**Figure 3.** (Upper) Generation-collection voltammograms of  $\text{Ag}^+$  in 1:4  $\text{LiCF}_3\text{SO}_3$ :repeat unit of MEEP. The generator microelectrode was scanned from -0.5 V to 1.2 V vs. Ag quasireference electrode at 50 mV/s. Dual collector electrodes are symmetrically disposed about the generator and are 1.4  $\mu\text{m}$  away from the generator. The collector electrodes were held at -0.5 V vs. Ag. (Lower) Collector current vs. time associated with the reduction of  $\text{Ag}^+$  generated with a 2 s step of the Ag-coated Pt generator to +1.4 V and back to +0.6 V vs. Ag in the same  $\text{LiCF}_3\text{SO}_3$ /MEEP electrolyte.


**Figure 4.** Time vs. collection flux are shown for various reflective boundary conditions in a random walk simulation. The diffusion coefficient was taken to be  $1 \times 10^{-8} \text{ cm}^2/\text{s}$ . (Upper) The reflective boundaries are taken as 27.4, 10.96, 6.85 and 4.11  $\mu\text{m}$  from the generator. (Lower) The reflective boundaries are taken as 4.11, 2.74 and 2.055  $\mu\text{m}$  from the generator.

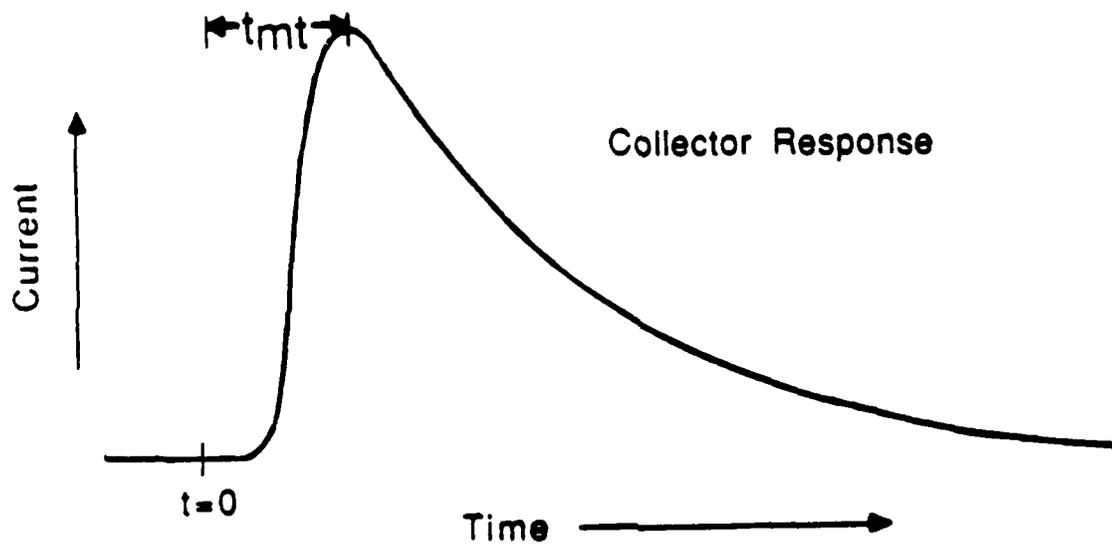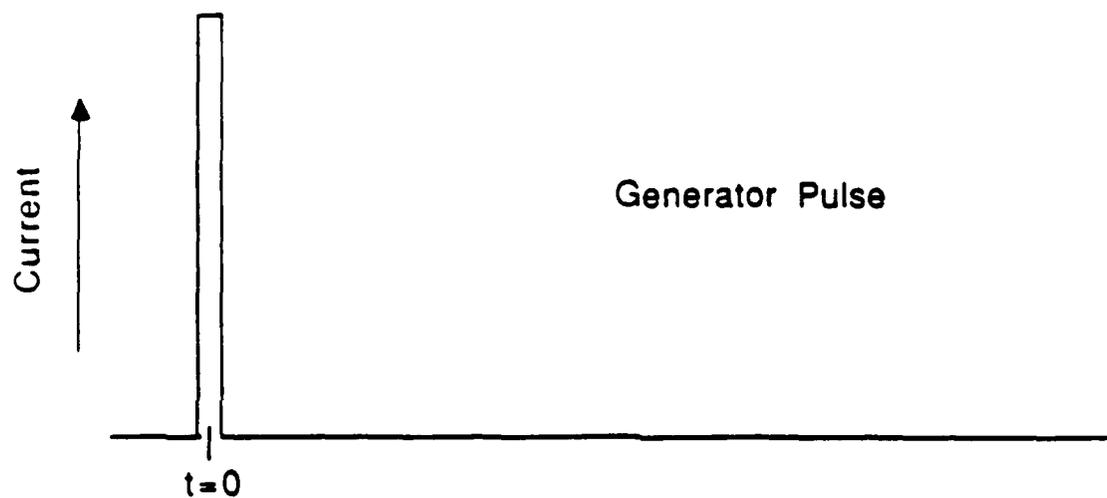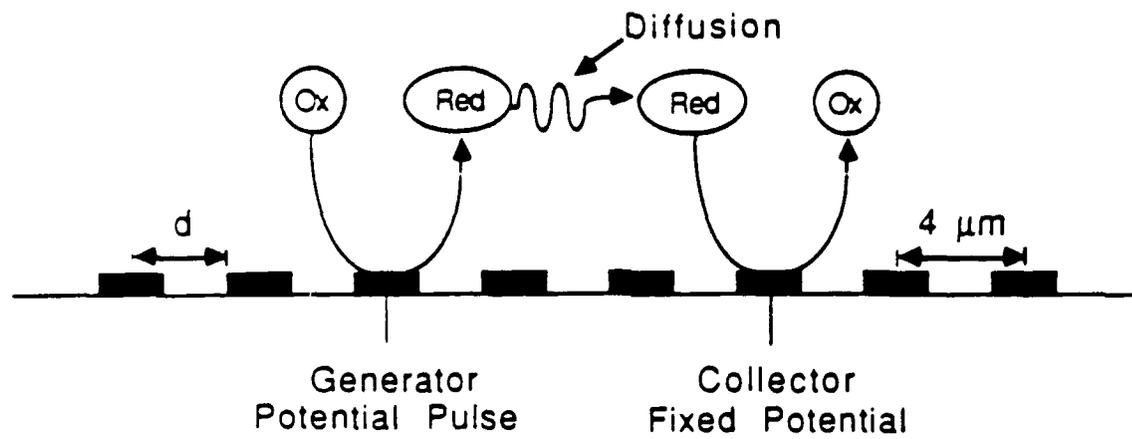

**Scheme I.** Experiment to measure diffusivity of electrogenerated species using a microelectrode array

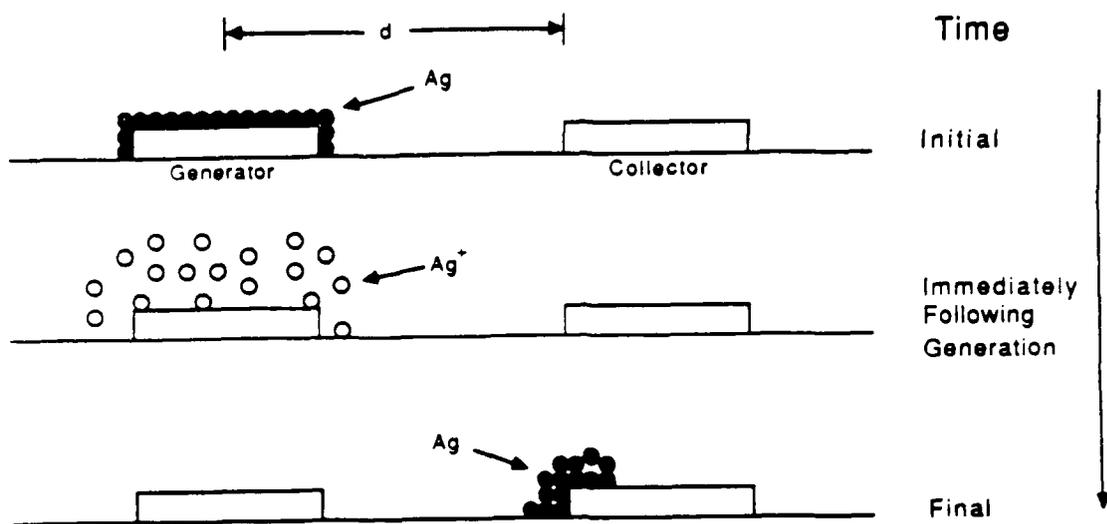


Scheme II. Experimental strategy for  $\text{Ag}^+$  transit time determination

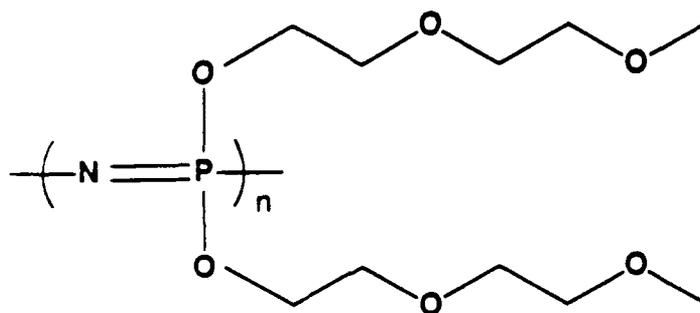

Poly[bis(2-(2-methoxyethoxy)ethoxy)phosphazene]


MEEP

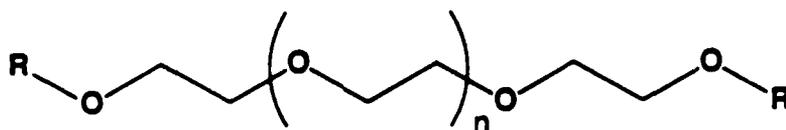




Poly(ethylene oxide)


PEO

Scheme III. Structures of MEEP and PEO

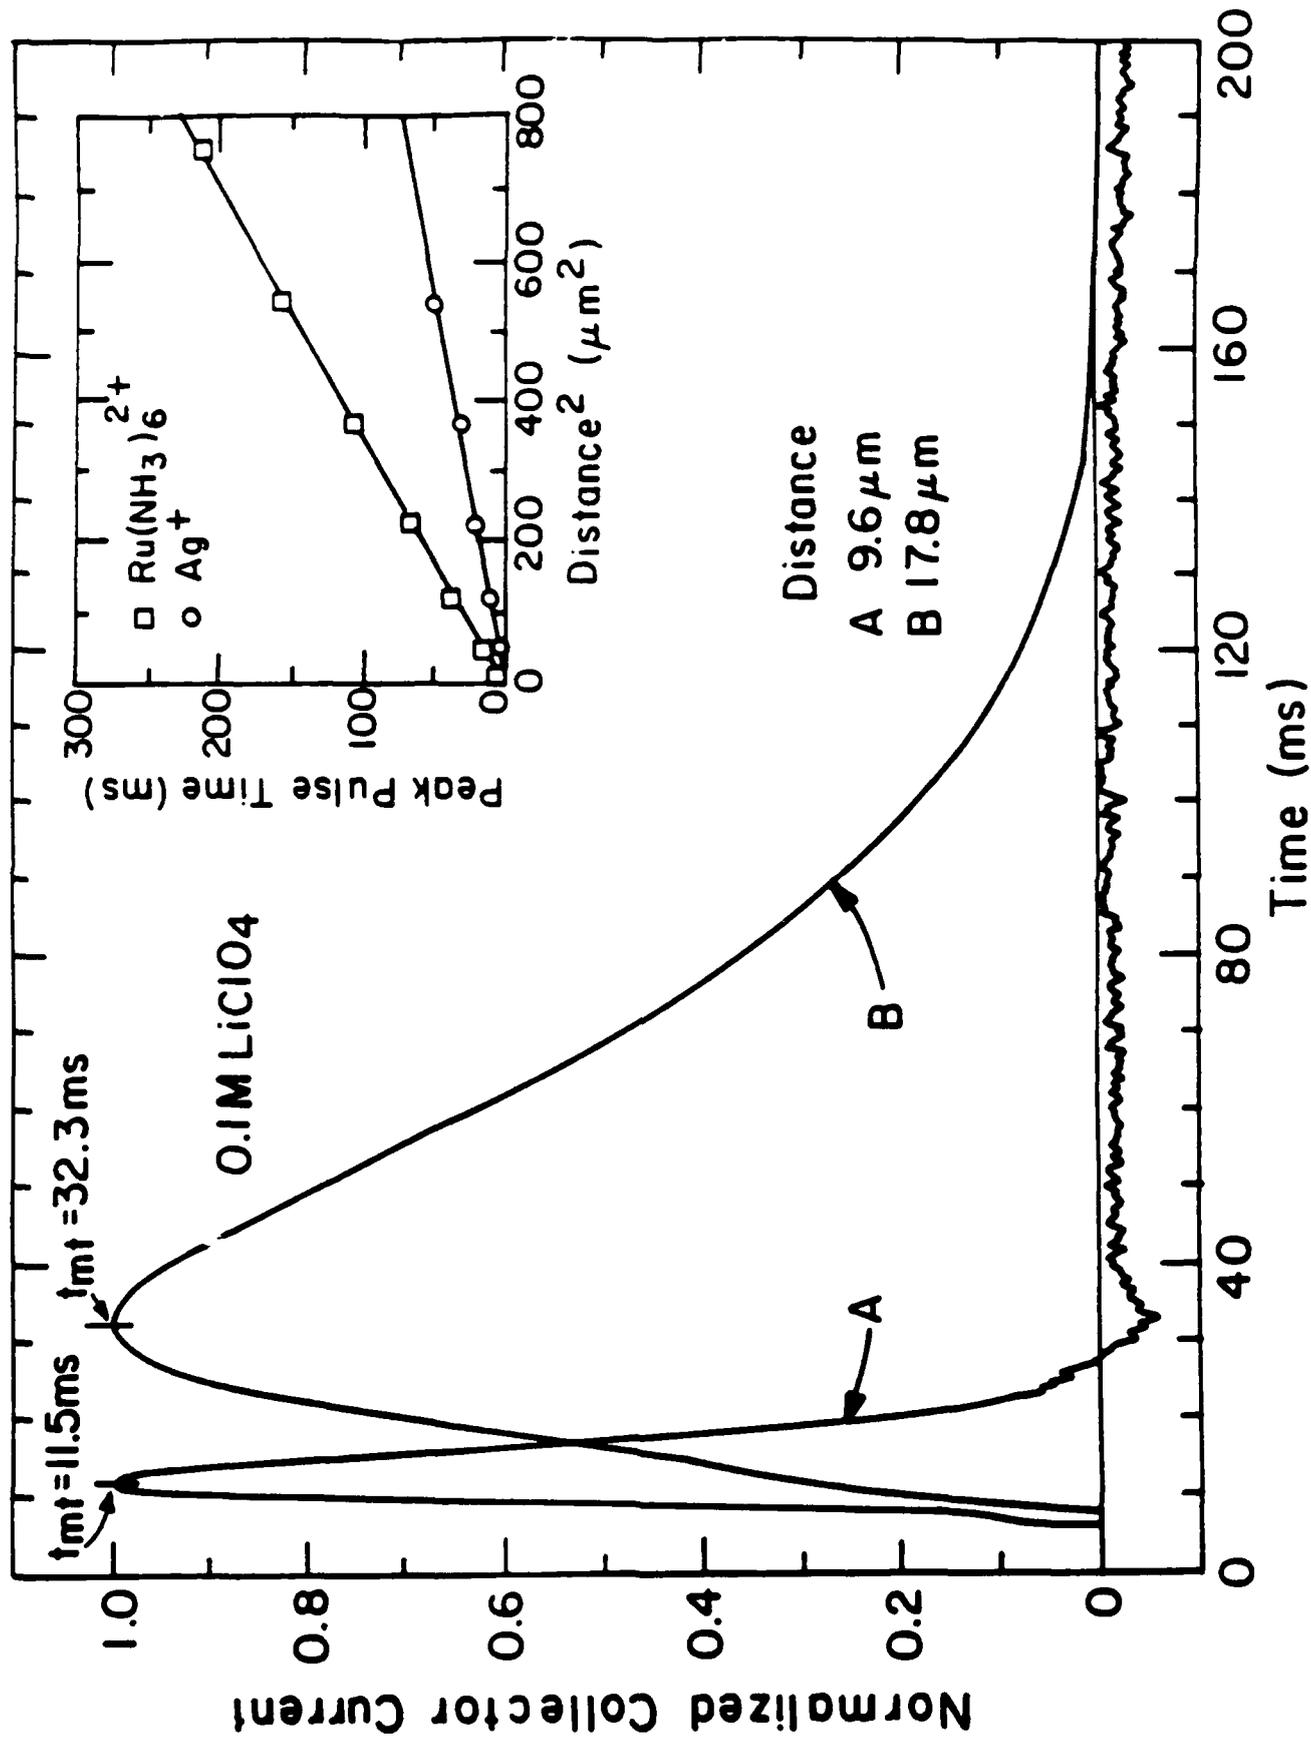

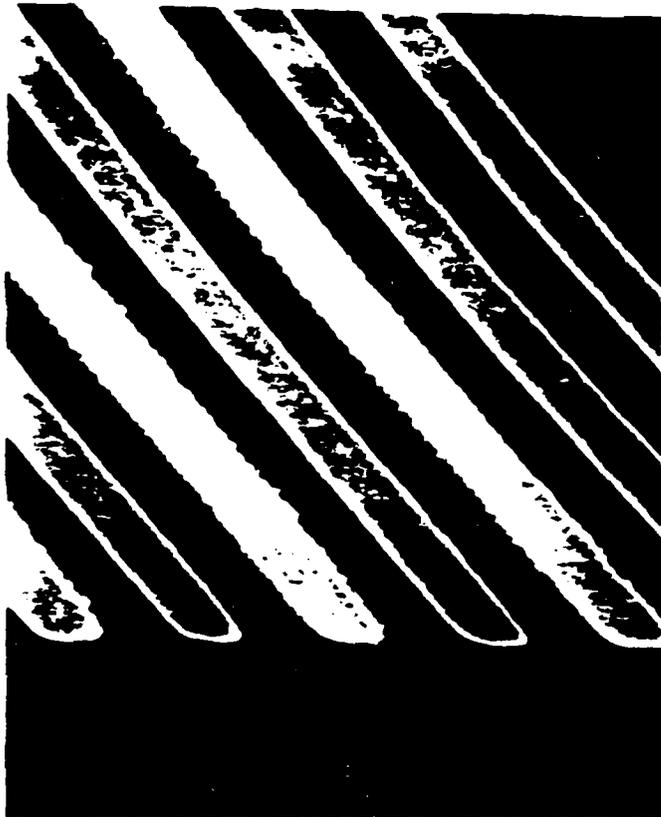

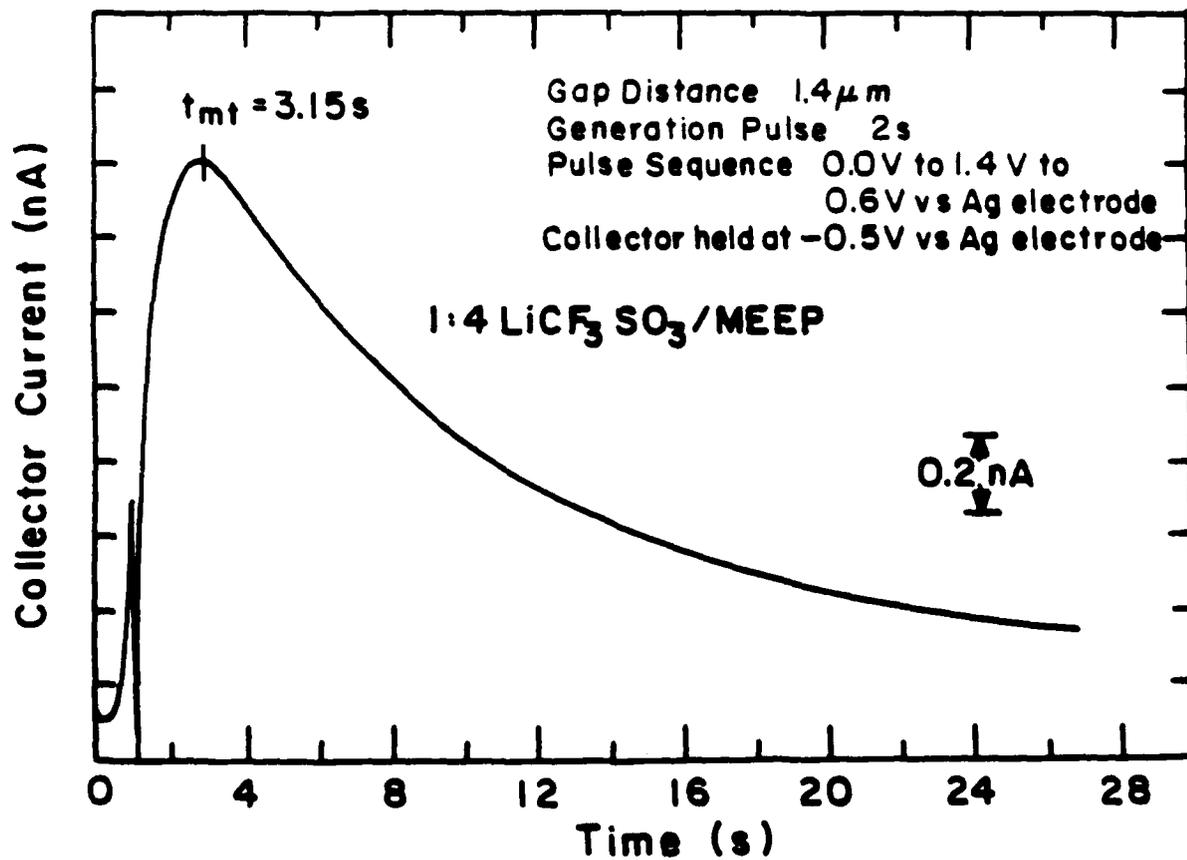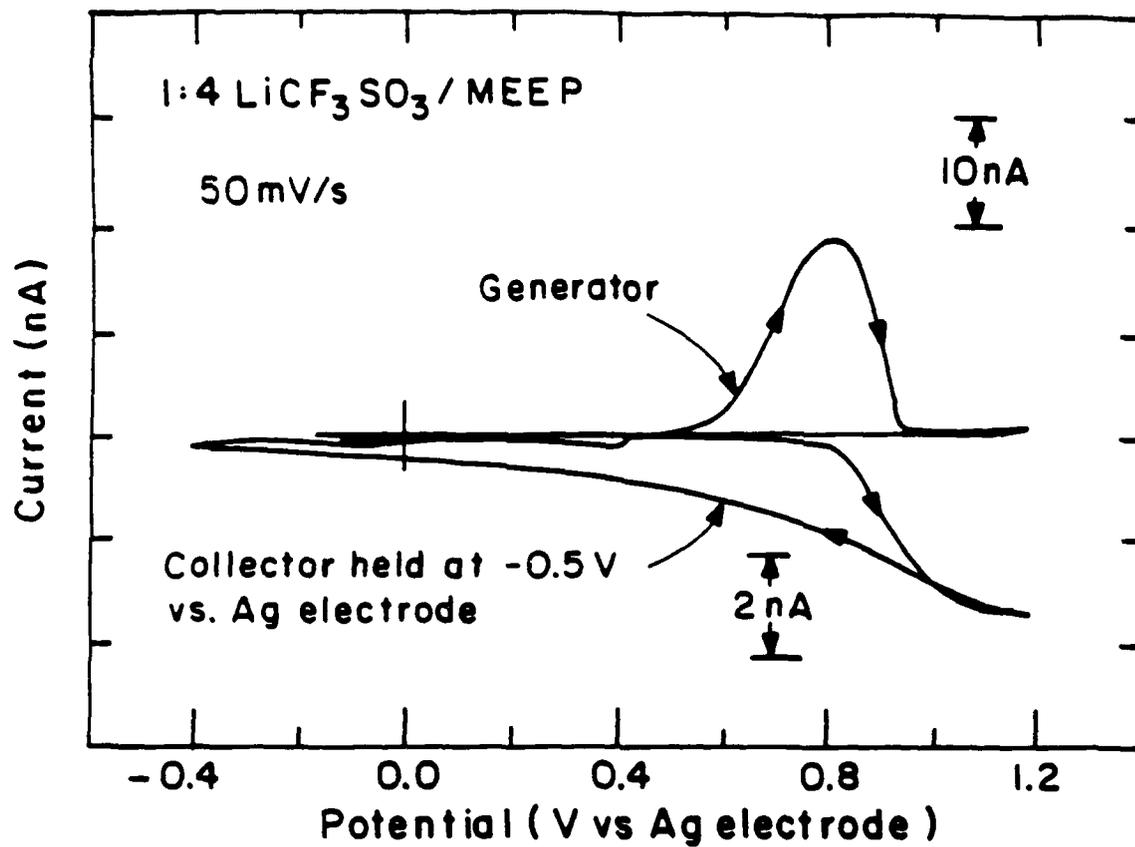

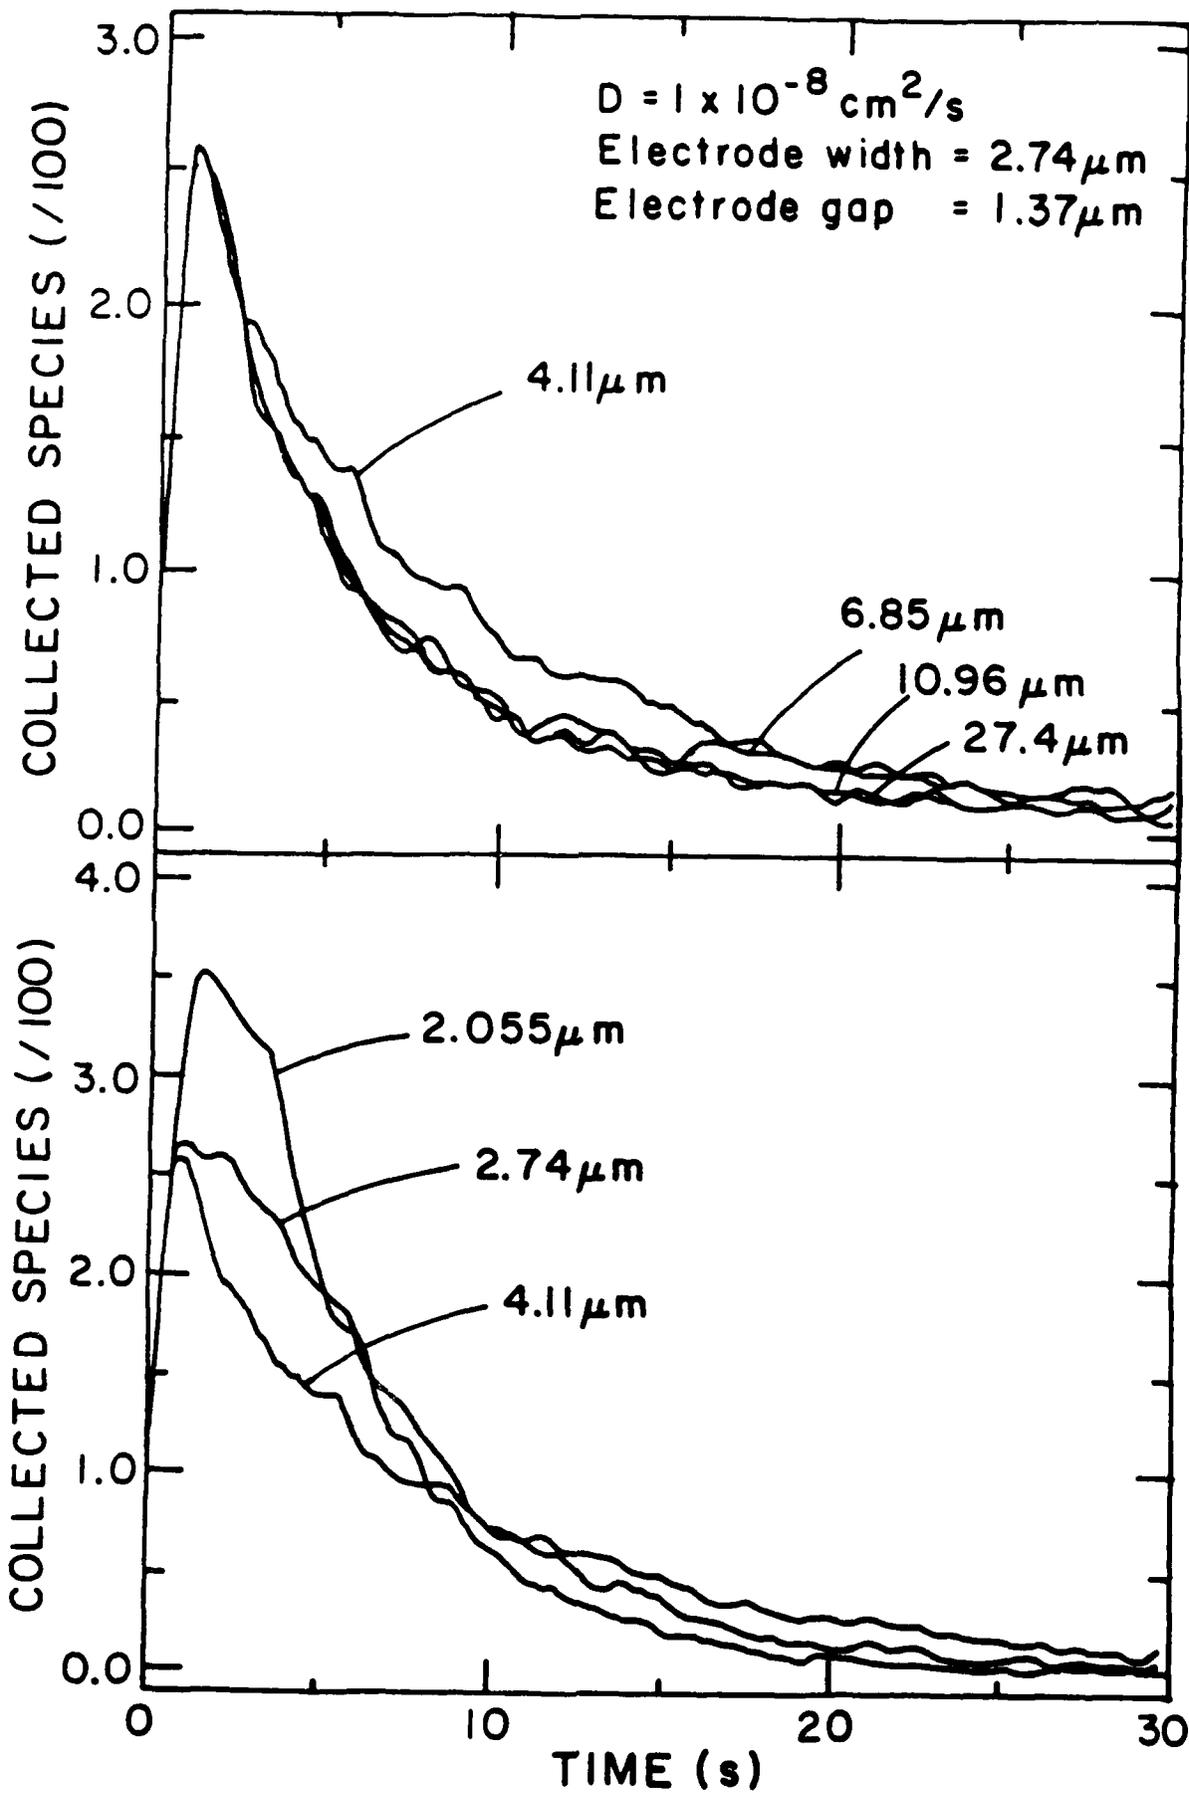

TECHNICAL REPORT DISTRIBUTION LIST - GENERAL

Office of Naval Research (2)  
Chemistry Division, Code 1113  
800 North Quincy Street  
Arlington, Virginia 22217-5000

Commanding Officer (1)  
Naval Weapons Support Center  
Dr. Bernard E. Douda  
Crane, Indiana 47522-5050

Dr. Richard W. Drisko (1)  
Naval Civil Engineering  
Laboratory  
Code L52  
Port Hueneme, CA 93043

David Taylor Research Center (1)  
Dr. Eugene C. Fischer  
Annapolis, MD 21402-5067

Dr. James S. Murday (1)  
Chemistry Division, Code 6100  
Naval Research Laboratory  
Washington, D.C. 20375-5000

Dr. Robert Green, Director (1)  
Chemistry Division, Code 385  
Naval Weapons Center  
China Lake, CA 93555-6001

Chief of Naval Research (1)  
Special Assistant for Marine  
Corps Matters  
Code 00MC  
800 North Quincy Street  
Arlington, VA 22217-5000

Dr. Bernadette Eichinger (1)  
Naval Ship Systems Engineering  
Station  
Code 053  
Philadelphia Naval Base  
Philadelphia, PA 19112

Dr. Sachio Yamamoto (1)  
Naval Ocean Systems Center  
Code 52  
San Diego, CA 92152-5000

Dr. Harold H. Singerman (1)  
David Taylor Research Center  
Code 283  
Annapolis, MD 21402-5067

ENCLOSURE(2)