

2

AD-A234 040

AD

TECHNICAL REPORT ARCCB-TR-91010

**MATERIALS EXAMINATION OF THE PALMARIA  
155-MM GUN TUBE - FOREIGN SCIENCE AND  
TECHNOLOGY PROJECT 60044**

JOHN J. ATCHINSON

MARCH 1991



**US ARMY ARMAMENT RESEARCH,  
DEVELOPMENT AND ENGINEERING CENTER  
CLOSE COMBAT ARMAMENTS CENTER  
BENÉT LABORATORIES  
WATERVLIET, N.Y. 12189-4050**



APPROVED FOR PUBLIC RELEASE; DISTRIBUTION UNLIMITED

91 4 28 040

#### DISCLAIMER

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

The use of trade name(s) and/or manufacturer(s) does not constitute an official indorsement or approval.

#### DESTRUCTION NOTICE

For classified documents, follow the procedures in DoD 5200.22-M, Industrial Security Manual, Section II-19 or DoD 5200.1-R, Information Security Program Regulation, Chapter IX.

For unclassified, limited documents, destroy by any method that will prevent disclosure of contents or reconstruction of the document.

For unclassified, unlimited documents, destroy when the report is no longer needed. Do not return it to the originator.

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER ARCCB-TR-91010	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) MATERIALS EXAMINATION OF THE PALMARIA 155-MM GUN TUBE - FOREIGN SCIENCE AND TECHNOLOGY PROJECT 60044	5. TYPE OF REPORT & PERIOD COVERED Final	
	6. PERFORMING ORG. REPORT NUMBER	
7. AUTHOR(s) John J. Atchinson	8. CONTRACT OR GRANT NUMBER(s)	
9. PERFORMING ORGANIZATION NAME AND ADDRESS U.S. Army ARDEC Benet Laboratories, SMCAR-CCB-TL Watervliet, NY 12189-4050	10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS AMCMS No. 6657,09.6500.000 PRON No. 1A8AZ8PGNMSC	
11. CONTROLLING OFFICE NAME AND ADDRESS U.S. Army ARDEC Close Combat Armaments Center Picatinny Arsenal, NJ 07806-5000	12. REPORT DATE March 1991	
	13. NUMBER OF PAGES 37	
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)	15. SECURITY CLASS. (of this report) UNCLASSIFIED	
	15a. DECLASSIFICATION/DOWNGRADING SCHEDULE	
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Self-Propelled Howitzers Gun Tubes (Italian) Materials Examination Foreign Science Technology		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The Advanced Engineering Branch, Benet Laboratories, conducted a comprehensive materials examination on two Palmaria 155-mm self-propelled howitzer gun tubes produced at Palmaria, Italy. Both tube forgings were manufactured by Breda Lucine Co., Milan, Italy. The purpose of this examination was to establish the dimensional and metallurgical characteristics of the subject gun tubes. Based on the results of our examination, we conclude that the Italians  (CONT'D ON REVERSE)		

20. ABSTRACT (CONT'D)

(Breda Fucine Co.) have the capability of producing 155-mm gun tubes that meet both dimensional and mechanical property requirements of 155-mm gun tubes manufactured in the U.S. (Watervliet Arsenal).

A-1



UNCLASSIFIED

## TABLE OF CONTENTS

INTRODUCTION .....	1
EXAMINATION PROCEDURE.....	1
RESULTS/DISCUSSION .....	1
Macrophotography and Visual Inspection.....	1
Dimensional Inspection.....	2
Metallurgical Evaluation .....	3
Residual Stress Determination.....	5
CONCLUSION .....	6
RECOMMENDATION .....	7
APPENDIX A.....	34

## LIST OF TABLES

I. BORE STRAIGHTNESS .....	8
II. BORE STRAIGHTNESS .....	9
III. O.D. TIR AND WALL VARIATION MEASUREMENTS.....	10
IV. O.D. TIR AND WALL VARIATION MEASUREMENTS.....	11
V. TENSILE AND CHARPY TESTS .....	12
VI. FRACTURE TOUGHNESS TESTS .....	13

## LIST OF ILLUSTRATIONS

1. Palmaria 155/41 self-propelled howitzer .....	14
2. Palmaria 155-mm self-propelled howitzer gun tube as-received.....	15
3. Tube #3141-221-OTO-291 showing breech end detail and poster ID .....	16
4. Tube #4082-123-OTO-286 showing breech end detail and poster ID .....	17
5. Close-up photograph revealing the ID number stamped on the muzzle end.....	18
6. Close-up photograph revealing the ID number stamped on the muzzle end.....	19
7. Overall view of the Palmaria 155-mm evacuator zone .....	20
8. Close-up view of the plug used to evacuate propellant gases and retain the ball check valve in the Palmaria tube. ....	21
9. U.S. 155-mm M185 bore evacuation system.....	22
10. Close-up view of the breech end and keyway of Palmaria 155-mm gun tube. ....	23
10a. Secondary keyways on the U.S. 155-mm XM284 .....	24

11.	Rifling configuration of the Palmaria tube which is finer than the U.S.155-mm M185 . .	25
12.	Rifling configuration of a U.S. 155-mm M185 .....	26
13.	Length and diameter measurements taken on tube #3141-221-OTO-291.....	27
14.	Length and diameter measurements taken on tube #4082-128-OTO-286.....	28
15.	Location of test discs taken from tube #3141-221-OTO-291 for mechanical property evaluation.....	29
16.	Cutting arrangement of tensile and Charpy test coupons as taken from each disc.....	30
17.	Photomicrograph of an as-polished sample showing stringer-type oxide inclusions present in the Palmaria gun tube material.....	31
18.	Photomicrograph of an etched breech end sample revealing the tempered martensitic microstructure found throughout the Palmaria tube .....	32
19.	Photomicrograph of an etched muzzle end sample revealing a tempered martensitic microstructure.....	32
20.	Photomicrograph illustrating the large grain size obtained in the breech end of the Palmaria 155-mm gun tube .....	33

## INTRODUCTION

The Advanced Engineering Branch, Benet Laboratories, conducted a comprehensive materials examination on two Palmaria 155-mm self-propelled howitzer finish-machined gun tubes (ID #3141-221-OTO-291 and #4082-128-OTO-286). Figure 1 shows the Palmaria gun system as installed in the 155/41 self-propelled howitzer. The purpose of this examination was to establish the dimensional and metallurgical characteristics of the subject gun tubes. Both tubes were manufactured by Breda Fucine Co., Milan, Italy, and procured through the U.S. Army Foreign Science and Technology Center as part of D650 Project No. 60044, "Exploitation of the Palmaria 155-mm Gun Tube (Italy)."

## EXAMINATION PROCEDURE

The following examinations and analyses were performed:

1. Macrophotography and visual inspection (both tubes)
  - \* Bore evacuation system
  - \* Breech end keyway
  - \* Rifle configuration
2. Dimensional inspection (both tubes)
3. Metallurgical evaluation (tube #3141-221-OTO-291)
  - \* Chemical analysis (breech and muzzle ends)
  - \* Mechanical property analysis along the length of tube #3141-221-OTO-291 and sample fracture toughness
  - \* Metallographic examination and grain size determination
4. Residual stress determination (tube #3141-221-OTO-291)

## RESULTS/DISCUSSION

### Macrophotography and Visual Inspection

Both tubes were photographed in detail. This included overall views and close-up photographs of any unique external or internal features observed during our visual inspection.

Figure 2 is an overall view of the subject gun tube as-received. Figures 3 and 4 are overall views of each gun tube, showing breech end detail and poster ID. Close-up photographs revealing the ID No. stamped on the muzzle end of each tube are shown in Figures 5 and 6.

The visual inspection also revealed the following information about the subject gun tube:

\* Bore Evacuation System. - An overall view of the Palmaria 155-mm evacuator zone is shown in Figure 7. This system utilizes four drilled, threaded, and staked plugs which allow propellant gases to exit the bore area. Each plug contains three holes as shown in Figure 8. In addition, the ball check valve which is free-floating and located inside the jet hole is contained through the use of this type plug.

The bore evacuation system for the U.S. 155-mm M185 gun tube is shown in Figure 9. This system consists of ten jet holes and ball check valves which are contained through the use of a valve ring.

\* Breech End Keyway - A close-up view of the breech end detail, which includes the breech keyway of the Palmaria 155-mm gun tube, is shown in Figure 10. Based on the dimensions and location of this keyway, it would appear that the Italians rely on one locking key to locate the breech ring and control torque during firing. However, the U.S. 155-mm cannons utilize a secondary long keyway in addition to the keyway on the breech end, for locking purposes. In fact, the 155-mm M284 employs two secondary, long keys to control torquing as shown in Figure 10a.

\* Rifle Configuration. - During the bore inspection portion of our visual inspection, it was observed that the Palmaria tube exhibited a rifling configuration consisting of 64 lands and grooves. This feature is shown in Figure 11; a comparison photograph of a U.S. 155-mm M185 rifled bore consisting of 48 lands and grooves is shown in Figure 12. The reason for the finer rifling exhibited by the Palmaria tube is unknown.

No other major geometric observations were made during the visual inspection of the Palmaria 155-mm gun tubes.

### **Dimensional Inspection**

A dimensional inspection was performed on both Palmaria 155-mm gun tubes in order to obtain the inside diameter (I.D.) and outside diameter (O.D.) and lengths of various segments (tapered sections). Wall variations and O.D. straightness (Total Indicator Runout (TIR)) measurements were taken every foot over the length of each tube. Bore straightness measurements were taken every two feet over the rifled portion of each tube.

The inspection data and results are given in Figures 13 and 14 and Tables I through IV.

Figures 13 and 14 are tube drawings consisting of length and diameter measurements taken on both gun tubes. Examination of the drawings reveals that no major dimensional (length and diameter measurements) differences exist between the Palmaria 155-mm gun tubes and the U.S.-made 155-mm gun tube.

The results of the bore straightness measurements taken on each Palmaria gun tube and the required bore straightness for U.S. 155-mm gun tubes are given in Tables I and II. The results indicate that the bore straightness for both Palmaria tubes is comparable to U.S. 155-mm gun tubes.

The results of the TIR and wall variation measurements taken on each Palmaria 155-mm gun tube along with the required wall variation for U.S. 155-mm gun tubes are listed in Tables III and IV. Examination of these data indicates that both Palmaria gun tubes meet U.S. 155-mm requirements for wall variations. There is no U.S. requirement for O.D. straightness (TIR). These measurements were taken for informational purposes only.

**Metallurgical Evaluation**

\* Chemical Analysis. - The results of the chemical analysis performed on specimens taken from the breech and muzzle ends of tube #3141-221-OTO-291 and the required chemical composition for a U.S. 155-mm follow:

	Weight %										
	<u>C</u>	<u>Mn</u>	<u>P</u>	<u>S</u>	<u>Si</u>	<u>Cu</u>	<u>Ni</u>	<u>Cr</u>	<u>V</u>	<u>Mo</u>	<u>Al</u>
Breech End	0.30	0.36	0.007	0.005	0.30	0.066	3.3	1.4	0.13	0.48	0.008
Muzzle End	0.30	0.37	0.007	0.006	0.30	0.069	3.4	1.4	0.14	0.49	0.008

Required chemical composition for the U.S. 155-mm M185 gun steel (as per Dwg. #11579755):

C	Mn	Mo	Si	Ti	Al	Cr	Ni	V	Pmax	Smax
0.32/0.36	0.55/0.65	0.45/0.55	0.25*	0.015*	0.01*	0.9/1.1	2.10/2.25	0.09/0.12	0.010	0.008

\* Maximum value

Examination of these data indicates that the Palmaria gun tube material is not a standard grade steel, i.e., SAE 4335 or SAE 4340, but a modified steel containing lesser carbon and higher nickel and chromium content than U.S.

\* Mechanical Property Analysis. - Our mechanical property analysis consisted of sectioning seven, 1-inch thick discs along the length of tube #3141-221-OTO-291. The exact location of each disc taken is shown in Figure 15. Tensile and Charpy test coupons were then cut from each disc, as shown in Figure 16. The number of test specimens per disc was dependent on the wall thickness and taper of the tube. The coupons were subsequently machined into standard size tensile (0.357 inch diameter) and Charpy V-notch specimens as per ASTM Standards E-8 and A-370, respectively. The specimens were then tested (tensile specimens at room temperature and Charpy V-notch specimens at -40 degrees F) by Benet Laboratories in order to determine the yield strength, ultimate tensile strength, percent reduction in area, and impact strength of this material. The results of these tests are given in Table V. Examination of the test data indicates that the material exhibits relatively high impact toughness, which is an important requirement in the mechanical property design and specification of gun tubes. Although some of the specimens tested did not meet the minimum yield strength requirement for U.S. 155-mm gun tubes, the material clearly shows this capability. Employing an adjusted heat-treat procedure (i.e., using a lower tempering temperature after quenching from the austenitizing temperature) would very likely increase the yield strength sufficiently to meet the U.S. requirement while maintaining acceptable levels of toughness and ductility. Further examinations of the average value obtained for all specimens tested indicate that except for a 1 Ksi (average) deficiency in yield strength, the Palmaria 155-mm gun tube meets all U.S. mechanical property requirements for 155-mm gun tubes manufactured in the U.S.

\* Fracture Toughness. - Three 1.5-inch thick discs were sectioned from tube #3141-221-OTO-291 as shown in Figure 15. After residual stress tests were completed, two arc (C)-shaped fracture toughness specimens were machined as per ASTM Standard E-399-83 from discs #1 and #2. The results of the fracture toughness tests performed on all four specimens are given in Table VI.

Although these measurements are not valid plane-strain fracture toughness ( $K_{Ic}$ ) values in strict accordance with ASTM Standard E-399, the standard for fracture toughness testing, our experience with modern gun tube materials allows us to conclude that the material tested is, from a fracture mechanics viewpoint, comparable in fracture toughness to modern U.S. made gun steels.

\* Metallographic Examination and Grain Size Determination. - Metallographic examination of selected as-polished samples revealed the presence of discontinuous stringer-type oxide inclusions (Figure 17) in this material. Overall, the inclusion content (size, composition, and distribution) appeared comparable to that of U.S.-made 155-mm gun steel. The microstructure found throughout the entire length of the gun tube was a uniformly tempered martensite, as shown in

Figures 18 and 19. This microstructure is desirable over other types of microstructures due to its combination of strength and toughness.

Grain size measurements ranged from 4.1 in the breech end to 4.4 in the muzzle end of the Palmaria tube. The typical grain size for a U.S. 155-mm determined as per ASTM Standard E-112, ranges from 8.1 (breech) to 8.5 (muzzle). As ASTM grain size number decreases, the actual diameter of grains increases. Therefore, the Palmaria gun tube material actually has a larger grain size or grain diameter. This grain size is illustrated in Figure 20. Although larger grain size is frequently associated with low toughness, this material did not exhibit any deficiency in Charpy impact energy. For a given chemical composition, grain size is a function of austenitization temperature and time at temperature. Therefore, we may conclude that the Italians used either a higher austenitizing temperature, a longer time at temperature, or a combination of the two to attain this relatively large grain size.

### **Residual Stress Determination**

Three 1.5-inch thick discs were sectioned from tube ID #3141-221-OTO-291 as shown in Figure 15. These discs were analyzed to determine the extent of autofrettage residual stresses contained in the gun tube. Two types of tests were utilized in measuring the amount of residual stress present. First, the splitting method was used on discs #1 through #3, followed by the hole drilling method conducted on discs #2 and #3. (See Appendix A for test procedures and graphic results.) The results of the tests are as follows:

#### **Splitting Method**

Disc #	% overstrain
1 (Breech end)	50%
2 (Midpoint)	35%
3 (Muzzle end)	0%

#### **Hole Drilling Method**

Disc #	% overstrain
2 (Midpoint)	35%
3 (Muzzle end)	NA

Gun tubes manufactured in the U.S. are typically autofrettaged on the order of 100 percent overstrain. However, the amount of overstrain measured in the Palmaria tube is considered sufficient for this application and is typical of gun tubes manufactured in Europe.

## CONCLUSION

Based on the results of this examination, we may conclude that the dimensional and metallurgical qualities of the Palmaria tubes are comparable to 155-mm gun tubes manufactured in the U.S. Although the rifling configuration, bore evacuation system, and the breech keyway design vary, the tubes are physically comparable to U.S. designed gun tubes.

Examination of the inspection data reveals that the Palmaria tubes exhibit excellent bore straightness and minimal wall variation. Our metallurgical examination revealed that the chemical composition of the Palmaria gun material was likely selected due to its high impact toughness capability. While this composition is very close to the U.S. 155-mm gun material, the elemental differences (increased nickel, increased chromium, and decreased carbon contents) in the Palmaria gun tube material give it a higher impact toughness capability than the U.S. material, assuming all other metallurgical factors are equal. The relatively large grain size present in the Palmaria material indicates that it was heat treated using either (1) a very high austenitizing temperature, (2) a very long austenitizing time at temperature, or (3) a combination of the first two possibilities. The fact that this large-grained material (ASTM grain size numbers 4.1 and 4.2) still essentially meets U.S. 155-mm mechanical property requirements, supports our conclusion that this material has both high hardenability and high impact toughness capability at the 160 Ksi yield strength level. The toughness could be increased even further if the material were heat treated to a smaller grain size range, for example, 8.1 to 8.5. The inclusion morphology and content of the Palmaria material was comparable to that of high quality gun steel type alloys. The microstructure (tempered martensite) of this material is also typically found in properly heat-treated low alloy steel. The low weight and percentage of sulphur present in the Palmaria material suggests that this material was subjected to a secondary melting operation. The metallurgical results indicate that the chemical composition of the Palmaria gun tube material is a modified steel containing lesser carbon and higher nickel and chromium content than U.S. gun steel. Mechanical testing (tensile, Charpy impact, fracture toughness) demonstrated that the Palmaria gun tube material exhibited high impact toughness, sufficient strength, and fracture toughness characteristics comparable to gun steel produced in the U.S.

The grain size in the breech and muzzle ends of the Palmaria gun tube was nearly 50 percent larger than that of U.S. 155-mm gun tubes. The reason for such a large variance is most likely due to differences in both chemical composition and material processing methods.

Any comparisons made during this examination were used to show differences in geometry or design only. Without a larger sample size, statistical comparisons are not possible.

## **RECOMMENDATION**

In order to metallurgically exploit the Palmaria 155-mm self-propelled howitzer gun tube material to the maximum extent possible, it is recommended that laboratory fatigue testing be conducted on the remaining Palmaria gun tube material. The data generated from this type test would enable us to predict the expected fatigue life for Palmaria 155-mm self-propelled howitzer gun tube.

**TABLE I. BORE STRAIGHTNESS  
TUBE #3141-221-OTO-291**

FEET FROM ORIGIN OF RIFLING	TRUE BEND	SET UP ON TRUE VERTICAL	SET UP 90° FROM TRUE VERTICAL
		POSITION 3	POSITION 9
2	0.016 <sup>1</sup>	0.006	0.015
4	0.014 <sup>8</sup>	0.009	0.029
6	0.013 <sup>6</sup>	0.013	0.042
8	0.011 <sup>4</sup>	0.016	0.053
10	0.003 <sup>6</sup>	0.013	0.051
12	0.014 <sup>8</sup>	0.010	0.037
14	0.015 <sup>5</sup>	0.006	0.007
16	0.016 <sup>1</sup>		
ME	0.007		

**BORE STRAIGHTNESS RESULTS:**

Maximum Amount Measured in Any 24-Inch Length - 0.016  
 Total Cumulative Measured - 0.055

**BORE STRAIGHTNESS REQUIREMENTS FOR U.S. 155-MM GUN TUBE PER DWG. #11578388:**

The bend (excluding droop) in the tube/rifled portion shall not exceed 0.020 inch in any 24 inches nor accumulate to more than 0.060 inch.

ID No. 3141-221/291  
 Inspector's Initials RGM  
 Date: 9/17/88

**TABLE II. BORE STRAIGHTNESS  
TUBE #4082-128-OTO-286**

FEET FROM ORIGIN OF RIFLING	TRUE BEND	SET UP ON TRUE VERTICAL	SET UP 90° FROM TRUE VERTICAL	
		POSITION 9	POSITION 3	POSITION 9
2	0.004	0.004	0.002	
4	0.004	0.008	0.002	
6	0.003	0.011	0.002	
8	0.005	0.015		
10	0.004 <sup>2</sup>	0.018		0.003
12	0.005	0.014		
14	0.004	0.010	0.001	
16	0.007	0.003	0.001	
ME	0.003			

**BORE STRAIGHTNESS RESULTS:**

Maximum Amount Measured in Any 24-Inch Length - 0.005  
 Total Cumulative Measured - 0.018

**BORE STRAIGHTNESS REQUIREMENTS FOR U.S. 155-MM GUN TUBE PER DWG. #11578388:**

The bend (excluding droop) in the tube/rifled portion shall not exceed 0.020 inch in any 24-inches nor accumulate to more than 0.060 inch.

ID No. 4082-128/286  
 Inspector's Initials TEC  
 Date: 9/17/88

**TABLE III. O.D. TIR AND WALL VARIATION MEASUREMENTS  
TUBE #3141-221-OTO-291**

<b>FEET</b>	<b>TIR</b>	<b>WALL VARIATION</b>	<b>12</b>	<b>3</b>	<b>6</b>	<b>9</b>
1	0 ROLLER	0.009	2.691	0.682	0.688	0.689
2	0.006	0.015	2.733	0.723	0.721	0.736
3	0.019	0.015	2.750	0.742	0.749	0.757
4	0.025	0.014	2.848	0.842	0.842	0.856
5	0.038	0.022	2.843	0.833	0.852	0.855
6	0.046	0.017	2.845	0.834	0.851	0.850
7	0.055	0.025	2.844	0.834	0.852	0.859
8	0.068	0.020	2.330	0.324	0.349	0.354
9	0.070	0.023	2.335	0.329	0.346	0.352
10	0.075	0.022	2.338	0.329	0.350	0.351
11	0.080	0.022	2.337	0.322	0.339	0.354
12	0.090	0.025	2.047	0.038	0.057	0.063
13	0.080	0.014	2.044	0.044	0.053	0.058
14	0.090	0.008	2.045	0.048	0.052	0.053
15	0.075	0.005	1.729	0.728	0.728	0.724
16	0.060	0.011	1.727	0.733	0.730	0.722
17	0.040	0.008	1.747	0.748	0.742	0.740
18	0.025	0.013	1.462	0.470	0.467	0.457
19	0 ROLLER	0.009	1.358	0.363	0.363	0.354
20	0.030	0.006	1.253	0.256	0.253	0.250
21	0.080 ME	0.008	0.756	0.752	0.759	0.760

**WALL VARIATION REQUIREMENTS FOR U.S. 155-MM GUN TUBE PER DWG. #11578388:**

From the breech end to 6.10 inches shall not exceed 0.010 inch and from 6.10 inches to the muzzle end shall not exceed 0.060 inch.

**TABLE IV. O.D. TIR AND WALL VARIATION MEASUREMENTS  
TUBE #4082-128-OTO-286**

FEET	TIR	WALL VARIATION	12	3	6	9
1	0 ROLLER	0.004	2.670	0.669	0.673	0.673
2	0.002	0.007	2.730	0.737	0.737	0.731
3	0.004	0.005	2.744	0.749	0.748	0.748
4	0.007	0.004	2.848	0.251	0.849	0.847
5	0.008	0.011	2.845	0.847	0.849	0.838
6	0.010	0.013	2.835	0.848	0.841	0.843
7	0.013	0.006	2.843	0.846	0.849	0.845
8	0.011	0.016	2.331	0.334	0.347	0.345
9	0.014	0.006	2.337	0.337	0.341	0.343
10	0.015	0.003	2.337	0.338	0.340	0.337
11	0.018	0.005	2.343	0.338	0.343	0.338
12	0.017	0.007	2.051	0.045	0.046	0.052
13	0.018	0.006	2.050	0.048	0.048	0.054
14	0.014	0.012	2.058	0.046	0.052	0.053
15	0.018	0.007	1.731	0.732	0.725	0.730
16	0.015	0.003	1.735	0.734	0.737	0.736
17	0.012	0.005	1.748	0.743	0.745	0.747
18	0.008	0.010	1.453	0.452	0.457	0.462
19	0 ROLLER	0.009	1.347	0.351	0.354	0.345
20	0 ROLLER	0.001	1.249	0.248	0.248	0.248
21	0.005 ME	0.002	0.754	0.752	0.754	0.754

WALL VARIATION REQUIREMENTS FOR U.S. 155-MM GUN TUBE PER DWG. #11578388:

From the breech end to 6.10 inches shall not exceed 0.010 inch and from 6.10 inches to the muzzle end shall not exceed 0.060 inch.

TABLE V. TENSILE AND CHARPY TESTS

ID#	Yield Strength (Ksi)	Ultimate Tensile Strength (Ksi)	% Reduction in Area	Charpy V-Notch (ft-lb)
A1A	162	176	41.0	24.0
A1B	162	176	33.1	20.0
A2A	161	176	37.6	28.5
A2B	161	176	46.4	29.0
B1A	154*	176	52.1	28.5
B1B	163	177	47.0	30.5
B1C	158*	177	47.3	35.0
B2A	151*	175	50.1	30.0
B2B	159*	176	52.5	31.5
B2C	156*	176	50.6	35.0
C1A	160	177	52.9	32.0
C1B	162	177	54.4	35.5
C2A	162	176	54.4	35.0
C2B	178	192	38.5	36.0
D1A	157*	175	51.3	39.5
D1B	154*	175	53.6	38.5
D2A	157*	175	54.6	36.5
D2B	158*	176	51.3	38.0
E1	153*	173	48.6	41.0/37.5
E2	153*	164	54.0	37.5/38.0
F1	158*	175	55.4	33.5
F2	155*	174	52.5	35.0
G1	153*	175	52.5	30.5
G2	156*	175	52.7	35.0
Average Value	159	176	49.4	33.5

\*Specimens which did not meet U.S. mechanical property requirement.

U.S. 155-MM MECHANICAL PROPERTY REQUIREMENTS AS PER DWG. #11579504 and MIL-S-46119:

Yield Strength	% Reduction in Area	Charpy V-Notch
160-180 Ksi	25 min.	15 ft-lb/min.

TABLE VI. FRACTURE TOUGHNESS TESTS

SPECIMEN ID #	(KSI $KQ_{\sqrt{in.}}$ )
1A	157.3
1B	153.5
2A	154.2
2B	148.6

NOTE: The values listed are not valid plain-strain properties.

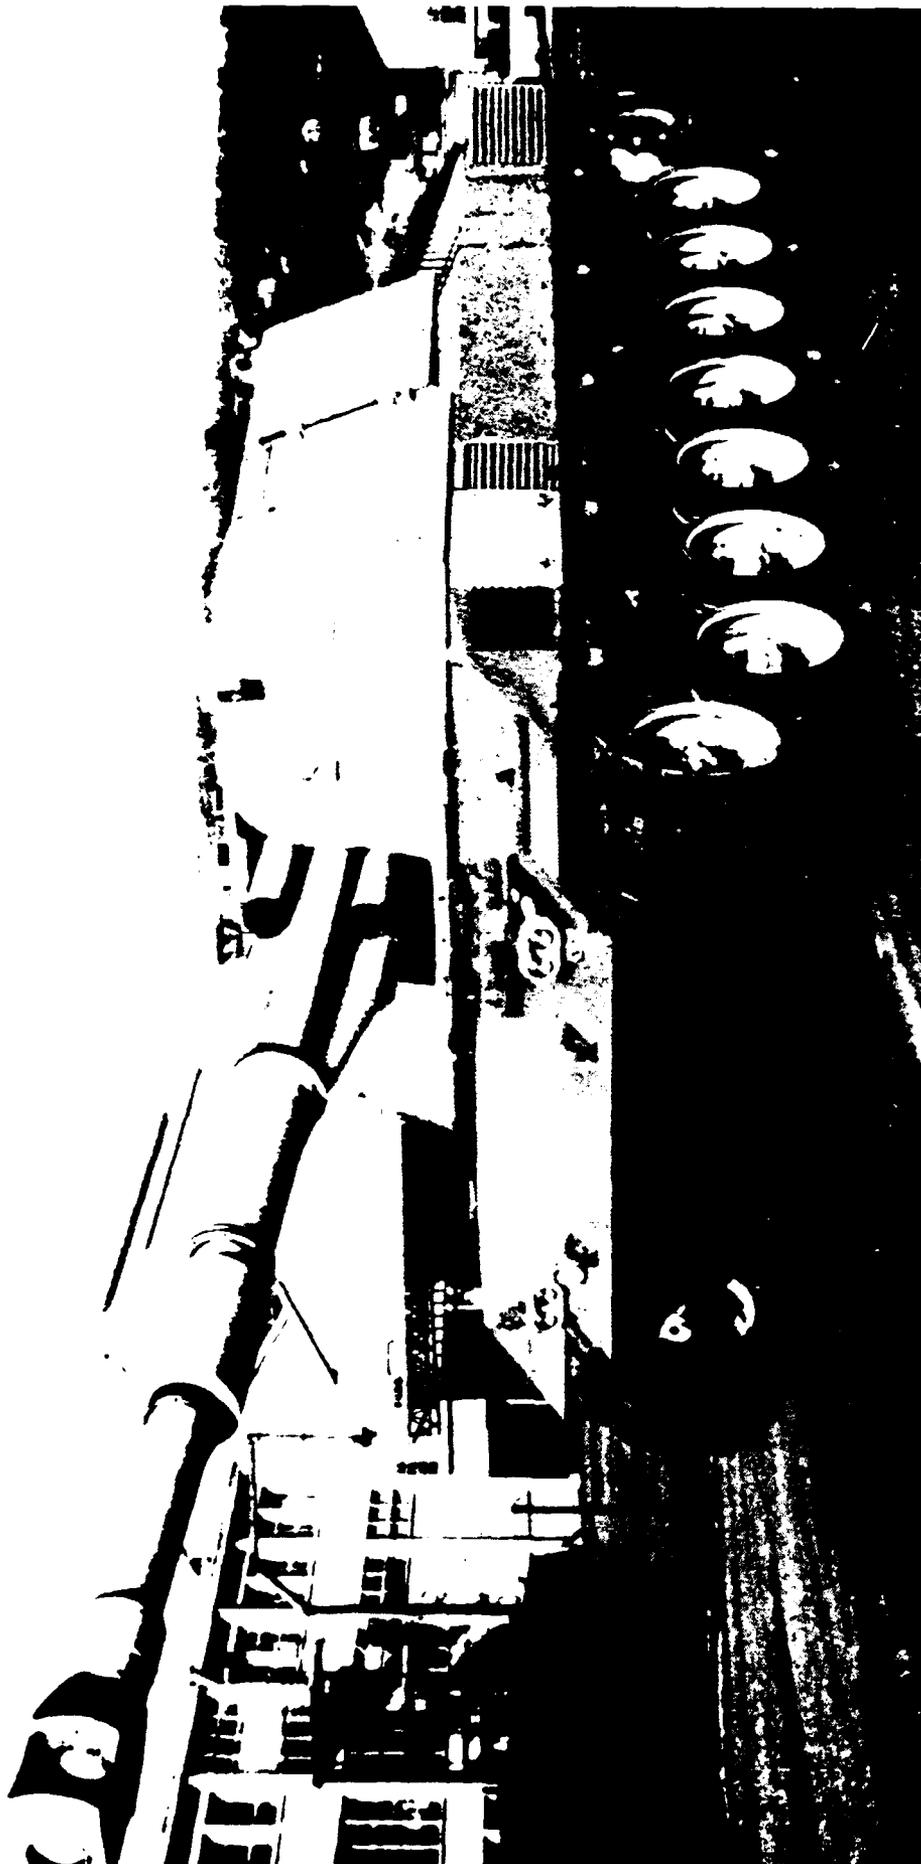


Figure 1. Palmaria 155/41 self-propelled howitzer.



Figure 2. Palmaria 155-mm self-propelled howitzer gun tube as-received.



Figure 3. Tube #3141-221-O1O-291 showing breach end detail and poster ID.

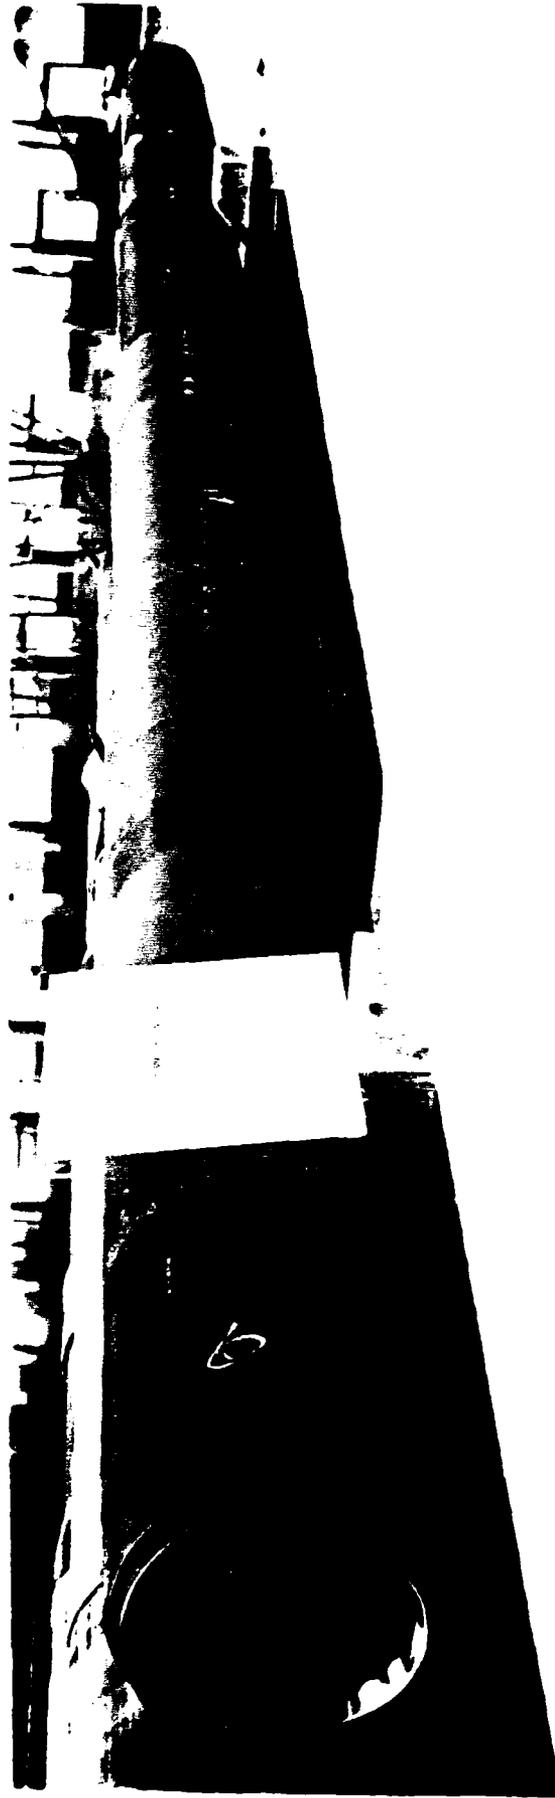


Figure 4. Tube #4082-128-OTO-286 showing breech end detail and poster ID.

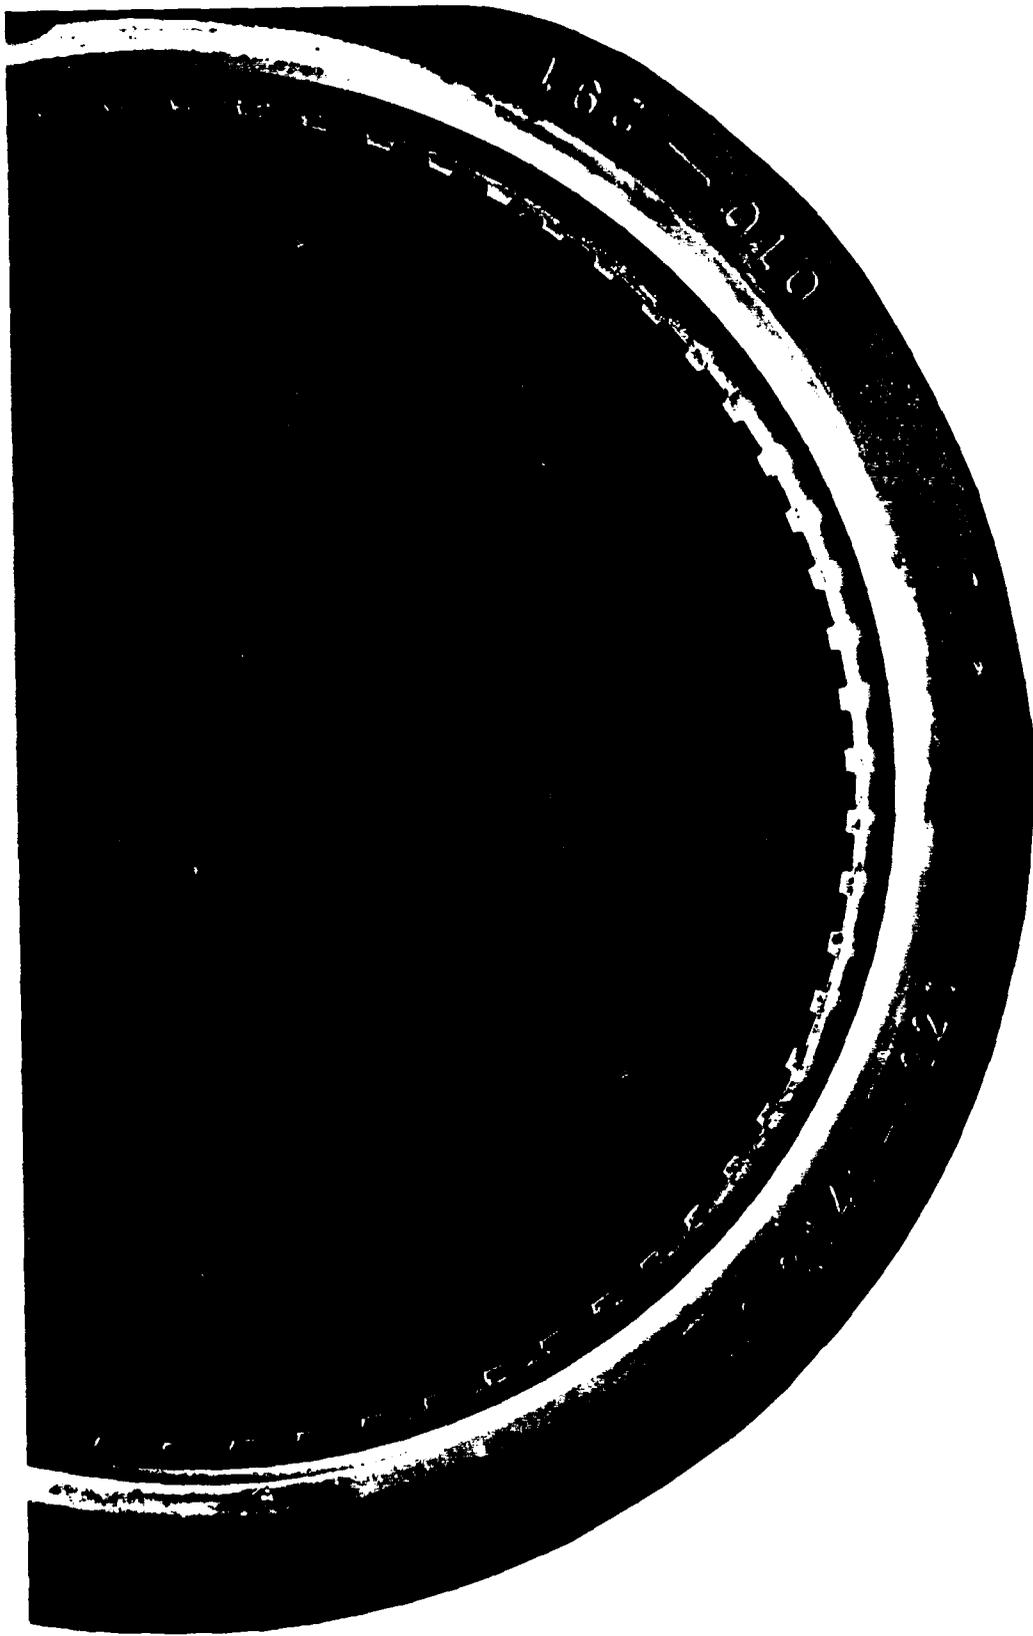


Figure 5. Close-up photograph revealing the ID number stamped on the muzzle end.



Figure 6. Close-up photograph revealing the ID number stamped on the muzzle end.

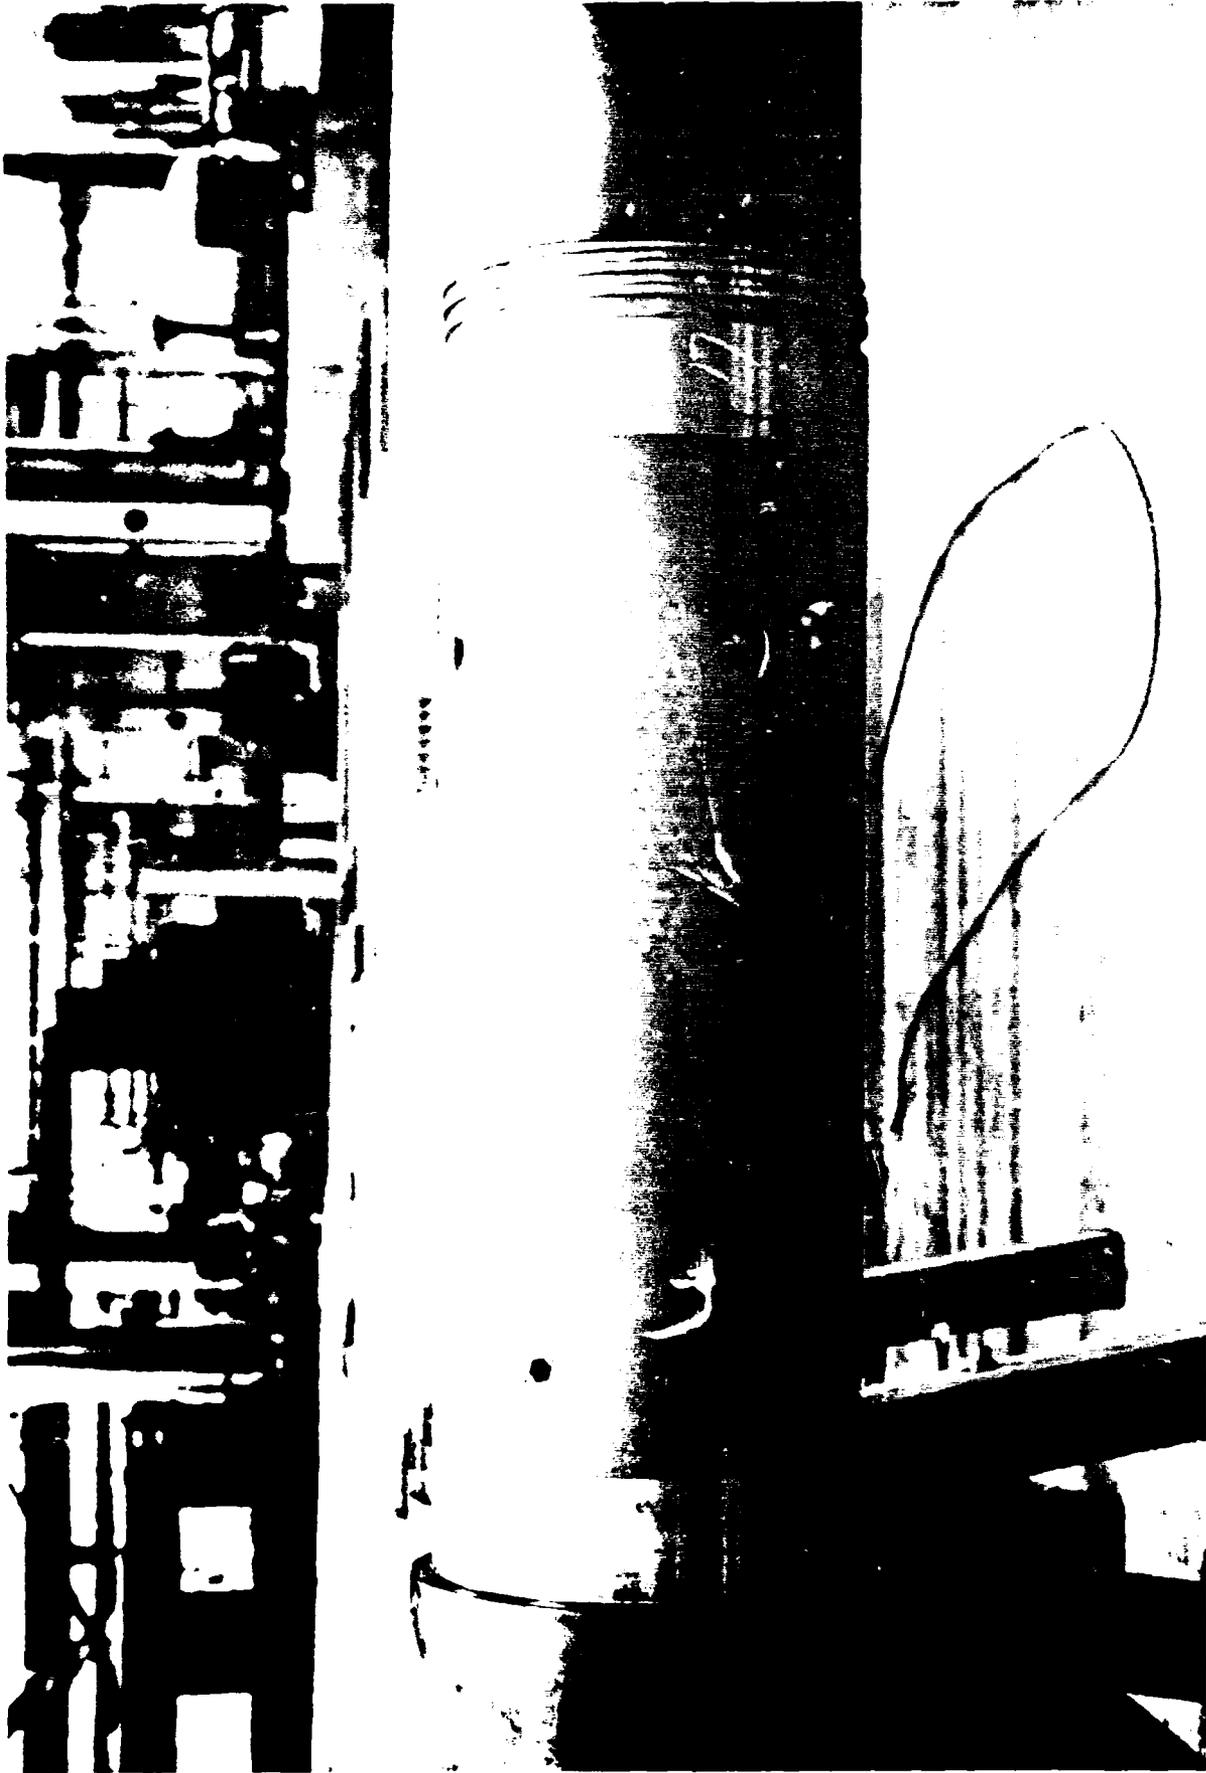


Figure 7. Overall view of the Palmaria 155-mm evacuator zone.

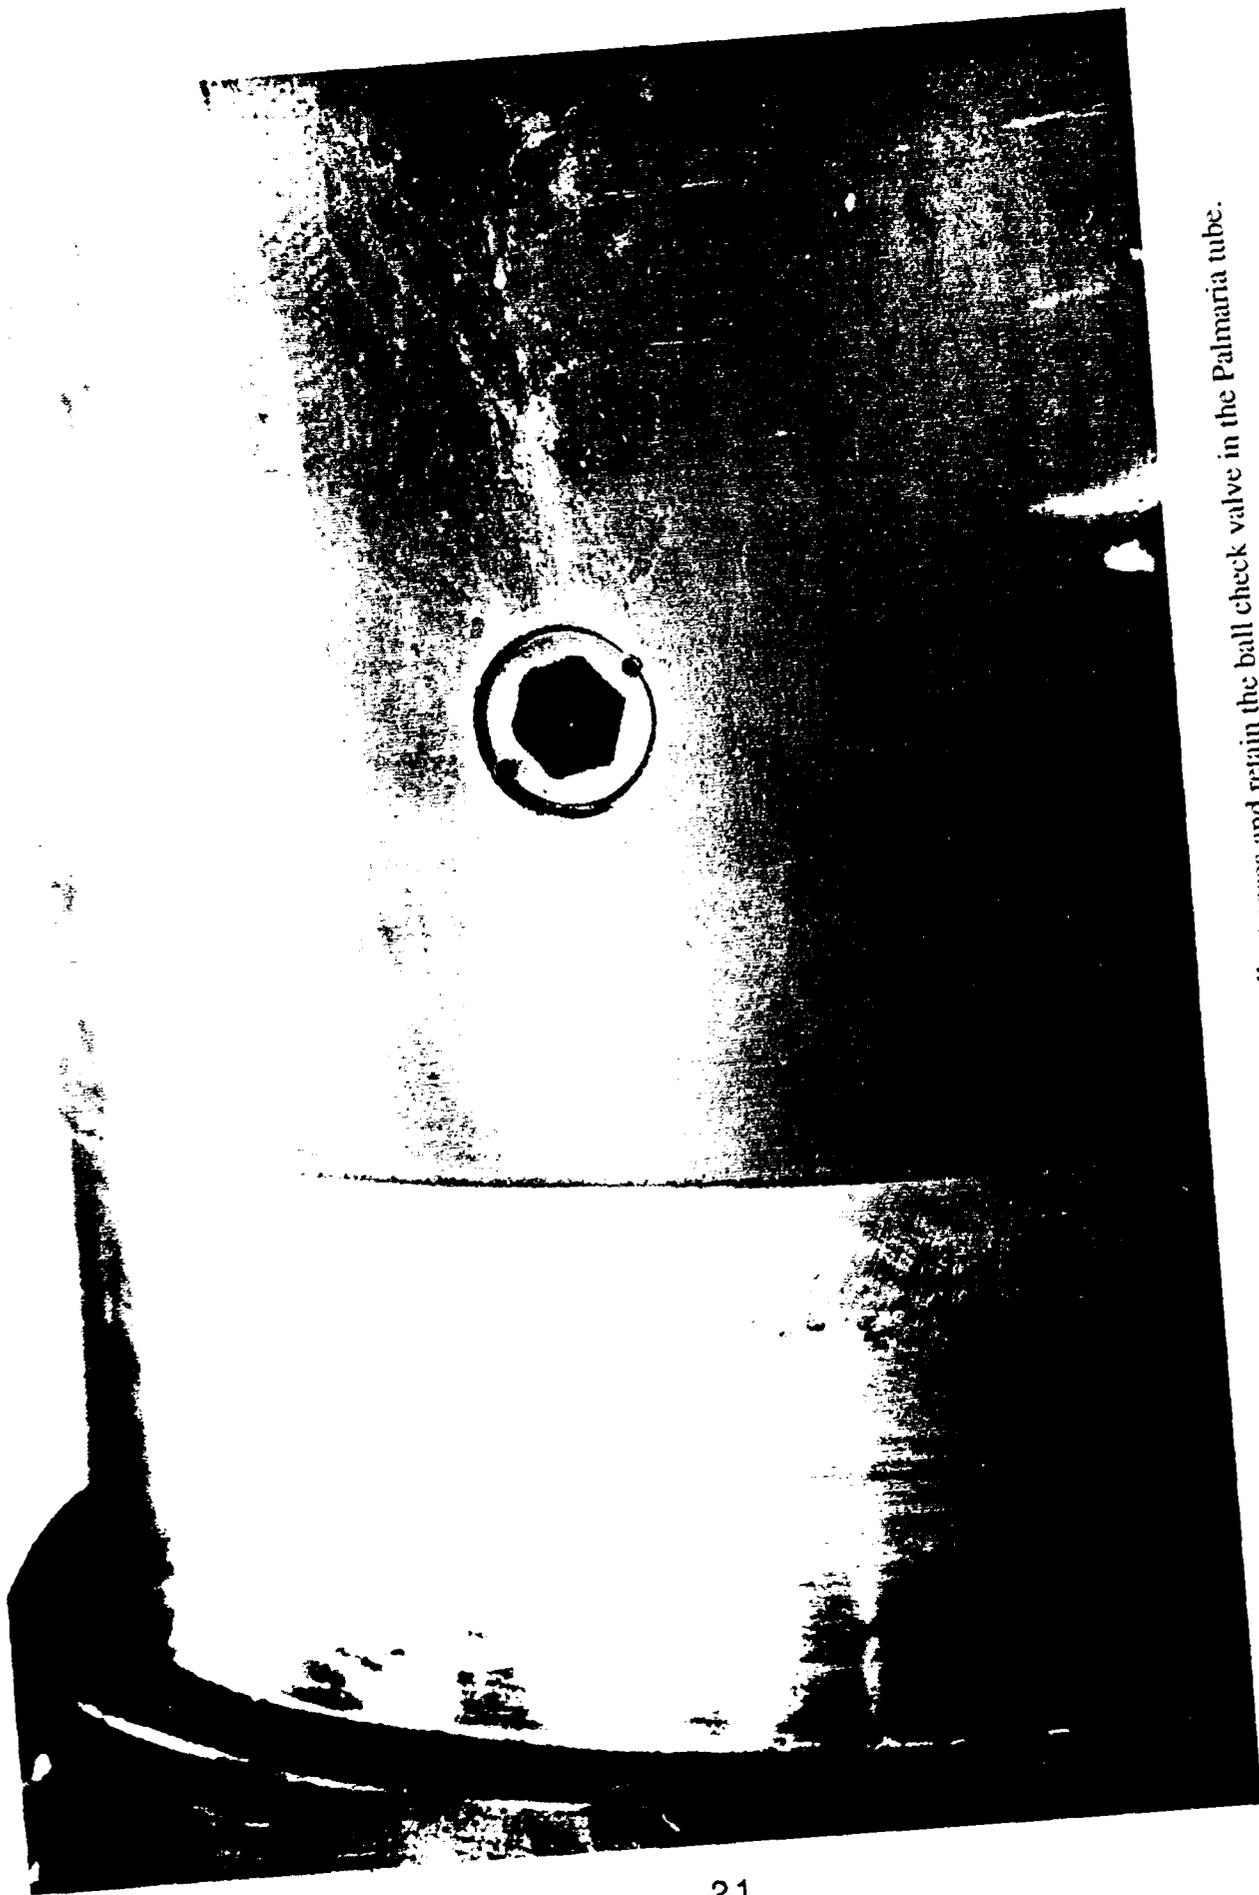


Figure 8. Close-up view of the plug used to evacuate propellant gases and retain the ball check valve in the Palmaria tube.

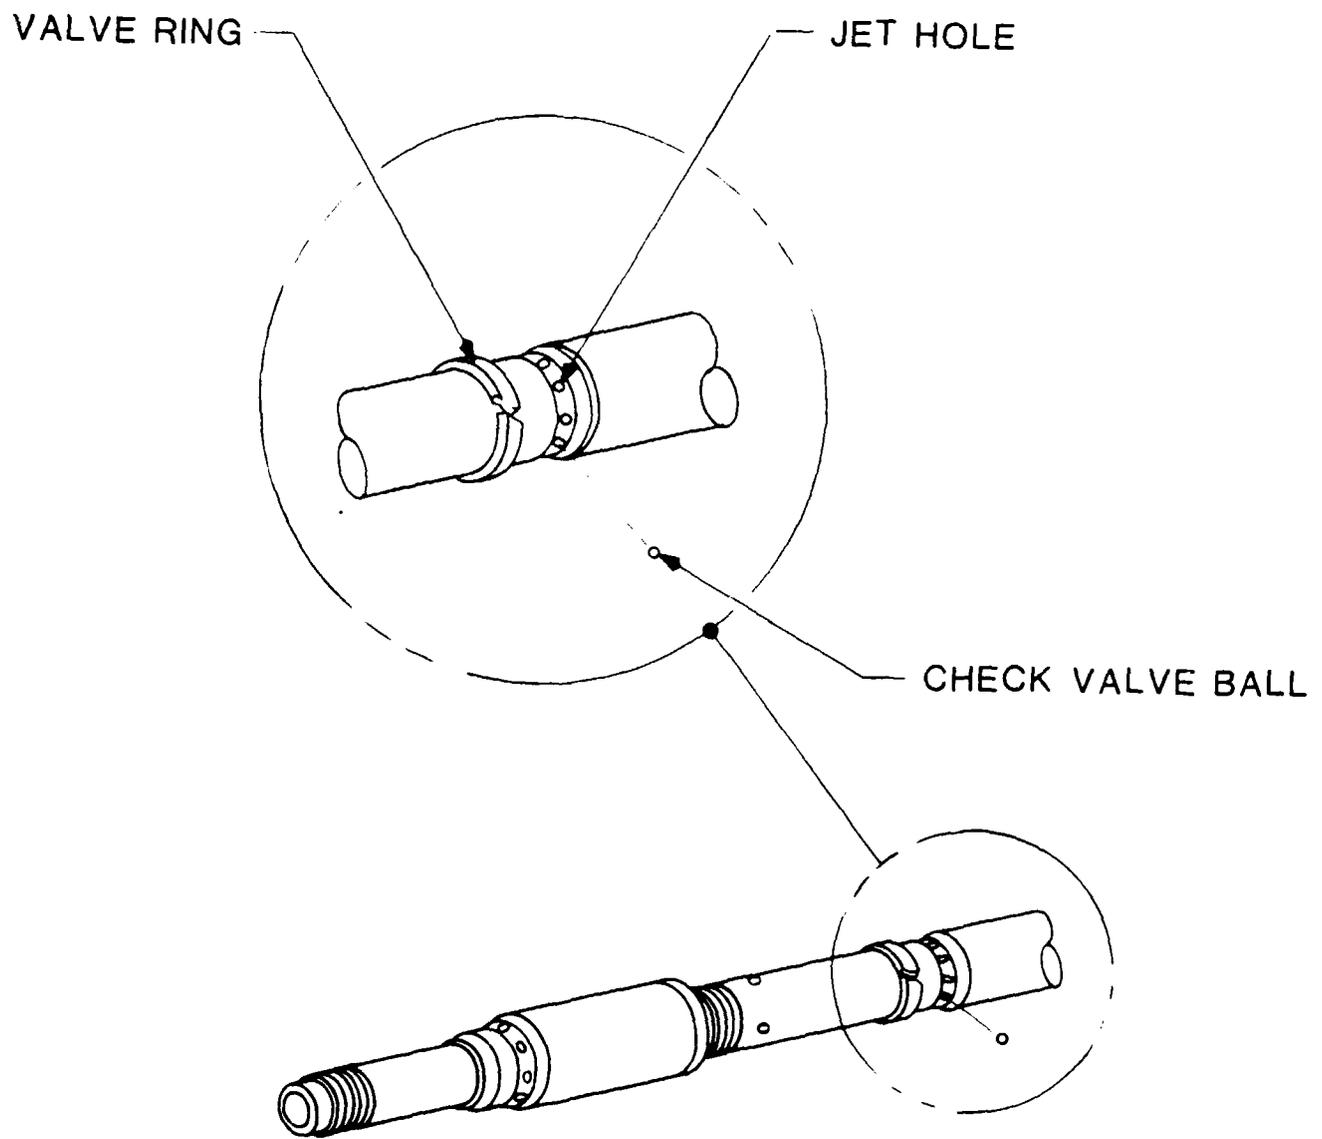


Figure 9. U.S. 155-mm M185 bore evacuation system.

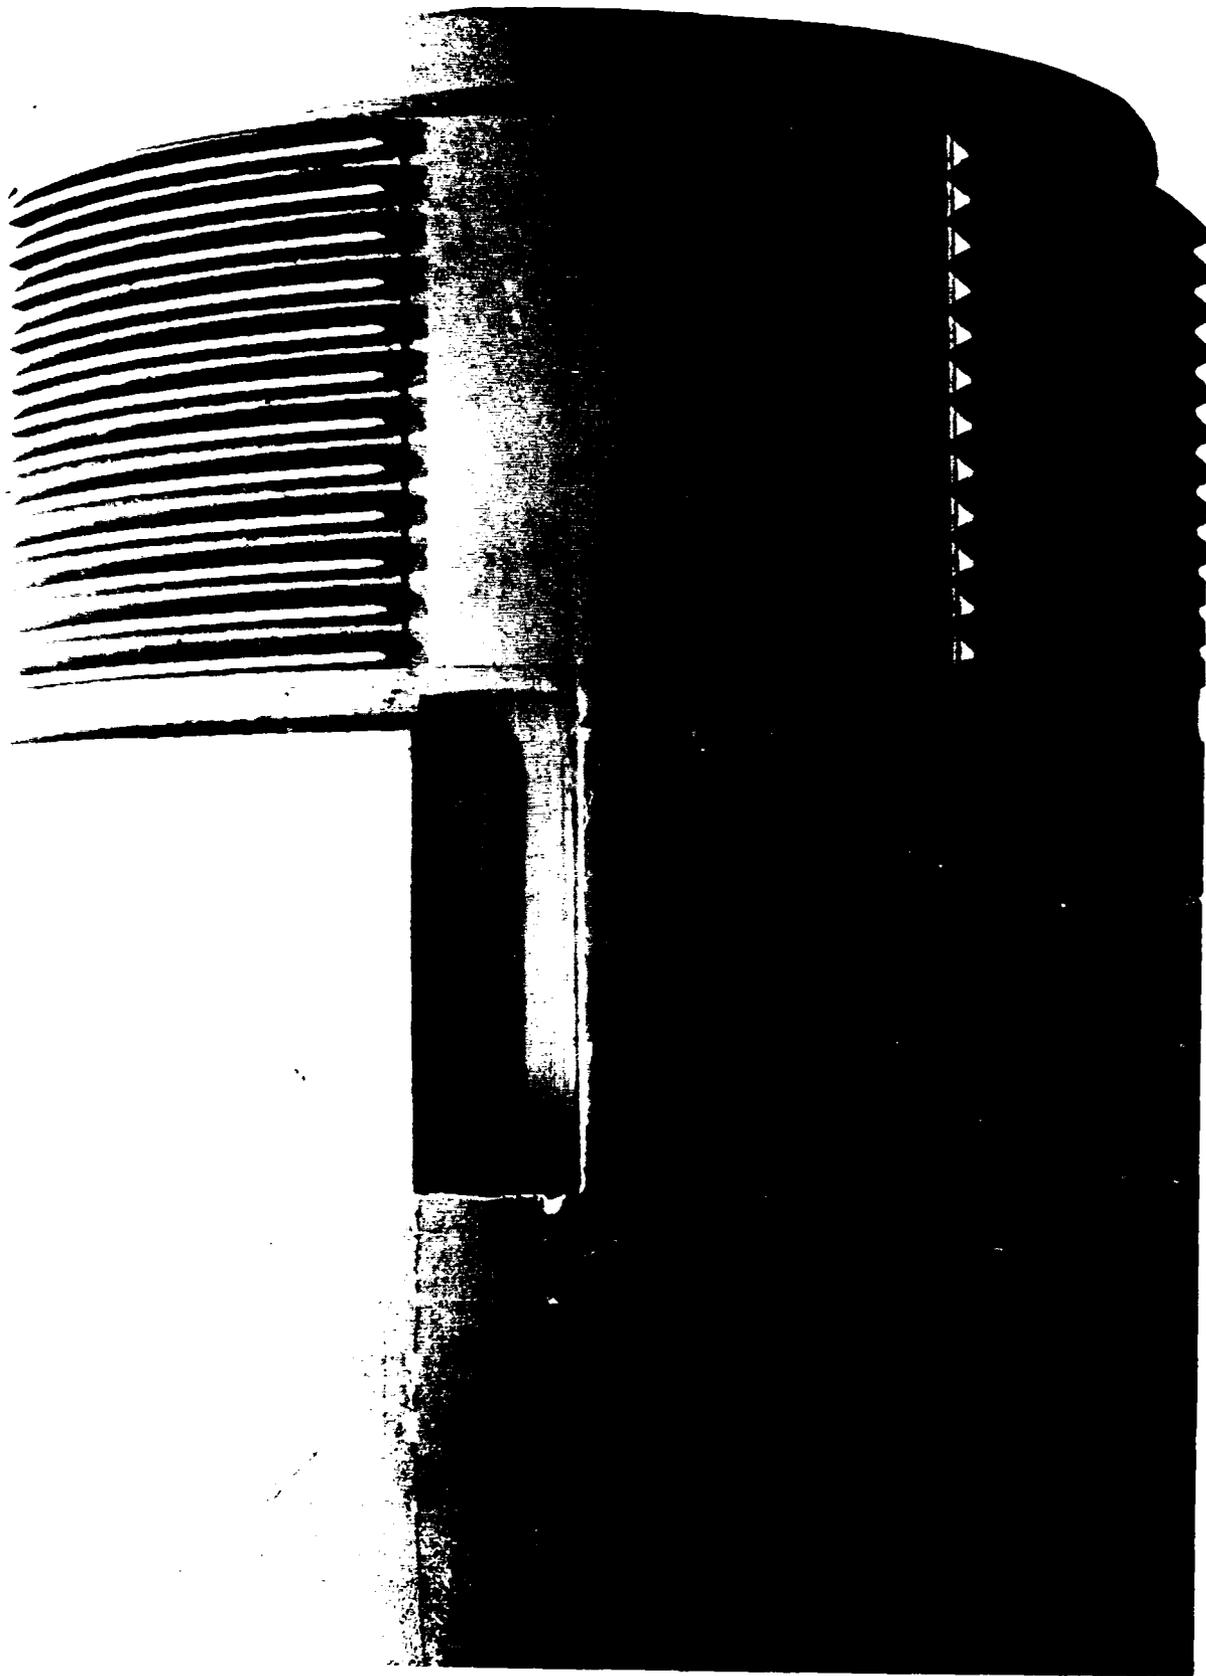


Figure 10. Close-up view of the breech end and keyway of Palmaria 155-mm gun tube.

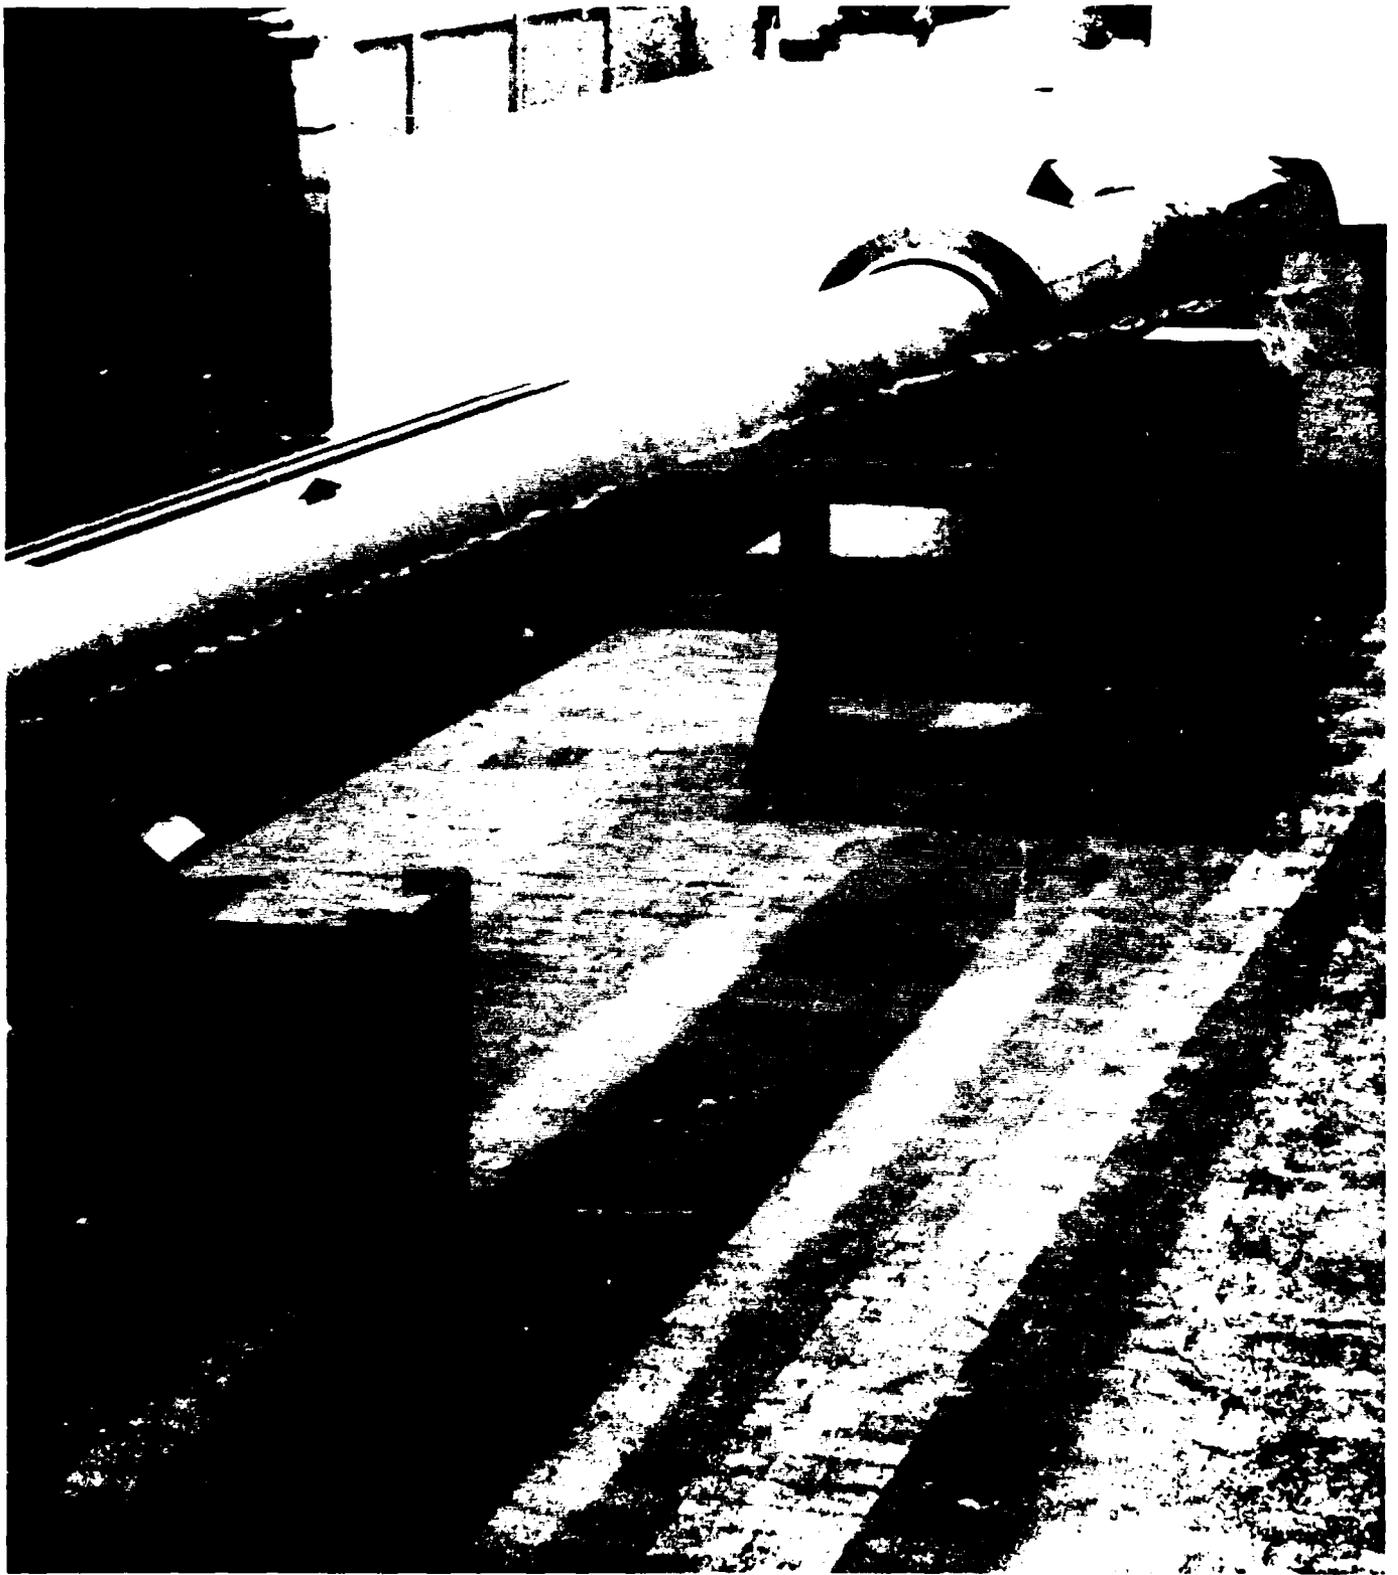


Figure 10a. Secondary keyways on the U.S. 155-mm XM284.

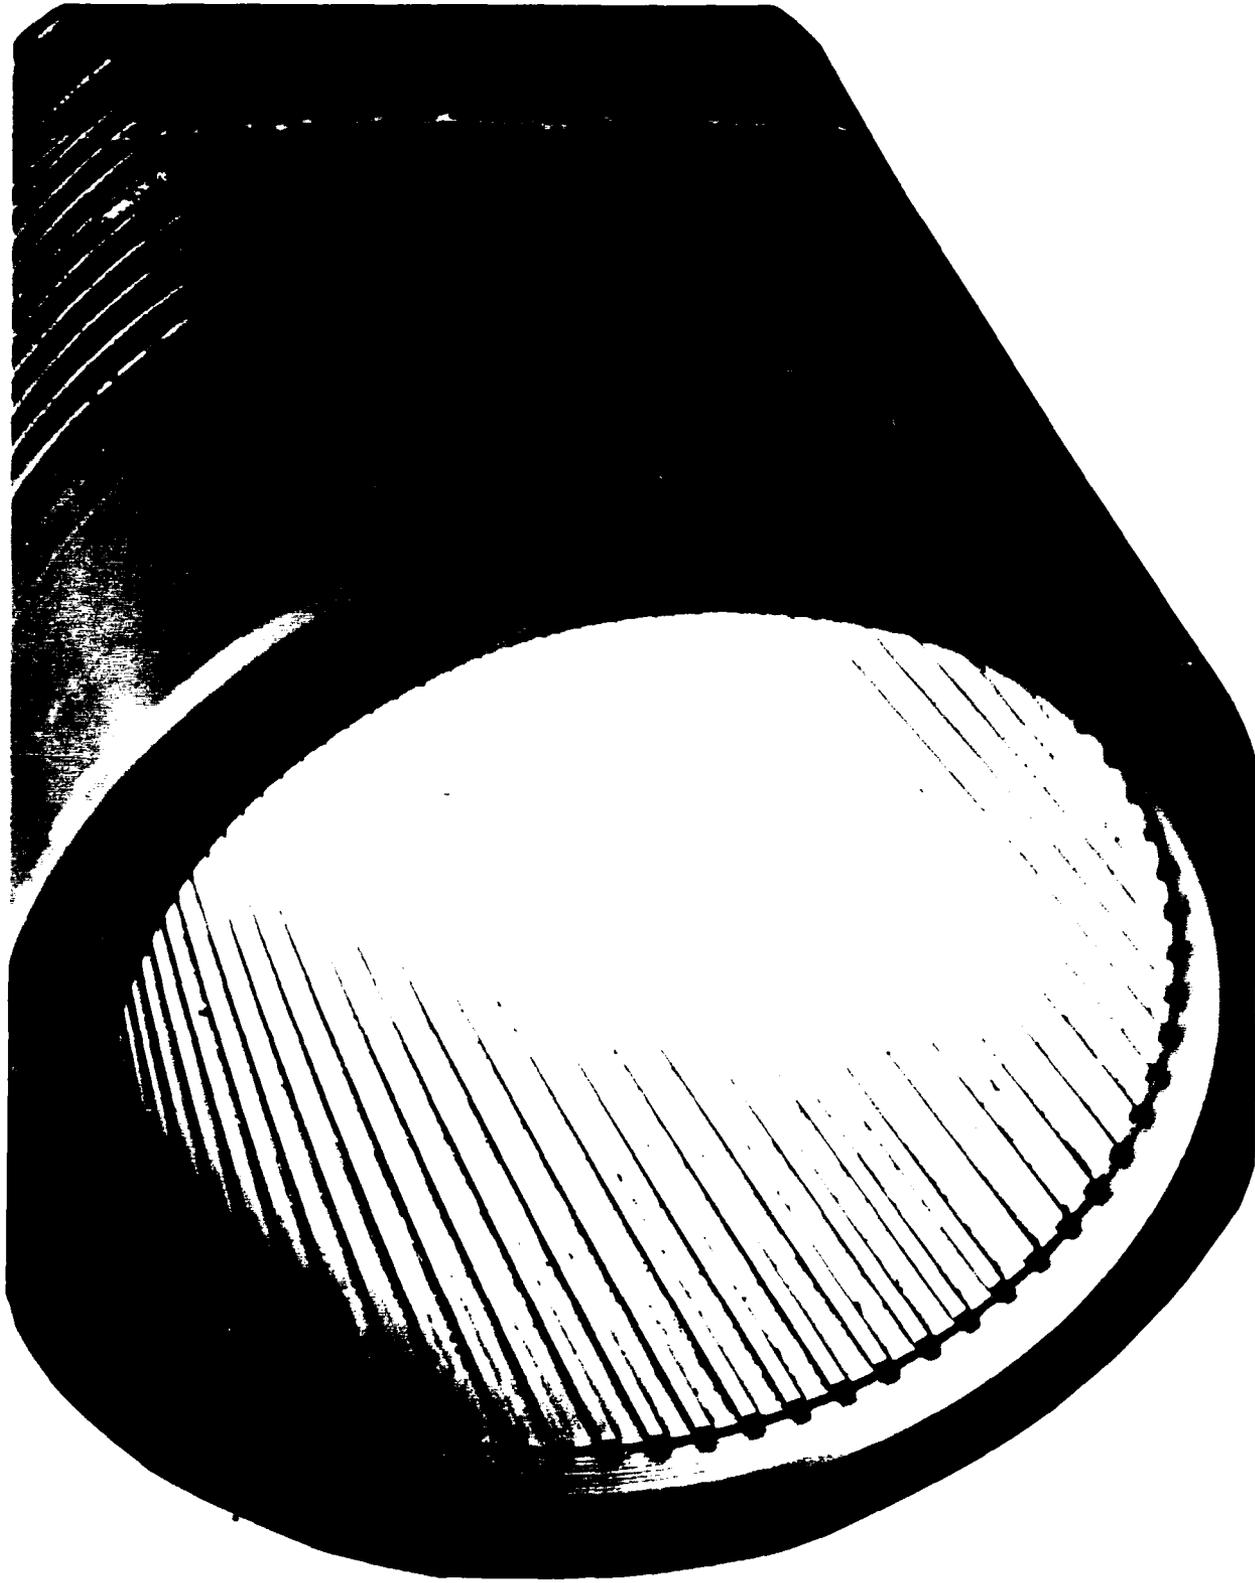


Figure 11. Rifling configuration of the Palmaria tube which is finer than the U.S. 155-mm M185.



Figure 12. Rifling configuration of a U.S. 155-mm M185.

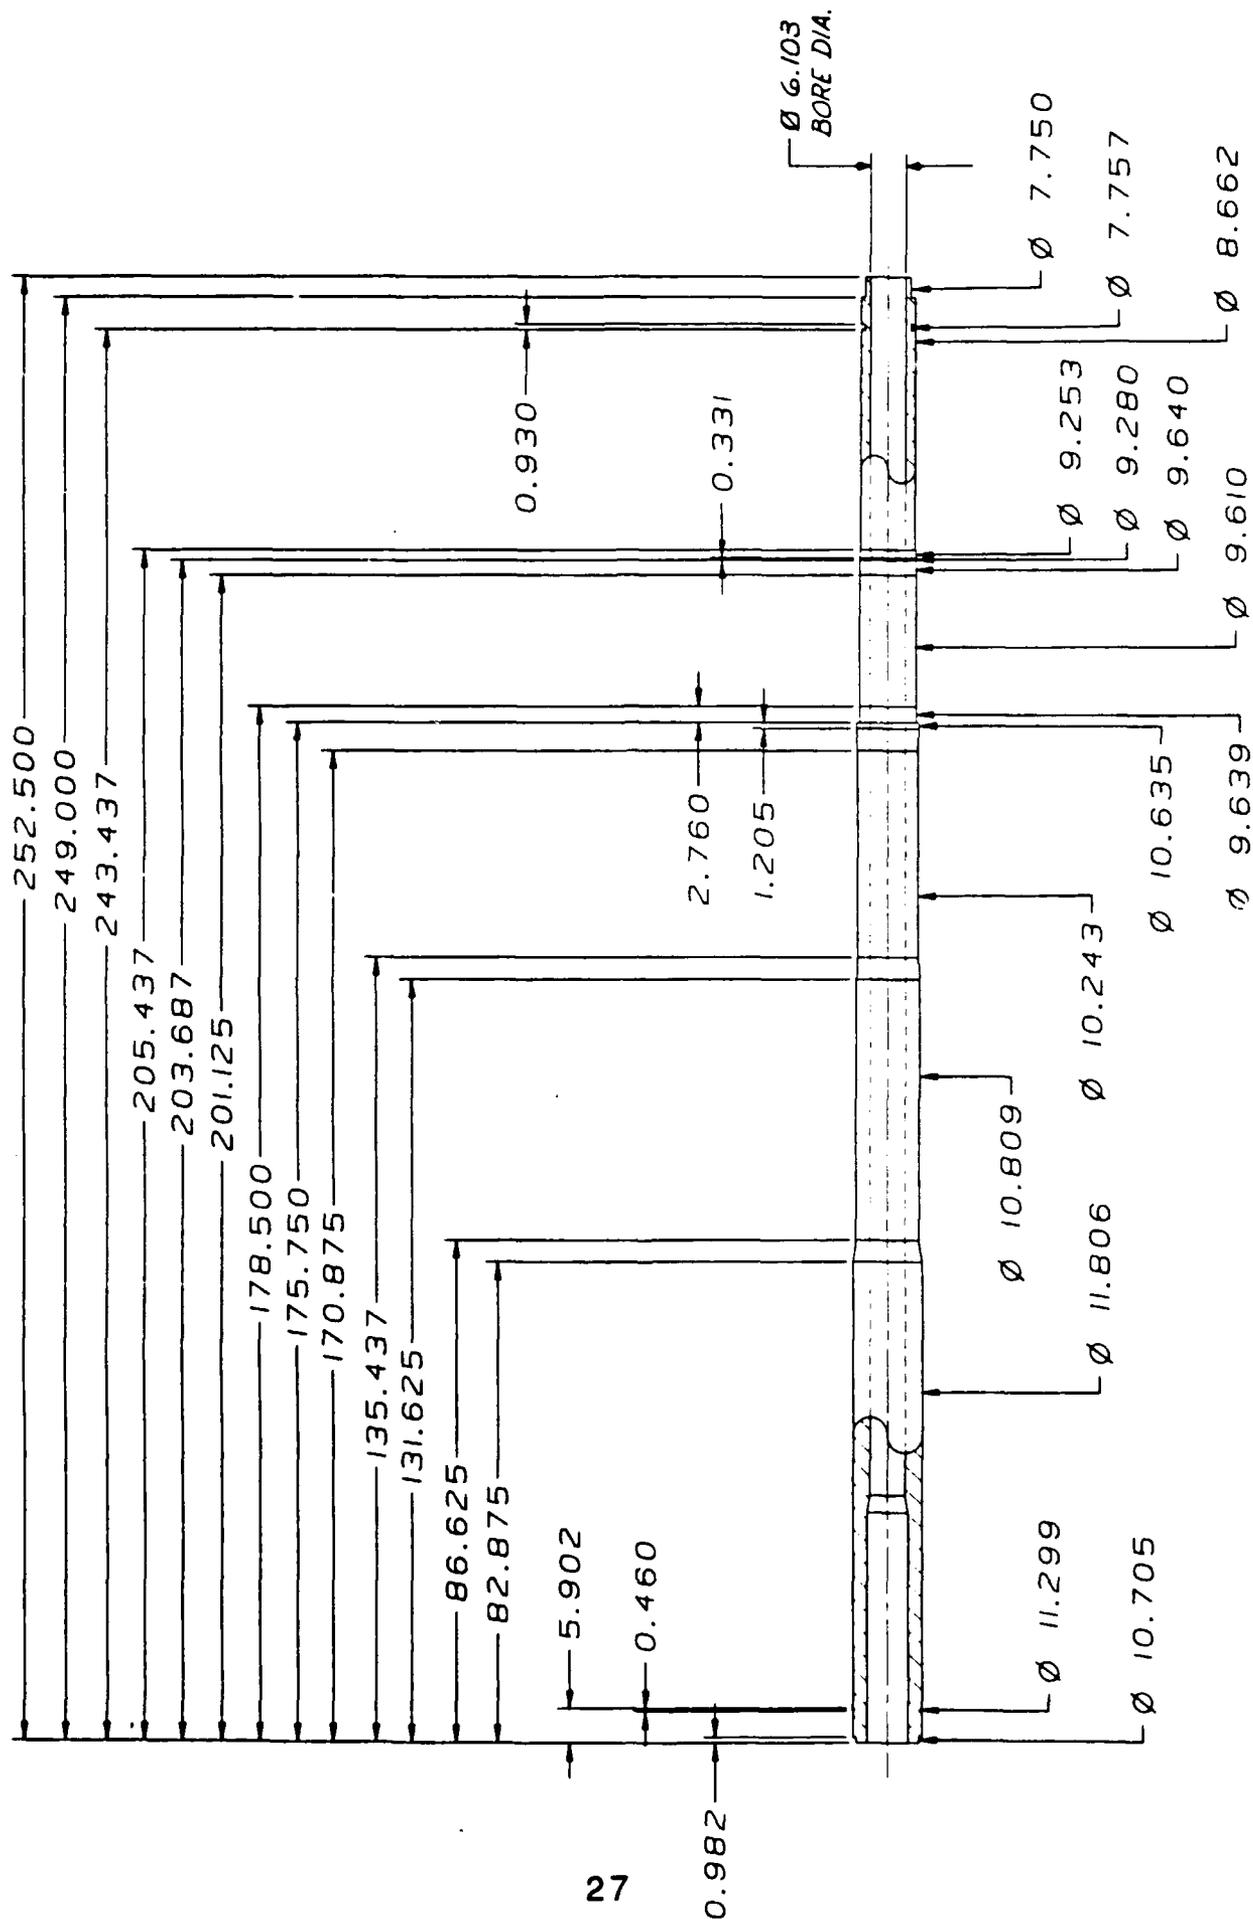


Figure 13. Length and diameter measurements taken on tube #3141-221-OTO-291.


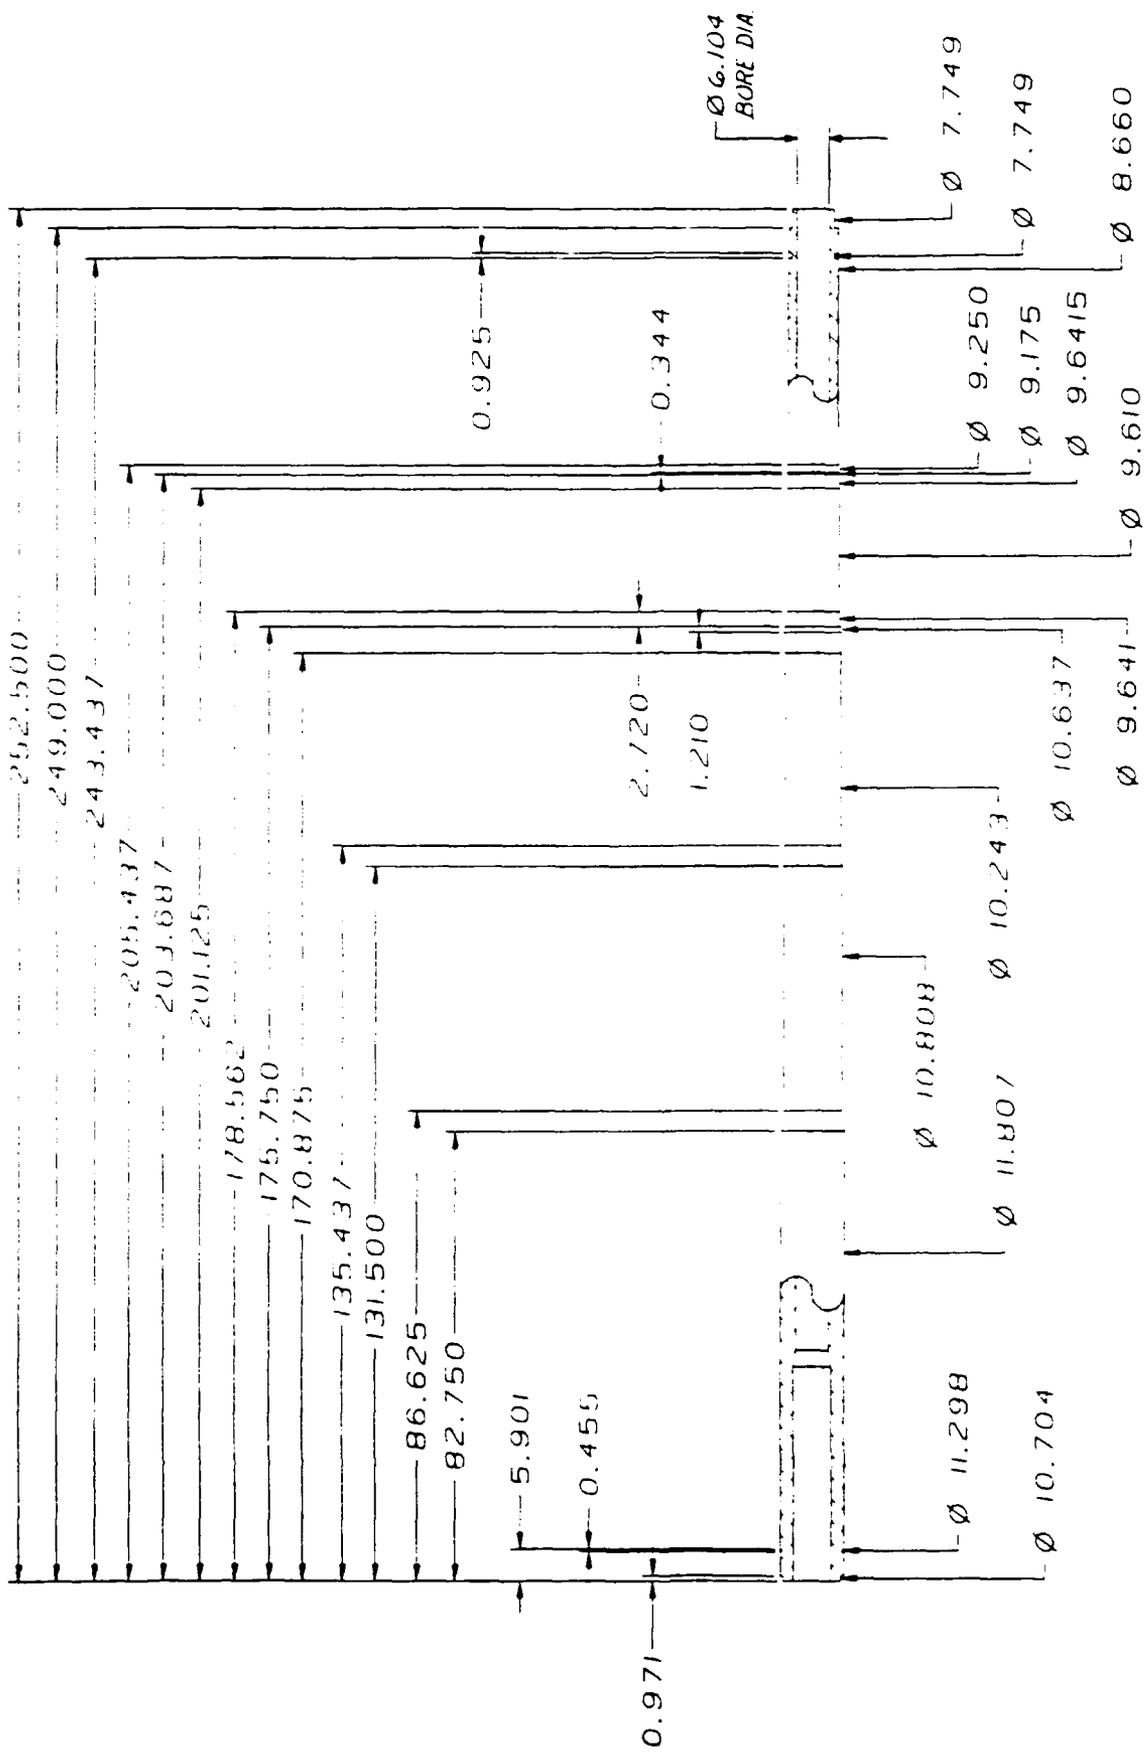


Figure 14. Length and diameter measurements taken on tube #4082-128-OTO-286.

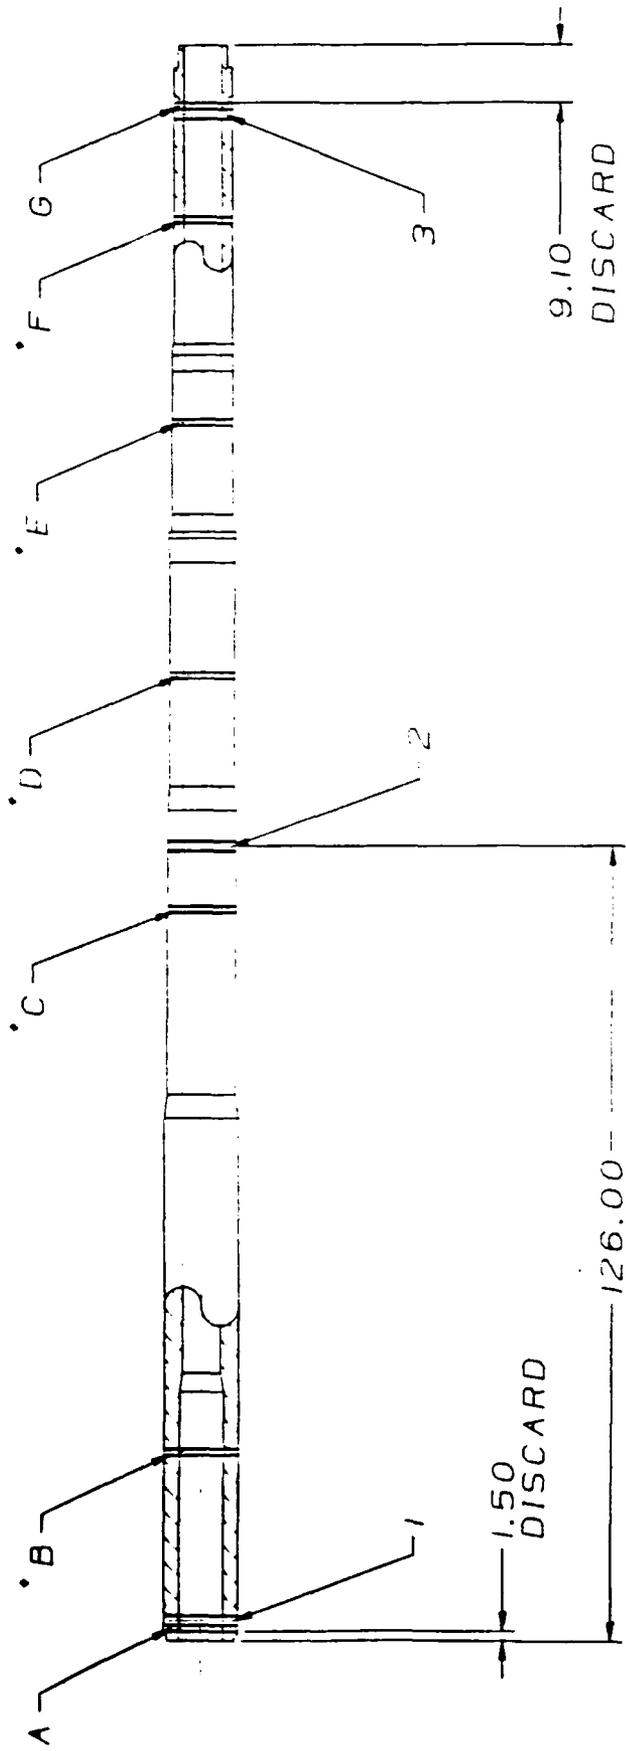

29

REMOVE DISCS INDICATED • FROM APPROXIMATE MIDDLE OF ZONE IN WHICH LOCATED

CUT TEN DISCS

SEVEN 1" THICK DISCS (TENSILE & CHARPY SPECIMENS) IDENTIFY A THRU G AS SHOWN

THREE 1.5" THICK DISCS (RESIDUAL STRESS & FRACTURE TOUGHNESS SPECIMENS) IDENTIFY 1 - 3 AS SHOWN


TOLERANCE ON DISC THICKNESS= +.25

TOLERANCE ON DISCARD LENGTH= +.25

TOLERANCE ON 126 LENGTH= +/- .25

SAVE ALL EXCESS

Figure 15. Location of test discs taken from tube #3141-221-OTO-291 for mechanical property evaluation.

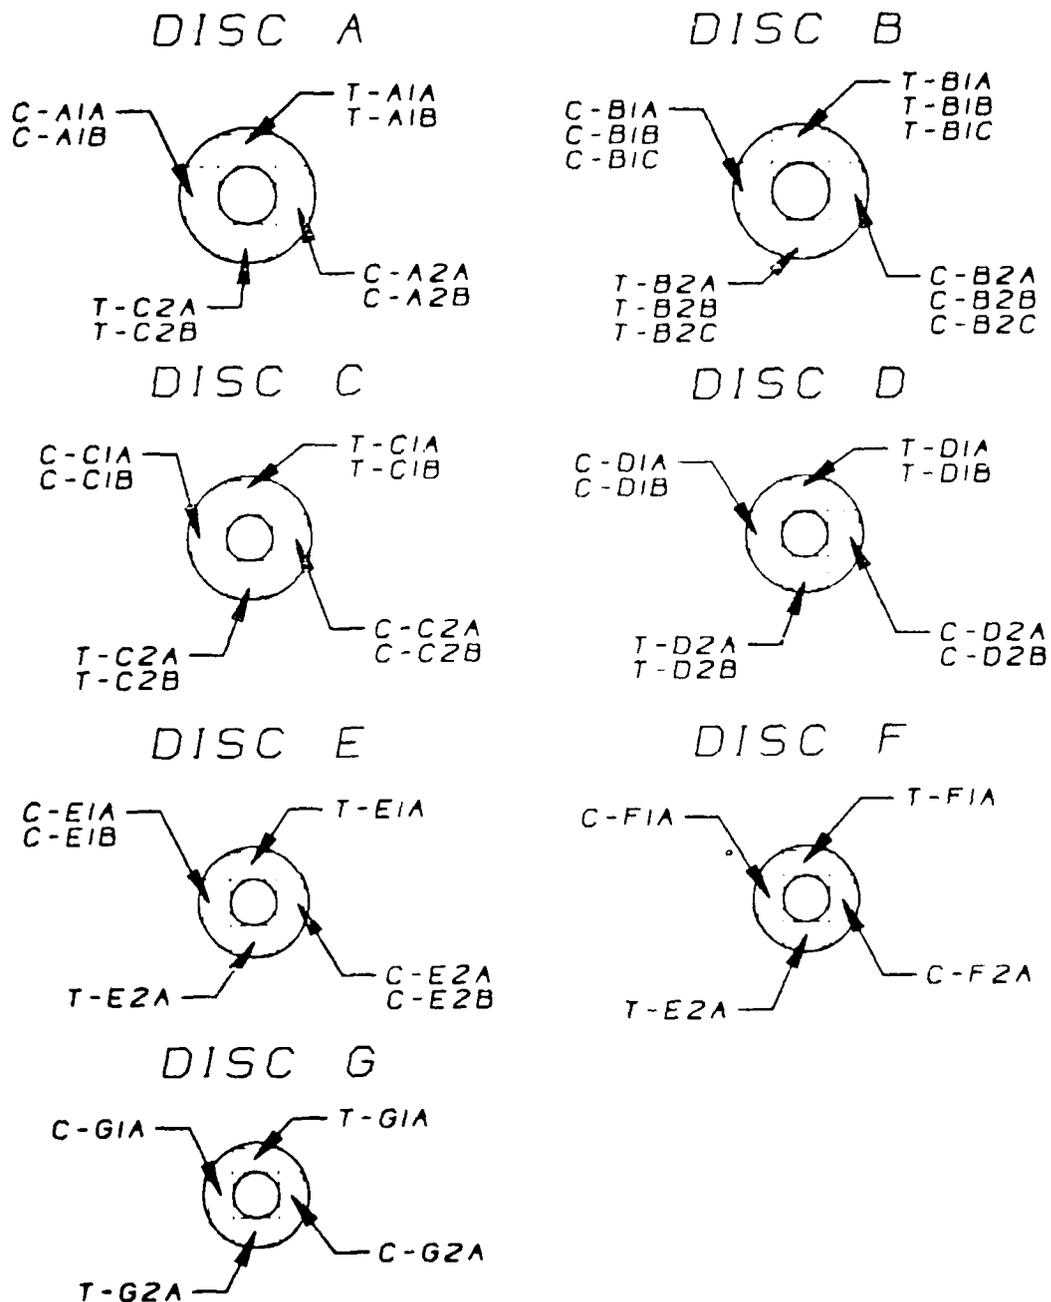

NOTE: THE CUTTING ARRANGEMENT OF TENSILE AND CHARPY COUPONS WAS ADJUSTED IN ORDER TO ACCOMMODATE THE VARIATION IN WALL THICKNESS OVER THE LENGTH OF THE TUBE.

CODE: EXAMPLE T-TENSILE SPECIMEN, C-CHARPY, A-DISC 1 OR 2-CLOCK POSITION, A-SPECIMEN LOCATION IN RELATIONSHIP TO THE BORE. (A-O.D., B-I.D.)

Figure 16. Cutting arrangement of tensile and Charpy test coupons as taken from each disc.




Figure 17. Photomicrograph of an as-polished sample showing stringer-type oxide inclusions present in the Palmaria gun tube material (100X).



Figure 18. Photomicrograph of an etched breech end sample revealing the tempered martensitic microstructure found throughout the Palmaria tube (1000X).



Figure 19. Photomicrograph of an etched muzzle end sample revealing a tempered martensitic microstructure (1000X).

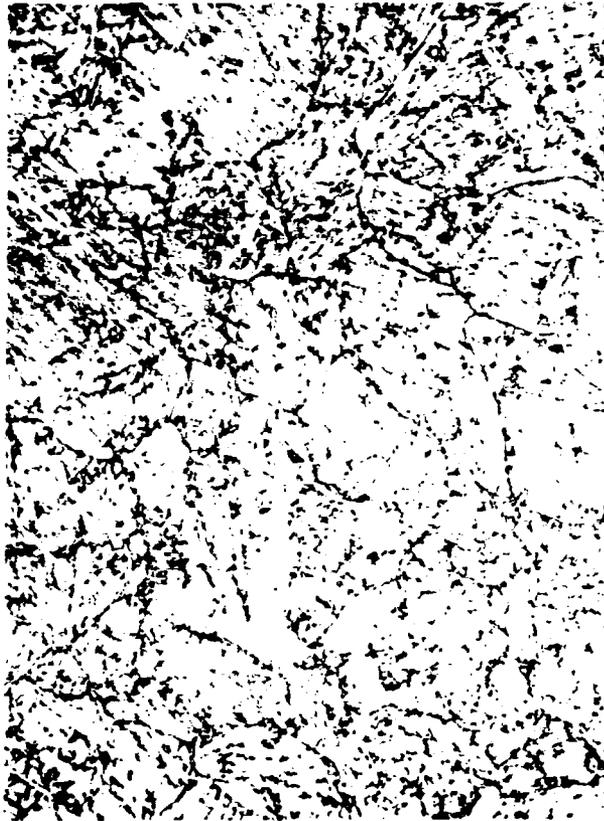


Figure 20. Photomicrograph illustrating the large grain size obtained in the breech end of the Palmaria 155-mm gun tube.

## APPENDIX A

### REPORT ON THE MEASURED RESIDUAL STRESS DISTRIBUTIONS IN THREE DISKS FROM A 155-MM ITALIAN MANUFACTURED HOWITZER

J.A.KAPP  
21 Dec 1988

Three disks from a 155-mm Italian manufactured howitzer were analyzed to determine the extent of autofrettage residual stresses contained in the tube. The three disks were from different locations in the tube. The first section was from the chamber region. This disk was 2 inches thick, had an O.D. of 11.79 inches and an I.D. of 6.54 inches, and had an O.D. keyway notch. The second disk was from a section of the tube where the I.D. was 6.1 inches (155-mm) and had an O.D. of 10.79 inches. The final section was from the muzzle section of the tube. The I.D. of this disk was 6.1 inches (155-mm) and the O.D. was 8.64 inches. Neither the muzzle section nor the intermediate section had a keyway notch on the O.D.


Residual stresses were measured in two ways. First, the splitting method of B. Brown (ARLCB-TR-83042, December 1983) was used, and on two of the disks, the hole drilling method was used. In the splitting method, the disk is cut radially from the O.D. towards the I.D. If autofrettage residual stresses are present, when the cut is through to the I.D., the now split disk will spring open. The angle of opening is directly related to the amount of autofrettage residual stress (presented as percent overstrain). The hole drilling residual stress measurement method is outlined in ASTM E-837-85, "Standard Test Method for Determining Residual Stresses by the Hole Drilling Strain Gage Method." To measure the residual stresses, a three-gage strain gage rosette is bonded to the structure that contains the residual stresses. The rosette is oriented such that the center of each strain gage grid lies on a circle of known radius. A small diameter hole is drilled concentric to the strain gage position circle. The drilled hole is small enough that it does not damage the strain gage grids. When the hole is drilled, the area around the hole now acts as if it were a plate with a hole in it. Since a hole in space cannot support residual stresses, by drilling the hole the residual stresses are also relieved and will result in some strain to be observed by the strain gage rosette. The magnitude of the strain recorded on the strain gages can be related to the residual stresses at the location of the hole.

The results of the testing are as follows: For the breech end disk (containing the O.D. notch), the splitting method predicts a residual stress of 50 percent overstrain. For the intermediate disk, the splitting method predicts autofrettage residual stresses of 35 percent overstrain, and for the muzzle end section, the amount of autofrettage residual stress is predicted to be zero percent overstrain. It should be mentioned, however, that the splitting method was developed assuming that there were no discontinuities in the disk being tested. The angle of opening is a function of the stiffness of the disk. It has been shown that by introducing discontinuities such as O.D. notches, the stiffness of the disk is reduced and the magnitude of the residual stresses is affected (see Transactions of the ASME, Journal of Pressure Vessel Technology, Vol. 103, February 1981, pp. 76-84, Kapp and Pflegl). The effect of the notch is that the magnitude of the residual stresses is reduced over what would be predicted. Since 50 percent overstrain was measured, the level of autofrettage residual stresses may be somewhat more than 50 percent overstrain. But it is conservative to state that the amount of autofrettage residual stress in the breech end disk is 50 percent overstrain.

The hole drilling method was applied to two of the three sections, the intermediate section and the muzzle end section. Since the hole drilling must from necessity be performed prior to the splitting method, we gained no information at all on the muzzle end section. The hole drilling results for this section were inconclusive. The results from the intermediate section, however, did yield results that confirm the splitting method results. The accompanying figure demonstrates this. Plotted here are the hole drilling measured hoop residual stresses as functions of radial position; these measurements appear as the solid diamonds. Also plotted in the figure are the theoretical residual stresses based on the Von Mises' yield criterion and assuming a yield strength of

160,000 psi, 35 percent overstrain, and the dimensions of the disk. It is clear from this plot that the agreement is quite good. The residual stresses close to the outside diameter are somewhat higher than would be expected theoretically, but I believe that the differences are not critical. Therefore, it is safe to assume that at the location of the intermediate disk, the amount of autofrettage residual stress present is 35 percent overstrain.

Comparison of Measured and Predicted Residual Stresses  
Intermediate Location (OD=10.79 in)

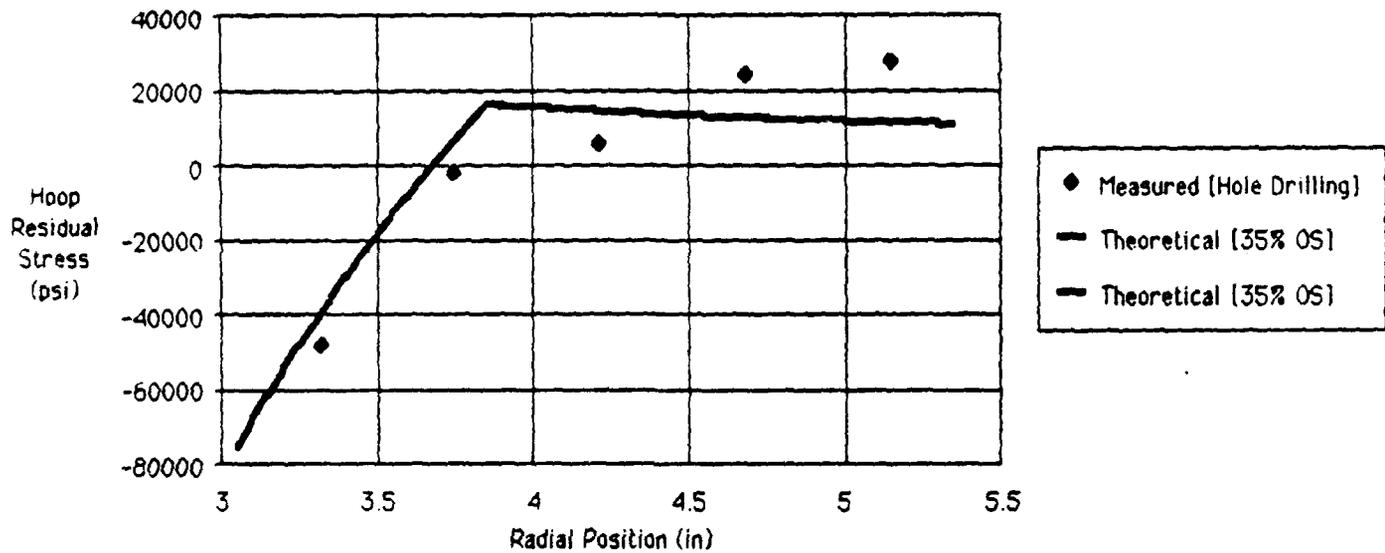

TECHNICAL REPORT INTERNAL DISTRIBUTION LIST

	<u>NO. OF COPIES</u>
CHIEF, DEVELOPMENT ENGINEERING DIVISION	
ATTN: SMCAR-CCB-D	1
-DA	1
-DC	1
-DI	1
-DP	1
-DR	1
-DS (SYSTEMS)	1
CHIEF, ENGINEERING SUPPORT DIVISION	
ATTN: SMCAR-CCB-S	1
-SE	1
CHIEF, RESEARCH DIVISION	
ATTN: SMCAR-CCB-R	2
-RA	1
-RE	1
-RM	1
-RP	1
-RT	1
TECHNICAL LIBRARY	
ATTN: SMCAR-CCB-TL	5
TECHNICAL PUBLICATIONS & EDITING SECTION	
ATTN: SMCAR-CCB-TL	3
OPERATIONS DIRECTORATE	
ATTN: SMCWV-ODP-P	1
DIRECTOR, PROCUREMENT DIRECTORATE	
ATTN: SMCWV-PP	1
DIRECTOR, PRODUCT ASSURANCE DIRECTORATE	
ATTN: SMCWV-QA	1

NOTE: PLEASE NOTIFY DIRECTOR, BENET LABORATORIES, ATTN: SMCAR-CCB-TL, OF ANY ADDRESS CHANGES.

TECHNICAL REPORT EXTERNAL DISTRIBUTION LIST

	<u>NO. OF COPIES</u>		<u>NO. OF COPIES</u>
ASST SEC OF THE ARMY RESEARCH AND DEVELOPMENT ATTN: DEPT FOR SCI AND TECH THE PENTAGON WASHINGTON, D.C. 20310-0103	1	COMMANDER ROCK ISLAND ARSENAL ATTN: SMCRI-ENM ROCK ISLAND, IL 61299-5000	1
ADMINISTRATOR DEFENSE TECHNICAL INFO CENTER ATTN: DTIC-FDAC CAMERON STATION ALEXANDRIA, VA 22304-6145	12	DIRECTOR US ARMY INDUSTRIAL BASE ENGR ACTV ATTN: AMXIB-P ROCK ISLAND, IL 61299-7260	1
COMMANDER US ARMY ARDEC ATTN: SMCAR-AEE	1	COMMANDER US ARMY TANK-AUTMV R&D COMMAND ATTN: AMSTA-DDL (TECH LIB) WARREN, MI 48397-5000	1
SMCAR-AES, BLDG. 321	1	COMMANDER US MILITARY ACADEMY	1
SMCAR-AET-O, BLDG. 351N	1	ATTN: DEPARTMENT OF MECHANICS WEST POINT, NY 10996-1792	
SMCAR-CC	1		
SMCAR-CCP-A	1	US ARMY MISSILE COMMAND	
SMCAR-FSA	1	REDSTONE SCIENTIFIC INFO CTR	2
SMCAR-FSM-E	1	ATTN: DOCUMENTS SECT, BLDG. 4484	
SMCAR-FSS-D, BLDG. 94	1	REDSTONE ARSENAL, AL 35898-5241	
SMCAR-IMI-I (STINFO) BLDG. 59	2		
PICATINNY ARSENAL, NJ 07806-5000			
DIRECTOR US ARMY BALLISTIC RESEARCH LABORATORY ATTN: SLCBR-DD-T, BLDG. 305	1	COMMANDER US ARMY FGN SCIENCE AND TECH CTR ATTN: DRXST-SD 220 7TH STREET, N.E. CHARLOTTESVILLE, VA 22901	1
ABERDEEN PROVING GROUND, MD 21005-5066			
DIRECTOR US ARMY MATERIEL SYSTEMS ANALYSIS ACTV ATTN: AMXSY-MP	1	COMMANDER US ARMY LABCOM MATERIALS TECHNOLOGY LAB ATTN: SLCMT-IML (TECH LIB)	2
ABERDEEN PROVING GROUND, MD 21005-5071		WATERTOWN, MA 02172-0001	
COMMANDER HQ, AMCCOM ATTN: AMSMC-IMP-L	1		
ROCK ISLAND, IL 61299-6000			

NOTE: PLEASE NOTIFY COMMANDER, ARMAMENT RESEARCH, DEVELOPMENT, AND ENGINEERING CENTER, US ARMY AMCCOM, ATTN: BENET LABORATORIES, SMCAR-CCB-TL, WATERVLIET, NY 12189-4050, OF ANY ADDRESS CHANGES.

TECHNICAL REPORT EXTERNAL DISTRIBUTION LIST (CONT'D)

	<u>NO. OF COPIES</u>		<u>NO. OF COPIES</u>
COMMANDER US ARMY LABCOM, ISA ATTN: SLCIS-IM-TL 2800 POWDER MILL ROAD ADELPHI, MD 20783-1145	1	COMMANDER AIR FORCE ARMAMENT LABORATORY ATTN: AFATL/MN EGLIN AFB, FL 32542-5434	1
COMMANDER US ARMY RESEARCH OFFICE ATTN: CHIEF, IPO P.O. BOX 12211 RESEARCH TRIANGLE PARK, NC 27709-2211	1	COMMANDER AIR FORCE ARMAMENT LABORATORY ATTN: AFATL/MNF EGLIN AFB, FL 32542-5434	1
DIRECTOR US NAVAL RESEARCH LAB ATTN: MATERIALS SCI & TECH DIVISION CODE 26-27 (DOC LIB) WASHINGTON, D.C. 20375	1 1	MIAC/CINDAS PURDUE UNIVERSITY 2595 YEAGER ROAD WEST LAFAYETTE, IN 47905	1
DIRECTOR US ARMY BALLISTIC RESEARCH LABORATORY ATTN: SLCBR-IB-M (DR. BRUCE BURNS) ABERDEEN PROVING GROUND, MD 21005-5066	1		

NOTE: PLEASE NOTIFY COMMANDER, ARMAMENT RESEARCH, DEVELOPMENT, AND ENGINEERING CENTER, US ARMY AMCCOM, ATTN: BENET LABORATORIES, SMCAR-CCB-TL, WATERVLIET, NY 12189-4050, OF ANY ADDRESS CHANGES.

DISTRIBUTION LIST

DIA

B231 \_\_\_ DIA  
B174 ✓ DIA/DT-FMO  
B072 ✓ DIA/DAM-3C

ARMY - AMC

C085 ✓ AMSAA	AMXSY-PF
C205 ✓ HEL	SLCHE-FI
C505 ✓ MTL	SLCMT-DDI
C509 ✓ BRL	SLCRB-DD-F
C510 ___ R&TDA LAB/AVSCOM	SAVRT-R
C511 ___ NRDEC	STRNC-AI
C512 ✓ AMC	AMCMI-FT
C513 ✓ ARDEC	SMCAR- <del>RA</del> ASF
C515 ✓ CRDEC	SMCCR-OFF
C521 ___ EPG	S'TEEP-CT-F
C522 ✓ YPG	STEYP-MT-F
C523 ✓ LABCOM	AMSEL-MI-FI
C525 ___ C2SW	
C532 ✓ VAL	SLCVA-FIO
C535 ✓ AVSCOM	AMSAV-OI
C536 ___ AVN ENGR FLT ACTY (AEFA)	SAVTE-P
C538 ✓ WSMR	STEWS-FI
C545 ✓ AMCCOM	AMSMC-SIF
C550 ___ CECOM	AMSEL-MI-I
C569 ✓ BRDEC	STRBE-Y
C588 ___ DPG	STEPD-SD-TA-F
C590 ✓ TACOM	AMSTA-SF
C619 ✓ MICOM	AMSMI-SI-FO
C697 ___ TECOM	AMSTE-SI-F

N/A \_\_\_ DIR Applied Technology Laboratory  
U.S. Army Research and Technology  
Laboratories  
ATTN: DAVDL-ATL-QA  
Fort Eustis, VA 23604

N/A \_\_\_ CDR U.S. Army Cold Regions Test  
Center  
ATTN: STECR-AD-SE  
APO Seattle 98733-7850

ARMY - AMC (CONT'D)

N/A \_\_\_ CDR U.S. Army Science &  
Technology Center - Europe  
APO New York 09079-4734

N/A \_\_\_ CDR U.S. Army Science &  
Technology Center - Far East  
APO San Francisco 96328

ARMY - TRADOC

C460 ___ ENG SCH	ATSE-Z-CDI
C461 ✓ INF SCH	ATZB-IS-T
C467 ___ MSL MUN CTR/ SCH	ATSK-CC
C468 ___ QTR SCH	ATSM-CDC
C500 ___ TRADOC	ATTE-P
C562 ___ TRANS SCH	ATSP-CD-CS
C587 ___ CDEC	ATEC-PL-TS
C632 ___ CHEMICAL SCH	ATZN-CM-CCL
C633 ✓ ORD CTR/SCH	ATSL-CD-TM
C635 ___ AIR DEF SCH	ATSA-CDT
C639 ✓ FLD ART SCH	ATSF-CCT
C641 ___ AVIATION CTR	ATZQ-CDT
C644 ___ LOG CTR	ATCL-FFO
C646 ___ CACDA	ATZL-CAT
C649 ___ SIG CTR	ATZH-CDS
C683 ___ INTEL CTR/SCH	ATSI-CD-CI
C684 ___ INTEL SCH	ATSI-ETD-T
C715 ✓ ARMOR CTR	ATSB-CD-TH

ARMY-OTHER

C003 ___ DUSA	(OR)
C043 <u>3</u> AFMIC	AFMIC-CR
C239 ___ 203D MI BN	IAM-T-O
C314 ___ 513TH MI GP	IAM-O/IC
C428 ___ OTEA	
C591 ✓ FSTC	___ AIAST-FM2 ___ AIAST-IS1
C619 ___ MSIC	AIAMS-YF
C763 ✓ HQDA	DAMI-FIT
C763 ___ HQDA	DAMA-WSW
C763 ___ HQDA	DAMA-CSE
C763 ___ HQDA	DAMI-RDM

ARMY - OTHER (Cont'd)

N/A \_\_\_ CDR U.S. Army Development  
and Employment Agency  
ATTN: MODE-OSD  
Fort Lewis, WA 98433

N/A \_\_\_ CDR INSCOM  
ATTN: IAOPS  
Arlington Hall Station, VA  
22212

N/A \_\_\_ CDR INSCOM  
ATTN: IAFM-SED  
Fort Meade, MD 20755

N/A \_\_\_ CDR USAITAC  
ATTN: IAX-RQC  
Arlington Hall Station, VA  
22212

N/A 4 DIR USAIA  
ATTN: AIA-IPD  
Washington, DC 20310-1015

N/A \_\_\_ President  
U.S. Army Intelligence and  
Security Board  
ATTN: ATSI-BD-P  
Fort Huachuca, AZ 85613

NAVY

D008 \_\_\_ NISC  
D151 \_\_\_ NAVEODTECHCEN  
D700 \_\_\_ CGMCDEC

AIR FORCE

E420 \_\_\_ FTD NIIS

N/A  AFSC  
ATTN: INJ  
Andrews AFB, DC 20334

OTHER

PO55 2 CIA/ <sup>NC-Format</sup> ~~OCR/DSD/SD~~  
PO90 \_\_\_ NSA T5321