

ERDC/CERL SR-04-8

Construction Engineering
Research Laboratory



**US Army Corps
of Engineers.**

Engineer Research and
Development Center

Field Evaluation of Self-Lubricated Mechanical Components for Civil Works Navigation Structures

Timothy D. Race, Ashok Kumar, and
L.D. Stephenson

June 2004

20050118 006

ERDC/CERL SR-04-8

Construction Engineering
Research Laboratory



**US Army Corps
of Engineers®**

Engineer Research and
Development Center

Field Evaluation of Self-Lubricated Mechanical Components for Civil Works Navigation Structures

Timothy D. Race, Ashok Kumar, and
L.D. Stephenson

June 2004

Field Evaluation of Self-Lubricated Mechanical Components for Civil Works Navigation Structures

Timothy D. Race

Corrosion Control Consultants & Labs, Inc.
135 N. Addison Avenue, Suite 108
Elmhurst, IL 60126-2800

Ashok Kumar and L.D. Stephenson

Construction Engineering Research Laboratory
PO Box 9005
Champaign, IL 61826-9005

Final Report

Approved for public release; distribution is unlimited.

Prepared for U.S. Army Corps of Engineers
Washington, DC 20314-1000

Under Civil Works Work Unit #33238

ABSTRACT: It is operationally and environmentally desirable to replace greased bronze bushings used in navigation lock machinery with self-lubricating bushings. Bronze bushings must be greased manually or with automatic lubricating machines. Grease lines are subject to damage from ice and debris. If the grease line breaks, the lubricating system fails, which may lead to component failure and delays in navigation. Introduction of grease into the riverine environment is also a concern.

The Corps of Engineers has been using self-lubricating bushings in navigation locks for the past 20 years. The purpose of this study was to evaluate mechanical properties and durability of emerging advanced self-lubricating bushing/bearing materials in the laboratory and under field conditions, and to provide additional knowledge, needed guidelines, and standard specifications for the proper selection and use of self-lubricating bushing materials for locks based on local environmental conditions and applications. The results of accelerated testing of quarter-scale model self-lubricating pintle bushings in simulated river are also reported.

DISCLAIMER: The contents of this report are not to be used for advertising, publication, or promotional purposes. Citation of trade names does not constitute an official endorsement or approval of the use of such commercial products. All product names and trademarks cited are the property of their respective owners. The findings of this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.
DESTROY THIS REPORT WHEN IT IS NO LONGER NEEDED. DO NOT RETURN IT TO THE ORIGINATOR.

Contents

List of Figures and Tables	vi
Conversion Factors	vii
Preface	viii
1 Introduction.....	1
Background	1
Objective	2
Approach.....	2
Scope	2
2 Applications and Product Descriptions.....	3
Applications.....	3
Product Descriptions	3
<i>Garlock DU</i>	3
<i>Tenmat Feroform T814</i>	3
<i>Kamatics KAron V</i>	3
<i>Oiles 500</i>	4
<i>Thordon SXL and HPSXL</i>	4
<i>Lubrite G10 and G12</i>	4
<i>Lubron AQ30, AQ100, and TF400</i>	4
<i>Orkot TXM Marine</i>	4
3 Product Specifications.....	5
4 Field Performance.....	10
Markland Locks and Dam	10
McAlpine Locks and Dam	10
Smithland Locks and Dam	11
Cannelton and Newburgh Locks and Dams	11
Cascade Locks.....	11
John Day Lock and Dam.....	12
Little Goose Lock and Dam.....	12
Colorado River Locks.....	13
Locks and Dam No. 27.....	13

Melvin Price Locks and Dam.....	13
Kentucky Lock.....	14
Barkley Lock.....	14
Old Hickory Lock.....	14
Chicago Harbor Lock.....	15
5 Olmsted Prototype Field Experiments.....	16
6 Powertech Laboratory Evaluation of Self-Lubricating Pintle Bearings.....	17
7 Field Experience With Self-Lubricating Pintle Bearing Materials.....	18
8 Self-Lubricated Mechanical Components: Field Performance vs Properties.....	20
9 Conclusions.....	21
Salient Characteristics.....	21
Problems Encountered in Service.....	21
Installation Techniques.....	21
Cost Relative to Greased Bronze Bushings.....	21
10 Commercial Availability.....	22
Engineering Support.....	22
Overall Ratings of Products.....	22
Recommended Products.....	22
Appendix A: Questionnaires on Self-Lubricating Bushings.....	24
Appendix B: Manufacturers' Literature.....	76
Attachment 1: Powertech Report on Scale Model Testing of Navigation Lock Pintle Self-Lubricating Bushings for the Corps of Engineers.....	111
Report Documentation Page.....	172

List of Figures and Tables

Figures

- 1 Self-lubricating pintle bearing with Thordon SXL material installed at Cannelton Lock in 1994; removed/replaced in July 2002; pintle shows very little wear after 8 years 19
- 2 Self-lubricating pintle bearing with Thordon SXL material installed at Cannelton Lock in 1994; removed/replaced in July 2002. Self-lubricating Thordon material about 80 percent eroded after 8 years 19

Tables

- 1 Garlock DU Bearings 6
- 2 Orkot – TXM Marine 6
- 3 Lubron – TF400 7
- 4 Kamatics KAron V 7
- 5 Tenmat Feroform T814 8
- 6 Thordon – SXL 8
- 7 Thordon – HPSXL 9
- 8 Lubrite G10 and G12 9
- 9 Self-lubricating material vs. performance 16
- 10 Pintle busing material costs/performance data (20/24-inch diameter) 18

Conversion Factors

Non-SI* units of measurement used in this report can be converted to SI units as follows:

Multiply	By	To Obtain
degrees (angle)	0.01745329	radians
degrees Fahrenheit	$(5/9) \times (^{\circ}\text{F} - 32)$	degrees Celsius
inches	0.0254	meters
pounds (force) per square inch	0.006894757	megapascals

* *Système International d'Unités* ("International System of Measurement"), commonly known as the "metric system."

Preface

This study was authorized by Headquarters, U.S. Army Corps of Engineers (HQUSACE) as part of the High Performance Materials and Systems (HPM&S) Research Program. This work was performed under Work Unit 33238, "Civil Works Advanced Materials Selection Guide," for which Dr. Ashok Kumar, U.S. Army Engineer Research and Development Center (ERDC), Construction Engineering Research Laboratory (CERL), was the Principal Investigator.

Dr. Tony Liu was the HPM&S Coordinator at the Directorate of Research and Development; the Research Area Manager was Mr. Roy Braden, and the Program Monitor was Mr. Andy Wu, HQUSACE. Dr. Mary Ellen Hynes, ERDC Geotechnical and Structures Laboratory (GSL) was the ERDC Lead Technical Director, Infrastructure Engineering and Management. Dr. William Grogan, GSL, was the HPM&S Program Manager.

This work was performed by the Materials and Structures Branch (CF-M) of the Facilities Division (CF), CERL. The report was prepared by Mr. Timothy D. Race (Corrosion Control Consultants & Labs, Inc.), under contract DACW42-03-P-0173, and Drs. Ashok Kumar and L.D. Stephenson (CERL). A portion of the work was performed by Powertech Laboratory, Surrey, BC, Canada, under contract DACW42-02-P-0187. The technical editor was Linda L. Wheatley, Information Technology Laboratory. Mr. Martin J. Savoie was Chief, CF-M, and Mr. L. Michael Golish was Chief, CF. Dr. Paul Howdysshell was the Technical Director for this work unit, and Dr. Alan Moore was Director of CERL.

At the time of preparation of this report, COL James R. Rowan, EN, was the Commander and Executive Director of ERDC, and Dr. James R. Houston was the Director.

1 Introduction

Background

The purpose of a lubricant is to prevent wear and damage of equipment components as they move relative to one another. Lubricants are broadly classified as either fluids or solids. Fluid lubricants include oils and greases and may be either synthetic or natural products. Solid lubricants are powders or thin films. Some solid lubricants, such as molybdenum disulfide, graphite, and zinc oxide, are used as additives in conjunction with fluid lubricants.

Solid lubricants are effective at high loads and speeds and resist deterioration over prolonged periods. They are more stable than fluid lubricants at high temperatures and pressures. Solid lubricants may simplify design because they do not require a means of introducing and sealing them in as do fluid lubricants. Solid lubricants, however, have poor self-healing properties relative to fluids as well as poor heat dissipation, especially in the case of polymeric bearings. In general, solid-lubricated bearings have a higher coefficient of friction and wear than fluid-lubricated bearings.

Types of solid lubricants include lamellar solids, soft metal films, surface-treated metals, and polymers. Solid lubricants may be used as a powder, bonded coatings, and self-lubricated composites. Bonded coatings and self-lubricating composites of the metal-solid type are of particular interest to this work.

Interest in self-lubricated wear components is driven by environmental and economic considerations. Self-lubricated bearings eliminate the undesirable introduction of fluid lubricants into the ecosystem. Self-lubricated bearings also reduce operating costs by eliminating the need for periodic application of the fluid lubricant. For navigation projects, periodic lubrication can be labor intensive and greases inevitably are introduced to the riverine environment.

Short-term laboratory testing of self-lubricated materials has been performed by the U.S. Army Corps of Engineers (USACE). However, the long-term field performance of these products under real-world operating conditions has not been evaluated.

Objective

The objectives of this research were to evaluate the field performance of self-lubricating materials at USACE navigation projects and to compile descriptive material and design specifications for these products.

Approach

Field performance of self-lubricated components was evaluated empirically by surveying USACE field and design personnel. Materials and design criteria were derived from data provided by manufacturers of self-lubricated bushings. Field performance and manufacturer data were also compared with the results of laboratory research on greaseless bushings in hydropower and navigation applications.

Scope

The results of this investigation apply to Civil Works navigation facilities. To the extent that similarities exist between navigation and other Civil Works installations, including hydropower and flood control facilities, the information contained herein may also be applicable to these other facilities. It may also apply to other similar facilities including, but not limited to, those operated by the Tennessee Valley Authority and the U.S. Bureau of Reclamation.

2 Applications and Product Descriptions

Applications

The surveyed navigation installations are using self-lubricated materials for a variety of applications including: guide rollers, reaction rollers, and thrust washers in floating mooring bitts; lock gate guide pins; tainter valve strut arm components; sector gear bearings; and pintle bearings. Some facilities have replaced the conventional lower roller assembly of floating mooring bitts with a simple self-lubricated guide block assembly.

Product Descriptions

Self-lubricating materials (e.g., lamellar solids, soft metal films, surface-treated metals, and polymers) may be used as powders, bonded coatings, and self-lubricated composites. Bonded coatings and self-lubricating composites of the metal-solid type are of particular interest to this work. Products in use on USACE navigation projects were identified and are described below.

Garlock DU

Garlock DU is a bonded coating product consisting of a 1-mil film of polytetrafluoroethylene (PTFE) mixed with lead on a porous 10-mil sintered copper-tin bronze coating over a steel substrate.

Tenmat Feroform T814

Feroform T814 is a self-lubricating composite product consisting of PTFE uniformly dispersed in a woven synthetic polyester fabric reinforced thermoset phenolic resin matrix.

Kamatics KAron V

KAron V is a bonded polyester coating incorporating PTFE particles. The coating is applied at various thicknesses to stainless steel, fiberglass, bronze, titanium, aluminum, phenolic, inconel, and other substrates.

Oiles 500

Oiles 500 bearings are dispersed-powder products consisting of either PTFE or graphite plugs in metal alloy substrates.

Thordon SXL and HPSXL

Thordon SXL and HPSXL are bonded-coating products consisting of thermosetting elastomeric resin on various backings. High-pressure TRAXL bearings are bronze-backed products coated with SXL or HPSXL.

Lubrite G10 and G12

Lubrite G10 and G12 lubricant are epoxy-base graphite-free materials extruded into recesses on the bearing surface. The bearings are available in a variety of alloys.

Lubron AQ30, AQ100, and TF400

Information has not been provided by the manufacturer. The Louisville District describes TF400 as a PTFE lubricant film on a metal alloy bearing.

Orkot TXM Marine

Orkot TXM Marine consists of a medium weave fabric backing impregnated with PTFE and lubricated with an evenly dispersed solid film lubricant (molybdenum disulphide).

3 Product Specifications

Product data were gathered from two primary sources. Most of the data were reported in CERL Technical Report 99/104, "Greaseless Bushings for Hydro-power Applications: Program, Testing, and Results" (December 1999). Materials evaluated in this research program include Tenmat Feraform T814, Kamatics Karon V, Orkot TXM Marine, Thordon TRAXL SXL and HPSXL, and Lubron TF400. The remainder of the bearing data is compiled from manufacturers' literature (Garlock DU and Lubrite G10 and G12). Coefficients of linear expansion are in all cases taken from the manufacturer's literature.

The coefficient of friction is perhaps the most important physical property of greaseless bushings. Static and dynamic coefficients of friction, measured under dry and wet conditions, are important to determine the friction torque and stick-slip characteristics of the bearing system. Stick-slip or "stiction" is caused by the difference between static and dynamic coefficients of friction when a system is moved from rest. The more nearly equal the coefficients are, the smoother the system will operate, usually even if actual friction is high.

Other parameters important to system design include load bearing capacities, coefficient of linear expansion, and swell. Properties of these self-lubricating materials are summarized in Tables 1 through 8. Appendix B contains manufacturers' literature for the evaluated products.

Table 1. Garlock DU Bearings.

Attribute	Value
Load Bearing Capacity: Static	36,000 psi
Load Bearing Capacity: Dynamic	20,000 psi
Load Bearing Capacity: Compressive	44,000 psi
Wear Rate: Dry	< 0.2 mils/100 hours
Wear Rate: Wet	NA
Coefficient of Static Friction: Dry	0.02 – 0.20
Coefficient of Static Friction: Wet	NA
Coefficient of Dynamic Friction: Dry	0.02 – 0.20
Coefficient of Dynamic Friction: Wet	NA
Delta* Coefficient of Friction: Dry	0 – 0.18
Delta* Coefficient of Friction: Wet	NA
Coefficient of Linear Expansion: Normal	$30 \times 10^{-6}/^{\circ}\text{C}$
Coefficient of Linear Expansion: Parallel	$11 \times 10^{-6}/^{\circ}\text{C}$
Swell: Water	NA
Swell: Oil	NA

* Delta is the difference between static and dynamic coefficients of friction. All data supplied by manufacturer. Delta values are inferred.

Table 2. Orkot – TXM Marine.

Attribute	Value
Load Bearing Capacity: Static	11,600 psi
Load Bearing Capacity: Dynamic	5800 psi
Load Bearing Capacity: Compressive	Normal to Laminate >40,700 psi Parallel to Laminate >13,000 psi
Wear Rate: Dry	0.199 mils/100 hours
Wear Rate: Wet	0.504 mils/100 hours
Coefficient of Static Friction: Dry	0.088 (0.05 to 0.10)
Coefficient of Static Friction: Wet	0.068
Coefficient of Dynamic Friction: Dry	0.061
Coefficient of Dynamic Friction: Wet	0.060
Delta* Coefficient of Friction: Dry	0.027
Delta* Coefficient of Friction: Wet	0.028
Coefficient of Linear Expansion: Normal	$90 \text{ to } 100 \times 10^{-6}/^{\circ}\text{C}$
Coefficient of Linear Expansion: Parallel	$50 \text{ to } 60 \times 10^{-6}/^{\circ}\text{C}$
Swell: Water	Zero (< 0.1%)
Swell: Oil	Zero

* Delta is the difference between static and dynamic coefficients of friction.

Table 3. Lubron – TF400.

Attribute	Value
Load Bearing Capacity: Static	NA
Load Bearing Capacity: Dynamic	NA
Load Bearing Capacity: Compressive	NA
Wear Rate: Dry	0.087 mils/100 hours
Wear Rate: Wet	0.232 mils/100 hours
Coefficient of Static Friction: Dry	0.072
Coefficient of Static Friction: Wet	0.059
Coefficient of Dynamic Friction: Dry	0.059
Coefficient of Dynamic Friction: Wet	0.049
Delta* Coefficient of Friction: Dry	0.013
Delta* Coefficient of Friction: Wet	0.010
Coefficient of Linear Expansion: Normal	NA
Coefficient of Linear Expansion: Parallel	NA
Swell: Water	NA
Swell: Oil	NA

* Delta is the difference between static and dynamic coefficients of friction.

Table 4. Kamatics KArOn V.

Attribute	Value
Load Bearing Capacity: Static	Metal backed = 67,000 psi Composite backed = 33,000 psi
Load Bearing Capacity: Dynamic	Metal backed = 30,000 psi Composite backed = 20,000 psi
Load Bearing Capacity: Compressive	NA
Wear Rate: Dry	1.169 mils/100 hours
Wear Rate: Wet	0.325 mils/100 hours
Coefficient of Static Friction: Dry	0.061
Coefficient of Static Friction: Wet	0.053
Coefficient of Dynamic Friction: Dry	0.053
Coefficient of Dynamic Friction: Wet	0.049
Delta* Coefficient of Friction: Dry	0.008
Delta* Coefficient of Friction: Wet	0.004
Coefficient of Linear Expansion: Normal	NA
Coefficient of Linear Expansion: Parallel	NA
Swell: Water	+ 3 mils
Swell: Oil	Zero

* Delta is the difference between static and dynamic coefficients of friction.

Table 5. Tenmat Feroform T814.

Attribute	Value
Load Bearing Capacity: Static	NA
Load Bearing Capacity: Dynamic	8990 psi
Load Bearing Capacity: Compressive	36,250 psi
Wear Rate: Dry	0.334 mils/100 hours
Wear Rate: Wet	0.023 mils/100 hours
Coefficient of Static Friction: Dry	0.041
Coefficient of Static Friction: Wet	0.061
Coefficient of Dynamic Friction: Dry	0.038
Coefficient of Dynamic Friction: Wet	0.038
Delta* Coefficient of Friction: Dry	0.003
Delta* Coefficient of Friction: Wet	0.023
Coefficient of Linear Expansion: Normal	50 to 100 x 10 ⁻⁶ /°C
Coefficient of Linear Expansion: Parallel	45 to 100 x 10 ⁻⁶ /°C
Swell: Water	- 7 mils
Swell: Oil	- 4 mils

* Delta is the difference between static and dynamic coefficients of friction.

Table 6. Thordon – SXL.

Attribute	Value
Load Bearing Capacity: Static	NA
Load Bearing Capacity: Dynamic	NA
Load Bearing Capacity: Compressive	NA
Wear Rate: Dry	0.426 mils/100 hours
Wear Rate: Wet	0.826 mils/100 hours
Coefficient of Static Friction: Dry	0.168
Coefficient of Static Friction: Wet	0.113
Coefficient of Dynamic Friction: Dry	0.103
Coefficient of Dynamic Friction: Wet	0.078
Delta* Coefficient of Friction: Dry	0.065
Delta* Coefficient of Friction: Wet	0.035
Coefficient of Linear Expansion: Normal	NA
Coefficient of Linear Expansion: Parallel	NA
Swell: Water	NA
Swell: Oil	NA

* Delta is the difference between static and dynamic coefficients of friction.

Table 7. Thordon – HPSXL.

Attribute	Value
Load Bearing Capacity: Static	NA
Load Bearing Capacity: Dynamic	NA
Load Bearing Capacity: Compressive	NA
Wear Rate: Dry	0.013 mils/100 hours
Wear Rate: Wet	0.564 mils/100 hours
Coefficient of Static Friction: Dry	0.092
Coefficient of Static Friction: Wet	0.076
Coefficient of Dynamic Friction: Dry	0.073
Coefficient of Dynamic Friction: Wet	0.057
Delta* Coefficient of Friction: Dry	0.019
Delta* Coefficient of Friction: Wet	0.019
Coefficient of Linear Expansion: Normal	NA
Coefficient of Linear Expansion: Parallel	NA
Swell: Water	+ 1 mil
Swell: Oil	Zero

* Delta is the difference between static and dynamic coefficients of friction.

Table 8. Lubrite G10 and G12.

Attribute	Value
Load Bearing Capacity: Static	NA
Load Bearing Capacity: Dynamic	1000 to 8000 psi (depending on bearing metal)
Load Bearing Capacity: Compressive	13,000 to 180,000 psi (depending on bearing metal)
Wear Rate: Dry	NA
Wear Rate: Wet	NA
Coefficient of Friction: Range	0.03 – 0.09
Delta* Coefficient of Friction: Dry	NA
Delta* Coefficient of Friction: Wet	NA
Substrate Substrate 4Coefficient of Linear Expansion:	4 to 7 x 10 ⁻⁶ /°C (depending on bearing metal)
Swell: Water	NA
Swell: Oil	NA

* Delta is the difference between static and dynamic coefficients of friction. All data supplied by manufacturer.

4 Field Performance

This section describes specific applications of self-lubricating bushings, including information on products used, application parameters, duration of service, installation methods, problems, manufacturer support, and product performance.

Markland Locks and Dam

Markland Locks and Dam are on the Ohio River in the Louisville District. The upper and lower gates of the 1,200-ft main and 600-ft auxiliary chambers were outfitted in September 1992 with self-lubricated vertical and horizontal rack bar rollers manufactured by Garlock. Some of the vertical rollers that receive higher loads failed and were replaced shortly after with greased bushings. No other information is available on this application.

Bushings for lock filling and emptying culvert valve trunnion pins, crosshead pins, lower connecting rod pins, fulcrum pins, upper strut spindle pins, and lower strut pins are self-lubricating. These bushings are Feroform T814, a standard product manufactured by Tenmat. Loads are either 3,500 or 7,000 psi and the arc of rotation is 45 degrees. Hard-chromed 17-4 stainless steel pins were shrink fitted using liquid nitrogen. Bushings were installed in 2000 and 2001. The field engineer rates these self-lubricated bushings as excellent and recommends them for similar applications.

McAlpine Locks and Dam

McAlpine Locks and Dam are on the Ohio River in the Louisville District. Lock filling and emptying culvert valve trunnion pins are self-lubricating. These bushings are Feroform T814, a standard product manufactured by Tenmat. Loads are 7,000 psi and the arc of rotation is 45 degrees. Hard-chromed 17-4 stainless steel pins were shrink fit using liquid nitrogen. Bushings were installed in February 2000. The field engineer rates these self-lubricated bushings as excellent and recommends them for similar applications.

Smithland Locks and Dam

Smithland Locks and Dam are on the Ohio River in the Louisville District. Lock filling and emptying culvert valve upper strut spindle pins and lower strut pins are self-lubricating. These bushings are Feroform T814, a standard product manufactured by Tenmat. Loads are 3,500 psi and the arc of rotation is 45 degrees. Hard-chromed 17-4 stainless steel pins were shrink fitted using liquid nitrogen. Bushings were installed in 1997, 1998, and 2000. The field engineer rates these self-lubricated bushings as excellent and recommends them for similar applications.

Cannelton and Newburgh Locks and Dams

The Louisville District also reports applications of Tenmat T814 and Thordon TRAXL self-lubricating bearings at Cannelton and Newburgh Locks and Dam on the Ohio River. Thordon pintle, gudgeon pin, and strut pin applications were installed on one leaf of one lock gate in 1994. At Cannelton, lock filling and emptying culvert valve trunnion pins, crosshead pins, lower connecting rod pins, fulcrum pins, upper strut spindle pins, lower strut pins, and hydraulic cylinder trunions are self-lubricating using Thordon TRAXL. This installation dates to 1992 or 1993. Cannelton also uses Kamatics crosshead pin and hydraulic cylinder trunion bushings on one gate leaf. At Newburgh, Thordon TRAXL bushings are used on the 600-ft lock chamber gate culvert strut spindle pins and lower strut pins. This application dates to 1991. No other information or ratings are available for applications at Cannelton and Newburgh.

Cascade Locks

The Cascade Locks are on the Columbia River above Bonneville Dam in the Portland District. The locks use self-lubricating bushings on floating mooring bitts. Roller bearings are KArOn V manufactured by Kamatics. The applied load is approximately 2,500 psi and the arc of rotation 360 degrees. The number of cycles averages about 240 full revolutions per day. The bearings were installed in 1997, and no problems have been reported to date. The District rates the KArOn V roller bearings as "better" than greased bronze with an overall rating of "excellent." Lubron AQ 100 bearings were previously used for this application, but were replaced after only 2 years. Squealing and stick/slip (stiction) were reported as problems. The District rates the AQ 100 roller bearings as "worse" than greased bronze with an overall rating of "poor." Thrust washer bearings are Tenmat Feroform T814. The applied load is minimal. The bearings were

installed in 1997 and no problems have been reported to date. The District rates the Feroform T814 bearings as "better" than greased bronze with an overall rating of "excellent." Floating mooring bitt guide blocks are Tenmat Feroform T814. The applied load is about 1,000 psi and the blocks experience about 720 feet of linear movement per day. The blocks were installed in 1997 and no problems have been reported to date. The District rates the T814 guide blocks as "better" than greased bronze bushings with an overall rating of "excellent."

The Cascade Locks also use self-lubricating Lubron AQ 30 miter gate pin bushings. The bearings were installed in 1996 by press fitting into a cast-steel housing. The approximated load is 2,500 psi and the arc of rotation is 40 degrees. The average number of cycles per day is 16. The District reports a problem with squealing and rates the AQ 30 miter gate pin bushings as "worse" than greased bronze with an overall rating of "poor."

The swing bridge center pivot bearing at Cascade Locks is Lubron TF 400. The applied load is about 2,500 psi and the arc of rotation is 110 degrees. The average number of cycles is 16 per day. The bearing was installed in 1994 and was replaced due to wear in 2001. The District rated wear resistance as fair, but considers the product to be better than greased bronze for this application, giving it an overall rating of only "fair." The year 2001 replacement bearing is a Kamatics KAron V with a smaller diameter and a somewhat higher load of about 3,500 psi. The District reports no problems with the new product.

John Day Lock and Dam

The John Day Lock and Dam are on the Columbia River in the Portland District. The lock uses self-lubricating bushings on the tainter valve trunnions. Bushings are TXM-Marine manufactured by Orkot. The applied load is 250 kips and the arc of rotation 40 degrees. The number of cycles averages about 1,000 per day. The bearings were installed in 2000 using an adhesive. The District has not yet rated the Orkot bushing for this application.

Little Goose Lock and Dam

The Little Goose Lock is on the Snake River in the Portland District. The District has reportedly used Garlock DU bearings in floating mooring bitts since 1984. The installation is an old one and records are sketchy. The District does not report any problems, however, and the bearings continue to function.

Colorado River Locks

The Colorado River Locks are on the Colorado River in the Galveston District. The top and bottom hinge pin bushings and thrust washer on the east lock are self-lubricating products manufactured by Thordon. The loads on the top, bottom, and thrust bearings are 285.9 kips, 809.5 kips, and 255.6 kips respectively. The arc of rotation is 60 degrees. Bearings were installed in 1998 and 1999. Top hinge pin bushings and thrust washers are HPSXL, and bottom hinge pin bushings are SXL. The District rates these self-lubricating products "equal" to greased bronze and "good" overall. Since this rating was assigned, however, the upper hinge bushing failed on the North River side sector of the East Lock. The cause of the failure is not known. The hinge has been temporarily repaired by supplying grease between the bushing and pin.

Locks and Dam No. 27

Locks and Dam No. 27 is on the Mississippi River in the St. Louis District. Miter gate hydraulic cylinder cardanic ring pillow blocks have Oiles 500 bearings manufactured by Oiles. The bearings, installed in 1998, see 60,000 cycles per year with a 20-degree arc of rotation. The District reports no problems and rates the bearing performance as "better" than greased bronze with an overall rating of "very good."

Melvin Price Locks and Dam

The Melvin Price Locks and Dam are on the Mississippi River in the St. Louis District. The dam's tainter gate trunnion bushings are Lubrite. The bushings were installed in 1982. The average number of cycles is estimated at greater than 1,000 per year with an 89-degree arc of rotation. Although the bushings have never been inspected, the District rates them "equal" to greased bronze bushings with an overall rating of "good."

Melvin Price culvert valve pivot bushings are also Lubrite. The bushings were installed in 1992 and see 60,000 cycles per year with a 60-degree arc of rotation. Some of the bushings were incorrectly sized and were cut to resize for installation. These bushings subsequently failed due to loss of lubricant plugs. The premature failure was not the fault of Lubrite or the bearing. The correctly sized bushings remain in service and are rated "equal" to greased bronze bushings with an overall rating of "good."

The lift gate downstream reaction roller bushings at Melvin Price are also Lubrite. The average number of cycles is 60,000 per year with a 360-degree arc of rotation. The bushings were installed in 1988 and the District reports no problems to date. The District rates the bushings as "better" than greased bronze bushings with an overall rating of "very good."

Kentucky Lock

The Kentucky Lock is on the Tennessee River in the Nashville District. Eight floating mooring bitts have been retrofit with self-lubricating roller bushings. Seven of these are TRAXL bushings manufactured by Thordon and one is Karon V manufactured by Kamatics. All of the retrofit mooring bitts use ultra-high molecular weight polyethylene guide blocks in place of the lower roller assembly. The bushings were installed by pressure fitting. The District has had no problems with the self-lubricating bushings, and they rate them as "better" than greased bronze and "excellent" overall.

Kentucky Lock also uses Thordon strut pin and sector gear bushings on the lower river gates. No other information is available from the District on this application.

Barkley Lock

Barkley Lock is on the Cumberland River in the Nashville District. A number of floating mooring bitts have been retrofit with self-lubricating roller bushings manufactured by Thordon. The retrofit mooring bitts use ultra-high molecular weight polyethylene guide blocks in place of the lower roller assembly. The bushings were installed by pressure fitting. The District has had no problems with the self-lubricating bushings, and they rate them as "better" than greased bronze and "excellent" overall.

Old Hickory Lock

Old Hickory Lock is on the Cumberland River in the Nashville District. A number of floating mooring bitts have been retrofit with Thordon SXL self-lubricating roller bushings. The retrofit mooring bitts use ultra-high molecular weight polyethylene guide blocks in place of the lower roller assembly. The bushings were installed by interference freeze fitting using liquid nitrogen. The applied loads on the parallel and perpendicular roller bushings are 17,333 psi

and 14,225 psi, respectively. The arc of rotation is 360 degrees. The District has had no problems with the self-lubricating bushings, and they rate them as "better" than greased bronze and "excellent" overall.

The upper and lower strut pin bearings on the upper gate at Old Hickory are Thordon TRAXL. The District has had no problems with the self-lubricating bushings, and they rate them as "better" than greased bronze and "excellent" overall.

Chicago Harbor Lock

Chicago Harbor Lock is on the Chicago River in the Chicago District. Lock sector gate rollers are equipped with Kamatics KAron V bushings. Two gates each were retrofit in 1998 and 1999. The bushings experience about 10,000 cycles per year with 360-degree arc of rotation. They were friction fitted and have snap-in side seals to prevent silt infiltration and subsequent particulate imbedment. No problems have been encountered in service. The District rates the bushings as "better" than greased bronze and gives them an overall rating of "excellent."

Sector gate upper hinge pins at Chicago Harbor Lock are also KAron V. Two gates each were retrofit in 1998 and 1999. The bushings experience about 10,000 cycles per year. No problems have been encountered in service. The District rates the bushings as "better" than greased bronze and gives them an overall rating of "excellent."

5 Olmsted Prototype Field Experiments

Experimental hydraulic-operated wicket gates were constructed in 1995 at Smithland Locks and Dam as a part of the design decision process for the Olmsted Locks and Dam project. Various materials, including greaseless bushings, were evaluated as a part of this prototype project. The wicket gate design was not used, but the data gathered on self-lubricating bushings are useful nonetheless.

Five types of self-lubricating bearings were tested and evaluated. Table 9 summarizes the products and their performance as reported by the Louisville District. According to the District, the Lubron and Thordon products were superior in performance, with Lubrite third, Rowend fourth, and Kamatics last.

Table 9. Self-lubricating material vs. performance.

Product	Performance
Lubron Bearing Systems – AQ100	The Lubron bearing showed no wear on either the main hinges of the gate or the prop bearing.
Kamatics – KAron V	Kamatics bearing failed dramatically. The inner lubricating material flaked off the housing of the bearing. The manufacturer stated they made a mistake in the design of the bearing for the test. The lubricant material also flaked off the inside of the prop bearing race.
Lubrite G12, on Bronze Alloy #424, ASTM B22-C86300 (manganese bronze)	Lubrite had begun to lose its inner lubricating surface.
Thordon SXL TRAXL on bronze – C93200	The bearings were in good condition.
Rowend R-8 - CDA 8630 (manganese bronze) with an inner lubricating material R-8.	The Rowend bearing experienced severe pitting of its base metal due to galvanic corrosion.

6 Powertech Laboratory Evaluation of Self-Lubricating Pintle Bearings

The U.S. Army Engineer Research and Development Center-Construction Engineering Research Laboratory (ERDC/CERL) contracted Powertech Labs, Inc. to perform scale model accelerated wear tests of navigation lock pintles. A scale model test frame was built to perform accelerated wear tests of current pintle bushing configurations, which serve as benchmark references, and on alternative self-lubricating pintle bushings. The experiments simulated the mechanical and environmental stresses of a lock miter gate pintle over an anticipated service life of 200,000 cycles.

Products tested were Thordon HPSXL, Tenmat T814, and Kamatics KAron V. All three products survived the tests using silt laden river water as the test medium.

Powertech observed that wear rates and even total displacement should not be used as part of the comparison criteria as each pintle/bushing combination is unique and the best criteria for assessing performance are friction levels and product appearance after the tests and, to a lesser extent, actual wear.

Based on the appearance and friction criteria, Kamatics KAron V and the Tenmat T814 survived the tests with little indication of stress. Performance levels were similar with relation to friction and appearance. However, Thordon HPSXL started showing the initial stages of material breakdown with wear debris observed clumped towards the bushing edge.

For further information on these laboratory tests, see Attachment 1.

7 Field Experience With Self-Lubricating Pintle Bearing Materials

The only self-lubricating bearing material used in an actual pintle application was for one of the upper miter gate leafs for Cannelton Lock on the Ohio River, Tell City, IN (Louisville District). The bushing material was Thordon SXL. Although it performed well, after 8 years of service it was 80 percent eroded and was removed and replaced with a similar material. Figure 1 shows that the pintle bushing displayed signs of severe wear and was completely worn away in several places. Note, however, that the pintle was undamaged (Figure 2).

Table 10 shows typical cost of miter gate pintle bushings materials, as reported by manufacturers, along with accelerated wear test results for a simulated 200,000 open/close cycles (see Attachment 1), and field experience in pintle applications.

Table 10. Pintle bushing material costs/performance data (20/24-inch diameter).

Manufacturer	Product	Cost (US \$)	Material	Accelerated Testing Results*	Field Experience (as of August 2003)
Thordon	HPSXL SXL	9,000 to 11,000	Polyurethane	Thordon HPSXL survived 200,000 cycles; clumping of wear debris shows signs of impending breakdown	Thordon SXL material performed well up to 7 yr in Ohio River (Cannelton Lock, Tell City, IN; Louisville District); 80% eroded after 8 yr
Tenmat	T814	12,000 to 14,500	Woven Phenolic	Survived 200,000 cycles; some evidence of overheating	None
Kamatics	KAron V	11,500 to 14,000	Glass flake epoxy with polytetrafluoroethylene (PTFE)	Survived 200,000 cycles; contact areas uniformly coated with lubricant; bushing contact areas polished smooth.	None

* Please see Attachment 1.

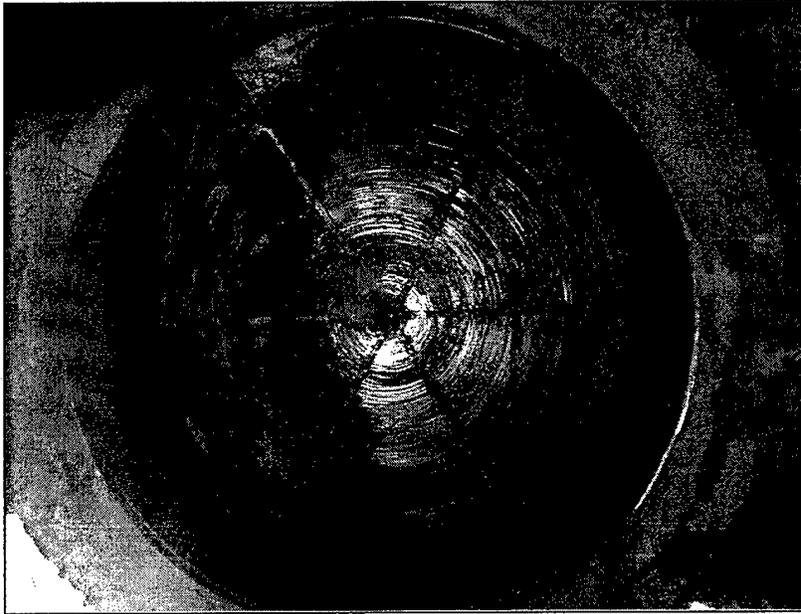


Figure 1. Self-lubricating pintle bearing with Thordon SXL material installed at Cannelton Lock in 1994; removed/replaced in July 2002; self-lubricating Thordon SXL material was approximately 80% eroded after 8 years.



Figure 2. Pintle that mated with bearing shown in Figure 1 shows very little wear after 8 years.

8 Self-Lubricated Mechanical Components: Field Performance vs Properties

No correlation was noted between material properties and actual field performance. This is not surprising given that the available data are fairly limited. There are some inconsistencies such as the unfavorable rating of KAron V by the Louisville District in the Olmsted prototype investigation. Granted the bearing did fail. This product has shown well in laboratory tests, however, and was rated excellent by field users. These discrepancies serve to highlight the relative importance of engineering design.

Another issue is that field ratings are subjective rather than analytical. For example, it is difficult to compare a subjective rating of "good" for a bearing that has provided trouble-free service for 18 years versus a bearing rated "excellent" after only 2 years of service. This may in fact merely represent pride in engineering rather than true excellence of performance.

9 Conclusions

Salient Characteristics

Important characteristics of self-lubricating bushings for navigation projects include load bearing capacity, wear rate, and coefficients of friction. Perhaps one of the most important characteristics is the difference between static and dynamic coefficients of friction. The smaller the difference in these values, the less likely it is that stick-slip will be a problem. Aside from the properties of the self-lubricating bushings, engineering design considerations are also important, particularly specifying proper clearances and mating surfaces.

Problems Encountered in Service

Stick-slip phenomena were the most frequently noted problems encountered in service. In one case, a bearing failed in service due to loss of lubricant plugs. In some cases, bearings were replaced due to wear.

Installation Techniques

The most common means of installing self-lubricating bushings is by press-fitting. Shrinking prior to installation by means of liquid nitrogen is also a common practice.

Cost Relative to Greased Bronze Bushings

Many users reported higher costs for self-lubricating bushings. In some cases, however, equal or lower cost was reported.

10 Commercial Availability

In general, all of the products found in use at USACE navigation facilities are commercially available. In some cases, bushings were not standard items and were custom fabricated due to unusual dimensions.

Engineering Support

Questionnaire respondents generally provided little information on the issue of engineering support from suppliers. The Portland District indicated that they did receive support from Kamatics and Tenmat. The Louisville District reported that Tenmat supplied them with an Microsoft Excel™ spreadsheet design tool. Garlock and Orkot both have extensive engineering literature available to customers over the Internet. None of the respondents indicated that engineering support was a problem. Lubrite Technologies reports that they offer technical design assistance and have a testing capability.

Overall Ratings of Products

It is not possible to rank order self-lubricating bushings in a meaningful manner using the available data. Bearing physical properties data vary in a nonlinear fashion. This fact complicates any simple rating scheme. In terms of making decisions about specific materials and applications, it is recommended that the specifier learn and borrow from the experience of the USACE engineering community as a whole. The information compiled herein is a useful starting point for those who wish to use self-lubricating products.

Recommended Products

Most of the bearings were found to be suitable for most of the applications where they have been employed. Most users reported performance equal to or better than greased bronze bushings. Garlock DU and Kamatics Karon V bushings are distinguished by their low coefficients of friction and smaller than average differences between static and dynamic coefficients of friction. Garlock and Orkot

provide extensive engineering data on their websites. The specification and engineering of other product installations requires significant input from the manufacturer. Garlock provides enough information to specify and design an installation without input from the supplier. This is beneficial to the extent that product selection is based on unbiased data rather than sales engineering. Although user experience is limited for Garlock DU, this product is highly recommended because of its properties, engineering data, and materials. Tenmat Ferroform T814 and Kamatics KAron V are also highly recommended because of their properties and the extensive positive field experience with these products. Tenmat also provides a software design program. Thordon TRAXL bearings are also recommended. Lubrite products have been used with uniform success. Limited field data are available at this time on the use of Orkot products within USACE.

Appendix A: Questionnaires on Self-Lubricating Bushings

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Bonneville Navigation Lock, Cascade Locks, Oregon
Name/Title/Phone Number of Contact	Ron Wridge, Mechanical Engineer (503) 808-4927
Application	Floating Mooring Bitt Guide Blocks
Bearing Manufacturer	Tenmat
Specific Product Installed	Feroform T814
Size of Bearing (length/diameter)	8"x 8"
Thickness	1"
Applied Load (if known)	~1,000 psi
Arc of Rotation (degrees)	N/A
Number of Cycles	~720 feet of linear travel/day
River Water Conditions	Fresh water with minimal contaminates
Commercial Availability (standard manufacturer product, custom item, no longer available)	Custom
Installed Cost Relative to Bronze Bushing (more, less, same)	More
Date Installed	1997
Length of Service (years/months)	4 years
How Installed	Bolted to floating mooring bitt
Mating Surface	Stainless Steel
Surface Finish	~125
Ease of Machining	Data Not Available
Problems During Installation	None
Engineering Support From Supplier	Yes
Ease of Installation	Data Not Available
Wear Resistance	Good for the mating surface's poor finish
Debris Imbedment or Contamination	
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered in Service	None

ATTRIBUTE	INFORMATION
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Better
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Excellent
Would you recommend this product for a similar application?	Yes
Additional Comments	The floating mooring bits continue to operate as intended with no operational or maintenance issues.

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Bonneville Navigation Lock, Cascade Locks, Oregon
Name/Title/Phone Number of Contact	Ron Wridge, Mechanical Engineer (503) 808-4927
Application	Floating Mooring Bitt Rollers
Bearing Manufacturer	Kamatics
Specific Product Installed	KAron V
Size of Bearing (length/diameter)	5" I.D.
Thickness	0.625"
Applied Load (if known)	~2,500 psi
Arc of Rotation (degrees)	360
Number of Cycles	240 revolutions/day
River Water Conditions	Not applicable, bearing out of water
Commercial Availability (standard manufacturer product, custom item, no longer available)	Custom
Installed Cost Relative to Bronze Bushing (more, less, same)	More
Date Installed	1997
Length of Service (years/months)	4 years
How Installed	Data Not Available
Mating Surface	300 series Stainless Steel with chrome overlay
Surface Finish	8
Ease of Machining	Data Not Available
Problems During Installation	Data Not Available
Engineering Support From Supplier	Yes
Ease of Installation	Data Not Available
Wear Resistance	Excellent
Debris Imbedment or Contamination	Data Not Available

ATTRIBUTE	INFORMATION
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered in Service	None
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Better
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Excellent
Would you recommend this product for a similar application?	Yes
Additional Comments	Rollers continue to operate as intended with no operational or maintenance issues.

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Bonneville Navigation Lock, Cascade Locks, Oregon
Name/Title/Phone Number of Contact	Ron Wridge, Mechanical Engineer (503) 808-4927
Application	Floating Mooring Bitt Rollers
Bearing Manufacturer	Lubron
Specific Product Installed	AQ 100
Size of Bearing (length/diameter)	5" I.D.
Thickness	0.625"
Applied Load (if known)	~2,500 psi
Arc of Rotation (degrees)	360
Number of Cycles	240 revolutions/day
River Water Conditions	Not applicable, bearing out of water
Commercial Availability (standard manufacturer product, custom item, no longer available)	Custom
Installed Cost Relative to Bronze Bushing (more, less, same)	More
Date Installed	1995
Length of Service (years/months)	2 years
How Installed	Press fit into stainless steel roller

ATTRIBUTE	INFORMATION
Mating Surface	300 series Stainless Steel
Surface Finish	63
Ease of Machining	Data Not Available
Problems During Installation	Data Not Available
Engineering Support From Supplier	Yes
Ease of Installation	Data Not Available
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered In Service	Squealing and stick/slip operation
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Worse
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Poor/unsatisfactory
Would you recommend this product for a similar application?	No
Additional Comments	Bearing squealed and exhibited stick/slip once the brake-in grease had dissipated. The rollers were replaced in 1997 with a new design and different self-lubricating material.

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Bonneville Navigation Lock, Cascade Locks, Oregon
Name/Title/Phone Number of Contact	Ron Wridge, Mechanical Engineer (503) 808-4927
Application	Floating Mooring Bitt Thrust Washers
Bearing Manufacturer	Tenmat
Specific Product Installed	Feroform T814
Size of Bearing (length/diameter)	5" I.D. and 7 1/2" O.D.
Thickness	3/8"
Applied Load (if known)	Minimal
Arc of Rotation (degrees)	N/A
Number of Cycles	N/A
River Water Conditions	Not in the water

ATTRIBUTE	INFORMATION
Commercial Availability (standard manufacturer product, custom item, no longer available)	Custom
Installed Cost Relative to Bronze Bushing (more, less, same)	More
Date Installed	1997
Length of Service (years/months)	4 years
How Installed	
Mating Surface	Stainless Steel
Surface Finish	32
Ease of Machining	
Problems During Installation	
Engineering Support From Supplier	Yes
Ease of Installation	Data Not Available
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered in Service	None
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Better
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Excellent
Would you recommend this product for a similar application?	Yes
Additional Comments	The floating mooring bits continue to operate as intended with no operational or maintenance issues.

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Bonneville Navigation Lock, Cascade Locks, Oregon
Name/Title/Phone Number of Contact	Ron Wridge, Mechanical Engineer (503) 808-4927
Application	Miter Gate Pin Bushings
Bearing Manufacturer	Lubron
Specific Product Installed	Lubron AQ 30
Size of Bearing (length/diameter)	Upper – Length 12", 11.25" ID Lower – Length 5 5/8", 5.2" ID
Thickness	Upper, 0.875" Lower, 0.625"
Applied Load (if known)	~2,500 psi
Arc of Rotation (degrees)	40
Number of Cycles	16/day
River Water Conditions	Not applicable, bearing out of water
Commercial Availability (standard manufacturer product, custom item, no longer available)	Custom
Installed Cost Relative to Bronze Bushing (more, less, same)	More
Date Installed	1996
Length of Service (years/months)	5 years
How Installed	Press fit into cast steel housing
Mating Surface	Stainless Steel
Surface Finish	63
Ease of Machining	
Problems During Installation	Tight Tolerances
Engineering Support From Supplier	Yes
Ease of Installation	Data Not Available
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	None
Inspection Method	
Inspection Results	Data Not Available
Problems Encountered in Service	Squealing of Joint
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Worse
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Poor/unsatisfactory

ATTRIBUTE	INFORMATION
Would you recommend this product for a similar application?	No
Additional Comments	Bearing squeals once the brake-in grease has dissipated.

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Bonneville Navigation Lock, Cascade Locks Oregon
Name/Title/Phone Number of Contact	Ron Wridge, Mechanical Engineer (503) 808-4927
Application	Swing Bridge Center Pivot Bearing
Bearing Manufacturer	Lubron
Specific Product Installed	TF400
Size of Bearing (length/diameter)	60" spherical
Thickness	~0.060 PTFE with fiberglass backing
Applied Load (if known)	~2,500 psi
Arc of Rotation (degrees)	110
Number of Cycles	16/day
River Water Conditions	Not applicable
Commercial Availability (standard manufacturer product, custom item, no longer available)	Custom
Installed Cost Relative to Bronze Bushing (more, less, same)	More
Date Installed	March 1994
Length of Service (years/months)	7 years
How Installed	
Mating Surface	304 stainless steel
Surface Finish	16
Ease of Machining	Moderate
Problems During Installation	None
Engineering Support From Supplier	Yes
Ease of Installation	
Wear Resistance	Fair
Debris Imbedment or Contamination	None
Last Inspected	March 2001
Inspection Method	Periodically analyze wear debris for fiberglass
Inspection Results	Fiberglass bundles mixed in wear debris after 6 ½ years of use.

Problems Encountered in Service	None
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Better
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Fair
Would you recommend this product for a similar application?	No
Additional Comments	A replacement bearing utilizing an improved design was installed in March 2001.

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Bonneville Navigation Lock, Cascade Locks, Oregon
Name/Title/Phone Number of Contact	Ron Wridge, Mechanical Engineer (503) 808-4927
Application	Swing Bridge Center Pivot Bearing
Bearing Manufacturer	Kamatics
Specific Product Installed	KAron V
Size of Bearing (length/diameter)	50 inch spherical
Thickness	0.040 self-lubricating liner thickness
Applied Load (if known)	~3,500 psi
Arc of Rotation (degrees)	110
Number of Cycles	16/day
River Water Conditions	Not applicable
Commercial Availability (standard manufacturer product, custom item, no longer available)	Custom
Installed Cost Relative to Bronze Bushing (more, less, same)	More
Date Installed	March 2001
Length of Service (years/months)	2 months
How Installed	
Mating Surface	17-4 PH, H900
Surface Finish	16
Ease of Machining	Moderate

ATTRIBUTE	INFORMATION
Problems During Installation	None
Engineering Support From Supplier	Yes
Ease of Installation	
Wear Resistance	Excellent
Debris Imbedment or Contamination	None
Last Inspected	March 2001
Inspection Method	Wear indication pins (continuity check across bearing)
Inspection Results	New bearing, no results yet
Problems Encountered In Service	TBD
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	TBD
Overall Rating (excellent, very good, good, poor, unsatisfactory)	TBD
Would you recommend this product for a similar application?	TBD
Additional Comments	New bearing

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Bonneville Navigation Lock, Cascade Locks, Oregon
Name/Title/Phone Number of Contact	Kevin Perletti, Mechanical Engineer (541) 374-4572
Application	Tainter Valve Connecting Rod Slide Bushings
Bearing Manufacturer	Lubron
Specific Product Installed	Lubron AQ 30
Size of Bearing (length/diameter)	Length 10", 6" ID
Thickness	0.625"
Applied Load (if known)	
Arc of Rotation (degrees)	Not Applicable, Use for sliding ²
Number of Cycles	16
River Water Conditions	Moderate silt, clams
Commercial Availability (standard manufacturer product, custom item, no longer)	Custom

ATTRIBUTE	INFORMATION
available)	
Installed Cost Relative to Bronze Bushing (more, less, same)	More
Date Installed	1993
Length of Service (years/months)	8
How Installed	Force fit, FN2
Mating Surface	17400 PH
Surface Finish	63
Ease of Machining	
Problems During Installation	
Engineering Support From Supplier	
Ease of Installation	
Wear Resistance	
Debris Imbedment or Contamination	
Last Inspected	
Inspection Method	Removal of connecting rods
Inspection Results	Never inspected
Problems Encountered in Service	None
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Same
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Very good
Would you recommend this product for a similar application?	Yes
Additional Comments	No known problems to date

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Bonneville Navigation Lock, Cascade Locks, Oregon
Name/Title/Phone Number of Contact	Kevin Perletti, Mechanical Engineer (541) 374-4572
Application	Tainter Valve Trunnion Bushings
Bearing Manufacturer	Lubron
Specific Product Installed	Lubron AQ 30
Size of Bearing (length/diameter)	Length 20", 15" ID
Thickness	0.75"
Applied Load (if known)	
Arc of Rotation (degrees)	52
Number of Cycles	16
River Water Conditions	Moderate silt, clams
Commercial Availability (standard manufacturer product, custom item, no longer available)	Custom
Installed Cost Relative to Bronze Bushing (more, less, same)	More
Date Installed	1993
Length of Service (years/months)	8
How Installed	Force fit
Mating Surface	A668
Surface Finish	63
Ease of Machining	Data Not Available
Problems During Installation	Data Not Available
Engineering Support From Supplier	Data Not Available
Ease of Installation	Data Not Available
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	1994
Inspection Method	Removal of Trunnion pins
Inspection Results	Corrosion was occurring on pins. Pin material was changed in 1994 from 668 to 8620
Problems Encountered in Service	Corrosion between A668 and Lubron bushing. Pin material replaced.
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Same
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Good

ATTRIBUTE	INFORMATION
Would you recommend this product for a similar application?	Yes with correct pin material
Additional Comments	None

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	John Day Lock & Dam, Columbia River, OR-WA
Name/Title/Phone Number of Contact	Mike Colesar, Mechanical Engineer, 541-298-7567
Application	Navlock tainter valve trunnion bushings
Bearing Manufacturer	Orkot
Specific Product Installed	TXM-Marine
Size of Bearing (length/diameter)	14" ID x 20" long, 2 bushings per valve
Thickness	0.84"
Applied Load (if known)	250 kip
Arc of Rotation (degrees)	40
Number of Cycles	1,000
River Water Conditions	Data Not Available
Commercial Availability (standard manufacturer product, custom item, no longer available)	Standard material, custom machined
Installed Cost Relative to Bronze Bushing (more, less, same)	Same
Date Installed	June 2000
Length of Service (years/months)	1 year
How Installed	Adhesive
Mating Surface	17-4 PH SS
Surface Finish	32
Ease of Machining	Fairly hard
Problems During Installation	
Engineering Support From Supplier	Data Not Available
Ease of Installation	Data Not Available
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available

ATTRIBUTE	INFORMATION
Problems Encountered In Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	TBD
Overall Rating (excellent, very good, good, poor, unsatisfactory)	TBD
Would you recommend this product for a similar application?	TBD
Additional Comments	None

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Little Goose, Dayton, WA
Name/Title/Phone Number of Contact	Phil Rider, 509-399-2233
Application	Floating Mooring Bits
Bearing Manufacturer	Garlock
Specific Product Installed	Garlock "DU" bearings
Size of Bearing (length/diameter)	Data Not Available
Thickness	Data Not Available
Applied Load (if known)	Data Not Available
Arc of Rotation (degrees)	Data Not Available
Number of Cycles	Data Not Available
River Water Conditions	Probably silty most of the year
Commercial Availability (standard manufacturer product, custom item, no longer available)	Garlock could still have some records.
Installed Cost relative to Bronze Bushing (more, less, same)	Data Not Available
Date Installed	August 1984
Length of Service (years/months)	Approx 18 years
How Installed	Nothing found on installation process, prints, or contracts.
Mating Surface	Data Not Available
Surface Finish	Data Not Available
Ease of Machining	Data Not Available
Problems During Installation	Data Not Available
Engineering Support From Supplier	Supplier was Garlock. Wayne John was the Project Engineer.

ATTRIBUTE	INFORMATION
Ease of Installation	Data Not Available
Wear Resistance	Appeared to be good.
Debris Imbedment or Contamination	Silt.
Last Inspected	Approx. 1994 or 5 (mooring bitt pulled because of other problem)
Inspection Method	Visual if problem reported (no problems reported)
Inspection Results	Didn't appear to be any major problems. They were a little tight because of silt, if I remember correct, but did move.
Problems Encountered in Service	None as yet
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Appears to be doing good.
Overall Rating (excellent, very good, good, poor, unsatisfactory)	We have had no problems with the mooring bitts.
Would you recommend this product for a similar application?	It did seem to be in pretty good shape.
Additional Comments	We had a bitt sinking, which was unrelated but while it was out we did some inspections and repairs (i.e., gaskets, anode replacement, guide repair, etc.). Mech. Foreman in 84 was Ken Weeks and the Project Engineer was Wayne John. I could not find any prints other than orig. inst. -LGN-1-5-10/1&2

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Barkley Lock – Nashville District
Name/Title/Phone Number of Contact	Rick Williams – 615-736-7824
Application	Floating mooring bitt rollers
Bearing Manufacturer	Data Not Available
Specific Product Installed	Data Not Available
Size of Bearing (length/diameter)	Data Not Available
Liner Thickness	Data Not Available
Applied Load and Pressure	Data Not Available
Arc of Rotation (degrees)	Data Not Available
Number of Cycles	Data Not Available
River Water Conditions	Data Not Available
Commercial Availability (standard manufacturer product, custom item, no longer available)	Data Not Available
Installed Cost Relative to Bronze Bushing (more, less, same)	Data Not Available
Date Installed	Data Not Available

Length of Service (years/months)	Data Not Available
How Installed	Data Not Available
Mating Surface	Data Not Available
Surface Finish	Data Not Available
Ease of Machining	Data Not Available
Problems During Installation	Data Not Available
Engineering Support From Supplier	Data Not Available
Ease of Installation	Data Not Available
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered In Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Data Not Available
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Data Not Available
Would you recommend this product for a similar application?	Data Not Available
Additional Comments	Data Not Available

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name and Location:	Rehabilitate East and West Locks, Colorado River Locks
Name and Phone Number of Contact:	Simon DeSoto – 979-863-2318 (office) - 979-863-2127 (fax)
Bearing Manufacturer:	Thordon Bearings, Inc.
Specific Bearing Product (Company Name, etc.):	Upper Bushing - HPSXL on Bronze Lower Bushing - SXL on Bronze Top Thrust Washer - SXL on Bronze Lower Thrust Washer - HPSXL on Bronze
Where Used, (Ex: "mooring bitt bushings"):	Top and Bottom Hinge Pin Bushings and Middle Thrust Washer on the East Lock-West Gate and East Lock-East Gate
Size of bearing, (Ex: "3.5" I.D. x 2.5" Long"):	Top Bushing - 10.0124" I.D. X 10" long Bottom Bushing - 12.0156" I.D. X 25.75" long Thrust Washer - 12.0156" I.D. X 24" O.D. X 0.75" thick
Applied load, if known:	Top Bushing 285.9 kips Bottom Bushing 809.5 kips Thrust Washer 255.6 kips
Date installed:	East Lock - West Gate June 1998 East Lock - East Gate February 1999
Length of service, in Years and Months:	East Lock – West Gate – 2 years and 8 months East Lock – East Gate – 2 years
Arc of Rotation, in Degrees:	60 degrees
Number of Cycles to date (or to failure, if failed). Give best estimate:	East Lock – West Gate – 100,000 cycles East Lock – East Gate – 36,000 cycles
Problems encountered:	a. During Installation Vibration initially noted on 1 (East Lock, West Gate, North Sector) of 4 sectors. Vibration eventually subsided after approximately 2 - 4 weeks; suspect bushings finally seated. b. In service The upper hinge bushing failed on the North River side sector of the East Lock (January 2004). The cause for failure is not known. The hinge has been temporarily repaired by supplying grease between the bushing and pin. c. Engineering Support from bearing manufacturer None
Bearing Performance: a. Relative to greased bronze: 1) Better than 2) Equal to 3) Poorer than 4) Much poorer than b. Overall rating as a bearing: 1) Outstanding 2) Very Good 3) Good 4) Poor 5) Totally Unsatisfactory	

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Kentucky Lock – Nashville District
Name/Title/Phone Number of Contact	Rick Williams – 615-736-7824
Application	Sector Gear
Bearing Manufacturer	Thordon
Specific Product Installed	
Size of Bearing (length/diameter)	L=7.25 inch, ID=12.500 inch
Liner Thickness	
Applied Load and Pressure	
Arc of Rotation (degrees)	
Number of Cycles	
River Water Conditions	Dry
Commercial Availability (standard manufacturer product, custom item, no longer available)	
Installed Cost Relative to Bronze Bushing (more, less, same)	
Date Installed	
Length of Service (years/months)	
How Installed	
Mating Surface	
Surface Finish	
Ease of Machining	
Problems During Installation	
Engineering Support From Supplier	
Ease of Installation	
Wear Resistance	
Debris Imbedment or Contamination	
Last Inspected	
Inspection Method	
Inspection Results	
Problems Encountered in Service	
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	
Overall Rating (excellent, very good, good, poor, unsatisfactory)	
Would you recommend this product for a similar application?	

ATTRIBUTE	INFORMATION
Additional Comments	

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Kentucky Lock – Nashville District
Name/Title/Phone Number of Contact	Rick Williams – 615-736-7824
Application	Strut Pins
Bearing Manufacturer	Thordon
Specific Product Installed	Data Not Available
Size of Bearing (length/diameter)	Data Not Available
Liner Thickness	Data Not Available
Applied Load and Pressure	Data Not Available
Arc of Rotation (degrees)	Data Not Available
Number of Cycles	Data Not Available
River Water Conditions	Data Not Available
Commercial Availability (standard manufacturer product, custom item, no longer available)	Data Not Available
Installed Cost Relative to Bronze Bushing (more, less, same)	Data Not Available
Date Installed	Data Not Available
Length of Service (years/months)	Data Not Available
How Installed	Data Not Available
Mating Surface	Data Not Available
Surface Finish	Data Not Available
Ease of Machining	Data Not Available
Problems during Installation	Data Not Available
Engineering Support from Supplier	Data Not Available
Ease of Installation	Data Not Available
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available

ATTRIBUTE	INFORMATION
Problems Encountered in Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Data Not Available
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Data Not Available
Would you recommend this product for a similar application?	Data Not Available
Additional Comments	Data Not Available

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Kentucky Lock – Nashville District
Name/Title/Phone Number of Contact	Rick Williams – 615-736-7824
Application	Floating mooring bitt rollers
Bearing Manufacturer	Thordon (7); Kamatics (1)
Specific Product Installed	Thordon TRAXL; Karon V (on 304 or 316 stainless steel)
Size of Bearing (length/diameter)	?? ; parallel rollers L=1.50 inch, ID=2.75 inch and perpendicular roller L=3.00 inch, ID=2.00 inch
Liner Thickness	??; 0.040 inch minimum
Applied Load and Pressure	Data Not Available
Arc of Rotation (degrees)	360
Number of Cycles	Data Not Available
River Water Conditions	Data Not Available
Commercial Availability (standard manufacturer product, custom item, no longer available)	Data Not Available
Installed Cost Relative to Bronze Bushing (more, less, same)	Data Not Available
Date Installed	Data Not Available
Length of Service (years/months)	Data Not Available
How Installed	Pressure fitted
Mating Surface	304 or 316 stainless
Surface Finish	32 RMS or better (shafts)
Ease of Machining	
Problems During Installation	Data Not Available

ATTRIBUTE	INFORMATION
Engineering Support From Supplier	Data Not Available
Ease of Installation	Data Not Available
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered in Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Data Not Available
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Data Not Available
Would you recommend this product for a similar application?	Data Not Available
Additional Comments	None

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Melvin Price Locks / Mississippi River – Alton, IL
Name/Title/Phone Number of Contact	Walter Wagner / 314-331-8272
Application	Lift Gate Downstream Reaction Rollers
Bearing Manufacturer	Lubrite Technologies., Hanover, MA
Specific Product Installed	ASTM B148, C95500, Type G10 internal surface lubrited
Size of Bearing (length/diameter)	12.5" long x 8" OD x 6.5" ID (nominal)
Thickness	0.711" thick
Applied Load (if known)	Data Not Available
Arc of Rotation (degrees)	360
Number of Cycles	60,000 per year
River Water Conditions	Silt, chemicals, etc.
Commercial Availability (standard manufacturer product, custom item, no longer available)	Standard manufactured product
Installed Cost Relative to Bronze Bushing (more, less, same)	N.A.
Date Installed	1988

Length of Service (years/months)	13 years
How Installed	Construction Contractor
Mating Surface	A668, Class H, 200 BHN (min.)
Surface Finish	125
Ease of Machining	N.A.
Problems During Installation	N.A.
Engineering Support From Supplier	N.A.
Ease of Installation	N.A.
Wear Resistance	N.A.
Debris Imbedment or Contamination	N.A.
Last Inspected	Never
Inspection Method	N.A.
Inspection Results	N.A.
Problems Encountered in Service	None to date.
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Better
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Very good
Would you recommend this product for a similar application?	Yes
Additional Comments	None

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Old Hickory Lock – Nashville District
Name/Title/Phone Number of Contact	Rick Williams – 615-736-7824
Application	Floating mooring bitt rollers
Bearing Manufacturer	Thordon
Specific Product Installed	Thordon SXL
Size of Bearing (length/diameter)	Parallel rollers L=2.983 inch, OD=2.896 inch Perpendicular roller L=2.796, OD=3.901 inch
Liner Thickness	

ATTRIBUTE	INFORMATION
Applied Load and Pressure	Parallel rollers 130,000 pounds and 17,333.33 PSI Perpendicular roller 130,000 pounds and 14,224.751 PSI
Arc of Rotation (degrees)	360
Number of Cycles	Data Not Available
River Water Conditions	Data Not Available
Commercial Availability (standard manufacturer product, custom item, no longer available)	Data Not Available
Installed Cost relative to Bronze Bushing (more, less, same)	Data Not Available
Date Installed	Data Not Available
Length of Service (years/months)	Data Not Available
How installed	Interference freeze fit
Mating Surface	Stainless steel
Surface Finish	Data Not Available
Ease of Machining	Data Not Available
Problems During Installation	Data Not Available
Engineering Support From Supplier	Data Not Available
Ease of Installation	Data Not Available
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered in Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Data Not Available
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Data Not Available
Would you recommend this product for a similar application?	Data Not Available
Additional Comments	None

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Old Hickory – Nashville District
Name/Title/Phone Number of Contact	Rick Williams – 615-736-7824
Application	Strut Pin Bearings, Upper and Lower
Bearing Manufacturer	Thordon
Specific Product Installed	Thordon TRAXL on ASTM B148 Bronze
Size of Bearing (length/diameter)	Upper L=6.5 inch, ID=9.011 inch Lower L=4.5 inch, ID=4.006 inch
Liner Thickness	0.125 inch
Applied Load and Pressure	Data Not Available
Arc of Rotation (degrees)	Data Not Available
Number of Cycles	Data Not Available
River Water Conditions	Data Not Available
Commercial Availability (standard manufacturer product, custom item, no longer available)	Data Not Available
Installed Cost Relative to Bronze Bushing (more, less, same)	Data Not Available
Date Installed	Data Not Available
Length of Service (years/months)	Data Not Available
How Installed	Data Not Available
Mating Surface	Data Not Available
Surface Finish	Data Not Available
Ease of Machining	Data Not Available
Problems During Installation	Data Not Available
Engineering Support From Supplier	Data Not Available
Ease of Installation	Data Not Available
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered in Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Data Not Available
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Data Not Available

ATTRIBUTE	INFORMATION
Would you recommend this product for a similar application?	Data Not Available
Additional Comments	None

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Melvin Price Locks / Mississippi River – Alton, IL
Name/Title/Phone Number of Contact	Walter Wagner / 314-331-8272
Application	Culvert Valve Pivot Bushings
Bearing Manufacturer	Lubrite Technologies, Hanover, MA
Specific Product Installed	ASTM B148, C95500, Type G10 internal surface lubricated
Size of Bearing (length/diameter)	21" long x 9" OD x 8" ID (nominal)
Thickness	0.5" thick
Applied Load (if known)	
Arc of Rotation (degrees)	60
Number of Cycles	60,000 per year
River Water Conditions	Silt, chemicals, etc.
Commercial Availability (standard manufacturer product, custom item, no longer available)	Standard manufactured product
Installed Cost Relative to Bronze Bushing (more, less, same)	More
Date Installed	1992
Length of Service (years/months)	9 years
How Installed	Hired Labor
Mating Surface	A668, Class J
Surface Finish	32
Ease of Machining	N.A.
Problems During Installation	None
Engineering Support From Supplier	N.A.
Ease of Installation	Data Not Available
Wear Resistance	N.A.
Debris Imbedment or Contamination	N.A.
Last Inspected	Never
Inspection Method	N.A.
Inspection Results	N.A.

ATTRIBUTE	INFORMATION
Problems Encountered in Service	Loss of lubricant plugs
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Worse
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Poor
Would you recommend this product for a similar application?	No
Additional Comments	The field assembly crew determined that the dimensions were incorrect. The cut through some of the lubricant holes, which caused a loss of lubricant.

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Melvin Price Locks / Mississippi River – Alton, IL
Name/Title/Phone Number of Contact	Walter Wagner / 314-331-8272
Application	Culvert Valve Pivot Bushings
Bearing Manufacturer	Lubrite Technologies, Hanover, MA
Specific Product Installed	ASTM B148, C95500, Type G10 internal surface lubricated
Size of Bearing (length/diameter)	12" long x 7" OD x 6" ID (nominal)
Thickness	0.5" thick
Applied Load (if known)	Data Not Available
Arc of Rotation (degrees)	60
Number of Cycles	60,000 per year
River Water Conditions	Silt, chemicals, etc.
Commercial Availability (standard manufacturer product, custom item, no longer available)	Standard manufactured product
Installed Cost Relative to Bronze Bushing (more, less, same)	More
Date Installed	1992
Length of Service (years/months)	9 years
How installed	Hired Labor
Mating Surface	A668, Class J
Surface Finish	32
Ease of Machining	N.A.
Problems during Installation	None

Engineering Support from Supplier	N.A.
Ease of Installation	
Wear Resistance	N.A.
Debris Imbedment or Contamination	N.A.
Last Inspected	Never
Inspection Method	N.A.
Inspection Results	N.A.
Problems Encountered In Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Same
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Good
Would you recommend this product for a similar application?	Yes
Additional Comments	None

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Locks No. 27 / Mississippi River – Granite City, IL
Name/Title/Phone Number of Contact	Walter Wagner / 314-331-8272
Application	Miter Gate Hydraulic Cylinder Cardanic Ring Pillow Blocks
Bearing Manufacturer	Oiles 500, Orebro, Sweden
Specific Product Installed	Johnson Metal JM3-15
Size of Bearing (length/diameter)	162 mm long x 225 mm OD x 200 mm ID (nominal)
Thickness	12.5 mm thick
Applied Load (if known)	Data Not Available
Arc of Rotation (degrees)	20
Number of Cycles	60,000 per year
River Water Conditions	Silt, chemicals, etc.
Commercial Availability (standard manufacturer product, custom item, no longer available)	Standard manufactured product
Installed Cost Relative to Bronze Bushing (more, less, same)	N.A.
Date Installed	1998

ATTRIBUTE	INFORMATION
Length of Service (years/months)	3 years
How installed	Construction Contractor
Mating Surface	34Cr NiMo6V, DIN 17200
Surface Finish	
Ease of Machining	N.A.
Problems during Installation	N.A.
Engineering Support from Supplier	N.A.
Ease of Installation	N.A.
Wear Resistance	N.A.
Debris Imbedment or Contamination	N.A.
Last Inspected	Never
Inspection Method	N.A.
Inspection Results	N.A.
Problems Encountered in Service	None to date.
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Better
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Very good
Would you recommend this product for a similar application?	Yes
Additional Comments	None

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	The Dalles Lock & Dam, OR/WA (Columbia River)
Name/Title/Phone Number of Contact	Steve Dingman, mech. engr., 541-298-7545
Application	Navigation Lock Operating Machinery
Bearing Manufacturer	(proposed: Orkot)
Specific Product Installed	*
Size of Bearing (length/diameter)	*
Thickness	*

Applied Load (if known)	(Upper Gate) 705K horiz. max. ; (valves) unknown
Arc of Rotation (degrees)	(Upper Gate) ~ 80 deg.; (valve) ~ 56 deg.
Number of Cycles	~ 10 lockages per day
River Water Conditions	Fresh water, moderate silt; temp. range ~ 30-70 °F
Commercial Availability (standard manufacturer product, custom item, no longer available)	*
Installed Cost Relative to Bronze Bushing (more, less, same)	*
Date Installed	*
Length of Service (years/months)	0
How Installed	*
Mating Surface	*
Surface Finish	*
Ease of Machining	*
Problems During Installation	(This page: see "Additional Comments", below)
Engineering Support From Supplier	
Ease of Installation	
Wear Resistance	
Debris Imbedment or Contamination	
Last Inspected	
Inspection Method	
Inspection Results	
Problems Encountered in Service	
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	
Overall Rating (excellent, very good, good, poor, unsatisfactory)	
Would you recommend this product for a similar application?	
Additional Comments	* No non-metallic bushings have been installed at The Dalles Dam yet. They are planning to do so on Navlock Drain Valve No. 2 in 2003, and we will replace both trunnion bushings and all operator guide bushings. Also, we are preparing to replace original bronze bushings with non-metallic bushings at the trunnions of Spill Gate No. 9.

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Melvin Price Locks / Mississippi River – Alton, IL
Name/Title/Phone Number of Contact	Walter Wagner / 314-331-8272
Application	Tainter Gate Trunnion Bushings
Bearing Manufacturer	Lubrite Technologies, Hanover, MA
Specific Product Installed	ASTM B148, C95500, Type G10 internal surface lubricated
Size of Bearing (length/diameter)	23.5" long x 25" OD x 23" ID (nominal)
Thickness	1" thick
Applied Load (if known)	Data Not Available
Arc of Rotation (degrees)	89
Number of Cycles	< 1,000 per year
River Water Conditions	Silt, chemicals, etc.
Commercial Availability (standard manufacturer product, custom item, no longer available)	Standard manufactured product
Installed Cost Relative to Bronze Bushing (more, less, same)	More
Date Installed	1982
Length of Service (years/months)	19 years
How Installed	Construction contractor
Mating Surface	A668, Class D (max. carbon = 0.30%)
Surface Finish	32
Ease of Machining	N.A.
Problems During Installation	None
Engineering Support From Supplier	N.A.
Ease of Installation	
Wear Resistance	N.A.
Debris Imbedment or Contamination	N.A.
Last Inspected	Never
Inspection Method	N.A.
Inspection Results	N.A.
Problems Encountered in Service	None
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Same
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Good
Would you recommend this product for a similar application?	Yes

ATTRIBUTE	INFORMATION
Additional Comments	None

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Chicago Harbor Lock
Name/Title/Phone Number of Contact	Steve Hungness
Application	Lock sector gates – rollers
Bearing Manufacturer	Kamatics
Specific Product Installed	KARON V
Size of Bearing (length/diameter)	9" id (2-sleeves each); ~ 7" long
Thickness	40 mils on FRP sleeve (ie. composite backing)
Applied Load (if known)	Data Not Available
Arc of Rotation (degrees)	360
Number of Cycles	10,000/year
River Water Conditions	Immersed, silt
Commercial Availability (standard manufacturer product, custom item, no longer available)	Standard product
Installed Cost Relative to Bronze Bushing (more, less, same)	Less
Date Installed	2 gates in 1998 and 2 gates in 1999
Length of Service (years/months)	
How Installed	Friction fit
Mating Surface	Stainless steel
Surface Finish	Data Not Available
Ease of Machining	Data Not Available
Problems During Installation	Data Not Available
Engineering Support From Supplier	Data Not Available
Ease of Installation	Data Not Available
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Side seal used to prevent – mfg Boosik and Champan
Last Inspected	Not
Inspection Method	N/A
Inspection Results	N/A

ATTRIBUTE	INFORMATION
Problems Encountered in Service	None
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Better
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Excellent
Would you recommend this product for a similar application?	Yes
Additional Comments	None

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Chicago Harbor Lock
Name/Title/Phone Number of Contact	Steve Hungness
Application	Upper hinge pin
Bearing Manufacturer	Kamatics
Specific Product Installed	KAron V
Size of Bearing (length/diameter)	
Thickness	
Applied Load (if known)	Low load
Arc of Rotation (degrees)	
Number of Cycles	10,000/year
River Water Conditions	In the dry
Commercial Availability (standard manufacturer product, custom item, no longer available)	Data Not Available
Installed Cost Relative to Bronze Bushing (more, less, same)	Data Not Available
Date Installed	2 gates in 1998 and 2 gates in 1999
Length of Service (years/months)	Data Not Available
How Installed	Data Not Available
Mating Surface	Data Not Available
Surface Finish	Data Not Available
Ease of Machining	Data Not Available
Problems During Installation	None reported
Engineering Support From Supplier	Data Not Available

ATTRIBUTE	INFORMATION
Ease of Installation	Data Not Available
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered in Service	None
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Data Not Available
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Data Not Available
Would you recommend this product for a similar application?	Data Not Available
Additional Comments	Data Not Available

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Markland
Name/Title/Phone Number of Contact	Todd Crutchfield – 859-567-7444
Application	Culvert valve trunnion pins 2 each per valve
Bearing Manufacturer	Tenmat
Specific Product Installed	Feroform T814
Size of Bearing (length/diameter)	13.625" dia x 24.125" L
Thickness	0.8"
Applied Load (if known)	7,000 psi
Arc of Rotation (degrees)	45
Number of Cycles	
River Water Conditions	Immersed, silt
Commercial Availability (standard manufacturer product, custom item, no longer available)	Standard item
Installed Cost Relative to Bronze Bushing (more, less, same)	About the same
Date Installed	April 2000
Length of Service (years/months)	Data Not Available

ATTRIBUTE	INFORMATION
How Installed	Data Not Available
Mating Surface	Data Not Available
Surface Finish	Data Not Available
Ease of Machining	Excellent
Problems During Installation	None
Engineering Support From Supplier	Yes, Excel spreadsheet
Ease of Installation	Very easy
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered in Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Not enough data
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Excellent
Would you recommend this product for a similar application?	Yes
Additional Comments	Very happy with installation and performance of this product to date. Installed with hard-chromed stainless steel pins, 17-4.

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	McAlpine
Name/Title/Phone Number of Contact	Todd Crutchfield – 859-567-7444
Application	Culvert valve trunnion pins 2 each per valve
Bearing Manufacturer	Tenmat
Specific Product Installed	Feroform T814
Size of Bearing (length/diameter)	13.625" ida x 24.125" L
Thickness	0.8"
Applied Load (if known)	7,000 psi

ATTRIBUTE	INFORMATION
Arc of Rotation (degrees)	45
Number of Cycles	
River Water Conditions	Immersed, silt
Commercial Availability (standard manufacturer product, custom item, no longer available)	Standard item
Installed Cost Relative to Bronze Bushing (more, less, same)	About the same
Date Installed	April 2000
Length of Service (years/months)	Data Not Available
How Installed	Data Not Available
Mating Surface	Data Not Available
Surface Finish	Data Not Available
Ease of Machining	Excellent
Problems During Installation	None
Engineering Support From Supplier	Yes, Excel spreadsheet
Ease of Installation	Very easy
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered in Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Not enough data
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Excellent
Would you recommend this product for a similar application?	Yes
Additional Comments	Very happy with installation and performance of this product to date. Installed with hard-chromed stainless steel pins, 17-4.

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Markland
Name/Title/Phone Number of Contact	Todd Crutchfield – 859-567-7444
Application	Culvert valve crosshead
Bearing Manufacturer	Tenmat
Specific Product Installed	Feroform T814
Size of Bearing (length/diameter)	8.625" dia x 6.5" L
Thickness	0.8"
Applied Load (if known)	3500 psi
Arc of Rotation (degrees)	45 degrees
Number of Cycles	Data Not Available
River Water Conditions	Data Not Available
Commercial Availability (standard manufacturer product, custom item, no longer available)	Standard product
Installed Cost Relative to Bronze Bushing (more, less, same)	Same
Date Installed	March 2000 and April 2001
Length of Service (years/months)	
How Installed	Shrink fit with liquid nitrogen
Mating Surface	Data Not Available
Surface Finish	Data Not Available
Ease of Machining	Excellent
Problems During Installation	None
Engineering Support From Supplier	Yes, Excel spreadsheet program
Ease of Installation	Very easy
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered in Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Not enough data
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Excellent

ATTRIBUTE	INFORMATION
Would you recommend this product for a similar application?	Yes
Additional Comments	Very happy with installation and performance of this product to date. Installed with hard-chromed stainless steel pins, 17-4.

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Markland
Name/Title/Phone Number of Contact	Todd Crutchfield – 859-567-7444
Application	Culvert valve lower connecting rod
Bearing Manufacturer	Tenmat
Specific Product Installed	Feroform T814
Size of Bearing (length/diameter)	8.625' dia x 12.968" L
Thickness	0.8"
Applied Load (if known)	3500 psi
Arc of Rotation (degrees)	45
Number of Cycles	Data Not Available
River Water Conditions	Data Not Available
Commercial Availability (standard manufacturer product, custom item, no longer available)	Standard product
Installed Cost Relative to Bronze Bushing (more, less, same)	Same
Date Installed	April 2000 and April 2001
Length of Service (years/months)	
How Installed	Shrink fit with liquid nitrogen
Mating Surface	Data Not Available
Surface Finish	Data Not Available
Ease of Machining	Excellent
Problems During Installation	None
Engineering Support From Supplier	Yes, Excel spreadsheet program
Ease of Installation	Very easy
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available

ATTRIBUTE	INFORMATION
Problems Encountered in Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Not enough data
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Excellent
Would you recommend this product for a similar application?	Yes
Additional Comments	Very happy with installation and performance of this product to date. Installed with hard-chromed stainless steel pins, 17-4.

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Markland
Name/Title/Phone Number of Contact	Todd Crutchfield – 859-567-7444
Application	Culvert valve fulcrum
Bearing Manufacturer	Tenmat
Specific Product Installed	Feroform T814
Size of Bearing (length/diameter)	9.125" dia x 12.344" L
Thickness	0.8"
Applied Load (if known)	3,500 psi
Arc of Rotation (degrees)	45
Number of Cycles	Data Not Available
River Water Conditions	Data Not Available
Commercial Availability (standard manufacturer product, custom item, no longer available)	Standard product
Installed Cost Relative to Bronze Bushing (more, less, same)	Same
Date Installed	April 2000 and April 2001
Length of Service (years/months)	Data Not Available
How Installed	Data Not Available
Mating Surface	Data Not Available
Surface Finish	Data Not Available
Ease of Machining	Excellent
Problems During Installation	None
Engineering Support From Supplier	Yes, Excel spreadsheet program

Ease of Installation	Very easy
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered in Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Not enough data
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Excellent
Would you recommend this product for a similar application?	Yes
Additional Comments	Very happy with installation and performance of this product to date. Installed with hard-chromed stainless steel pins, 17-4.

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Markland
Name/Title/Phone Number of Contact	Todd Crutchfield – 859-567-7444
Application	Culvert valve upper strut spindle
Bearing Manufacturer	Tenmat
Specific Product Installed	Feroform T814
Size of Bearing (length/diameter)	9.125" dia x 11.219" L
Thickness	0.8"
Applied Load (if known)	3,500 psi
Arc of Rotation (degrees)	45
Number of Cycles	Data Not Available
River Water Conditions	Immersed, silt
Commercial Availability (standard manufacturer product, custom item, no longer available)	Standard product
Installed Cost Relative to Bronze Bushing (more, less, same)	Same
Date Installed	March/April 2000 and 2001
Length of Service (years/months)	
How Installed	Shrink fit with liquid nitrogen

ATTRIBUTE	INFORMATION
Mating Surface	Data Not Available
Surface Finish	
Ease of Machining	Excellent
Problems During Installation	None
Engineering Support from Supplier	Yes, Excel spreadsheet program
Ease of Installation	Very easy
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered In Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Not enough data
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Excellent
Would you recommend this product for a similar application?	Yes
Additional Comments	Very happy with installation and performance of this product to date. Installed with hard-chromed stainless steel pins, 17-4.

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Smithland
Name/Title/Phone Number of Contact	Todd Crutchfield – 859-567-7444
Application	Culvert valve upper strut spindle
Bearing Manufacturer	Tenmat
Specific Product Installed	Feroform T814
Size of Bearing (length/diameter)	9.125" dia x 11.219" L
Thickness	0.8"
Applied Load (if known)	3500 psi
Arc of Rotation (degrees)	45
Number of Cycles	Data Not Available
River Water Conditions	Immersed, silt

ATTRIBUTE	INFORMATION
Commercial Availability (standard manufacturer product, custom item, no longer available)	Standard product
Installed Cost Relative to Bronze Bushing (more, less, same)	Same
Date Installed	October 2000
Length of Service (years/months)	
How Installed	Shrink fit with liquid nitrogen
Mating Surface	Data Not Available
Surface Finish	Data Not Available
Ease of Machining	Excellent
Problems During Installation	None
Engineering Support From Supplier	Yes, Excel spreadsheet program
Ease of Installation	Very easy
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered in Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Not enough data
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Excellent
Would you recommend this product for a similar application?	Yes
Additional Comments	Very happy with installation and performance of this product to date. Installed with hard-chromed stainless steel pins, 17-4. Replaced failed Thodon TRAXL bushings with Tenmat.

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Markland
Name/Title/Phone Number of Contact	Todd Crutchfield – 859-567-7444
Application	Culvert valve lower strut
Bearing Manufacturer	Tenmat
Specific Product Installed	Feroform T814
Size of Bearing (length/diameter)	9.125" dia x 13" L
Thickness	0.8"
Applied Load (if known)	3,500 psi
Arc of Rotation (degrees)	45
Number of Cycles	
River Water Conditions	Immersed, silt
Commercial Availability (standard manufacturer product, custom item, no longer available)	Standard product
Installed Cost Relative to Bronze Bushing (more, less, same)	Same
Date Installed	March/April 2000 and 2001
Length of Service (years/months)	
How Installed	Shrink fit with liquid nitrogen
Mating Surface	Data Not Available
Surface Finish	Data Not Available
Ease of Machining	Excellent
Problems During Installation	None
Engineering Support From Supplier	Yes, Excel spreadsheet program
Ease of Installation	Very easy
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered in Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Not enough data
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Excellent
Would you recommend this product for a similar application?	Yes
Additional Comments	Very happy with installation and performance of this product to date. Installed with hard-chromed stainless steel pins, 17-4.

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Smithland
Name/Title/Phone Number of Contact	Todd Crutchfield – 859-567-7444
Application	Culvert valve lower strut
Bearing Manufacturer	Tenmat
Specific Product Installed	Feroform T814
Size of Bearing (length/diameter)	9.125" dia x 13" L
Thickness	0.8"
Applied Load (if known)	3500 psi
Arc of Rotation (degrees)	45
Number of Cycles	Data Not Available
River Water Conditions	Immersed, silt
Commercial Availability (standard manufacturer product, custom item, no longer available)	Standard product
Installed Cost Relative to Bronze Bushing (more, less, same)	Same
Date Installed	November 1997, November 1998, October 2000
Length of Service (years/months)	
How Installed	Shrink fit with liquid nitrogen
Mating Surface	Data Not Available
Surface Finish	Data Not Available
Ease of Machining	Excellent
Problems During Installation	None
Engineering Support From Supplier	Yes, Excel spreadsheet program
Ease of Installation	Very easy
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered In Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Not enough data
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Excellent
Would you recommend this product for a similar application?	Yes

ATTRIBUTE	INFORMATION
Additional Comments	Very happy with installation and performance of this product to date. Installed with hard-chromed stainless steel pins, 17-4. Replaced failed Thodon TRAXL bushings with Tenmat.

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Markland
Name/Title/Phone Number of Contact	Todd Crutchfield -- 859-567-7444
Application	Rack bar rollers vertical (4 ea) and horizontal (3 ea); all gates on both locks
Bearing Manufacturer	Garlock
Specific Product Installed	Data Not Available
Size of Bearing (length/diameter)	Data Not Available
Thickness	Data Not Available
Applied Load (if known)	Data Not Available
Arc of Rotation (degrees)	Data Not Available
Number of Cycles	Data Not Available
River Water Conditions	Data Not Available
Commercial Availability (standard manufacturer product, custom item, no longer available)	Data Not Available
Installed Cost Relative to Bronze Bushing (more, less, same)	Data Not Available
Date Installed	September 1992
Length of Service (years/months)	Data Not Available
How Installed	Data Not Available
Mating Surface	Data Not Available
Surface Finish	Data Not Available
Ease of Machining	Data Not Available
Problems During Installation	Data Not Available
Engineering Support From Supplier	Data Not Available
Ease of Installation	Data Not Available
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available

ATTRIBUTE	INFORMATION
Problems Encountered in Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Data Not Available
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Data Not Available
Would you recommend this product for a similar application?	Data Not Available
Additional Comments	Data Not Available

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Markland
Name/Title/Phone Number of Contact	Todd Crutchfield – 859-567-7444
Application	Crosshead pin, lower connecting rod pin, fulcrum pin, strut spindle pin, and trunnion pins
Bearing Manufacturer	Thordon
Specific Product Installed	TRAXL
Size of Bearing (length/diameter)	Data Not Available
Thickness	Data Not Available
Applied Load (if known)	Data Not Available
Arc of Rotation (degrees)	Data Not Available
Number of Cycles	Data Not Available
River Water Conditions	Data Not Available
Commercial Availability (standard manufacturer product, custom item, no longer available)	Data Not Available
Installed Cost Relative to Bronze Bushing (more, less, same)	Data Not Available
Date Installed	May 1998
Length of Service (years/months)	Data Not Available
How Installed	Data Not Available
Mating Surface	Data Not Available
Surface Finish	Data Not Available
Ease of Machining	Data Not Available
Problems During Installation	Data Not Available

Engineering Support From Supplier	Data Not Available
Ease of Installation	Data Not Available
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered in Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Data Not Available
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Data Not Available
Would you recommend this product for a similar application?	Data Not Available
Additional Comments	Data Not Available

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	McAlpine
Name/Title/Phone Number of Contact	Todd Crutchfield – 859-567-7444
Application	Crosshead pin, lower connecting rod pin, fulcrum pin, strut spindle pin, lower strut pin, and trunnion pins
Bearing Manufacturer	Thordon
Specific Product Installed	TRAXL
Size of Bearing (length/diameter)	Data Not Available
Thickness	Data Not Available
Applied Load (if known)	Data Not Available
Arc of Rotation (degrees)	Data Not Available
Number of Cycles	Data Not Available
River Water Conditions	Data Not Available
Commercial Availability (standard manufacturer product, custom item, no longer available)	Data Not Available
Installed Cost Relative to Bronze Bushing (more, less, same)	Data Not Available
Date Installed	June 1998 and April 1999

Length of Service (years/months)	Data Not Available
How Installed	Data Not Available
Mating Surface	Data Not Available
Surface Finish	Data Not Available
Ease of Machining	Data Not Available
Problems During Installation	Data Not Available
Engineering Support From Supplier	Data Not Available
Ease of Installation	Data Not Available
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered in Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Data Not Available
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Data Not Available
Would you recommend this product for a similar application?	Data Not Available
Additional Comments	None

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Cannelton
Name/Title/Phone Number of Contact	Todd Crutchfield – 859-567-7444
Application	Gates – pintle, gudgeon pin, strut pin at gate
Bearing Manufacturer	Thordon
Specific Product Installed	Data Not Available
Size of Bearing (length/diameter)	Data Not Available
Thickness	Data Not Available
Applied Load (if known)	Data Not Available

ATTRIBUTE	INFORMATION
Arc of Rotation (degrees)	Data Not Available
Number of Cycles	Data Not Available
River Water Conditions	Data Not Available
Commercial Availability (standard manufacturer product, custom item, no longer available)	Data Not Available
Installed Cost Relative to Bronze Bushing (more, less, same)	Data Not Available
Date Installed	June 1994
Length of Service (years/months)	Data Not Available
How Installed	Data Not Available
Mating Surface	Data Not Available
Surface Finish	Data Not Available
Ease of Machining	Data Not Available
Problems During Installation	Data Not Available
Engineering Support From Supplier	Data Not Available
Ease of Installation	Data Not Available
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered in Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Data Not Available
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Data Not Available
Would you recommend this product for a similar application?	Data Not Available
Additional Comments	None

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Cannelton
Name/Title/Phone Number of Contact	Todd Crutchfield – 859-567-7444
Application	Crosshead pin, lower connecting rod pin, fulcrum pin, strut spindle pin, lower strut pin, trunnion pins, and hydraulic cylinder trunnion
Bearing Manufacturer	Thordon
Specific Product Installed	TRAXL
Size of Bearing (length/diameter)	Data Not Available
Thickness	Data Not Available
Applied Load (if known)	Data Not Available
Arc of Rotation (degrees)	Data Not Available
Number of Cycles	Data Not Available
River Water Conditions	Data Not Available
Commercial Availability (standard manufacturer product, custom item, no longer available)	Data Not Available
Installed Cost Relative to Bronze Bushing (more, less, same)	Data Not Available
Date Installed	1992 or 1993
Length of Service (years/months)	Data Not Available
How Installed	Data Not Available
Mating Surface	Data Not Available
Surface Finish	Data Not Available
Ease of Machining	Data Not Available
Problems During Installation	Data Not Available
Engineering Support From Supplier	Data Not Available
Ease of Installation	Data Not Available
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered in Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Data Not Available
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Data Not Available

ATTRIBUTE	INFORMATION
Would you recommend this product for a similar application?	Data Not Available
Additional Comments	None

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Cannelton
Name/Title/Phone Number of Contact	Todd Crutchfield - 859-567-7444
Application	Crosshead pin and hydraulic cylinder trunnion
Bearing Manufacturer	Kamatics
Specific Product Installed	Data Not Available
Size of Bearing (length/diameter)	Data Not Available
Thickness	Data Not Available
Applied Load (if known)	Data Not Available
Arc of Rotation (degrees)	Data Not Available
Number of Cycles	Data Not Available
River Water Conditions	Data Not Available
Commercial Availability (standard manufacturer product, custom item, no longer available)	Data Not Available
Installed Cost Relative to Bronze Bushing (more, less, same)	Data Not Available
Date Installed	1992 or 1993
Length of Service (years/months)	Data Not Available
How Installed	Data Not Available
Mating Surface	Data Not Available
Surface Finish	Data Not Available
Ease of Machining	Data Not Available
Problems During Installation	Data Not Available
Engineering Support From Supplier	Data Not Available
Ease of Installation	Data Not Available
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available

ATTRIBUTE	INFORMATION
Problems Encountered In Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Data Not Available
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Data Not Available
Would you recommend this product for a similar application?	Data Not Available
Additional Comments	None

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Newburgh
Name/Title/Phone Number of Contact	Todd Crutchfield -- 859-567-7444
Application	strut spindle pin and lower strut pin
Bearing Manufacturer	Thordon
Specific Product Installed	TRAXL
Size of Bearing (length/diameter)	Data Not Available
Thickness	Data Not Available
Applied Load (if known)	Data Not Available
Arc of Rotation (degrees)	Data Not Available
Number of Cycles	Data Not Available
River Water Conditions	Data Not Available
Commercial Availability (standard manufacturer product, custom item, no longer available)	Data Not Available
Installed Cost Relative to Bronze Bushing (more, less, same)	Data Not Available
Date Installed	July 1991
Length of Service (years/months)	Data Not Available
How Installed	Data Not Available
Mating Surface	Data Not Available
Surface Finish	Data Not Available
Ease of Machining	Data Not Available
Problems During Installation	Data Not Available
Engineering Support From Supplier	Data Not Available

ATTRIBUTE	INFORMATION
Ease of Installation	Data Not Available
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered in Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Data Not Available
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Data Not Available
Would you recommend this product for a similar application?	Data Not Available
Additional Comments	None

*** Please submit a separate Questionnaire for each application at each installation ***

ATTRIBUTE	INFORMATION
Project Name/Location	Smithland
Name/Title/Phone Number of Contact	Todd Crutchfield – 859-567-7444
Application	strut spindle pin, lower strut pin, and thrust washer
Bearing Manufacturer	Thordon
Specific Product Installed	TRAXL
Size of Bearing (length/diameter)	Data Not Available
Thickness	Data Not Available
Applied Load (if known)	Data Not Available
Arc of Rotation (degrees)	Data Not Available
Number of Cycles	Data Not Available
River Water Conditions	Data Not Available
Commercial Availability (standard manufacturer product, custom item, no longer available)	Data Not Available
Installed Cost Relative to Bronze Bushing (more, less, same)	Data Not Available
Date Installed	July 1992 and November 1998
Length of Service (years/months)	Data Not Available

How Installed	Data Not Available
Mating Surface	Data Not Available
Surface Finish	Data Not Available
Ease of Machining	Data Not Available
Problems During Installation	Data Not Available
Engineering Support From Supplier	Data Not Available
Ease of Installation	Data Not Available
Wear Resistance	Data Not Available
Debris Imbedment or Contamination	Data Not Available
Last Inspected	Data Not Available
Inspection Method	Data Not Available
Inspection Results	Data Not Available
Problems Encountered in Service	Data Not Available
Bearing Performance Relative to Greased Bronze (better, same, worse, much worse)	Data Not Available
Overall Rating (excellent, very good, good, poor, unsatisfactory)	Data Not Available
Would you recommend this product for a similar application?	Data Not Available
Additional Comments	None

Appendix B: Manufacturers' Literature

1. Orkot TXM Marine	77
2. Lubrite Technologies G10 and G12.....	82
3. Garlock DU	88
4. Tenmat Feroform T814.....	90
5. Thordon SXL and HPSXL	93
6. Kamatics KAron V	100

Orkot Composites

Orkot® TXM Marine

Orkot® TXM Marine is manufactured from medium weave fabrics with excellent mechanical strength. Additionally it has a unique low friction bearing surface incorporating molybdenum disulphide and PTFE. Orkot® TXM Marine is recommended for all bearings where a combination of strength and very low friction is required. Due to these properties TXM Marine can eliminate stick-slip in many applications.

Mechanical Properties

	IMPERIAL	METRIC
TENSILE STRENGTH	>8500 lbf/in ²	>55 N/mm ²
TENSILE MODULUS	46.5 x 10 ⁴ lbf/in ²	0.32 x 10 ⁴ N/mm ²
COMPRESSIVE STRENGTH		
Normal to Laminate	>40700 lbf/in ²	>280 N/mm ²
Parallel to Laminate	>13000 lbf/in ²	>90 N/mm ²
FLEXURAL STRENGTH	>8400 lbf/in ²	>65 N/mm ²
FLEXURAL MODULUS	27.6 x 10 ⁴ lbf/in ²	0.19 x 10 ⁴ N/mm ²
SHEAR STRENGTH	11600 lbf/in ²	80 N/mm ²
HARDNESS ROCKWELL M	100	100
IMPACT STRENGTH	-	> 120 kJ/m ²
DENSITY	0.047 lbf/in ³	1.3 g/cm ³
SWELL IN WATER	< 0.1%	< 0.1%
STATIC COEFFICIENT OF FRICTION DRY AT 15 N/mm ²		0.05 – 0.10

Thermal Properties

LINEAR EXPANSION COEFFICIENTS	86-212°F (per°F x 10 ⁻⁵)	20-100°C (per°C x 10 ⁻⁵)
Normal to Laminate	5.0 – 5.5	9 – 10
Parallel to Laminate	2.7 – 3.3	5 – 6

THE ABOVE VALUES ARE TYPICAL

For further information visit : www.orkot.us

North & South America

Orkot Composites
2535 Prairie Road
Eugene
Oregon, 97402
Tel: +1 (541) 6885523
Fax: +1 (541) 6882079
Email: enquiries.americas@orkot.com

Europe, Africa, Asia

Orkot Composites
Bradmarsh Business Park
Rotherham
S601BX
Tel: +44 (0)1709 789800
Fax: +44 (0)1709 374819
Email: enquiries@orkot.com

The information in this document is based on many years of experience in the manufacture and application of Orkot Composites products. However, unknown parameters and conditions may restrict general statements during usage. It is vital that customers satisfy themselves as to the suitability of individual products through adequate testing. For this reason, and due to the wide range of applications of our products, Smiths Group plc and Orkot Composites can accept no liability as to the suitability or correctness of our general recommendations in individual cases. For specific operating conditions please consult your Orkot Composites technical representative. Orkot® is a registered trade mark of Polymer Sealing Solutions Limited.

Orkot Composites**Orkot Materials**

Orkot manufacture a range of thermoset composite bearing materials incorporating advanced polymer technologies. These are made from technical fabrics impregnated with thermosetting resins, evenly dispersed solid lubricants and further additives to ensure the optimum solution is reached to satisfy many engineering applications.

Orkot materials have many advantages over more traditional metallic bearing materials and other polymeric bearings including:

- Low coefficient of friction
- High load capacity
- Good chemical resistance
- Operates in fresh or salt water without lubrication
- Damping of vibration
- Accommodation of shaft misalignment
- Ease of machining
- Fitting by pressing, freezing, adhesives and mechanical methods
- Dimensional stability
- Reduced thermal softening and minimal creep
- Does not encourage galvanic corrosion
- Orkot contains no asbestos or environmentally hazardous/toxic substances

Many successful applications for Orkot involve highly loaded bearings or pads operating with intermittent or oscillating movements.

Manufacturing composite bearings since 1954, Orkot have supplied components to thousands of satisfied customers world-wide in a diverse range of markets, under both the Orkot and Luytex brand names as part of a long standing relationship with the B+S Group, including:

- Railways
- Off-road vehicles
- Process equipment
- Injection moulding machines
- Pumps and Valves
- Lifting and handling equipment
- Hydropower
- Formula one racing cars
- Roll coverings
- Marine (specialised marine applications covered by other publications)

Properties / Specification

Grade	Modulus of Elasticity (GPa)	Yield Strength (MPa)	Tensile Strength (MPa)	Hardness (HV0.05)	Density (g/cm ³)	
C320/1/2 C335/C361	>300	80	60	2800	85	1.25
C324 C338	>350	80	60	3400	85	1.25
C363	>200	80	60	2800	85	1.25
C369 C378	>280	80	60	2800	85	1.25

Note, all data based on tests to BS EN ISO604:1997, BS EN ISO 178:1997, BS 2782:1993 and Orkot standard methods.

Mechanical


Under compressive load, standard Orkot grades behave in an elastic manner up to a yield point. Beyond this, permanent deformation may occur.

For most static applications, a maximum design load of 80N/mm² should be used, with 40N/mm² maximum for dynamic applications. However, dynamic application is also dependant on the PV (pressure x velocity) value (see page 12).

These values are with fully supported bearing surfaces and forces perpendicular to the laminations. For forces applied parallel to the laminations, such as on the end face of a flanged bush, only light loads should be used, typically to a maximum of 40N/mm² for static loading and 20N/mm² for dynamic. Higher loads may require the use of, for example, separate thrust washers made from a flat laminate sheet.

Higher load values than those indicated above have been used for specific applications. Please contact Orkot Product Management for assistance if your application exceeds these values.

Typical deflection under load for a cylindrical bearing

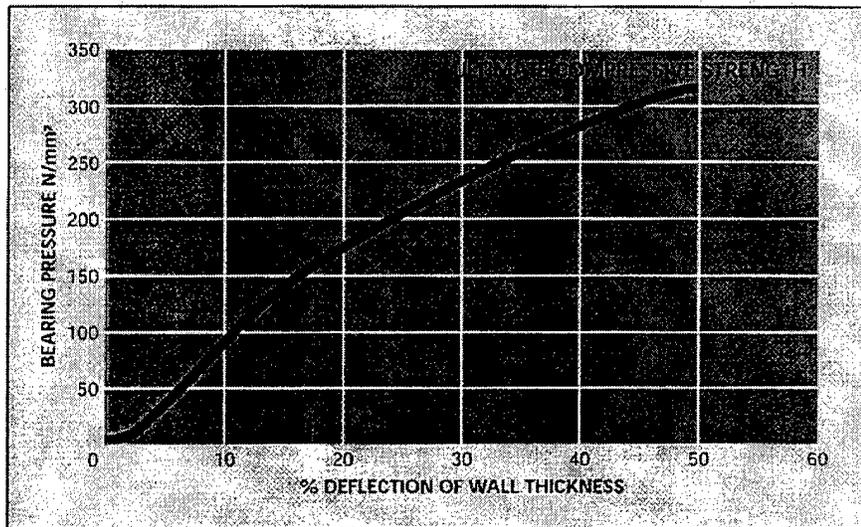

As with all composite bearings, the effective Young's Modulus in application for Orkot materials is very dependent upon the shape of the component and the support provided for it. Modulus values for Orkot standard grades range from 800 to 3000N/mm². Thus, calculating the deformation of a pad or the degree by which a shaft moves off the centre line when under load is complex and depends on the wall thickness, any shaft misalignment and the bearing clearance. Please contact Orkot Product Management for assistance if bearing deflection is important in your application.

Thermal

Orkot materials have low thermal conductivity and operate as thermal insulators. As with all polymer bearing materials, the thermal expansion of Orkot must be taken into consideration during the design process, particularly when operating at higher temperatures or with components having thick sections. As a laminate material, the coefficient of thermal expansion is different perpendicular or parallel to the layers.

The wall thickness of a bush should be kept to a minimum to limit the effect of thermal expansion and to better control clearance levels.

Orkot Composites**Swell**

Orkot endeavour to minimise the swell of their material in water, a common issue affecting polymers. The swell of Orkot standard grades is very low compared with many other materials at < 0.1% of wall thickness whilst C324 and C338 grades have a swell of <1%.

Food and potable water contact

Orkot produces a range of materials which are safe for contact with food, with all constituents listed by the Food and Drug Administration (FDA). The materials available include compounds which, by use of special resin systems, offer improved temperature and cleaning chemical resistance compared with many traditional plastic materials. The dispersed PTFE lubricant used by Orkot is also FDA listed.

C322 (TLM) has been approved for cold water applications following extensive testing to BS6920 (2000) in accordance with the Water Regulations Advisory Scheme (WRAS).

Further information on these approvals is available on request.

PV and Coefficient of friction

A major advantage of Orkot materials is their ability to withstand high loads with intermittent/oscillating movement. However, as with many polymer bearing materials, consideration must be given to the sliding faces causing frictional heat if moving for long periods.

Additives included in Orkot materials reduce the coefficient of friction and thus the heat generation. This can be further improved by use of external lubricants in the form of oil, grease, water or other process chemicals.

Many factors effect the coefficient of friction for a bearing, particularly the counter face surface finish, bearing pressure and contamination. Please contact Orkot Product Management for assistance if the coefficient of friction is critical to an application.

For information, the following table indicates some typical values found in oscillating motion with bearing pressures between 10 and 80N/mm²:

Standard & Specification		No 9103740	Rev.: A
Title: Hydroelectric Bearings with Type G10 Lubricant			
Prep. By: Manganiello ESM	Date: 5/12/00	Appr. By.: Moy 	Sheet: of

SPECIFICATION FOR LUBRITE® TYPE G10 LUBRICANT
FOR HYDROELECTRIC SERVICE

A. Bearings shall be Lubrite Self-lubricating Bearings designed and manufactured by Lubrite Technologies, 18649 Brake Shoe Road, Meadville, PA 16335 or Engineer approved equal. They shall be suitable for exposure to their applicable environment. The bearings shall be a standard product of an established bearing manufacturer with a successful performance record of ten (10) years in similar applications.

B. The bronze alloy employed in the manufacture of the bushings shall be High Strength Manganese Bronze centrifugally cast to the requirements of ASTM B271-C86300.

C. The lubricant shall consist of a combination of solids having non-deteriorating characteristics as well as inherent lubricating qualities. The lubricant shall be capable of withstanding the effects of long-term atmospheric exposure and submersion in seawater, fresh water, and most solvents. Graphite, molybdenum disulfide or other ingredients that tend to promote electrolytic or chemical action are prohibited. The use shellac, tars, solvents or other non-lubricating binder materials will not be acceptable. The Type G10 lubricant shall have a Durometer hardness of 90 on the Shore 'A' Scale when tested in accordance with ASTM D2240.

D. The lubricant shall be integrally molded and compressed into recesses provided for containment of the lubricant. The recesses shall be of sufficient depth to properly contain the lubricant and shall comprise not less than 30 percent of the total bearing area. The recesses shall be arranged in an overlapping geometric pattern with successive rows overlapping in the direction of motion. Trepan recesses, not drilled holes, shall be used for diameters 10 inches and larger.

E. The lubricant shall cover 100 percent of the bearing area and be dense and lubricative. The lubricant shall not be scraped or machined in any way after manufacture. The surface roughness of the lubricated surface shall not exceed 125 micro-inches.

F. The bushings shall have a general design capacity of not more than 8,000 psi at 10 surface feet per minute. The static coefficient of friction between the bushing and the journal shall not exceed 0.07 when subjected to a design unit loading of 2.0 KSI or greater.

G. The bushing wall thickness, fits, and tolerances shall be as recommended by the manufacturer.

H. Certificate of Compliance and Certified Mill Test Reports shall be furnished.

I. When required by the Engineer, the manufacturer shall furnish facilities for testing and inspection of the completed bearings or representative samples. If the manufacturer's facility does not permit testing, an approved independent testing laboratory may be used.

FORM 110	LUBRITE® TECHNOLOGIES, 145 Webster Street, Suite J, Hanover MA, 02339
----------	---

Standard & Specification		No 9103403	Rev.: E
Title: Lubrite® Bearings with Type G12 Lubricant			
Prep. By: Manganiello ESM	Date: 8/24/00	Appr. By.: Moy 	Sheet: of

Page 1 of 2

SPECIFICATION FOR LUBRITE® BEARINGS USING
TYPE G12 LUBRICANT

1.0 PURPOSE:

This specification is intended to provide general requirements and information for use in the design of Lubrite Bearings utilizing the Type G12 Lubrication System.

2.0 SCOPE:

This specification applies to all types of Lubrite Bearings that may be in a Bushing, Flat, Radial or Spherical configuration. Information contained in this specification should be used only as a guide. Design specific requirements and operating parameters should be forwarded to Lubrite's Design Engineering Group for review and recommendations.

3.0 DESCRIPTION:

Type G12 Lubricant is a self-lubricating, reinforced polymeric composite system that is highly wear-resistant and capable of excellent performance under extreme operating conditions. The lubricant may be re-machined or left as applied dependent upon design and/or operational requirements. This material contains no metallic or other components that may cause electrolytic or other chemical actions. Due to its polymeric nature the lubricant is unaffected by many solvents and petroleum based compounds including most greases and oils commonly encountered in structural or machine environments. Lubrite should approve any specific materials that may come in contact with the lubricated surface.

4.0 SPECIFICATIONS:

- 4.1 Design Bearing Pressures: Up to 40,000 psi
- 4.2 Coefficient of Friction Range: 0.03 - 0.10
- 4.3 Operating Temperature Range: -40°F (-40°C) to 500°F (260°C)
- 4.4 Intermittent Temperature: Up to 600°F (315°C)
- 4.5 Volume Resistivity: 1×10^{16} ohm-cm (@ 27°C)
- 4.6 Thermal Conductivity: 8.2×10^{-4} Cal - cm/sec - cm² - °C
- 4.7 Hardness: ASTM D2240, "D": 70-90^{A B}
- 4.8 Density: 0.043 Lbs./In³

5.0 APPLICATIONS:**5.1 Bushings (Radial and Spherical):**

- 5.1.1 Unless otherwise specified the lubricant shall be applied to the substrate and re-machined to obtain a minimum clearance between mating surface and lubricant of .004 inch (.10mm). The minimum lubricant film thickness shall be .009 inch (.23mm) after final machining.

Standard & Specification		No 9103403	Rev.: E
Title: Lubrite® Bearings with Type G12 Lubricant			
Prep. By: Manganiello ESM	Date: 8/24/00	Appr. By: Moy 	Sheet: of

Page 2 of 2

5.1.2 Clearances and lubricant thickness may vary dependent upon bearing size, configuration and operating conditions.

5.1.3 The substrate material shall conform to alloys UNS C95500 or UNS C95800 Nickel Aluminum Bronze. For Hydroelectric applications use Alloy UNS C86300 High Strength Manganese Bronze.

5.1.4 The bearing substrate surface shall contain retention cavities comprising not less than 25% nor more than 35% open area. Unless otherwise specified, the lubricant shall cover 100% of the lubricated surface and shall completely fill and cover all cavities to the specified minimum film thickness.

5.1.5 The mating surface of the bearing should be a corrosion resistant material such as Type 304/316 stainless steel or Inconel 625. For optimum lubricant performance the surface should be finished to a roughness no greater than 63 micro-inch RMS (1.6 micro-meter). A ground or polished surface is preferable to a finish that has been achieved through a single point tool operation.

5.2 Flat or Spherical Plates: All the preceding specifications shall apply except that lubricant film thickness shall be maintained to 0.010 inch (0.254mm) minimum and for certain applications may not necessitate re-machining.

6.0 Installation:

During installation of Lubrite Bearings, the following recommendations should be followed to avoid possible damage to the lubricant or substrate material.

- For bushing applications designed with a press fit should be inserted into the housing bore using smooth even pressure. Do not impact in any way. Do not shrink fit the bushing by means of dry ice or other cooling methods. When handling the bushing care should be exercised to avoid contact with the lubricated surface. Do not use metallic cable slings or clamps, if possible. If required, lifting eyes may be incorporated into the bearing.

Bushings are shipped complete and ready for installation when received and therefore no further machining or alterations should be done prior to or after installation. The bushing should be clean and free of dirt, dust or other foreign material prior to installation – a clean damp cloth should be used. Do not use solvents of any kind.

- For other bearing configurations the above requirements shall also apply. In addition, if any welding is to be performed in the vicinity of the bearing, care must be taken to avoid temperatures above 350°F (176°C). Temperature indicating pencils or other suitable means should be used.

FORM 110	LUBRITE® TECHNOLOGIES, 145 Webster Street, Suite J, Hanover MA, 02339
----------	---

Standard & Specification		No 9103398	Rev.: II
Title: Hydroelectric Bearings with Type G12 Lubricant			
rep. By: Manganiello ESM	Date: 5/12/00	Appr. By: Moy 7	Sheet: of

SPECIFICATION FOR LUBRITE® TYPE G12 LUBRICANT
FOR HYDROELECTRIC SERVICE

- A. Bearings shall be Lubrite Self-lubricating Bearings designed and manufactured by Lubrite Technologies, 18649 Brake Shoe Road, Meadville, PA 16335 or Engineer approved equal. They shall be suitable for exposure to their applicable environment. The bearings shall be a standard product of an established bearing manufacturer with a successful performance record of ten (10) years in similar applications.
- B. The bronze alloy employed in the manufacture of the bushings shall be High Strength Manganese Bronze centrifugally cast to the requirements of ASTM B271-C86300.
- C. The lubricant shall consist of a combination of solids having non-deteriorating characteristics as well as inherent lubricating qualities. The lubricant shall be capable of withstanding the effects of long-term atmospheric exposure and submersion in seawater, fresh water, and most solvents. Graphite, molybdenum disulfide or other ingredients that tend to promote electrolytic or chemical action are prohibited. The use shellac, tars, solvents or other non-lubricating binder materials will not be acceptable. The Type G12 lubricant shall have a Durometer hardness of between 70 - 90 on the Shore 'D' Scale when tested in accordance with ASTM D2240.
- D. The lubricant shall be integrally molded and compressed into recesses provided for containment of the lubricant. The recesses shall be of sufficient depth to properly contain the lubricant and shall comprise not less than 30 percent of the total bearing area. The recesses shall be arranged in an overlapping geometric pattern with successive rows overlapping in the direction of motion. Trepan recesses, not drilled holes, shall be used for diameters 10 inches and larger.
- E. The lubricant shall cover 100 percent of the bearing area and be dense and lubricative. The lubricant shall not be scraped or machined in any way after manufacture. The surface roughness of the lubricated surface shall not exceed 125 micro-inches.
- F. The bushings shall have a general design capacity of not more than 8,000 psi at 10 surface feet per minute. The static coefficient of friction between the bushing and the journal shall not exceed 0.07 when subjected to a design unit loading of 2.0 KSI or greater.
- G. The bushing wall thickness, fits, and tolerances shall be as recommended by the manufacturer.
- H. Certificate of Compliance and Certified Mill Test Reports shall be furnished.
- I. When required by the Engineer, the manufacturer shall furnish facilities for testing and inspection of the completed bearings or representative samples. If the manufacturer's facility does not permit testing, an approved independent testing laboratory may be used.

Standard & Specification		No 9103454	Rev.: C
Title: Hydroelectric Bearings with Type G12 Lubricant			
Prep. By: Manganiello ESM	Date: 5/12/00	Appr. By.: Mof <i>(Signature)</i>	Sheet: of

SPECIFICATION FOR LUBRITE® TYPE G12 LUBRICANT
FOR HYDROELECTRIC SERVICE

- A. Bearings shall be Lubrite Self-lubricating Bearings designed and manufactured by Lubrite Technologies, 18649 Brake Shoe Road, Meadville, PA 16335 or Engineer approved equal. They shall be suitable for exposure to their applicable environment. The bearings shall be a standard product of an established bearing manufacturer with a successful performance record of ten (10) years in similar applications.
- B. The bronze alloy employed in the manufacture of the bushings shall be Nickel Aluminum Bronze centrifugally cast to the requirements of ASTM B271-C95500 or C95800.
- C. The lubricant shall consist of a combination of solids having non-deteriorating characteristics as well as inherent lubricating qualities. The lubricant shall be capable of withstanding the effects of long-term atmospheric exposure and submersion in seawater, fresh water, and most solvents. Graphite, molybdenum disulfide or other ingredients that tend to promote electrolytic or chemical action are prohibited. The use shellac, tars, solvents or other non-lubricating binder materials will not be acceptable. The Type G12 lubricant shall have a Durometer hardness of between 70 – 90 on the Shore 'D' Scale when tested in accordance with ASTM D2240.
- D. The lubricant shall be integrally molded and compressed into recesses provided for containment of the lubricant. The recesses shall be of sufficient depth to properly contain the lubricant and shall comprise not less than 30 percent of the total bearing area. The recesses shall be arranged in an overlapping geometric pattern with successive rows overlapping in the direction of motion. Trepan recesses, not drilled holes, shall be used for diameters 10 inches and larger.
- E. The lubricant shall cover 100 percent of the bearing area and be dense and lubricative. The lubricant shall not be scraped or machined in any way after manufacture. The surface roughness of the lubricated surface shall not exceed 125 micro-inches.
- F. The bushings shall have a general design capacity of not more than 5,000 psi at 10 surface feet per minute. The static coefficient of friction between the bushing and the journal shall not exceed 0.07 when subjected to a design unit loading of 2.0 KSI or greater.
- G. The bushing wall thickness, fits, and tolerances shall be as recommended by the manufacturer.
- H. Certificate of Compliance and Certified Mill Test Reports shall be furnished.
- I. When required by the Engineer, the manufacturer shall furnish facilities for testing and inspection of the completed bearings or representative samples. If the manufacturer's facility does not permit testing, an approved independent testing laboratory may be used.

Standard & Specification		No 9103165	Rev.: F
Title: Hydroelectric Bearings with Type G10 Lubricant			
rep. By: Manganiello <i>ESM</i>	Date: 5/12/00	Appr. By.: <i>Mo</i>	Sheet: of

**SPECIFICATION FOR LUBRITE® TYPE G10 LUBRICANT
FOR HYDROELECTRIC SERVICE**

- A. Bearings shall be Lubrite Self-lubricating Bearings designed and manufactured by Lubrite Technologies, 18649 Brake Shoe Road, Meadville, PA 16335 or Engineer approved equal. They shall be suitable for exposure to their applicable environment. The bearings shall be a standard product of an established bearing manufacturer with a successful performance record of ten (10) years in similar applications.
- B. The bronze alloy employed in the manufacture of the bushings shall be Nickel Aluminum Bronze centrifugally cast to the requirements of ASTM B271-C95500 or C95800.
- C. The lubricant shall consist of a combination of solids having non-deteriorating characteristics as well as inherent lubricating qualities. The lubricant shall be capable of withstanding the effects of long-term atmospheric exposure and submersion in seawater, fresh water, and most solvents. Graphite, molybdenum disulfide or other ingredients that tend to promote electrolytic or chemical action are prohibited. The use of shellac, tars, solvents or other non-lubricating binder materials will not be acceptable. The Type G10 lubricant shall have a Durometer hardness of 90 on the Shore 'A' Scale when tested in accordance with ASTM D2240.
- D. The lubricant shall be integrally molded and compressed into recesses provided for containment of the lubricant. The recesses shall be of sufficient depth to properly contain the lubricant and shall comprise not less than 30 percent of the total bearing area. The recesses shall be arranged in an overlapping geometric pattern with successive rows overlapping in the direction of motion. Trepan recesses, not drilled holes, shall be used for diameters 10 inches and larger.
- E. The lubricant shall cover 100 percent of the bearing area and be dense and lubricative. The lubricant shall not be scraped or machined in any way after manufacture. The surface roughness of the lubricated surface shall not exceed 125 micro-inches.
- F. The bushings shall have a general design capacity of not more than 5,000 psi at 10 surface feet per minute. The static coefficient of friction between the bushing and the journal shall not exceed 0.07 when subjected to a design unit loading of 2.0 KSI or greater.
- G. The bushing wall thickness, fits, and tolerances shall be as recommended by the manufacturer.
- H. Certificate of Compliance and Certified Mill Test Reports shall be furnished.
- I. When required by the Engineer, the manufacturer shall furnish facilities for testing and inspection of the completed bearings or representative samples. If the manufacturer's facility does not permit testing, an approved independent testing laboratory may be used.



Languages:



Glacier Garlock Bearings

Self-lubricating and Prelubricated Bearings

Glacier Garlock Bearings is proud to be the world's largest manufacturer of metal-polymer plain bearings.

More than 50,000 customers worldwide use products from our full line of self-lubricated, marginally lubricated and fully lubricated plain bearings. Our products are available in a variety of forms such as cylindrical wrapped bushes, flanged bushes, thrust washers, or as special parts manufactured to customer requirements. Whatever your project requires, our experts will work with you to find the perfect bearings solution.

To meet your bearings needs, we offer:

- an extensive product range including lead-free, self-lubricated bearings compliant with ELV legislation
- sophisticated R&D facilities and test centers
- superior Application Engineering support
- flexible manufacturing for diverse applications
- 20 locations in 17 countries
- a comprehensive network of distributors

[Home](#) | [Contact Us](#) | [Site Map](#) | [Search](#)

News

9/29/2003

[New hydropower bearings brochure for U.S.](#)

9/29/2003

[AUMA names Glacier Garlock Bearings supplier of the year](#)

9/29/2003

[Fischer named president of Glacier Garlock Bearings](#)

EnPro
Industries

Glacier Garlock Bearings is an operation of EnPro Industries, Inc. (NYSE: NPO), a leader in sealing products, metal polymer bearings, compressor systems and other engineered products for use in critical applications by industries worldwide.

©2003 Glacier Garlock Bearings. All rights reserved.

[Legal Disclaimer](#) | [Environmental Management Policy Statement](#)




Metal-Polymer Materials

Solid Polymer

Fibre-Reinforced Plastic Composite Materials

Monometallic Materials

Other Products


Products
Products

Metal-Polymer Materials

Bearing materials for non-lubricated applications (DU®, DU™-B, DP4™, DP20™ DM™), marginally lubricated (DX®, DS™, HX™) and lubricated applications (DP4™, DP30™, DP31™).


Solid Polymer

Compound materials processed using injection-moulding techniques. These engineering polymers include PBT (Polyester) based (MF™41, MF™31, MF™38), POM (Acetal) based (Glacetal KA™, MF™52), PA (Nylon) based (EP™), PPS-based (MF™62) and high temperature based materials (Torton®, MF™15 and EP™72). These materials are available as special parts and geometries including co-injected forms (HP).


Fibre-Reinforced Plastic Composite Materials

Various fibre-reinforced thermosetting plastic bearings, including high-performance, filament-wound products such as GAR-FIL™, GAR-MAX®, High Strength GAR-MAX®, deva.tex®.


Monometallic Materials

A range of oil-impregnated sintered bronze bearings, solid bronze bushes. Products include sintered bronze (DIN 1850) and solid bronze (LB9-Machined Bronze, MBZ-B09™, LD™, LDD™).


Other Products

Additional product families to complement the above GGB product portfolio, e.g. specialized housings and assemblies, bi-metallic bearings.

EP™, KA™, MULTI-FIL™, DU®, DU™-B, DP4™, DP20™, DP30™, DP31™, DM™, DX®, DS™, and HX™ are trademarks of Glacier Garlock Bearings.
 MF™ and HP™ are trademarks of L+S Kunststofftechnologie GmbH, Germany.
 Torton® is a registered trademark of Solvay Advanced Polymers, LLC.
 MBZ-B09™, LD™, LDD™ are trademarks of Wieland Werke GmbH, Germany.
 DEVA™, deva.bm®, deva.metal®, deva.glide® and deva.tex® are trademarks of Federal Mogul Devs GmbH, Germany.
 Exalign™ is a product of Cryptic Arvis Ltd, England.
 Mini™ and UNI™ are trademarks of EnPro Industries Inc., USA.

©2003 Glacier Garlock Bearings. All rights reserved.

[Legal Disclaimer](#) | [Environmental Management Policy Statement](#)

FEROFORM HYDRO INDUSTRY COMPOSITES

CONTENTS

	Page
A World of Materials from TENMAT	2
Introduction	3
Benefits	4
Applications	5
Technical Data	6
Availability	6
Treatments	6
Machining	7
Quality Assurance	7
Health & Safety	7
TENMAT Companies	8


FEROFORM

The FEROFORM range of materials has been developed by TENMAT to offer the design engineer the chance of replacing metallic, rubber and asbestos based materials with unique, non-asbestos, wearing and bearing composites capable of duplicating, and in some cases exceeding, the performance of asbestos composites.

FEROFORM materials possess strength, durability, dimensional stability and excellent wear characteristics besides exhibiting good resistance to attack by many chemicals.

The resins used have been selected for their good mechanical properties and high thermal and dimensional stability. Both organic and synthetic fibres employed for reinforcement of the resins have been selected from the many types available for their high modulus and stability in water and various chemicals.

The addition of selected friction modifiers such as PTFE (T814) or oil, graphite and molybdenum disulphide enhances the wear properties and life of the materials, enabling them to be operated at higher speeds and loads.

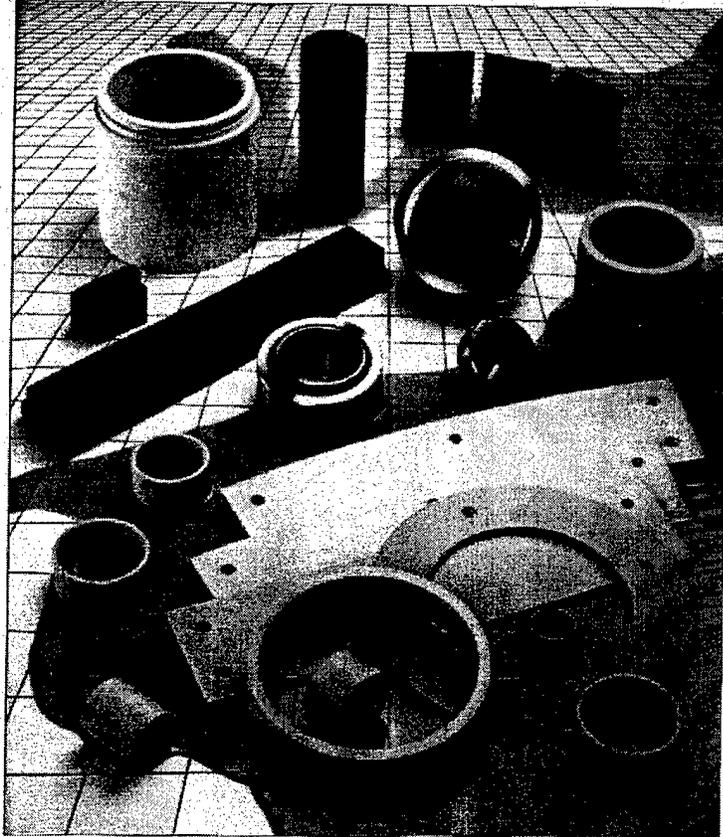

Tenmat Feroform

The U.S. Army Corps of Engineers identified a need for a self lubricating bearing material to replace its existing grease lubricating bronze bearings in some 300 large hydro-turbines in the USA when they come up for rehabilitation. However, there was a lack of any detailed historical data regarding performance and life span, so an extensive laboratory test program was set up which simulated worst case conditions, carried out at Powertech Labs in Vancouver, a subsidiary of BC Hydro. TENMAT FEROFORM T814 proved itself capable of operating in both dry and wet conditions of shaft mis-alignment

or deflection underload. Extremely low wear rates indicating long life projection were recorded and the journal showed no sign of wear throughout the test.



Sludge Gate

BENEFITS

ADVANTAGES

FEROFORM composites are extremely versatile materials which have the following advantages over conventional materials in wearing and bearing applications.

Excellent resistance to wear - FEROFORM materials show consistently low wear rates in all application areas.

Excellent abrasion resistance - FEROFORM materials can be used in environments where abrasive particles are present.

Low coefficient of friction - enabling higher speeds to be used and heavier payloads to be carried. This minimises inertial problems (stick slip) and affords lower power requirements. FEROFORM shows consistently lower friction rates than all other competitive materials.

A degree of elasticity - enabling misalignment to be taken up without damage or fracturing.

User friendly - the lubricant is evenly dispersed throughout the matrix. Bearings can be machined in situ or modified on site without loss of lubricational properties.

Excellent resilience - FEROFORM has the ability to absorb high shock loading and impact which would extrude other materials.


Lightweight - approximately 1/5 to 1/8 the weight of phosphor bronze making refurbishment work easier.

Good chemical resistance - all FEROFORM grades perform satisfactorily in the presence of most mineral and organic acids, solvents, organic bases and non-caustic alkali.


Easy installation - Can be installed by press, draw bar or freeze (dry ice or liquid nitrogen) fitting.

PERFORMANCE


FEROFORM T814 PERFORMANCE-STATIC FRICTION

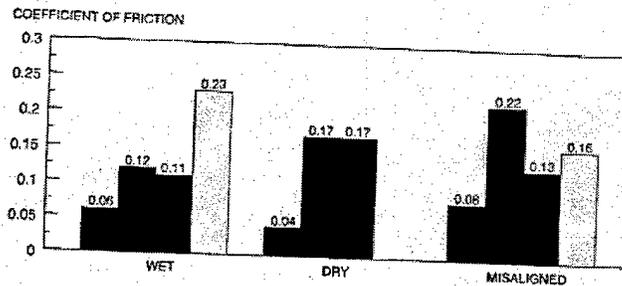

FEROFORM T814 PERFORMANCE-WEAR

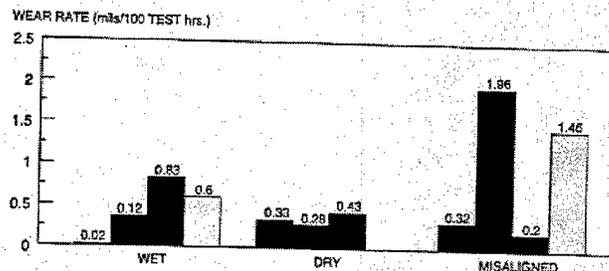

FEROFORM T814 PERFORMANCE-DYNAMIC FRICTION

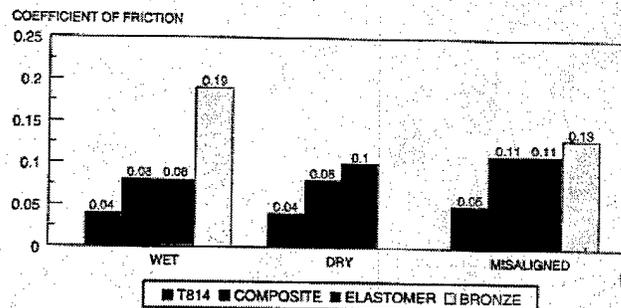

Test results taken from Powertech Labs INC. A subsidiary of B.C. Hydro, Canada

TECHNICAL DATA

Properties	Units	T814	T11	T12	T14
Ultimate Compressive Strength	MPa (psi)	250 (36,250)	280 (40,600)	280 (40,600)	300 (43,300)
Normal Maximum Working Pressure	MPa (psi)	62 (8,990)	62 (8,990)	62 (8,990)	65 (9,425)
Compressive Yield @ 68.9 MPa (@10,000psi)	%	5	2	2	2.2
Flexural Strength	MPa (psi)
Impact Strength (Notched Charpy)	KJ/m ²	35	45	45	50
Shear Strength	MPa (psi)	70 (10,150)	70 (10,150)	70 (10,150)	80 (11,600)
Inter Laminae Bond Strength	kN	2.5 (560)	2.5 (560)	2.5 (560)	3 (672)
Density	g/cm ³	1.25*	1.32	1.32	1.35
Brinell Hardness		25	25	25	25
% Swell in Water (Normal to Laminae)	@20°C (70°F)	0.35	0.35	0.35	0.35
	@50°C (125°F)	1	1	1	1
Coefficient of Friction	Dry	0.04-0.08	0.09-0.12	0.08-0.16	0.13-0.18
	Wet	0.06-0.09	0.11-0.15	0.11-0.18	0.16-0.22
Coefficient of Linear Expansion (Normal to Laminae) x10 ⁻⁶ (Parallel to Laminae) x10 ⁻⁴	per°C (per°F)	50 (28)	50 (28)	50 (28)	50 (28)
	per°C (per°F)	45 (25)	45 (25)	45 (25)	45 (25)
Maximum Working Temperature	°C (°F)	100 (212)	100 (212)	100 (212)	100 (212)
Intermittent Temperature Capability	°C (°F)	120 (250)	120 (250)	120 (250)	120 (250)

* Due to the flexibility of T grades it is not possible to measure flexural strength but no fracturing occurred.

Ultimate Compressive strengths of tube wrapped materials are typically :-
T814 220 MPa, T11 240 MPa, T12 240 MPa, T14 250 MPa

Friction levels in hydrodynamic conditions have been recorded at 0.01 with water and 0.016 with oil.

Tests above conducted generally in accordance with BS2782 and ASTM test methods. The values above are typical test results on sheet material and should not be taken as guaranteed, for specifications or primary selection of materials. The information herein is presented in good faith but TENMAT does not warrant the conformity of its materials to the listed properties or the suitability of its materials for any particular purpose. In the event of any uncertainty regarding suitability for any application please contact our technical staff on Tel: +44 (0) 161 872 2181 Fax: +44 (0) 161 872 7596

AVAILABILITY

FEROFORM can be supplied in tube, sheet or rod form and as fully machined components.

Tube

- 20-200mm (¾" - 7¾") ID & 30-250mm (1¼" - 10") OD
Minimum Wall Thickness 5mm (¾") Tolerance +0/-1mm (+0/-0.04") ID
 - 200-600mm (8" - 23¾") ID & 260-700mm (10" - 27¾") OD
Minimum Wall Thickness 10mm (¾") up to 400mm (15 ¾") OD and 20mm (¾") thereafter. Tolerance +0/-2mm (+0/-0.08") ID
- All OD is sanded to +/-1% of nominal OD

Rod

- 19 - 111mm (¾" - 4¾") OD x 1220mm (48") long
Tolerance +0/-1mm
- 117 - 158mm (4¾" - 6¼") OD x 305mm (12") long
Tolerance +0/-1mm

Sheet

- 1.6 - 100mm (¼" - 4") thickness 1220 x 1220mm (48"x48")
Tolerance thickness 1.25 - 10mm (0.05" - ¾") unsanded,
+/-0.1mm (+/-0.004") sanded; -0/+3mm (-0/+¼") length & width
Larger sizes and special mouldings available on request

TREATMENTS

For applications above 70°C (160°F) we recommend that FEROFORM is heat stabilised prior to machining to maintain their required dimensions. Heat treatment is denoted by suffix 7 e.g. T127.

Oil impregnation (suffix 1) can reduce running friction and aid bedding in.

MoS₂ (suffix 8) treatment can be used instead of oil for dusty environments.


Special TENMAT bedding in paste is recommended for T814 to reduce friction and minimise wear.

Thordon Bearings Applications

CoppedgeMarine Inc. Business Partners

Thordon

Industrial Bearing Grades and Related Products

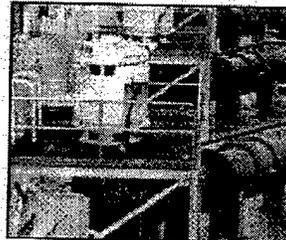


Thordon Bearings offer many proven user benefits:


- Self-lubricating
- Long Life
- High Resilience/Impact Resistance
- Low Operating Friction
- High Abrasion Resistance
- Easily Machined and Installed
- Corrosion Resistance
- Accommodates Edge Loading
- Pollution-Free
- Noise Reduction

Industrial Bearing Grades and Associated Products

The XL Grade is the standard grade for pump bearing applications. These bearings are available in a wide range of sized in both grooved and un-grooved configurations.

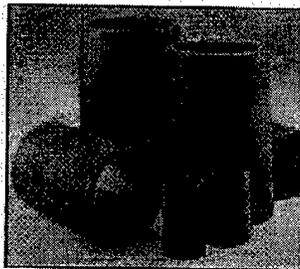


The SXL Grade is the preferred choice for dry start-up operation, the SXL offers a lower dry coefficient of friction and similar wear life and abrasive resistance when compared to the XL grade.

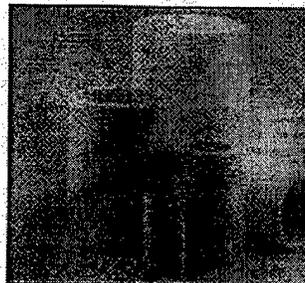


Thordon Bearings Applications


Thordon Composite Bearings are specifically formulated to provide outstanding wear life in abrasive operating conditions. These bearings out lasts other bearings by a factor of several times and are available in a wide range of sizes in a grooved configuration only.

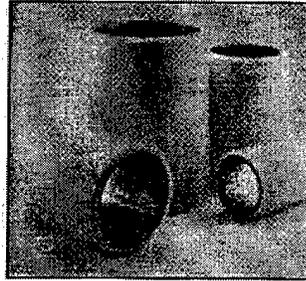


Thordon Metal Backed Bearings are produced by polymerizing any of the three Thordon Grades into a metallic housing. Originally developed to meet the needs of the nuclear power industry, this design is now specified in many other applications.

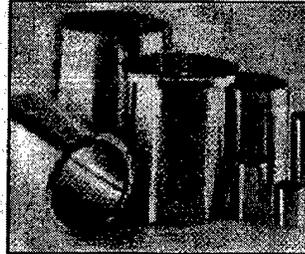

Thordon HPSXL is a harder, stiffer polymer compared to SXL, can be specified to higher design pressures and has a lower dry coefficient of friction than SXL.

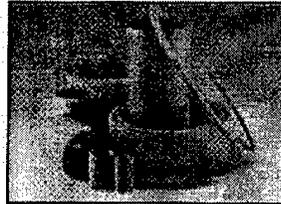

Thordon TRAXL refers to a special bearing configuration developed for high pressure applications with slow speed oscillating or full rotation motion where frictional heat generation is minimal.

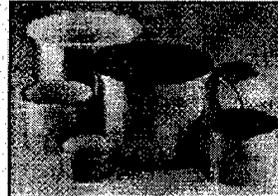

Thordon Wear Strips: The SXL or HPSXL can be supplied in strip or sheet form, or molded to the exact requirements of the application.



Thor-tape: Thordon SXL is also available as Thor-tape, a product supplied in a range of thicknesses up to 0.125" (3.2mm) and widths up to 12" (300mm). Ask us about other applications of this product.

The Recognized Choice For Long Life, Low Friction Bearing Systems

Reliability, long life and superior customer service have made Thordon Bearings Inc. the standard with hydro-electric power producers for pollution free, low friction bearing systems. When specifying operating mechanism bearings, water-lubricated turbine main shaft guide bearings and pump bearings; Thordon is the proven choice for value and performance for both rehabilitation and new turbine projects.

Thordon Bearings' design engineers provide customers with bearing system designs that meet or exceed their specifications. Depending on the application, the optimum bearing can be selected from several Thordon grades and configurations.

Recently, concern over down-stream pollution caused by grease and oil lubricated bearings has placed increased emphasis on non-polluting bearing systems. Thordon Bearings, a pioneer in the development of grease-free bearing designs, supplied bearings in 1974 for installation at Ontario Hydro's Niagara Fall's station. Today, these bearings continue to perform well.

Originally developed over 25 years ago as a high performance pump bearing, Thordon is an elastomeric polymer alloy that provides exceptional wear life. Thordon SXL, with its inherent low coefficient of friction and grease-free operation, is particularly well suited for high pressure hydro-turbine applications. Thordon's

proven performance in vertical pumps led to its use in water-lubricated turbine main shaft guide bearings, with shaft diameters ranging from mini-turbines to the largest units in service.


Today, with trouble free installations around the world, Thordon Bearings Inc. is a recognized leader in the design, manufacture and supply of hydro-turbine bearing systems. All Thordon bearings are manufactured to **ISO 9002 Quality System** requirements ensuring high quality and consistency.

For power utilities and turbine manufacturers who demand the best in value, performance and service; Thordon hydro-electric turbine bearing systems are the proven, reliable solution.

Thordon Features Offer Proven User Benefits

Thordon Bearings' field proven hydro-turbine bearing systems offer significant technical and customer benefits:

- **Low Friction**
- **Long Life**
- **Pollution Free**
- **Sizing Flexibility - Easily Machined**
- **High Abrasion Resistance**
- **High Resilience/Impact Resistance**
- **No Need for Hardened, Ground Journals**
- **High Pressure Capacity**
- **Accommodate Edge Loading**
- **Wet Or Dry Operation**
- **Lip Seal Availability**
- **Extensive Application References**

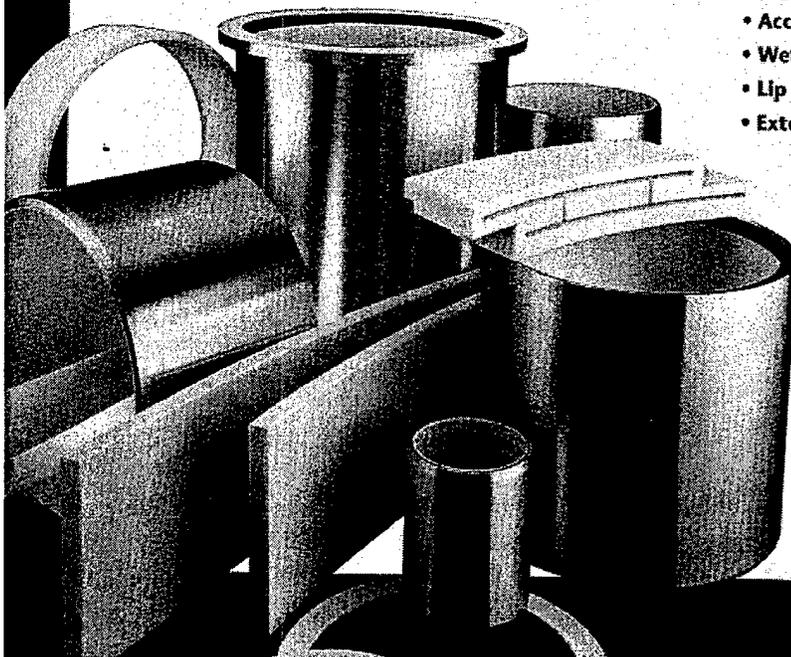

Low Friction: Thordon SXL bearings exhibit a very low coefficient of friction. This is true whether the bearing is operating dry or submerged in water. A low bearing coefficient of friction is essential in the smooth and reliable functioning of hydro-turbine operating mechanisms.

Tests conducted by an independent hydro-turbine laboratory determined that the dry coefficient of friction of Thordon SXL TRAXL bearings falls in a range from 0.09 to 0.05 tested at pressures ranging from 18 to 70 MPa (2,600 to 10,000 psi). Thordon's coefficient of friction decreases as bearing operating pressures increase, whereas metallic bearings experience dramatic increases in the coefficient of friction and tend to gall as operating pressures rise. This characteristic makes Thordon an ideal choice for high head installations where pressures are high and smooth precise operation of the gates is vital. Thordon performs well as an un-sealed wicket gate bearing because the coefficient of friction of Thordon wet is lower than dry.

Wet or dry; low or high pressure; static or dynamic; Thordon SXL TRAXL bearings operate smoothly and without stick-slip in hydro-turbine operating mechanisms.


Long Life: Since 1974, Thordon bearings have been fitted to hydro-turbine operating mechanisms. The bearings of the first installation remain in operation today as a testament to Thordon's exceptional wear life. Thordon continues to provide outstanding life in a large and growing number of installations since that time.

Only 0.13 mm (0.005") wear on an 88.9 mm (3.500") I.D. Thordon SXL TRAXL bearing was predicted in 25 years of simulated operation in a pump-turbine wicket gate application when tested by an independent hydro-turbine laboratory. Test pressures were 20.7 MPa (3000 psi) with operational parameters appropriate for a highly utilized pump storage turbine. Self-lubricated metallic bearings in the same test were predicted to show the same wear after less than nine years. Bearing journal wear was also examined and there was no significant wear of the shaft running against Thordon whereas the metallic bearings tested wore the journal proportionally to their own wear rate.


In the field, Thordon bearings have earned a reputation for performing particularly well in abrasive environments and in the extreme duty cycles of pump turbine applications. Thordon SXL TRAXL bearings were chosen over competitive metallic bearings in a recent test in a pump storage turbine experiencing accelerated bearing wear. Thordon was selected after less than one year's operation showed negligible wear compared to significant wear on the metallic bearings.

Evaluation of Bearing Friction and "Stick Slip"


Recent tests in the Thordon Bearings Test Facility evaluated the frictional performance of several competitive bearings compared to Thordon. The tests also detected induced stick-slip vibration. 101 mm (4.0") diameter bearings were loaded to a constant pressure of 24.0 MPa (3500 psi) and cycled through an oscillation of $\pm 35^\circ$ at a velocity of 0.003 m/sec. (0.62 ft./min). Tests were run for 8 hours with coefficient of friction, temperature and pressure readings taken 20 times per second for a 60 second period at the start, at 0.5 hours and then on the hour for the balance of the test. Temperature values were measured at the shaft immediately adjacent to the bearing. The test results are summarized in the graphs below.

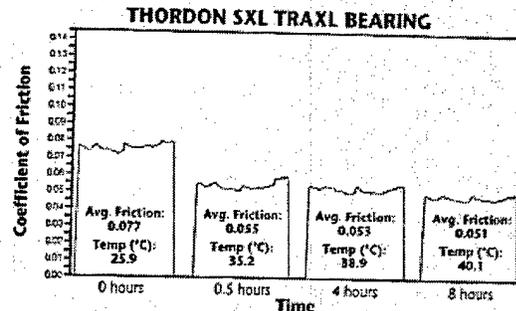

The Thordon SXL TRAXL bearing had initial dynamic friction of 0.077 but quickly bedded in, decreased to 0.055 after 30 minutes and to 0.051 by the end of the test. The temperature rose from 25.9°C to 40.2°C, rising only 1.3°C during the last 4 hours. No evidence of stick-slip was observed.

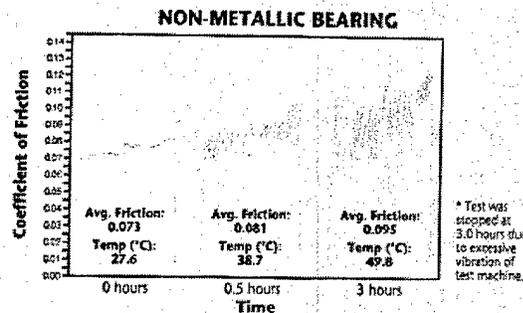

A non-metallic bearing tested had initial dynamic friction of 0.073 and a temperature of 27.6°C. Over a 3 hour period the coefficient of friction increased to 0.095 and the temperature rose to 49.8°C. By the end of the first half hour rapid fluctuations in friction were occurring (stick-slip). The magnitude of these fluctuations increased until the test was halted after 3 hours due to excessive vibration of the test machine.

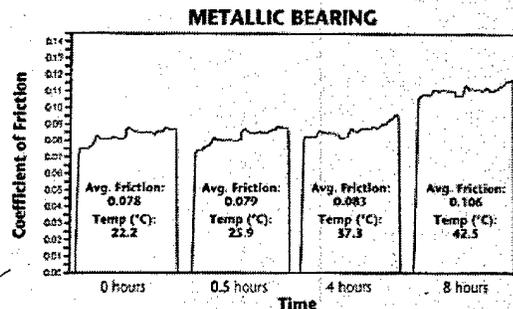

A metallic bearing tested had initial dynamic friction of 0.078. Over the course of the test the coefficient of friction rose to 0.106 and the temperature rose to 42.5°C. No evidence of stick-slip was observed.

The Thordon SXL TRAXL bearing operated with the lowest coefficient of friction of the group and was the only bearing to exhibit a decrease in friction as the test progressed. Operation was smooth and quiet, corroborating the performance history of Thordon bearings in the field.

Low Friction: Thordon SXL bearings exhibit a very low coefficient of friction. This is true whether the bearing is operating dry or submerged in water. A low bearing coefficient of friction is essential in the smooth and reliable functioning of hydro-turbine operating mechanisms.

Tests conducted by an independent hydro-turbine laboratory determined that the dry coefficient of friction of Thordon SXL TRAXL bearings falls in a range from 0.09 to 0.05 tested at pressures ranging from 18 to 70 MPa (2,600 to 10,000 psi). Thordon's coefficient of friction decreases as bearing operating pressures increase, whereas metallic bearings experience dramatic increases in the coefficient of friction and tend to gall as operating pressures rise. This characteristic makes Thordon an ideal choice for high head installations where pressures are high and smooth precise operation of the gates is vital. Thordon performs well as an un-sealed wicket gate bearing because the coefficient of friction of Thordon wet is lower than dry.

Wet or dry; low or high pressure; static or dynamic; Thordon SXL TRAXL bearings operate smoothly and without stick-slip in hydro-turbine operating mechanisms.


Long Life: Since 1974, Thordon bearings have been fitted to hydro-turbine operating mechanisms. The bearings of the first installation remain in operation today as a testament to Thordon's exceptional wear life. Thordon continues to provide outstanding life in a large and growing number of installations since that time.

Only 0.13 mm (0.005") wear on an 88.9 mm (3.500") I.D. Thordon SXL TRAXL bearing was predicted in 25 years of simulated operation in a pump-turbine wicket gate application when tested by an independent hydro-turbine laboratory. Test pressures were 20.7 MPa (3000 psi) with operational parameters appropriate for a highly utilized pump storage turbine. Self-lubricated metallic bearings in the same test were predicted to show the same wear after less than nine years. Bearing journal wear was also examined and there was no significant wear of the shaft running against Thordon whereas the metallic bearings tested wore the journal proportionally to their own wear rate.


In the field, Thordon bearings have earned a reputation for performing particularly well in abrasive environments and in the extreme duty cycles of pump turbine applications. Thordon SXL TRAXL bearings were chosen over competitive metallic bearings in a recent test in a pump storage turbine experiencing accelerated bearing wear. Thordon was selected after less than one year's operation showed negligible wear compared to significant wear on the metallic bearings.

Evaluation of Bearing Friction and "Stick Slip"


Recent tests in the Thordon Bearings Test facility evaluated the frictional performance of several competitive bearings compared to Thordon. The tests also detected induced stick-slip vibration. 101 mm (4.0") diameter bearings were loaded to a constant pressure of 24.0 MPa (3500 psi) and cycled through an oscillation of $\pm 35^\circ$ at a velocity of 0.003 m/sec. (0.62 ft./min). Tests were run for 8 hours with coefficient of friction, temperature and pressure readings taken 20 times per second for a 60 second period at the start, at 0.5 hours and then on the hour for the balance of the test. Temperature values were measured at the shaft immediately adjacent to the bearing. The test results are summarized in the graphs below.

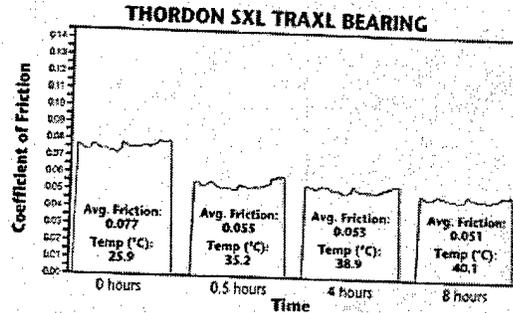

The Thordon SXL TRAXL bearing had initial dynamic friction of 0.077 but quickly bedded in, decreased to 0.055 after 30 minutes and to 0.051 by the end of the test. The temperature rose from 25.9°C to 40.2°C, rising only 1.3°C during the last 4 hours. No evidence of stick-slip was observed.

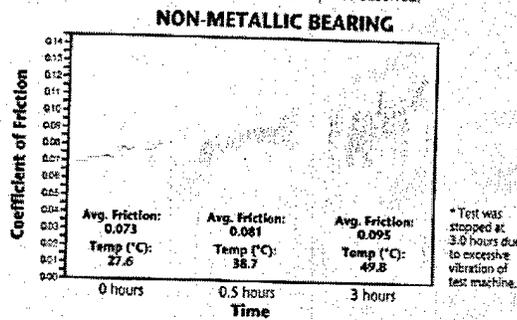

A non-metallic bearing tested had initial dynamic friction of 0.073 and temperature of 27.6°C. Over a 3 hour period the coefficient of friction increased to 0.095 and the temperature rose to 49.8°C. By the end of the first half hour rapid fluctuations in friction were occurring (stick-slip). The magnitude of these fluctuations increased until the test was halted after 3 hours due to excessive vibration of the test machine.

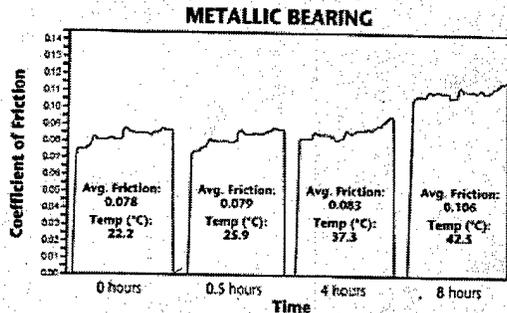

A metallic bearing tested had initial dynamic friction of 0.078. Over the course of the test the coefficient of friction rose to 0.106 and the temperature rose to 42.5°C. No evidence of stick-slip was observed.

The Thordon SXL TRAXL bearing operated with the lowest coefficient of friction of the group and was the only bearing to exhibit a decrease in friction as the test progressed. Operation was smooth and quiet, corroborating the performance history of Thordon bearings in the field.

Pollution Free: Thordon SXL is a homogenous low friction polymer alloy. Grease or other lubrication techniques are not required to lower the coefficient of friction or reduce the wear of a Thordon SXL bearing. Thordon eliminates both the pollution concerns associated with grease lubrication and the lubricant dispersion problems of other "self-lubricating" bearings. Bearings equipped with lubrication plugs require significant rotation of the shaft to spread the lubricant over the bearing surface. In actual operation many of the shaft movements are very minor - only a few degrees either way. Other "self-lubricating" bearings require wear to occur before internal lubricants are accessed. Special coatings to lower friction and minimize wear are often specified, but these can disappear over time resulting in dramatically increased friction and wear.

Thordon SXL's inherent low coefficient of friction does not change. It remains unchanged over many years of operation.

Sizing Flexibility - Easily Machined: Thordon bearings are typically supplied finish machined to specifications engineered for the rehabilitation project; but are often also supplied with overbuild on the inside and outside dimensions to facilitate finish machining on site. Sizing problems resulting from misalignment and dimensional inconsistencies that are often encountered with "standard" sized bearings during turbine rehabilitation are not a problem for Thordon. Optimum alignment and custom sizing of the bearings is possible with Thordon. Bearings that are only supplied in standard sizes and are difficult to machine to close tolerances make custom sizing impossible or extremely expensive. Thordon bearings, while available in a range of standard sizes, can be easily sized at the

factory, or in the field, to meet the dimensional requirements of the project.


Quick turnaround can be achieved by pre-manufacturing bearings to a semi-finished state and then finish machining them during the outage after exact size requirements are known. A free machining elastomer, Thordon contains no asbestos or other hazardous materials, machines cleanly and quickly and is free of nuisance dust. An instructional video providing information on quick accurate machining of Thordon is available.

High Abrasion Resistance: Thordon's superior wear life when operating in abrasives is a direct result of its elastomeric nature. An elastomer, Thordon tends to deflect and then reject abrasive particles. This is not the case with other non-metallic or metallic bearing surfaces. Non-metallics that are not elastomers tend to deform plastically, allowing abrasives to bed into the bearing acting as a permanent abrasive on the shaft. Metallic bearings experience accelerated wear on both the bearing and the mating shaft surface. Grooves to allow abrasive particles and wear debris to clear the bearing are not required with Thordon.

High Resilience/Impact Resistance: In high head hydro-electric and pump turbine installations shorter operating mechanism bearing life is often expected. Higher wear rates and occasional bearing failures are often a result of the impact loading and high frequency low amplitude oscillations encountered. "Pounding out" can occur even though the loads and pressures are below the theoretical yield point of the material.

When a load is applied to a bearing relatively smoothly, the bearing deflects a given amount for each unit of load. As long as the loading does not exceed the yield point of the bearing it will elastically return to its original position when the load is removed. If, however, the load is applied rapidly the bearing may lack the resilience to absorb the energy and completely release it before the next loading cycle. Permanent deformation can occur, even though the theoretical yield point does not appear to have been exceeded. The higher the Modulus of Resilience of a bearing, the greater the bearing's ability to absorb impact and high frequency oscillatory loading without permanent deformation.

Although the yield point of bronze is almost 6 times that of SXL as shown in Table 1, the Modulus of Resilience of bronze is only 5% that of SXL. Metallic bearings, as a result, can tend to "pound out" and transmit impact loading into the operating system whereas Thordon tends to absorb impact loads and

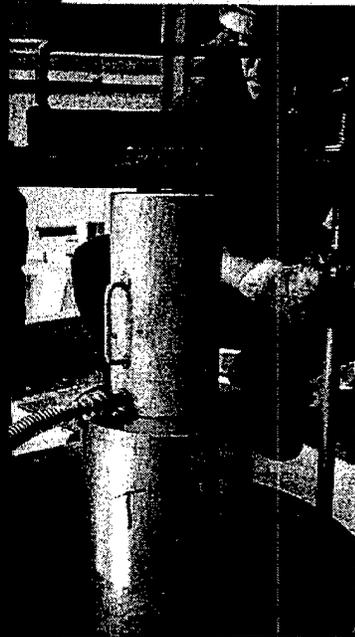

Special tools are not required to install SXL TRAXL bearings.

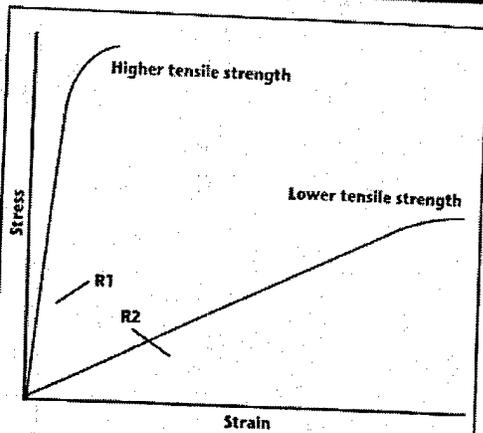


Figure 1: Impact Resistance Comparison

The Modulus of Resilience of a material is determined by calculating the area under the elastic portion of the stress/strain curve up to the yield point. The example in Figure 1 illustrates how a high tensile strength material has a much lower resilience (represented by the shaded area R1), than a lower tensile strength material with resilience (represented by the shaded area R2).

Table 1

Resilience Comparison

Material	Yield Stress		Modulus of Elasticity		Modulus of Resilience	
	psi	MPa	psi	MPa	psi	MPa
Thordon SXL	3,500	24.1	20,000	138	306.0	2.11
Bronze C93200	20,000	138.0	14.5 x 10 ⁶	100 x 10 ³	13.8	0.10
Leaded Bronze with graphite	7,500	51.7	7.3 x 10 ⁶	50 x 10 ³	3.9	0.03

Note: Yield stress for the graphite filled bronze is based on 55% of the maximum tensile strength.

cushion the operating system from shock. Tensile strength, although a good indication of a bearing's physical properties, is of less importance in selecting an optimum bearing. Thordon SXL TRAXL bearings have been proven to resist impact loading and provide superior wearlife in highly loaded hydro turbines.


No Need for Hardened, Ground Journals: Hard journals are required for hard bearings. With Thordon the journal material need not be more sophisticated than 304 or 316 stainless steel with no hardening. Surface smoothness should be 0.8 μM (32 μ inches).

High Pressure Capacity: Although typically loaded to pressures of 20 to 25 MPa (3,000 to 3,600 psi) in a hydro-turbine, Thordon TRAXL bearings are performing well in many industrial applications at pressures as high as 70 MPa (10,000 psi) or higher.


Accommodate Edge Loading: Under the edge loading conditions that can occur as a result of minor mis-alignment or wicket gate deflection, Thordon deflects slightly, effectively spreading, and thereby reducing, the pressure. The galling of metallic bearings that often occurs due to edge loading under these conditions is eliminated with Thordon.

Wet Or Dry Operation: Thordon operating mechanism bearings function well either sealed and dry, or immersed in water. In fact, Thordon's coefficient of friction immersed is less than operating dry.

Lip Seal Availability: In the event that sealed wicket gate bearings are preferred, Thordon SXL TRAXL bearings can be supplied from the factory with high quality Thorseal lip seals installed. Formulated from a high strength polymer with internal lubricants, Thorseals provide effective sealing, low friction and long life.

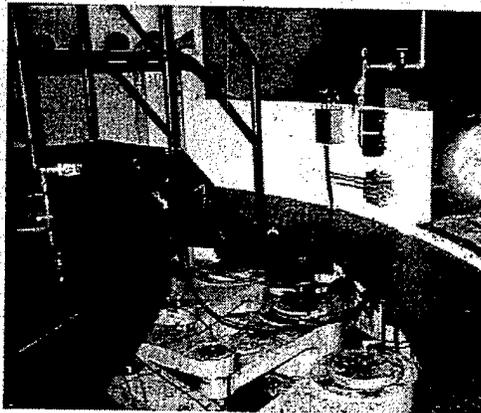

Greased operating mechanism before installation of SXL TRAXL bearings.

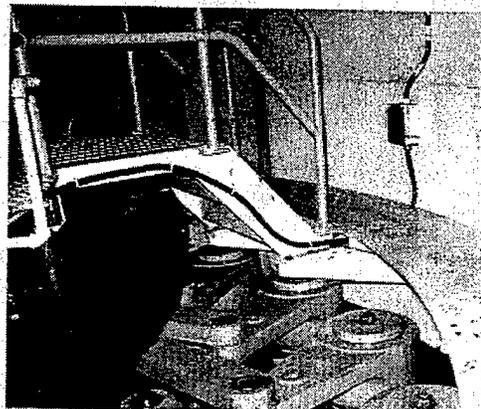

Operating mechanism after installation of SXL TRAXL bearings.

KAMATICS CORPORATION

KAMAN

TABLE I

Liner	Approximate Physical Properties	Characteristics	Typical Applications
KAron B High Load	Density - 1.51 gm/cc Hardness Rockwell M95 Thickness Range .005 - .060" (.127 - 1.5 mm)	Dynamic operating Pressures to 50,000 psi (345 mPa). Velocities to 3 fpm (1 M/min) Temp Range -100° to 400° F (-73° to >205°C) SAE AS81820 & SAE AS81934 Qualified	Aircraft controls, landing gears etc. Highly loaded linkages. Jet engine controls. Other high loaded demanding, maintenance free applications.
KAron V High Load / Low Friction	Density - 1.36 gm/cc Hardness Rockwell M85 Thickness Range .005 - .060" (.127 - 1.5 mm)	Dynamic operating Pressures to 40,000 psi (276 mPa). Velocities to 10 fpm (3 M/min) Temp Range -100° to 300° F (-73° to 150°C) Mil-B-8943 Qualified	Track rollers. Cam followers. Marine/naval applications. Aircraft shock struts. Other high loaded, low friction applications.
KAron F Low Friction	Density - 1.36 gm/cc Hardness Rockwell M85 Thickness Range .003" - min (.076 mm min.)	Rubbing surface is a predominately PTFE enriched outer surface, providing low coefficient of friction at low loads and at low temperatures. The general operating parameters are the same as KAron V. A minimum thickness liner of .003" (.076 mm) can be obtained.	Spherical bearings Track rollers. Cam followers Other moderately high loaded, low friction applications.
KAron VS Low Friction	Density - 1.56 gm/cc Hardness Rockwell 15X 88 Thickness Range .005 - .060" (.127 - 1.5 mm)	Dynamic operating pressures up to 12,000 psi (83 mPa), excellent low temperature friction capabilities. Temp Range -100° to 300° F (-73° to 150°C)	Spherical bearings Track rollers. Cam followers Other moderate loaded, low friction applications.
KAron RP Low Friction	Density - 1.60 gm/cc Hardness Rockwell M80 Thickness Range .005 - .060" (.127 - 1.5 mm)	Dynamic operating Pressures to 30,000 psi (205 mPa). Velocities to 10 fpm (3 M/min) Temp Range -100° to 250° F (-73° to 120°C) Mil-B-8943 Qualified	Landing gear shock struts and other moderate load, relatively high speed, low friction applications.
KAron M Ductile	Density - 1.36 gm/cc Hardness Rockwell M80 Thickness Range .005 - .060" (.127 - 1.5 mm)	Dynamic operating Pressures to 35,000 psi (240 mPa). Velocities to 10 fpm (3 M/min) Temp Range -100° to 250° F (-73° to 120°C) Mil-B-8943 Qualified	Landing gear shock struts. Other applications requiring low friction and low rates of wear along with a degree of ductility to accommodate system deflections.
KAron SP Ductile	Density - 1.44 gm/cc Hardness Rockwell 15X 77 Thickness Range .005 - .060" (.127 - 1.5 mm)	Dynamic operating pressures up to 25,000 psi (145 mPa), excellent low temperature friction capabilities. Temp Range -100° to 250° F (-73° to 121°C) Designed for Mil-B-8943	Landing gear shock struts. Other applications requiring low friction and low rates of wear along with a degree of ductility to accommodate system deflections.
KAron H High Speed	Density - 1.85 gm/cc Hardness Rockwell M90 Thickness Range .005 - .060" (.127 - 1.5 mm)	Dynamic operating Pressures to 20,000 psi (140 mPa). Velocities to 30 fpm (9 M/min) Temp Range -100° to 250° F (-73° to 120°C) Designed for SAE AS81819	Helicopter rotor controls. Other high speed, moderate load low friction applications.
KAtherm T87 High Speed / High Temperature 500°F (260°C)	Density - 1.37 gm/cc Hardness Rockwell M80/90 Thickness Range .005 - .030" (.127 - .75 mm)	Dynamic operating Pressures to 20,000 psi (140 mPa). Velocities to 30 fpm (9 M/min) Temp Range -100° to 500° F (-73° to 260°C) Designed for SAE AS81819	Formulated for high temperature applications to 500°F (260°C) such as VG bushings, engine linkages, thrust reverser, cam followers, track rollers and helicopter rotor control bearing.
KAtherm T88 High Speed / High Temperature 600°F (316°C)	Density - 1.30 gm/cc Hardness Rockwell M80/90 Thickness Range .005 - .030" (.127 - .75 mm)	Dynamic operating Pressures to 10,000 psi (70 mPa). Velocities to 30 fpm (9 M/min) Temp Range -100° to 600° F (-73° to 316°C)	Formulated for high temperature applications to 600°F (316°C) such as VG bushings, engine linkages, thrust reverser, cam followers, track rollers and helicopter rotor control bearing.

KAMATICS CORPORATION

KAMAN

Typical Karon Characteristics

- *Self adhering - No secondary bonding*
- *Large thickness range....>.060"*
- *Excellent fluid compatibility*
- *Excellent abrasion resistance*
- *Homogenous - uniform wear & friction*
- *Ability to refurbish components*
- *It is Machinable*

The slide above lists significant attributes for Karon liner systems. All Karon formulations are made from the same basic resin system, insuring consistent performance.


Karon Fluid Compatibility

- *Mil-H-5606 & Mil-H-83282 (Hydraulic Oil)*
- *Mil-A-8243 (Deicing Fluid)*
- *Mil-L-7808 (Lubricating Oil)*
- *JP-4 & JP-5 (Aircraft Fuel)*
- *Skydrol (Hydraulic Fluid)*
- *TT-S-735 Type VII (Standard Test Fluid)*
- *Distilled Water*
- *Sea Water*
- *Many Other Fluids..Contact Kamatics*


It is important that a liner system be capable of operating in hostile environments. This includes the ability to function in various fluids without degrading, softening or swelling. The Karon liner system operates exceptionally in most industrial and aerospace fluids, including those listed above.

KAMATICS CORPORATION

KAMAN

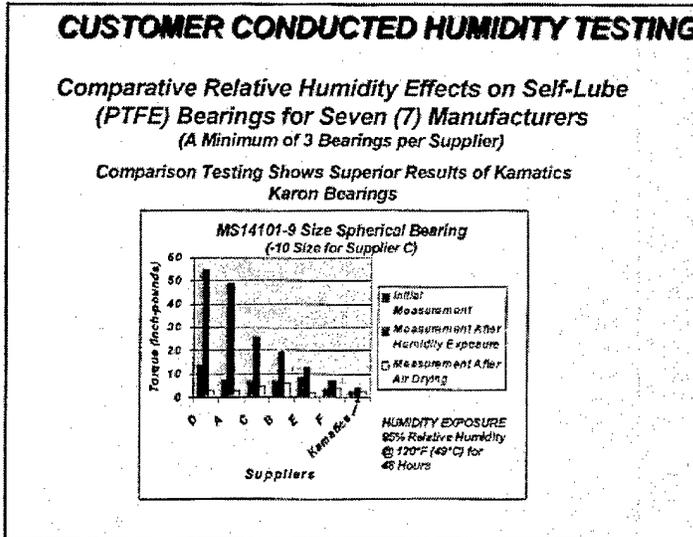


The results shown above were obtained from testing conducted by a major aerospace company. It clearly shows that the Karon liner system was affected the least of the seven suppliers submitting specimens.

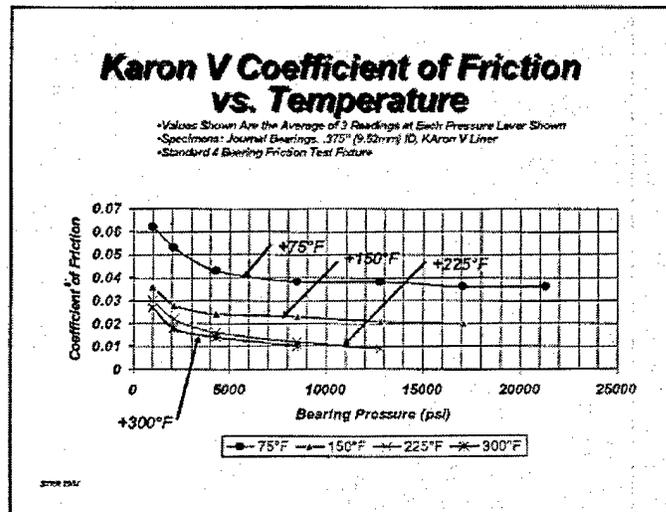


The slide above offers typical coefficient of friction values for the Karon V liner system at various temperatures and bearing pressures. If information as to the coefficients of other Karon liners is required, contact a Kamatics representative at 860-243-9704

KAMATICS CORPORATION

KAMAN

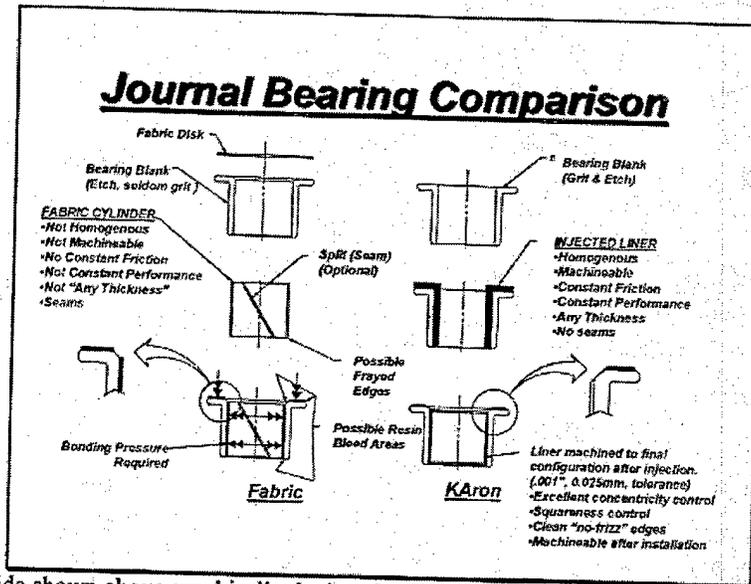

The slide shown above graphically depicts the difference in the manufacture of a Karon lined journal bearing and that of a fabric lined journal bearing. It is readily apparent that a Karon lined bearing will allow trouble-free installation and provide constant operating performance. There is no the concern the realistic possibility of raised and/or frayed liner edges to interfere with the shaft/pin installation.

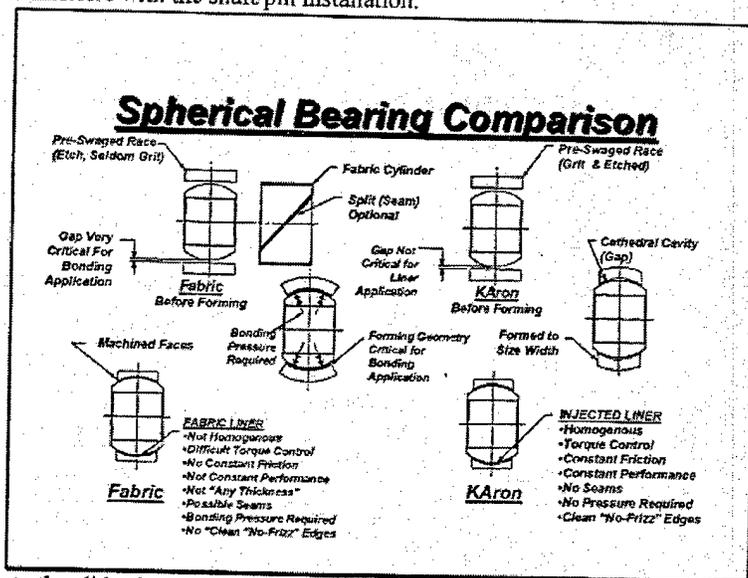

Similar to the slide above, this slide also depicts the differences in manufacture between a Karon lined spherical bearing and a fabric lined spherical bearing. The Kamatics cathedral cavity and no requirement for bonding pressure sets the Karon bearing apart

KAMATICS CORPORATION

KAMAN

Kamatrics Data Sheet 131

HONING, MACHINING, CLEANING & MEASUREMENT
KARON and KATHERM**Honing:**

The following information is supplied as an aid in KARON or KATHERM honing operations. A honing machine, Sunnen or similar, should be used and the finished ID be sized with standard GO/NO-GO plug gages. Tooling may be required to properly position the part being honed to insure alignment, squareness, and/or position.

- **Stone** - Sunnen K6-A63 or K6-A65 or similar (280 grit medium hard aluminum oxide).
- **Speed** - 300 to 1000 rpm, depending upon the diameter of the bushing being honed.
- **Coolant** - Sunnen MB30 (oil base) or similar.

After honing, ultrasonic clean the bushing in any of the cleaners noted below, to remove honing stone debris.

Machining:

The following information is supplied as an aid in KARON or KATHERM machining operations. The finished ID should be sized with standard GO/NO-GO plug gages. Tooling may be required to properly position the location of the ID.

- **Inserts** - Diamond inserts for best results, Carbide inserts acceptable. 0.030" nose radius minimum.
- **Speed** - 1000 surface feet per minute (300 meters per minute) minimum.
- **Depth of Cut** - as required.
- **Feed Rate** - 0.001/0.003 inches (0.025/0.075 mm) per revolution.
- **Coolant** - water-soluble coolant (if necessary).

Depending on size and the degree of accuracy required, special fixtures and/or holding devices may be required (as would be the case for machining any material). KARON is easily machined and therefore the use of a coolant is not necessary. The machining debris will be in the form of small chips and powder.

Cleaning:

Cleaning of the Kamatrics bearings can be accomplished with practically any normal factory cleaner or solvent. Obviously those that do not leave a undesirable residue are preferred. Suggested is Turco 4215 alkaline detergent followed with a fresh water rinse, or Citrikleen XPC citric based solvent followed with a methanol rinse. Nitrosol, alcohol, acetone, and Tri-chlor 111 (when/if environmentally acceptable) can also be used. Avoid acids (hot or cold) and caustic "paint removers" as these can be a problem if left on the liner for an extended period of time (over 3 minutes).

Dimensional Inspection:

Dimensional inspection of KARON and KATHERM lined surfaces requires special consideration. Because of the fibrous nature of the material and its hardness relative to metals, we suggest the use of "GO-NO GO" gages when inspecting inside diameters. Light pressure on micrometer measurements on external surfaces readily measured with this type of instrument, should be used.

If conventional dial bore indicators are used, where there are several small pressure probes employed, it has been established that the reading on the gage should allow .00015 inches (0.0038 mm) for the probe penetration into the liner.

For example, if the high limit dimension on an inside diameter is 1.0000 inches (25.40 mm), a "dial bore" reading of 1.0003 inches (25.408 mm) would be an acceptable reading. The low limit value would be similarly affected.

KAMATICS CORPORATION

KAMAN

Kamatiks Data Sheet 134

KAron® V Wear Strip

Product Data Sheet

Description:

Kamatiks KAron® V Wear Strip consists of standard KAron Grade V self-lubricating bearing material applied onto a thin fiberglass substrate. It is designed to be bonded onto surfaces that are subjected to light to medium duty rubbing pressure, or as a fretting resistant barrier.

Physical Properties:⁽¹⁾

Coefficient of friction:	.04 - .08	
Compressive strength:	30,000 psi	(207 mPa)
Max dynamic load:	10,000 psi	(69 mPa)
Max operating temp:	250°F	(120°C)

Available Sizes:

Standard KAron V Wear Strip material is available in cut sheets of 12" x 48" (305 x 1219 mm), 3/4" and 1" (19mm and 25.4mm) wide strips, washers of various sizes, and custom die cut shapes. The material is available in two thicknesses:

<i>KAron V Wear Strip Grade</i>	<i>Product Description</i>	<i>Nominal Thickness</i>
KWS100	Light Duty Wear Strip	.018" ± .003 (.46 mm ± .075)
KWS200	Medium Duty Wear Strip	.036" ± .003 (.91 mm ± .075)

Standard Part Numbering System:

For standard cut strip dimension parts, Kamatiks uses the following part numbering system:

$$KWS[M]xxx[T] - yyy - zzz$$

Where:

M = Metric dimensions

xxx = Wear strip grade, i.e. KWS100 = Light Duty Wear Strip, .018" (.46mm) nominal thickness

T = 3/8" (9.5mm) pull tab included along edge (pull-tab allows for easy removal of peel ply backing)

yyy = Part width in 1/8" increments up to 12", i.e. 024 = 3" wide

(Metric: 5mm increments up to 300mm, i.e. 020 = 100mm wide)

zzz = Part length in 1/4" increments up to 48", i.e. 096 = 24" long

(Metric: 10mm increments up to 1200mm, i.e. 050 = 500mm long)

Bonding Procedure:

KAron V Wear Strip comes with a woven nylon peel-ply on the back of the fiberglass to protect the bonding surface from dirt and debris. When the pull-tab (*T*) option is called out in the part number, a 3/8" (9.5mm) long breakaway tab will be provided for easy removal of the peel ply backing. With the peel-ply removed and the back surface exposed, the KAron V Wear Strip is prepared for bonding onto a suitable surface. A room temperature curing structural epoxy adhesive⁽²⁾ is recommended for bonding KAron V Wear Strip material.

Notes:

- Above reported values based on wear strip only. Physical properties in service will be largely dependent upon the adhesive bond integrity, the substrate material, and surface preparation of the substrate.
- Suggested structural adhesives: EA9460, EA9309, EA9394 (Dexter Hysol), Scotchweld 460 (3M Co.), Araldite 2011 (Ciba Specialty Polymers).

KAMATICS CORPORATION

KAMAN

KAMATICS Tech Note 15

Kamatics KAron Wear Strip Bonding Procedure for General Purpose Installations. <160°F (<70 °C)

Introduction

Kamatics KAron coated Wear Strips offer the capability to coat and protect moving parts by field application of self lubricating bearing materials. When attaching the Kamatics Wear Strip, care should be taken in the field bonding procedure to assure adequate adhesion of the Wear Strip to the substrate to be protected. The Kamatics Engineering Technical Note provides a procedure for general purpose bonding of Kamatics Wear Strips where operating temperature will not exceed 160°F (70°C) and operating loads are low.

General

A reliable bonding procedure requires care in the following:

- ⇒ - Adhesive selection and control
- ⇒ - Substrate cleaning
- ⇒ - Substrate preparation
- ⇒ - Bond line thickness control
- ⇒ - Curing procedure.

This Engineering Technical Note addresses each of the above elements to provide the user with a step-by-step procedure for general purpose bonding of Kamatics Wear Strips.

Adhesive Selection and Control

For bonding Wear Strips, Kamatics recommends the use of Hysol Epoxy Adhesive EA 9309.3 NA, or equivalent. Important characteristics of the adhesive are:

- ⇒ - Adequate working time for the particular installation
- ⇒ - 160°F (70°C) operating temperature
- ⇒ - Integral bond line control (suspended glass beads or fabric carriers)

The final bond quality can be adversely affected by improper handling and storage of the adhesive. Therefore, all adhesives must be stored and handled strictly in accordance with the manufacturer's instructions and must not be used beyond their published shelf life.

Substrate Cleaning

The substrate should be thoroughly cleaned to remove all traces of dirt, oils, and other contaminants. For substrates which are heavily contaminated, the surfaces to be bonded should first be cleaned using a detergent cleaner and thoroughly rinsed with hot water.

Cleaning of the surface to be coated should be by washing or wiping with trichloroethane, acetone, or alcohol.

No cleaning of the Kamatics Wear Strip is required. The surface of the Wear Strip to be bonded is protected by an integral "peel ply" applied to the surface to be bonded. Removal of this "peel ply" exposes a surface which is clean, roughened, and ready for bonding.

All parts, following cleaning, should be handled only by personnel using clean, lint free gloves. Contamination of cleaned surfaces must be avoided, and any such contamination requires re-cleaning of the parts.

Substrate Preparation

In order to achieve a reliable bond between the Kamatics Wear Strip and the substrate, both surfaces should be mechanically roughened to provide a surface most receptive to adhesion.

As mentioned previously, the "peel ply" applied to the back of the Wear Strip, when removed exposes a surface which is already clean, properly roughened, and ready for bonding.

The substrate should be mechanically roughened using an alumina grit paper (80-200 grit is adequate) or

KAMATICS CORPORATION

KAMAN

KAMATICS Tech Note 15

Page 2 of 2

using alumina grit in a grit blast operation, to remove all surface deposits. Re-clean the surfaces after roughening. Bond as soon as possible.

Proper Bond Line Thickness Control

In order to achieve the highest possible bond strength, the bond line thickness must be controlled. The best method for controlling the bond line thickness is to use an adhesive with an integral method of bond line control.

Adhesive EA 9309.3 NA is a liquid which incorporates 0.005" diameter glass beads for bond line control. The liquid is applied to one or both surfaces to be bonded, and the surfaces are pressed together until the excess adhesive is squeezed out from between the surfaces. The glass beads prevent the surfaces from being pressed closer together than 0.005" (0.125 mm), providing the optimum bond line thickness.

Proper Curing Procedure

The final bond quality can be adversely affected by improper curing of the adhesive. Therefore, all curing operations must be performed strictly in accordance with the manufacturer's instructions. EA 9309.3 NA provides optimum strength when cured at 70°-80°F (20°-25°C) for 5 to 7 days. The bond will develop sufficient strength for handling after 6 hours at room temperature, and fixturing to hold the part pressed together should be used until handling strength is developed. Time to develop handling strength can be greatly reduced by application of heat (do not exceed 250°F for this purpose).

Kamatics Wear Strip Bonding Procedure Summary

Adhesive:

- Hysol EA9309.3 NA or equivalent.

Cleaning:

- Clean heavily contaminated surfaces using a detergent cleaner and thoroughly rinse with hot water.
- Clean the surface by washing in trichloroethane, acetone, or alcohol.

Surface Preparation (Substrate):

Mechanically roughen using an alumina grit paper (80-200 grit is adequate) or using alumina grit in a grit blast operation, to remove all surface deposits. Re-clean after roughening.

- Handle only with clean, lint free gloves.
- Apply adhesive as soon as possible.

Surface Preparation (Wear Strip):

Remove the "peel ply" from the back of the wear strip (a sharp object such as a knife is useful for initiating separation of the "peel ply" from the Wear Strip).

- Handle only with clean, lint free gloves.
- Apply adhesive as soon as possible.

Bond Line Control:

Apply a thin coat of adhesive to both the surface and to the back surface of the Wear Strip (or, if using a film adhesive, apply the pre-cut adhesive film to the back of the Wear Strip).

Press the Wear Strip against the substrate until excess adhesive no longer is squeezed from between the parts. (Wiping the excess adhesive from the parts at this point will reduce the effort required for cleanup of the parts.)

Bond Curing:

Keeping the parts pressed together, cure the bond to handling strength at room temperature 70°-80°F (20°-25°C) for 6 hours. Fully cure the bond at room temperature for 5 to 7 days.

- Clean up excess adhesive as required.

KAMATICS CORPORATION

KAMAN

KAMATICS Tech Note 18

**ROLLER SWAGING KARON LINED
SELF-LUBRICATED SPHERICAL BEARINGS**

General:

The information given in Tech Note 18 is offered as a guide when designing a tool to roll swage a bearing into a housing. The data pertains to the manufacture of a tool for any particular bearing size. It is obvious that a "basic" tool can be designed with interchangeable spacers, sleeves, and rollers that would accommodate a family of bearing sizes. The user is encouraged to consider this option when designing tooling.

Introduction

Installation of Karon lined self lubricated spherical bearings is best performed by using a roller swaging tool similar to that shown in Figure 1 or the Appendix. Roller swaging requires less force than anvil staking, is easier to adjust to variations in swaging groove geometry, and allows finer control of the actual swaging process. Because the sleeves (or pilots) and adjustable spacers allow one basic rolling tool to be adapted to a variety of bearing sizes, roller swaging tools are also more economical than anvil staking tools.

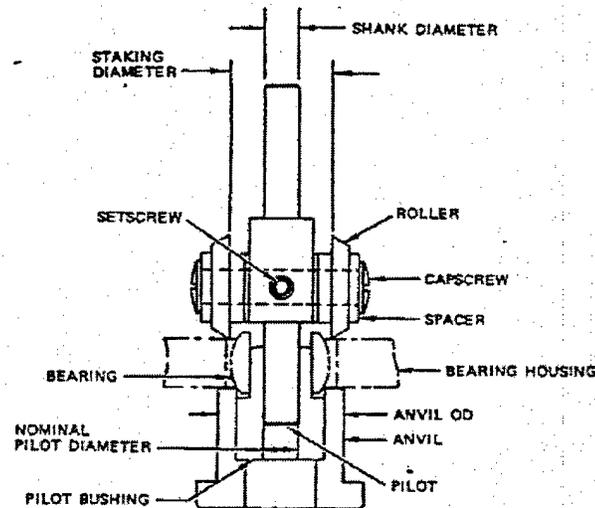


Figure 1 - Typical Roller Staking Tool Set Up

Most users find it easier and more convenient to manufacture their own roller swaging tools in accordance with the formula and drawings contained in the Appendix or similar designs. In addition, Kamatics can provide individual tools or sets for users without the facilities to easily produce their own tools.

Procedure

The following step-by-step procedure provides the instructions needed to successfully install Karon-lined self lubricated spherical bearings in a shop environment. Installation of Karon-lined self lubricated spherical bearings in parts which are mounted on the aircraft require modified versions of the roller swaging tool, but the basic procedure is the same.

KAMATICS CORPORATION

KAMAN

KAMATICS Tech Note 18
Sheet 2 of 4

- (1) Use a heavy duty drill press with a quill diameter of not less than 2 inches, and gearing that will give not less than 200 pounds of force at the chuck with usual operator input. Set the drill press for approximately 80 rpm for 1 inch or smaller bore diameters, or proportionately slower for larger bearings.
- (2) Set the rollers of the swaging tool to agree with the diameter of the bearing swage groove. The distance between the inside edges of the rollers should be .005-.010" larger than the diameter of the center of the groove, as a starting point. Tighten all the parts, making sure the rollers turn freely. The fit of the pilot in the guides of the primary and the secondary anvils should be tight without binding.
- (3) Install the swaging tool in the chuck of the drill press.
- (4) Apply the specified installation finish (primer, sealant, etc.) to the ID of the housing and the OD of the bearing.
- (5) Install the bearing centered in housing. Make sure the outer race of the bearing is flush to 0.010 inch above the housing surface, or as specified on the installation drawing.
- (6) Apply a thin layer of general purpose grease to the swaging groove to prevent galling. Try not to let the grease get on the Karon surfaces of the inner race.

CAUTION: MINIMIZE THE AMOUNT OF GREASE OR OTHER LUBRICANTS WHICH MIGHT GET INTO KARON-LINED BEARINGS. LUBRICANTS CAN COLLECT CONTAMINATION AND THUS SHOULD BE AVOIDED.

- (7) Set the surface to be swaged perpendicular to the axis of the spindle.
- (8) Swage the first side of until the lip is swaged out into the swaging groove. Inspect the swaging lip to insure that sufficient swaging has occurred. There should be less than .005" gap between the outside of the lip and the housing, which can be checked with a wire feeler gage. If the lip has not swaged over adequately after two attempts, increase the distance between the inside edges of the rollers an additional .005" and re-swage.
- (9) Turn the assembly over and swage the second side.

NOTE: Do not let the rollers touch the bottom or the inner face of the swaging groove in the bearing outer race. This can cause binding of the bearing to the extent that the ball cannot be turned in the housing.

- (10) Clean the lubricant from the bearing with a rag wet with a small amount of methyl ethyl ketone, acetone, or similar solvent. Protect the inner race from the solvent and all lubricants.
- (11) Examine the swaged lip for clearance and galling. Gall marks should be avoided, and is caused when the rollers did not turn or the roller lubrication was insufficient.
- (12) The stake is completed when the swaged lip touches the housing chamfer and the gap at the outer edge is less than .005".
- (13) Unless specified by the overhaul instructions, the no-load breakaway torque of an installed Karon-lined spherical bearing must not be more than two times the uninstalled maximum breakaway torque specified in the bearing specification or standard.
- (14) If required, give the bearing a push-out load test. Apply the load only to the outer race. The bearing must not move in the housing or come loose.

DIMENSIONS FOR ROLLER SUPPORT

A DIA = AS REQ TO FIT DRILL OR MILL CHUCK (BEARING I.D. MIN)

B DIA = SLIP FIT IN BEARING I.D. (PRESS FIT ON SUPPORT)

C MIN = (BALL WIDTH - RACE WIDTH)/2 + MAX BRG GROOVE DEPTH + .020

KAMATICS CORPORATION**KAMAN**KAMATICS Tech Note 18
Sheet 3 of 4

C MAX = C MIN + .005
 D DIA = B-.06 (PRESS FIT WITH SLEEVE LD.)
 E MIN = NOMINAL BOLT DIA
 E MAX = E MIN + .010
 F MIN = C MAX + E MAX (2 ROLLERS REQUIRED, O.D. MUST BE WITHIN .001 OF EACH OTHER)
 F MAX = F MIN + .010
 G MIN = MAX BRG GROOVE DIA + .005
 G MAX = G MIN + .005
 H DIA = SLIP FIT WITH BOLT DIA
 L MIN = C + (1.5 x BRG BALL WIDTH)
 L MAX = L MIN + .030
 W MAX = G MIN - .06 (ALLOWS 2 .030 THICK SPACERS) SEE NOTE 3

DIMENSIONS FOR ROLLER BASE

J MIN = MAX BRG I.D. + .005
 J MAX = J MIN + .005
 K MIN = G MIN
 K MAX = MIN BRG O.D.
 M MIN = SUGGEST 1.00 MIN (TO SUIT USER EQUIPMENT)
 N MIN = ((BRG BALL WIDTH - RACE WIDTH)/2) + .030
 N MAX = N MIN + .030
 $P \text{ MIN} = (2 \times \sqrt{(\text{BRG BALL DIA}/2)^2 @ (\text{RACE WIDTH}/2)^2} + .020$
 P MAX = P MIN + .010
 R MIN = K MAX + .25 (MAX = TO SUIT CUSTOMERS EQUIPMENT)

NOTES:

1. REFER TO MIL-STD-1599 REQUIREMENT 202, PARA.6 FOR INSTALLATION AND SUBSEQUENT INSPECTION OF INSTALLED BEARINGS.
2. ASSEMBLE NUT AND BOLT AS SHOWN. TIGHTEN THE NUT SUCH THAT THERE IS APPROXIMATELY .005" LOOSENESS TO ALLOW THE ROLLERS TO ROTATE WITHOUT CATCH OR BINDING.
3. SPACER THICKNESS *AS REQUIRED TO OBTAIN PROPER WIDTH TO MATCH DIM. "G" (BEARING GROOVE DIAMETER). THE SUPPORT CAN BE MANUFACTURED WITHOUT THE NEED FOR SPACERS BUT THE TOOL IS THEN LIMITED TO THAT ONE SIZE UNLESS MODIFIED LATER.
4. THE UNDERCUT IS NOT MANDATORY BUT THE POTENTIAL FOR INTERFERENCE WITH MATING HOUSING WILL EXIST.

ROLL SWAGING TOOL - MATERIAL

ROLLER SUPPORT- STEEL, Rc40 MIN
 ROLLER (2) - TOOL STEEL, Rc55 MIN
 SLEEVE- ACETAL RESIN, PTFE, NYLON, ETC
 SPACER (AS NEEDED, 2 MIN)- STEEL, Rc25 MIN
 BOLT- .250 DIA. CLOSE TOLERANCE. HARDENED (Rc35 MIN) (SUGGESTED)
 NUT- .250 THREAD (SELF-LOCKING SUGGESTED)
 ROLLER BASE- STEEL, Rc40 MIN

**Attachment 1: Powertech Report on Scale Model Testing of
Navigation Lock Pintle Self-Lubricating Bushings for USACE**

POWERTECH LABS INC.

Project Report

**SCALE MODEL TESTING OF NAVIGATION LOCK PINTLE
BUSHINGS FOR CORPS OF ENGINEERS**

Project: 13608-36-00

August 2003

Prepared for:
Dr. L. David Stephenson
ERDC-CERL

Keywords: Self-lubricating bushings, pintles, navigation locks

Prepared by: _____

R. A. Palylyk
Sr. Project Specialist II
Materials Engineering

Approved by: _____

Avaral Rao
Director
Materials Engineering

TABLE OF CONTENTS

	<u>Page</u>
1.0 INTRODUCTION	4
2.0 OBJECTIVE AND WORK PROGRAM	4
2.1 Tasks.....	4
2.1.1 Task 1: Scale Model Test Frame	4
2.1.2 Task 2: Scale Model Pintle/bushing Combinations.....	4
2.1.3 Test Conditions – Loading and Operating Rate	5
3.0 SCALE MODEL ASSEMBLY	5
4.0 INSTRUMENTATION	6
5.0 TEST PINTLES AND BUSHINGS.....	6
5.1 Bushing Test Sleeves.....	6
5.2 Bushing Requirements	6
6.0 TEST RESULTS	7
6.1 Thordon HPSXL	7
6.2 Kamatics Karon V.....	7
6.3 Tenmat T814 (retaining collar type).....	7
7.0 DISCUSSION	9
8.0 CONCLUSIONS.....	9
APPENDIX A MODEL CONSTRUCTION AND ASSEMBLY	11
APPENDIX B THORDON HPSXL TEST RESULTS.....	17
APPENDIX C KAMATICS KARON V SELF-LUBRICATING BUSHINGS/PINTLE TEST.....	29
APPENDIX D TENMAT SELF-LUBRICATING BUSHING (RETAINING COLLAR) TEST RESULTS	41

LIST OF FIGURES

	<u>Page</u>
Figure A1: Schematic overview of scale model pintle bearing test frame.....	12
Figure A2: Location of displacement transducers for wear measurements.....	13
Figure A3: Location of torque transducer for measuring frictional load	14
Figure A4: Top and bottom actuators assembly	14
Figure A5: Overview of test set-up.....	15
Figure A6: Close-up view of 6" pintle side.....	15
Figure A7: Close-up view of 5" pintle side.....	16
Figure B1: Close-up view 5" pintle contact side. There is marked scoring towards stepped edge of the pintle	19
Figure B2: Thordon HPSXL 5" pintle bushing.....	20
Figure B3: Close-up view of loaded side of bushing. Note accumulated wear debris.....	20
Figure B4: Pintle bearing tests 5" pintle/bushing coefficient of friction.....	21
Figure B5: Pintle bearing tests 5" pintle/bushing wear.....	22
Figure B6: Pintle bearing tests 5" pintle/bushing wear and temperature	23
Figure B7: Overview of Thordon HPSXL 6" pintle. Note staining of pintle on loaded side.....	24
Figure B8: Close-up view of Thordon HPSXL 6" pintle bushing. Primary contact area is at top of image	24
Figure B9: Close-up view above image on loaded side. Note accumulation of wear debris above darker contact area	25
Figure B10: Pintle bearing tests 6" pintle/bushing coefficient of friction.....	26
Figure B11: Pintle bearing tests 6" pintle/bushing wear	27
Figure B12: Pintle bearing tests 6" pintle/bushing wear and temperature	28
Figure C1: Close-up view of 5" pintle from Kamatics KAron V test	31
Figure C2: Close-up view of 5" KAron V bushing. Note uniform polished contact areas	31
Figure C3: Close-up view of 5" KAron V bushing. Note highly polished contact area. There is no indication of stress to the lubricant layer	32
Figure C4: Pintle bearing tests 5" pintle/bushing coefficient of friction.....	33
Figure C5: Pintle bearing tests 5" pintle/bushing wear.....	34
Figure C6: Pintle bearing tests 5" pintle/bushing wear and temperature	35
Figure C7: View of 6" Kamatics KAron V pintle	36
Figure C8: View of Kamatics KAron V bushing. Note dark band, which is next to top edge. This is the pintle contact area.....	37
Figure C9: Close-up view of above image on loaded side. Note polished contact area. There does not appear to be any stress to this area	37
Figure C10: Pintle bearing tests 6" pintle/bushing coefficient of friction.....	38
Figure C11: Pintle bearing tests 6" pintle/bushing wear	39
Figure C12: Pintle bearing tests 6" pintle/bushing wear and temperature	40
Figure D1: Overview of 5" Tenmat T814 pintle. Due to the thickness of the bushing-retaining ring, the first row of pintle anchoring holes had to be machined away	43
Figure D2: Close-up view of 5" Tenmat T814 bushing	44
Figure D3: Close-up view of Tenmat T814 5" bushing. Note darker contact areas.....	44
Figure D4: Pintle bearing tests 5" pintle/bushing coefficient of friction	45
Figure D5: Pintle bearing tests 5" pintle/bushing wear.....	46
Figure D6: Pintle bearing tests 5" pintle/bushing wear and temperature.....	47
Figure D7: Overview of 6" T814 pintle. Note transferred lubricant material on side of pintle contact surface	48
Figure D8: Close-up view 6" bushing. There is no indication damage to the bushing. Contact is over 95% of the bushing surface.....	49
Figure D9: Pintle bearing tests 6" pintle/bushing coefficient of friction	50
Figure D10: Pintle bearing tests 6" pintle/bushing wear.....	51
Figure D11: Pintle bearing tests 6" pintle/bushing wear and temperature	52

INTRODUCTION

The U.S. Army Engineering Research and Development Center-Construction Engineering Research Laboratory (ERDC-CERL) had contracted Powertech Labs Inc. to perform scale model accelerated wear tests of navigation lock pintles and pintle lubricating methods for the Panama Canal Authority (Project 13568-36-00). Powertech designed and built a scale model (1/4-scale) test frame to perform accelerated wear tests of existing pintle bushing configurations, which would be benchmark references, and on alternative self-lubricating pintle bushings, in a simulated brackish Panama Canal water environment.

CERL contracted Powertech Labs Inc. to perform additional pintle bushing tests following the same format as the Panama Canal tests with two differences: (1) silt laden river water was used instead of brackish water; (2) the horizontal loadings and vertical loadings on the quarter-scale model pintle were 870.9 psi. and 665.8 psi, respectively.

The following is a report of the test results on three bushing materials tested for the Corps of Engineers navigation lock gates.

OBJECTIVE AND WORK PROGRAM

The objective was to simulate the mechanical and environmental stresses of a typical Corps of Engineers lock miter gate pintle over its anticipated service life of 200,000 cycles.

Accelerated testing and analysis was conducted on 6 lock gate pintle/bushing assemblies, constructed to 1/4 scale, placed in brackish water. Two of the test sets simulated the existing configuration, while a third set used a self-lubricating composite material. It was anticipated that each test would require approximately 35 days of testing time to complete the tasks described below.

TASKS

Task 1: Scale Model Test Frame

A device was designed and constructed to test the 6 scale model pintle/bushing assemblies that would be built in Task 2. Three of the assemblies were to be 5 inches in diameter and the other three were to be 6 inches in diameter. These pintle/bushing assemblies were 1/4 of the actual size of typical Corps of Engineer lock gate pintles. Instrumentation was incorporated to monitor pintle rotation for torque and from this data a value for the coefficient of friction every four (4) hours. Wear was to be monitored on a continuous basis with eddy current probes for both the vertical and horizontal directions. Bushing temperature was monitored adjacent to the loaded contact surface. All data was recorded with a data logger and a personal computer.

Task 2: Scale Model Pintle/bushing Combinations

Three scale model pintle/bushing assemblies, each 5 inches in diameter, and three scale model pintle/bushing assemblies, each 6 inches in diameter, were designed and constructed. All the scale model pintles were made of 316 stainless steel (ASTM A473) with a 16 RMS finish. The bushings were self-lubricating products from three different manufacturers. The pintles and bushings were assembled and tested in silt laden river water to simulate typical conditions found in Corps projects. The water, for these tests was taken directly from the Fraser River across from the city of New Westminster, BC.

Test Conditions – Loading and Operating Rate

Pintle Cycles and Loading

The duration of the test was approximately 200,000 cycles, designed to simulate 25 years of operation. The 6-inch pintles are a ¼ scale representation of the existing pintles, which are 24 inches in diameter. The rotation of the scale model was 63.5°, consistent with the rotation of the full-sized gates.

The actual bearing pressure of the full-sized gates on projected pintle areas for a vertical load is 870.9 psi, and for a side load (from a cantilevered gate mass) is 665.8 psi (based on projected areas of 28.3 in vertical and 14.15 in² horizontal). For the scale model tests, this translates to a load of 12.3 tons vertical and a side load of 4.71 tons.

The 5-inch pintle represents a full-sized 20-inch pintle. Using the same loads as for the 6-inch pintle, the bearing pressures are equivalent to a vertical value of 1254.1 psi and a side load of 961.2 psi (based on projected areas of 19.6 in² vertical and 9.8 in² horizontal).

Pintle Speed

Typical Corps of Engineers navigation lock gates operate at a speed of 110 seconds for a 63.5° swing to open to allow a vessel to pass through, then 110 seconds for the swing to close. This translates to a bearing speed of 0.12 in./sec for a 24-inch diameter pintle. It was decided to set the travel speed of the 6-inch diameter scale model pintle to approximately 0.48 in./sec. to reduce the test period to a reasonable length. The total travel distance for the 6-inch scale model pintle is 6.65 in. (close to open – open to close), and the duration for one complete cycle was 13.75 seconds. Due to the test configuration, the cycle period for the 5-inch pintle was the same. It took approximately 35 days to run the 200,000 cycles.

SCALE MODEL ASSEMBLY

The main concept of the scale model is to statically load two bushings on the same axis at the same time, thereby simplifying the fabrication of a sufficiently strong test frame. A pintle is mounted on each end of a test shaft, with the pintle bushings mounted in test blocks that are fitted to the pintles. The blocks are located on steel pads that have a layer of self-lubricating strips attached with epoxy to their contact surface to allow for free side movement from the lateral loading. The shaft is long enough to mount “frictionless” double taper roller bearings adjacent to each pintle for shaft support, and to mount a large diameter sprocket in the center of the shaft. The sprocket serves as the connector link to the two hydraulic actuators that are used to rotate the shaft correctly. (Note: In this simulation, the pintle bearing is fixed and the pintle rotates, whereas the pintle an actual navigation lock gate is fixed to the bottom of the lock chamber embedded in concrete and the bearing rotates with the miter gate. The relative motions, COF, and wear are expected to be similar in the actual case, versus the simulation).

An Enerpac RCS502 hydraulic cylinder was used to apply the static load, and each test block had an Enerpac RCS201 hydraulic cylinder applying a side load. The axial hydraulic jack was connected to a hand pump. The pressure (axial load) was increased until the correct load was attained. The pressure was monitored by a large diameter dial type pressure gauge. A small bladder-type accumulator connected in the circuit was used to maintain a constant pressure and to compensate for any changes due to wear. The same technique was used for the side load jacks, but they were connected in parallel on their own circuit.

Two custom-built hydraulic actuators were mounted to the side rails to rotate the shaft. The actuators were connected in parallel to a hydraulic pump. A simple control circuit was set up, using proximity probes to switch a two-way valve to change actuator direction. A flow control valve set the operating rate. Figure A1 shows an overview of the test setup.

A critical part of the test environment was to simulate immersing the pintle/bushing combination in brackish water. Powertech's Applied Chemistry Unit prepared the brackish water, and its oxygen content was maintained by bubbling dry nitrogen through the water reservoir until the required level was reached. The oxygen level was measured with an Oakton Dissolved Oxygen Series DO 300 meter. Tanks were built around the test block and shaft, and the brackish water was pumped into the tanks from a main reservoir. A cooling coil was installed in the reservoir to maintain the water at the correct temperature.

Appendix A shows details of the scale model.

INSTRUMENTATION

The test program required monitoring of three critical parameters: frictional load, wear and temperature.

Frictional load values were derived from the output of the strain gauges that measured shaft torque at each pintle (on the inside of the support bearings – Figure A3). There were two torque outputs, one for each pintle. A Vishay 2100 strain amplifier was used to monitor the torque output. Each torque channel was calibrated in a special test frame.

Wear was monitored with Dymac eddy current probes and drivers. The axial probes were mounted on the top of the test block to measure the gap between the block and a plate mounted on the shaft (Figures A2 and A6). The lateral or side load wear probes were mounted on the support plate to measure the gap between the test block and the static probe mount (Figures A2 and A6).

Bushing temperature was measured by a thermocouple mounted in a drill hole on the loaded side of the bushing. The hole was drilled at an angle such that the bottom was close to the bushing's internal edge.

All voltage outputs were connected to an Agilent 34970A Data Acquisition/Switch Unit linked to a desktop computer. On the first day of testing, data were logged hourly. For the remainder of the test, data were logged once every four hours.

TEST PINTLES AND BUSHINGS

The test pintles and bushing were installed as described below:

Bushing Test Sleeves

Radius	2.500/2.499 inches and 3.000/2.999 inches
Material	316 stainless steel, ASTM A473
Hardness	RB = 83
Surface finish	16 RMS finish
Pintle replacement	A new test pintle was used for each test

Bushing Requirements

Specifications were given to the suppliers that the self-lubricating test bushings should have a minimum clearance of approximately 0.000in/0.001 in and no grooving.

TEST SET	TEST A (6-inch scale model pintle-bushing)	TEST B (5-inch scale model pintle-bushing)
1	Thordon HPSXL	Thordon HPSXL
2	Kamatics KAron V	Kamatics KAron V
3	TENMAT T814 (retaining collar)	TENMAT T814 (retaining collar type)

TEST RESULTS

Thordon HPSXL

The Thordon HPSXL bushings started the test with significant audible noise (vibration). Relatively high friction levels contributed to this vibration (Figures B4 and B9). This vibration decreased as the test proceeded and disappeared by the 50,000 cycle point along with lower friction levels and lower temperatures.

The bushings and pintles survived the test regime; the self-lubricating HPSXL was intact and continued to function. However, both bushings (more so with the five (5) inch bushing) had bands of built up wear debris. These bands were forming into clumps and beneath the clumps the lubricant layer was showing signs of breaking down (Figure B3). The six (6) inch bushing just started showing the signs of clumping of the wear debris. Direct wear measurements on both sides indicate initial seating in period of approximately 50,000 cycles. This is most likely a combination of the HPSXL and the degree of fit to the pintle profile. The five (5) inch bushing had, at the end of the test, an approximate 80-90% fit (contact) to the pintle. The six (6) inch bushing is estimated to have about a 30-40% contact fit to the pintle at the end of the test.

The five (5) inch pintle, due to the greater contact was coated with transferred lubricant material. The location where the debris was clumping left some scoring. The six (6) inch pintle was coated in the small areas where there was contact with the bushing.

In general, there was high friction at the start of the test reducing down to a lower constant level by mid point. Direct wear, after seating in, was not significant in either direction (axial and lateral) (Table 1).

By the end of the test, both bushings were showing signs of lubricant layer breakdown as evidenced by the clumping of the wear debris.

Kamatics Karon V

The Kamatics Karon V started at a relatively high friction level but rapidly dropped down to much lower levels (< 0.1) within the first 20,000 cycles (Figures C4 and C10). They functioned quietly and smoothly without any apparent stress. Direct wear measurements indicated little wear taking place other than from the initial seating in period. Where the pintles contacted the bushings, they were coated with transferred lubricant material.

The six (6) inch bushing direct wear did not appear to seat in. After the initial wearing in period, and possibly due to the small contact area, there was a constant indicated increase in the direct wear measurement suggesting a wear rate. It appears this maybe a combination of seating in and wearing taking place. This did not occur with the five (5) inch bushing and could be an artifact of the lower per unit bearing load. Table 2 provides details of the friction and wear levels.

The Kamatics Karon V bushings performed well in the tests. This performance was good despite the fact the contact areas in both bushings were small. This self-lubricating material is tolerant of high bearing loads (small contact area). This lubricant layer is thin and can accommodate minor deformation for seating the pintle. However, a different protocol may be necessary (such as different bushing radii) to permit more contact with the pintle.

Tenmat T814 (retaining collar type)

The Tenmat T814 bushings did not operate at the designated static axial load. The dial gauge used to monitor the pressure was found to be reading higher than actual values by 10 %. The friction values have been corrected for this reduced axial load. The bushings have survived the tests without any apparent damage. In general, the five (5) inch pintle/bushing operated quietly with little apparent vibra-

tion (low friction levels throughout the test). The six (6) inch pintle/bushing combination started with relatively high friction levels as evidenced by audible noise and vibration. This continued for approximately 115,000 cycles. After this break-in period the friction levels and temperatures dropped along with reduced noise levels.

The direct wear measurements on the five (5) inch bushing indicated little wear taking place from side loading. The axial load indicated a net wear of approximately 0.5 mils. The six (6) inch had performed somewhat differently. After the 115,000 cycle point, friction started to increase and at the same time the axial wear also increased. At approximately the 167,000 cycle point, the side load direct wear suddenly jumped to a lower value (dropped 3 mils). This suggests the pintle may be seating in possibly due to wear material shifting around in the interface. The amount of transferred lubricant material and the black colour on the pintle edge (Figure D7) suggests a major event had occurred. The texture of this dark area is unlike the five (5) inch pintle. The dark colour also suggests heating is occurring. The amount of lubricant film was sufficient to appear to be smeared over the pintle surface and thick enough to not be able to see the pintle surface.

These are the only self-lubricating bushings, which due to their wall thickness and resilient properties, had virtually 100 % contact on the pintles.

Table 1
Summary of Test Results – Five (5) inch

Test	Static COF (Steady State)	Dynamic COF (Steady State)	Seating In Displacement – Axial (mils)	Total Direct –Axial Wear (after seating in) (mils)	Seating In Displacement – Side (mils)	Total Direct –Side Wear (after seating in) (mils)
Thordon HPSXL	0.10	0.075	2.5	0.8	0	0
Kamatix Karon V	0.07	0.05	2.25	0.45	0	-0.25
Tenmat T814 (retaining collar)	0.11	0.065	-0.5	0.5	2.6	0.1

Table 2
Summary of Test Results – Six (6) inch

Test	Static COF (Steady State)	Dynamic COF (Steady State)	Seating In Displacement – Axial (mils)	Total Direct –Axial Wear (after seating in) (mils)	Seating In Displacement – Side (mils)	Total Direct –Side Wear (after seating in) (mils)
Thordon HPSXL	0.13	0.11	3.5	0.9	0	1.0
Kamatix Karon V	0.135	0.125	-0.5	1.0	0	0
Tenmat T814 (retaining collar)	0.16	0.135	-4.5	5.0	5.5	-3.0*

* Anomaly in the test results as the side wear dropped suddenly possibly due to material shift or test setup shift.

The COF values were derived from the last half of the test period, when friction was stable and no drastic changes occurred

DISCUSSION

Coefficients of friction and direct wear measurements methodology were discussed in the Powertech Lab Inc. Report 13568-36-00 "Scale Model Testing of Navigation Lock Pintle Bushings". However, the testing of these self-lubricating materials has introduced a set of different criteria to assess the various products performance.

All three products essentially survived the tests using silt laden river water as the test medium. First of all, two of the products, Thordon HPSXL and Kamatic Karon V, have thin lubricant layers bonded to a metallic backing. Tenmat T814 is a much thicker material. The Tenmat T814 generated almost one hundred percent (100%) contact to the pintle surface. The other two materials had contact areas (physical change to the bushing surface from the pintle contact) ranging from approximately twenty percent (20%) to eighty percent (80%). The difference is due to the Tenmat T814 being able to allow some flexing to shape to the pintle. The other two products have limited flexing to shape to the pintle surface.

Thus, the smaller the contact area, the greater the unit loading on the bushing. In the case of the Thordon HPSXL and Kamatics Karon V, the pintles were contacting the bushing edges initially instead of a more uniform contact. This makes it difficult to assign a wear rate to the bushings as both wear and seating into the bushings are simultaneously taking place in a manner unique to the individual pintle/bushing combination (slight but significant differences in pintle/bushing radii). It is estimated the pintle/bushing should have at least a ninety percent (90%) contact area to generate a measured wear rate. Wear rates and even total displacement should not be used as part of the comparison criteria as it appears each pintle/bushing combination is unique. Possibly a different method should be specified when ordering pintle bushings to provide a better fit to the pintles. This has not been an issue with traditional bronze bushings and pintles. The bushings have usually been lapped in place to fit the pintle.

Therefore the criteria for assessing the performance of these three products are friction levels and product appearance after the tests and to a lesser extent actual wear. Using appearance and friction, the Thordon HPSXL started showing the initial stages of material breakdown where wear debris was clumping towards the bushing edge. Once this occurs, the lubricant layer underneath appears to be breaking down compounding the clumping. This occurred in both six (6) inch and five (5) inch pintles.

The Kamatics Karon V and the Tenmat T814 survived the tests with little indication of stress. Performance levels were similar with relation to friction and appearance. The Tenmat T814 was showing typical darkening of the lubricant material in all contact areas although there did appear to be a build-up of wear debris on the side loaded area of the bushing. It also had a significant break-in period on the six (6) inch bushing as evidenced by the audible noise and shaft vibration. The Kamatics Karon V appeared to show the least amount of stress on the contact areas (smaller contact areas – higher unit loading), and operated with little or no vibration in the initial stages.

CONCLUSIONS

Three accelerated wear tests were performed on self-lubricating bushing/pintle combinations in silt laden river water. All three products essentially survived the tests with no total destruction of the lubricant layers. Thordon HPSXL had started to show signs of the lubricant layer breaking down (clumping of wear debris) with fluctuating friction levels. The Tenmat T814 operated at an axial load ten (10) percent lower than the other two tests, however, the six (6) inch side required over half the test time to settle in (as indicated by audible noise and vibration). Upon conclusion of the test, the lubricant liner

had turned black particularly on the side load area, an indication of over heating. In spite of this, the bushings did survive the test.

The Kamatics Karon V had the least amount of contact area with the pintle (thus the highest unit loading), however, the contact areas were uniformly coated with lubricant and the bushing contact areas were polished smooth. This product appears to have performed in the tests with the least amount of stress.

There is another issue with self-lubricating bushings fitting the pintle profile. This appears to be a problematic issue as two of the products (thin lubricant layers) had relatively low percentage of contact with the pintle (particularly the Kamatics Karon V). There is limited flexibility with thin layered bushings to adapt to the pintle profile whereas the Tenmat T814 provided virtually 100% contact. Perhaps a different protocol for specifying fit could be developed and/or a different design could be employed to provide a greater contact with the pintle.

**APPENDIX A
MODEL CONSTRUCTION AND ASSEMBLY**

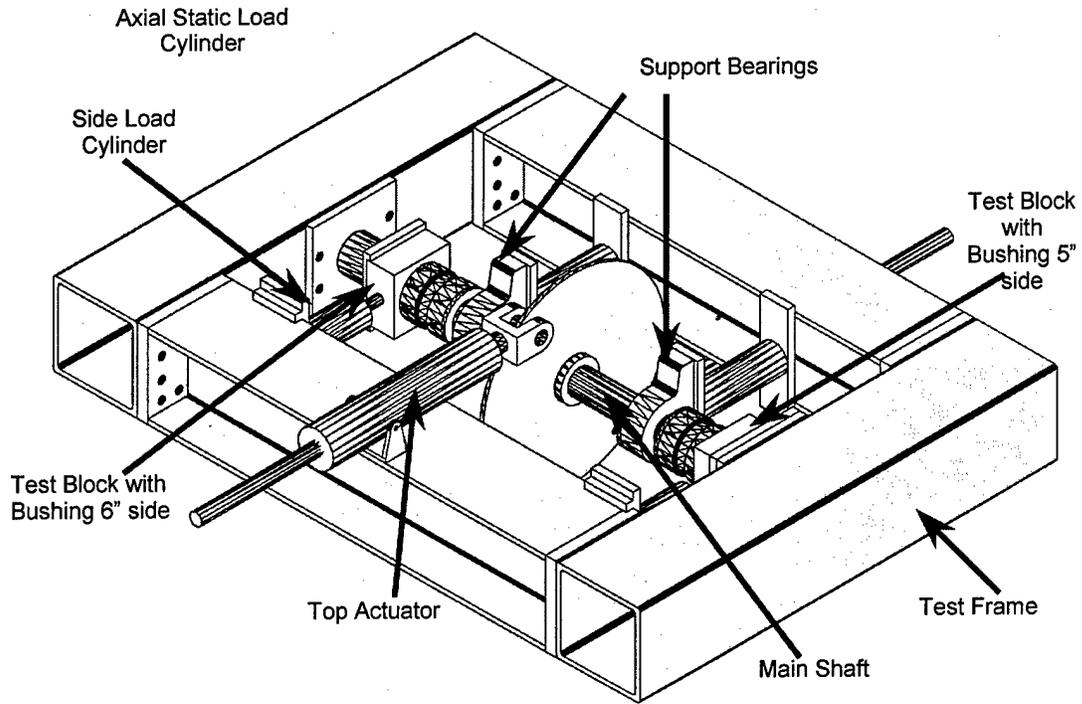


Figure A1. Schematic overview of scale model pintle bearing test frame.

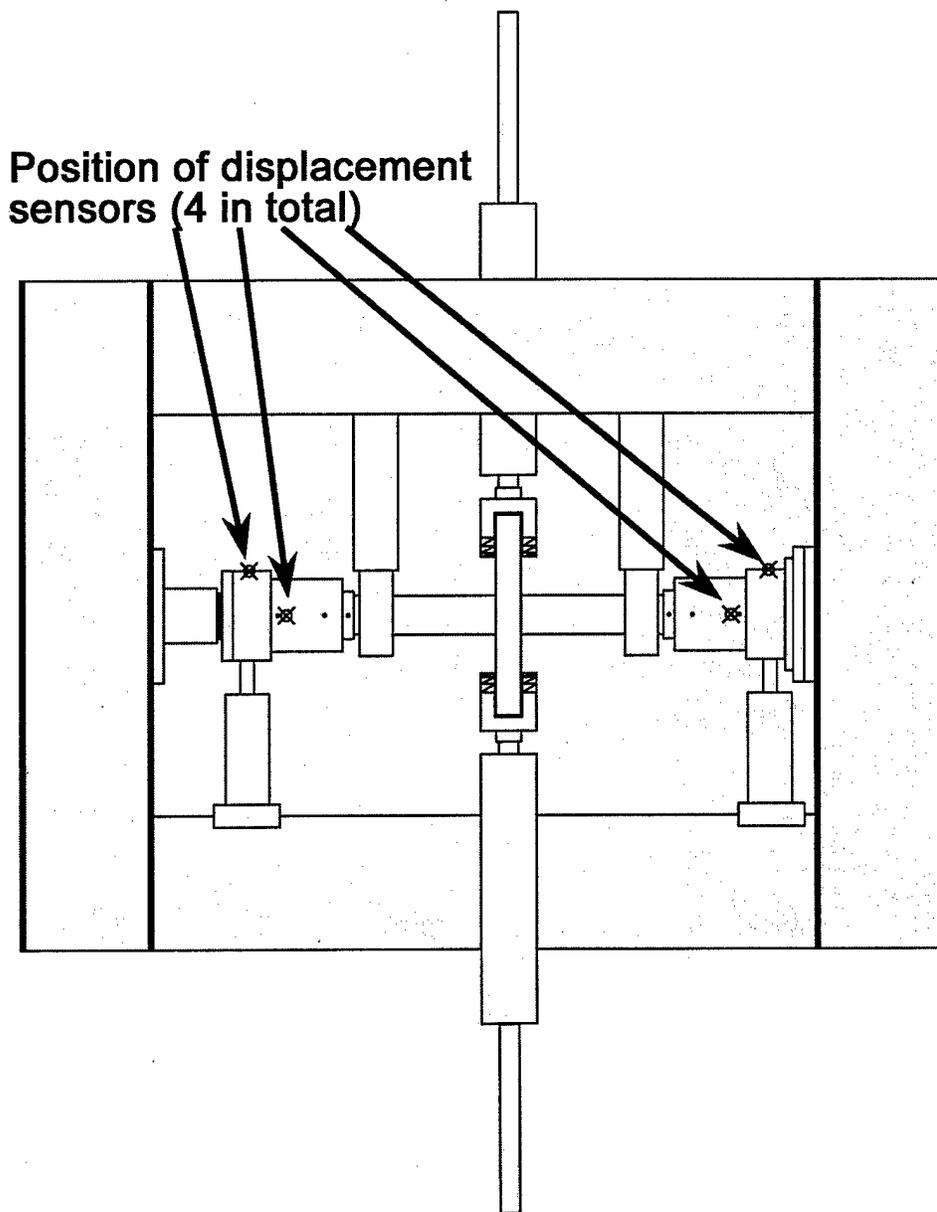


Figure A2. Location of displacement transducers for wear measurements.

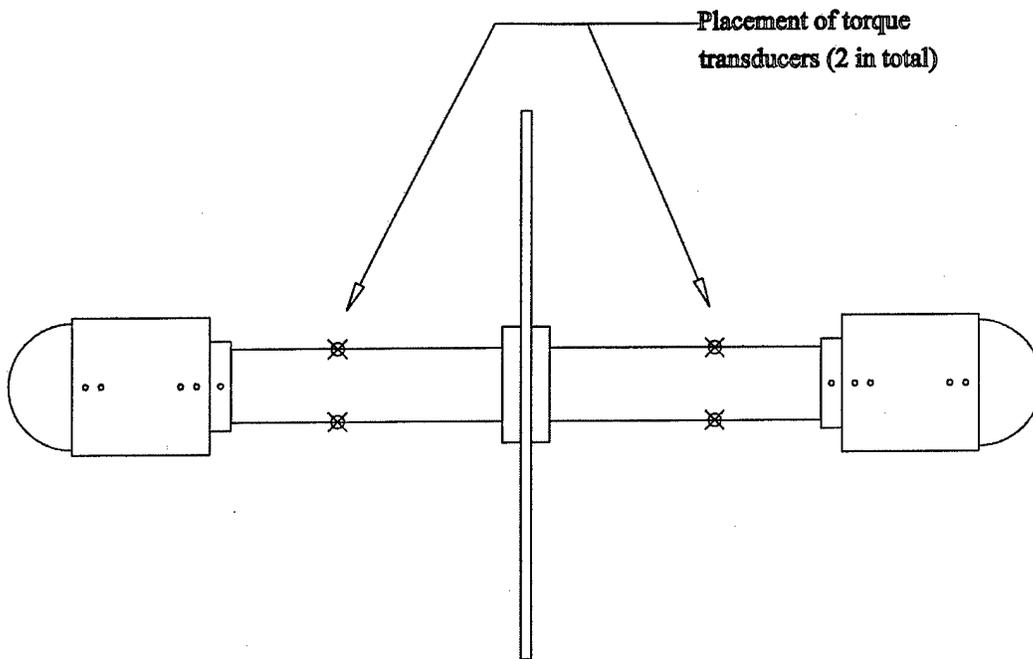


Figure A3. Location of torque transducer for measuring frictional load.

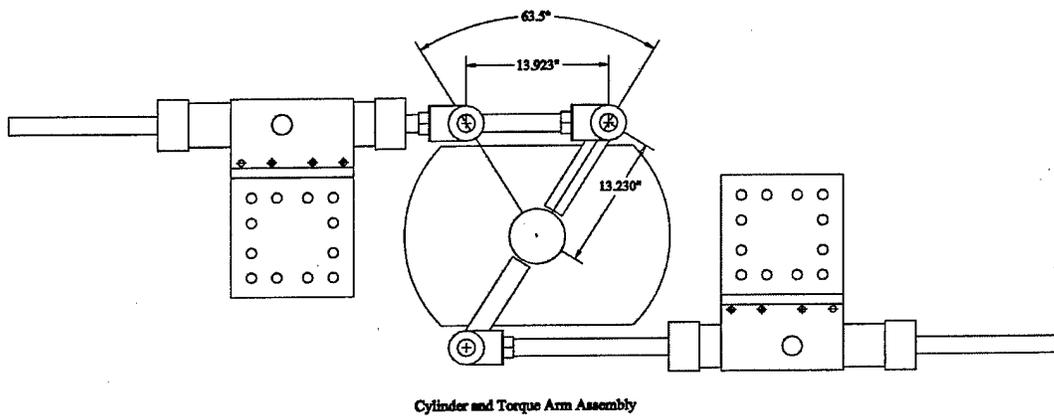


Figure A4. Top and bottom actuators assembly.

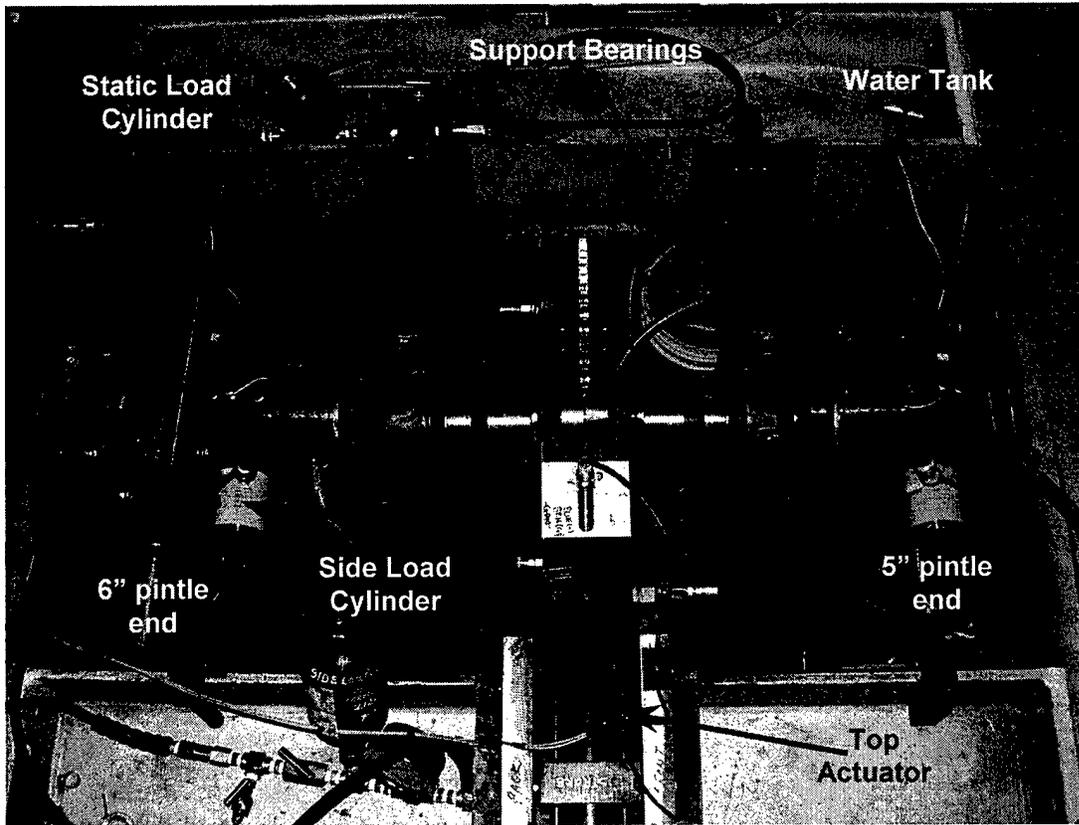


Figure A5. Overview of test set-up.

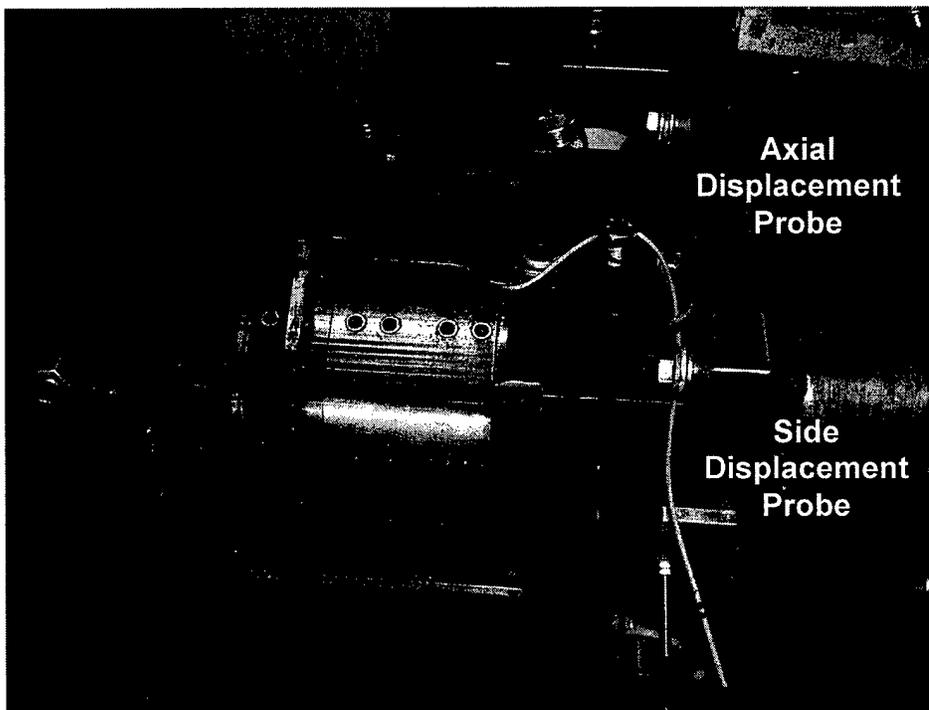


Figure A6. Close-up view of 6" pintle side.

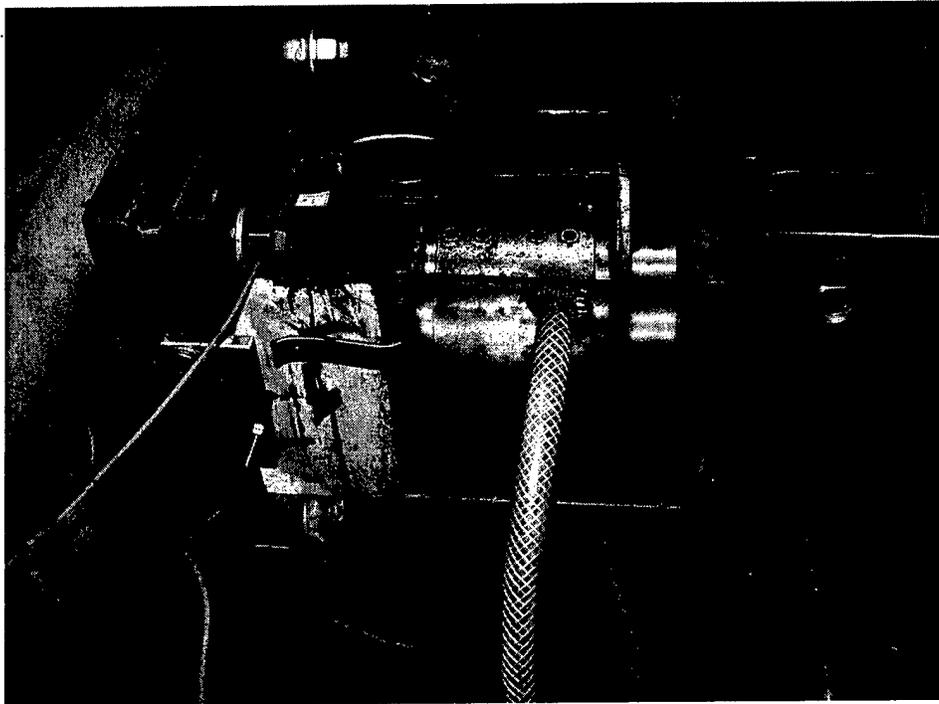


Figure A7. Close-up view of 5" pintle side.

**APPENDIX B
THORDON HPSXL TEST RESULTS**

THORDON HPSXL PINTLE/BUSHING TEST

The Thordon HPSXL pintle bushings initially started with noticeable vibration (chatter) particularly on the 6" pintle side. There was less vibration noticed on the 5" pintle side. This eventually changed to a high frequency squeal as the test progressed. The squeal continued, primarily from the 5" side, until the approximately the 50,000 cycle mark. At this point, light coloured powdered wear debris was observed in both tanks (more so on the 5" side). After approximately the 50,000-cycle point, as the squealing noise decreased, the friction levels and temperature started dropping. This continued until the end of the test.

Post Test Examination:

Five (5) inch pintle/bushing combination: There was a substantial build-up of wear debris as clumps of compacted light coloured powder side loaded area of the bushing (Figure B3). A darker coloured circular band below the accumulated wear debris indicates the principal area of pintle contact axially (Figure B2). This contact area is approximately at 45-degree angle to the pintle axis and covers about 20 degree arc. This darker band is smooth with no depressions such as in the area directly above.

There is some scoring/galling on the bushing edge loaded side of the pintle. The bushing was highly polished in all the contact areas. The pintle contact area where the dark band is on the bushing shows a light shading due to material transfer from the bushing. This is a good indication of as self-lubricating bushing functioning. The location where the wear debris had accumulated in bushing (as clumps) has some surface roughness along with polishing. The edge of the pintle shows some discolouring from the contact with the bushing.

Six (6) inch pintle/bushing combination: This bushing showed a similar pattern of contact and wear debris build-up (although to a lesser extent) compared to the 5-inch pintle (Figure B8). The dark contact band is at approximately a 60-degree angle to the pintle axis and covers about a 10-degree arc.

The 6-inch pintle indicated a contact area of approximately 20 degrees of arc. Where the dark band is in the bushing, the same area on the pintle is coated with transferred bushing material (a good indication of self-lubrication taking place) (Figure B7). The contact area where wear debris had built-up (next to the bushing edge) had darker striations of deposited material.



Figure B1. Close-up view of 5" pintle contact side. There is marked scoring towards stepped edge of the pintle.

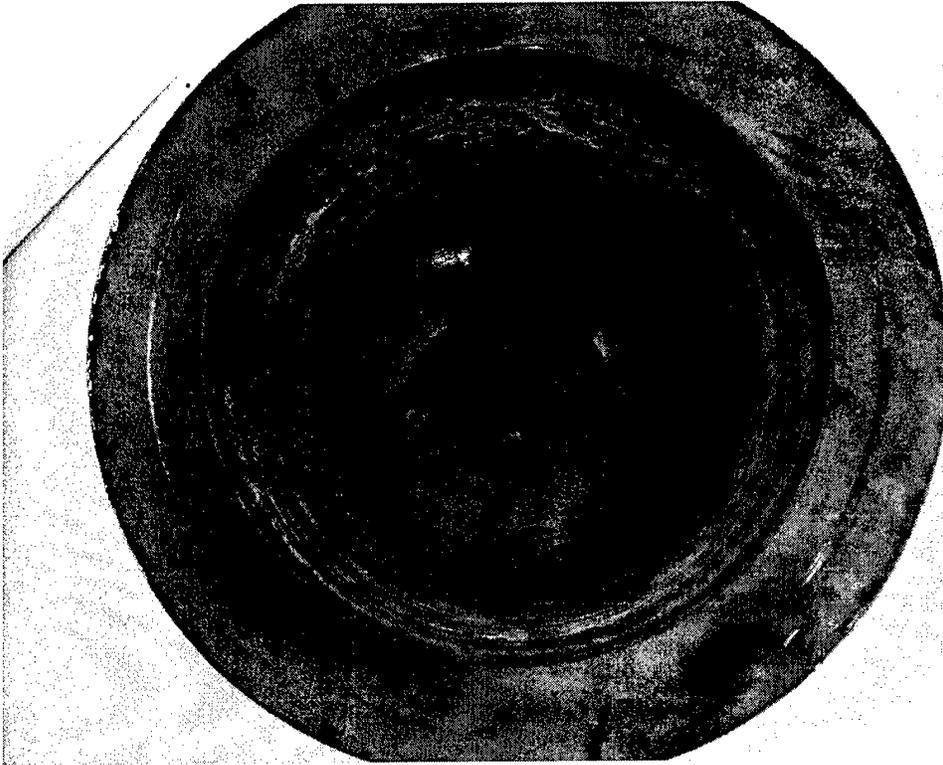


Figure B2. Thordon HPSXL 5" pintle bushing.

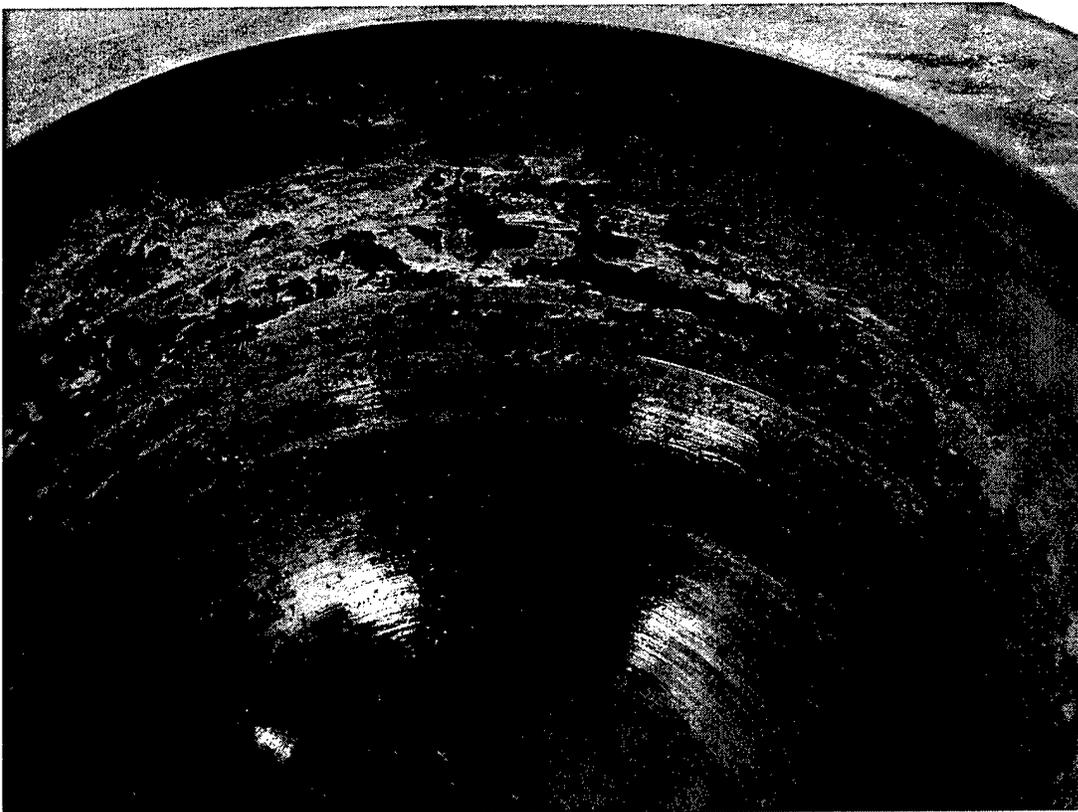



Figure B3. Close-up view of loaded side of bushing. Note accumulated wear debris.



Figure B4.

PINTLE BEARING TESTS
5" PINTLE/BUSHING
WEAR

Thordon HPSXL

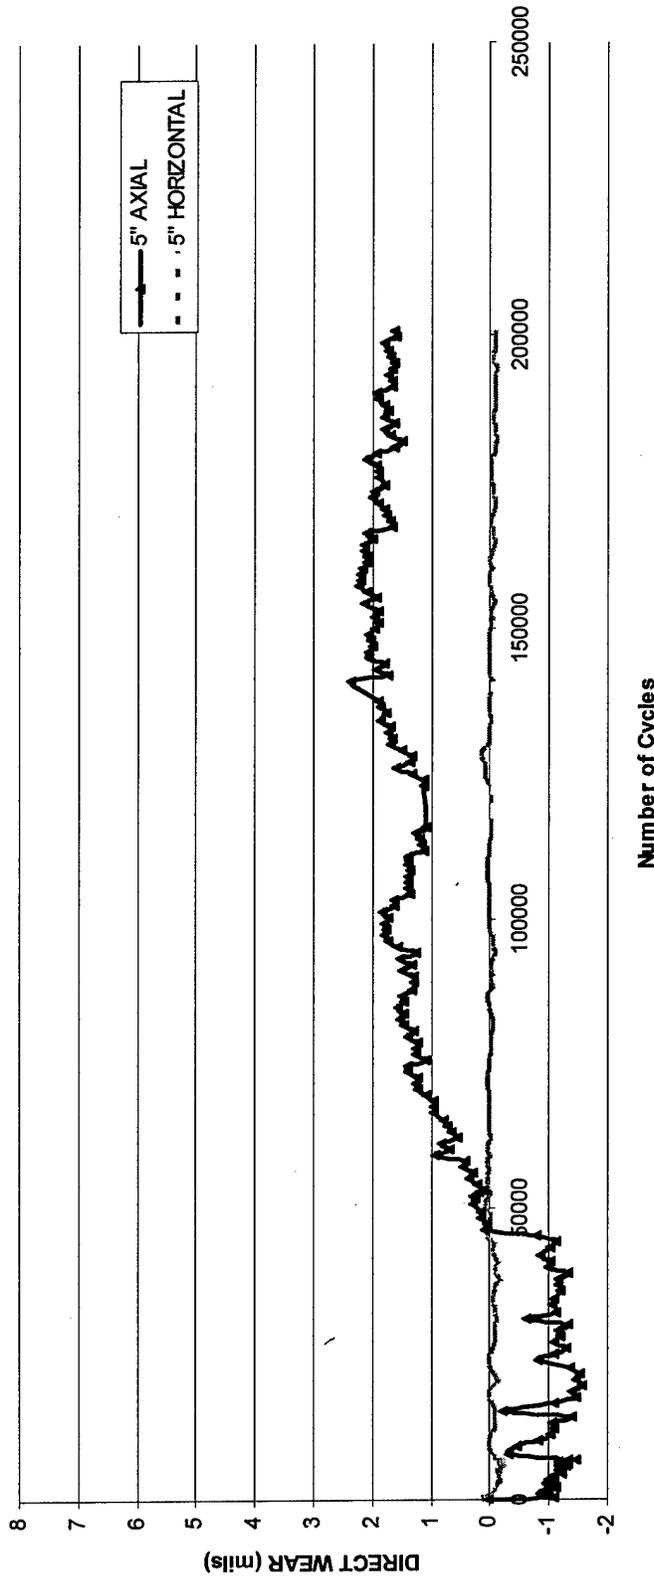

Number of Cycles

Figure B5.

**PINTLE BEARING TESTS
 5" PINTLE/BUSHING
 WEAR AND TEMPERATURE**

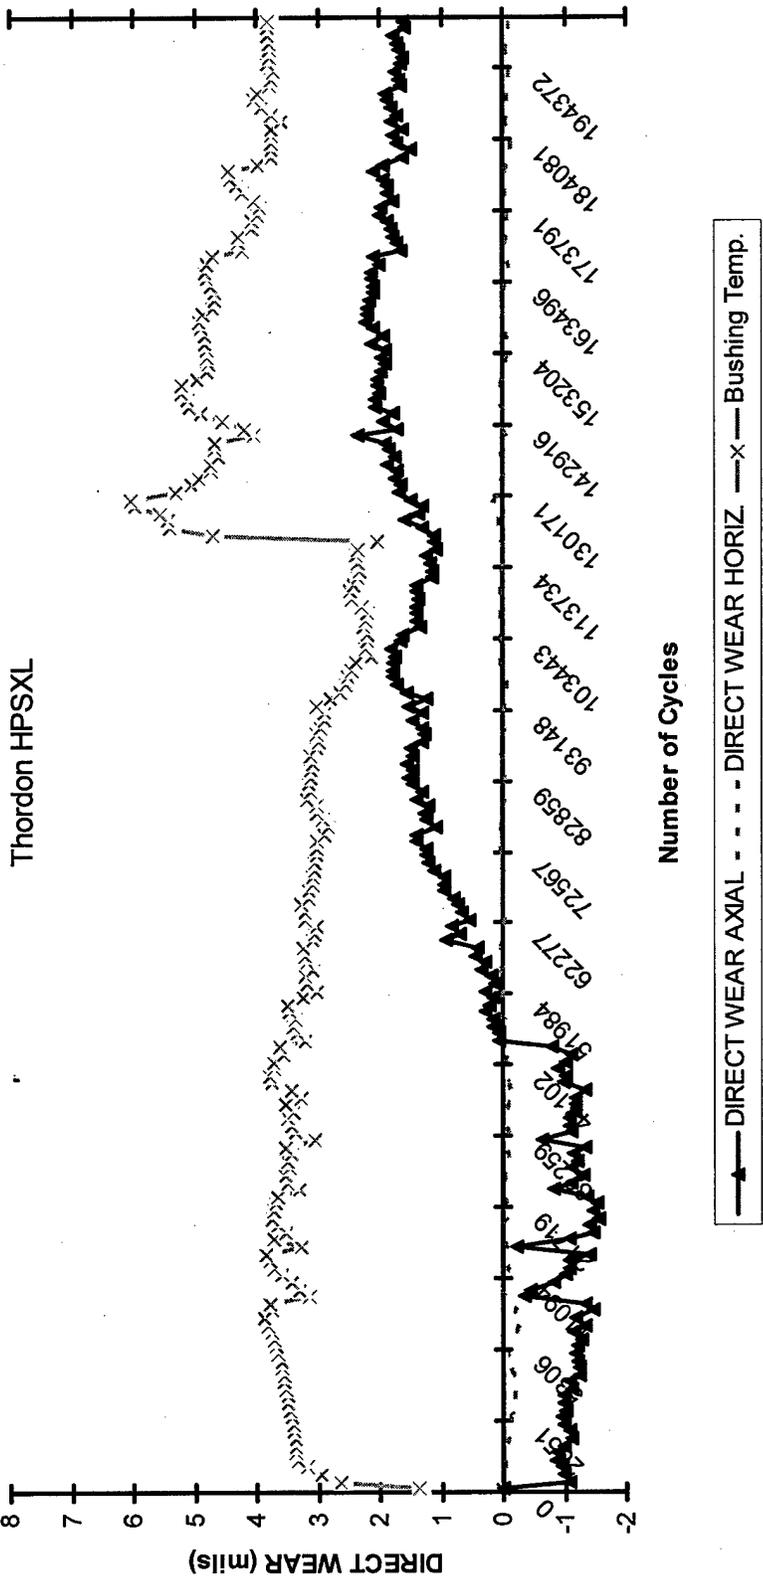


Figure B6.

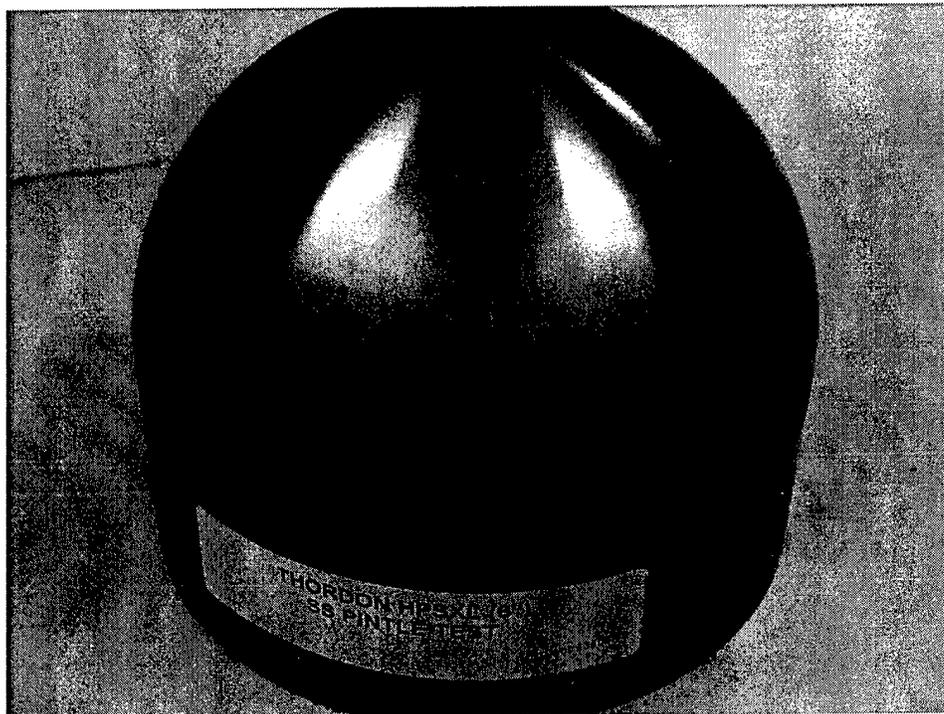


Figure B7. Overview of Thordon HPSXL 6" pintle. Note staining of pintle on loaded side.



Figure B8. Close-up view of Thordon HPSXL 6" pintle bushing. Primary contact area is at top of image.



Figure B9. Close-up view above image on loaded side. Note accumulation of wear debris above darker contact area.

PINTLE BEARING TESTS
6" PINTLE/BUSHING
COEFFICIENT OF FRICTION

Thordon HPSXL

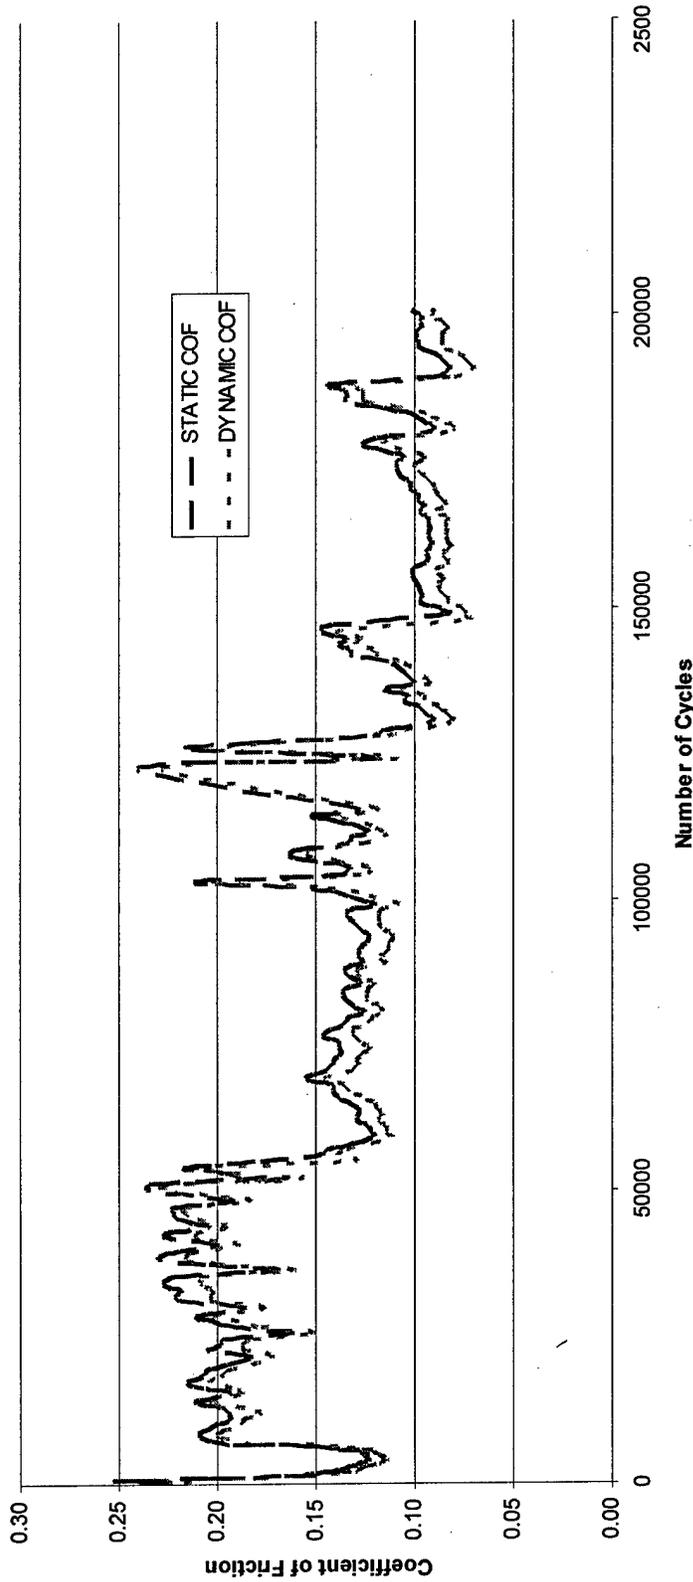


Figure B10.

**PINTLE BEARING TESTS
6" PINTLE/BUSHING
WEAR**

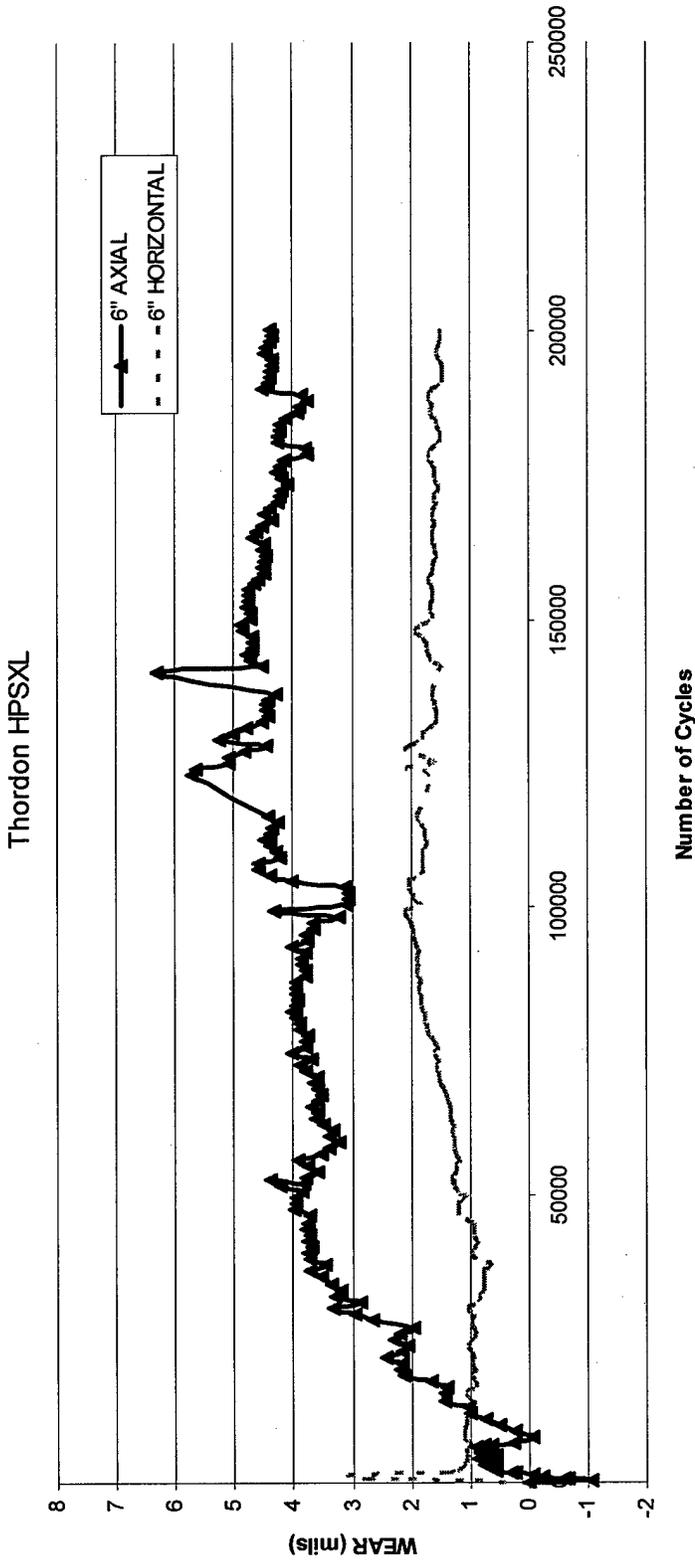


Figure B11.

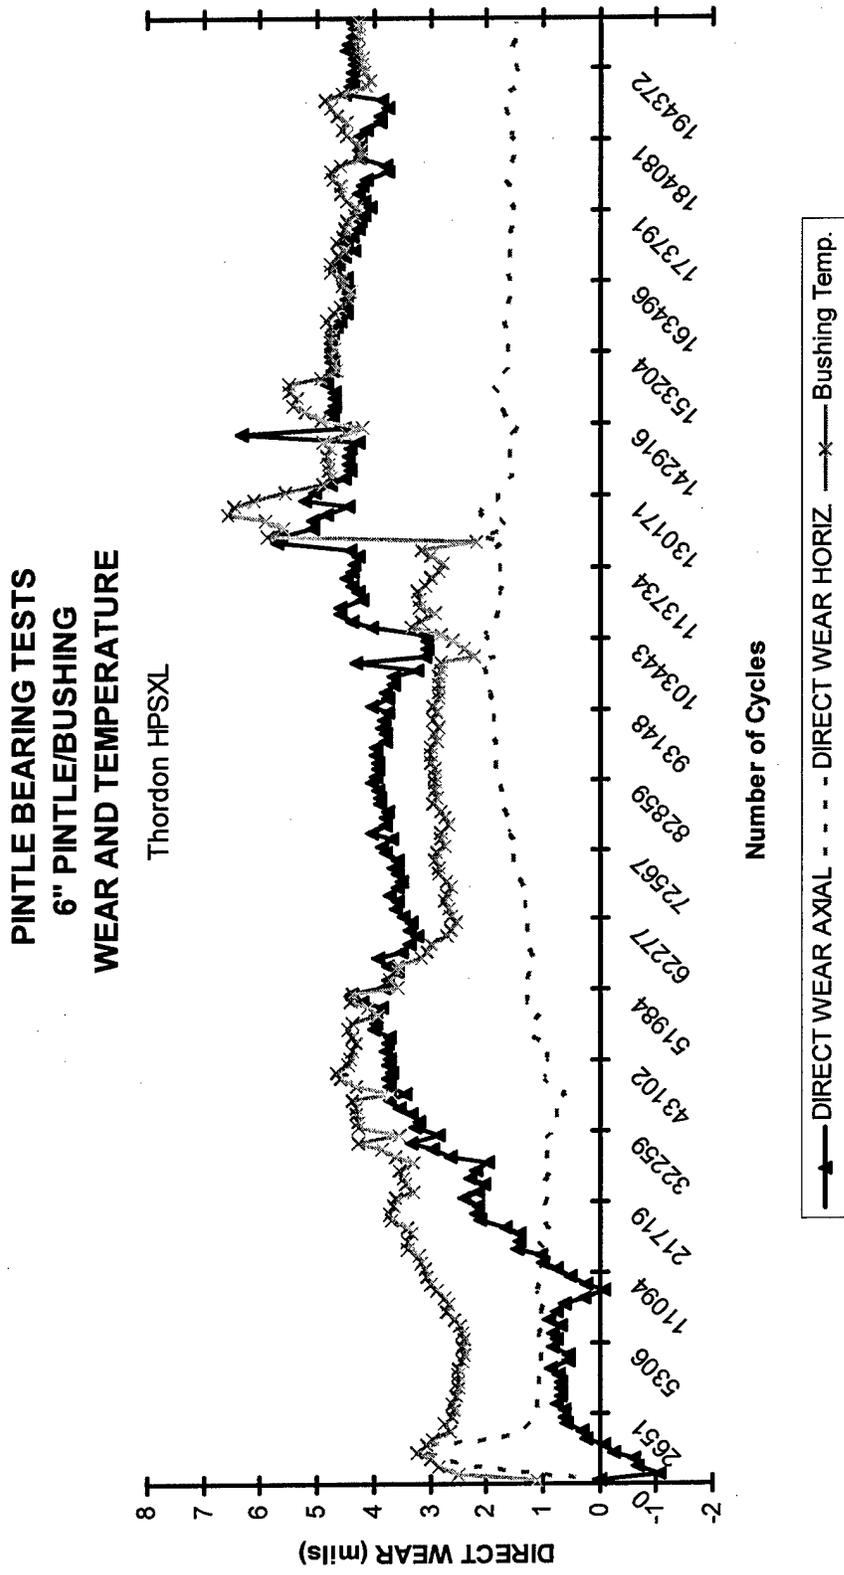


Figure B12.

**APPENDIX C
KAMATICS KARON SELF-LUBRICATING BUSHINGS/PINTLE TEST**

KAMATICS KARON V SELF-LUBRICATING BUSHINGS/PINTLE TEST

The Kamatics Karon V bushing/pintle combinations operated throughout the test without any indication of stress. The test ran quietly with low friction and low temperatures after the pintles had settled in.

Post Test Examination:

Five (5) inch pintle/bushing combination. The test started with relatively high friction (no audible indications the stress was excessive). As the pintle settled into the bushing, the friction levels and operating temperatures dropped. The pintle contact area was next to the top and extended over an arc of approximately 30 degrees (Figure C1). The area was uniformly coated with transferred lubricant material indicating the self-lubricating bushing was performing, as it should.

The bushing contact area was limited to the top of the bushing over an arc of approximately 30 degrees. A dark highly polished band evidenced this, which was slightly wider on the side-loaded area of the bushings (Figure C2). This contact area did not show any signs of stress although there were small amounts of wear debris on the edges of the contact areas.

Six (6) inch pintle/bushing combination. The six (6) inch bushing followed a similar pattern as in the five (5) inch greased bushing test. The contact areas were highly polished and next to the top edge of the bushing (Figures C8 and C9). The pintle contact area was over approximately 20 degrees of arc (at right angles to the pintle axis) and had a uniform light colour from the transfer of lubricant material from the bushing (Figure C7).



Figure C1. Close-up view of 5" pintle from Kamatics Karon V test.

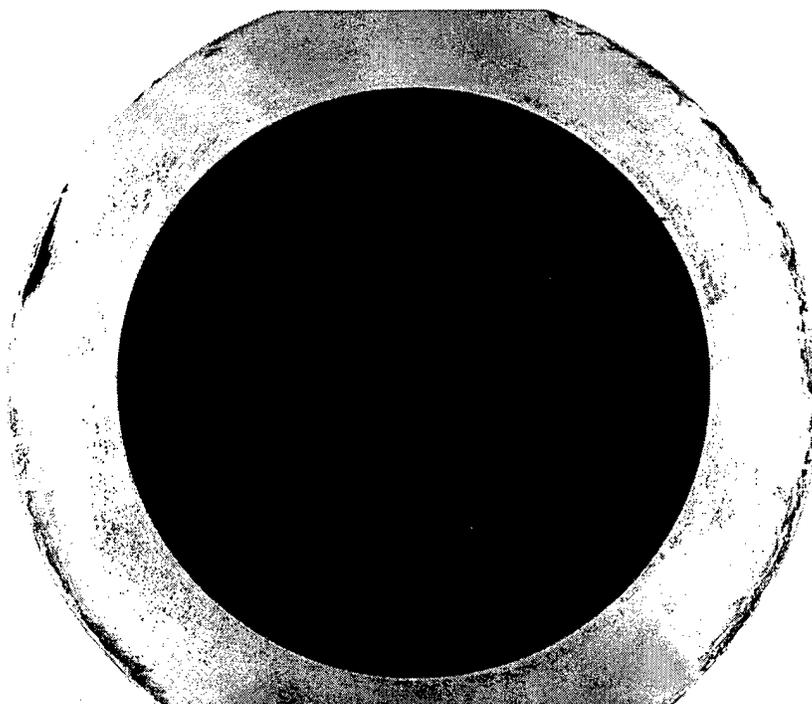


Figure C2. Close-up view of 5" Karon V bushing. Note uniform polished contact areas.




Figure C3. Close-up view of 5" Karon V bushing. Note highly polished contact area. There is no indication of stress to the lubricant layer.

**PINTLE BEARING TESTS
5" PINTLE/BUSHING
COEFFICIENT OF FRICTION**
Kamatics KAron V

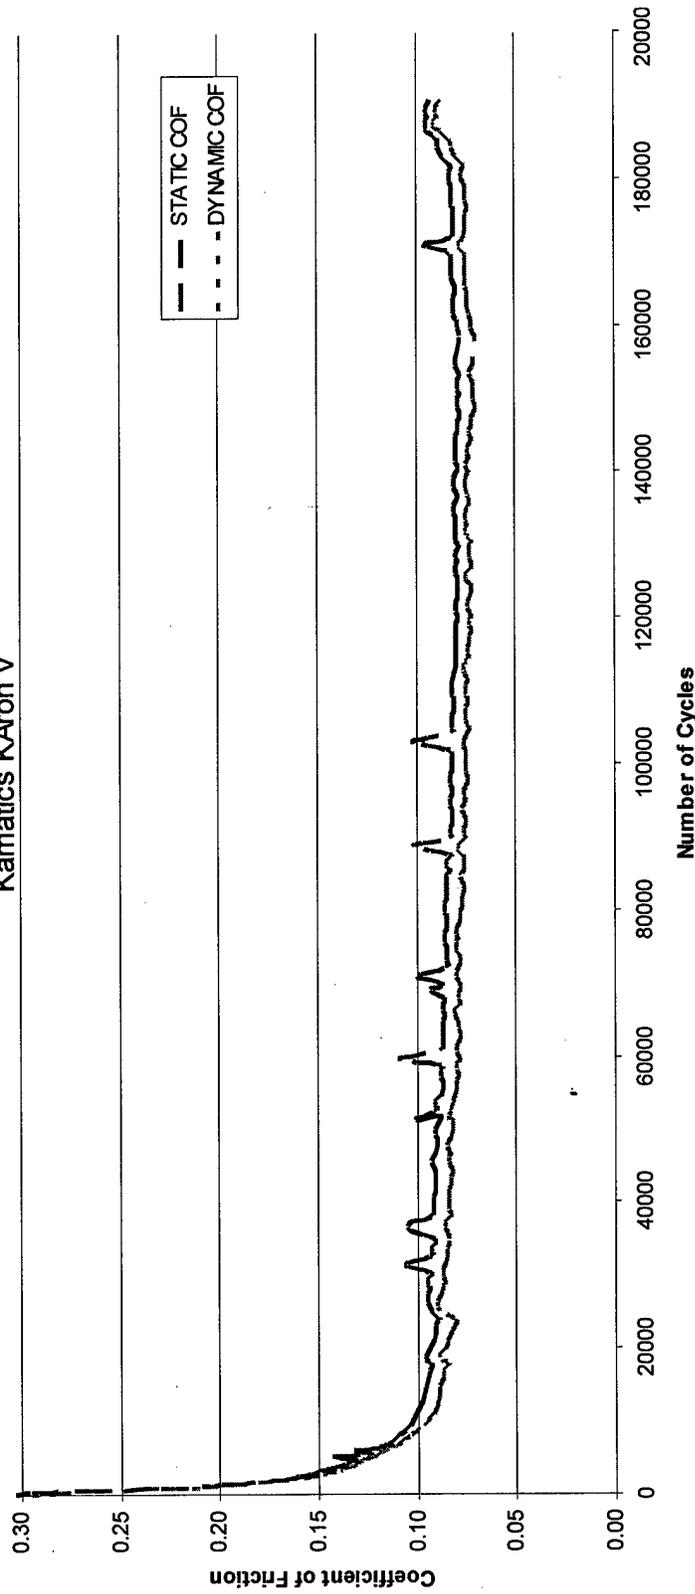


Figure C4.

**PINTLE BEARING TESTS
5" PINTLE/BUSHING
WEAR**

Kamatics Karon V

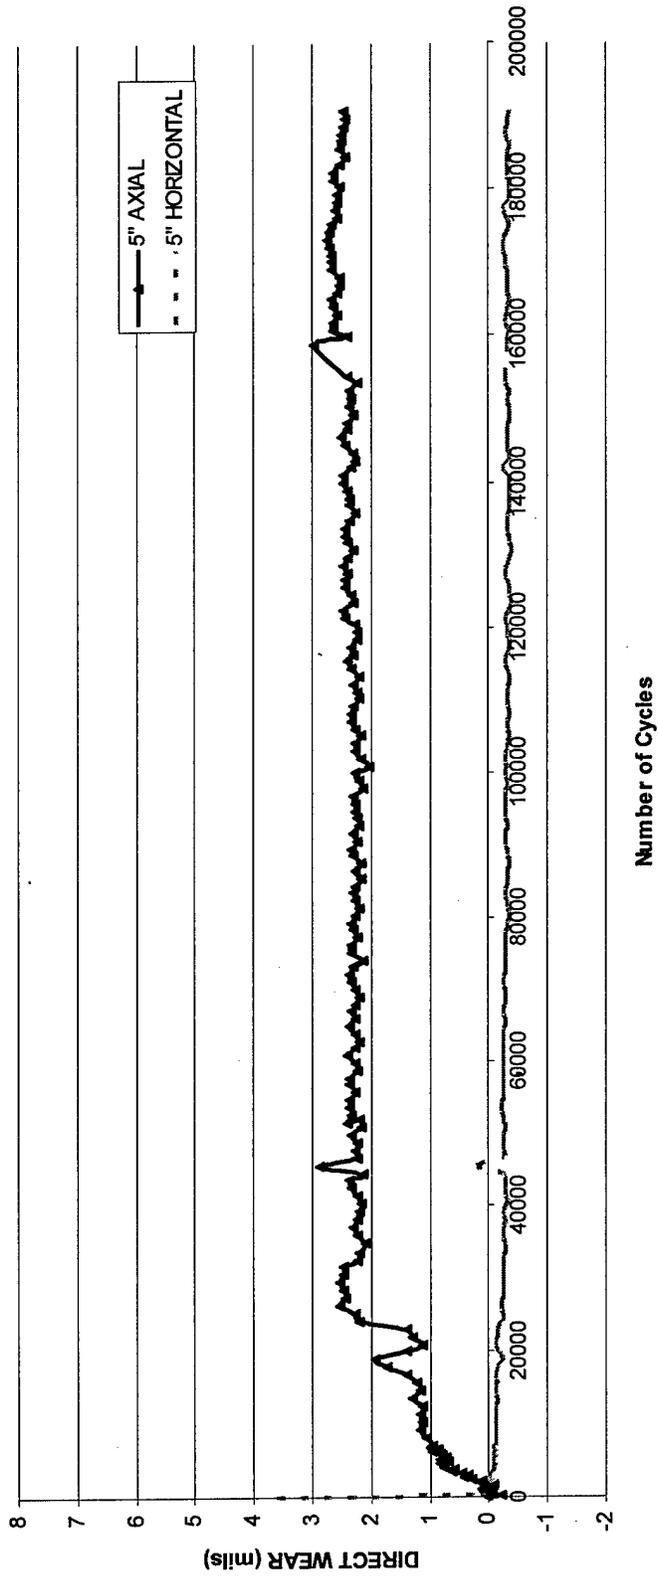


Figure C5.

**PINTLE BEARING TESTS
5" PINTLE/BUSHING
WEAR AND TEMPERATURE**

Kamatics Karon V

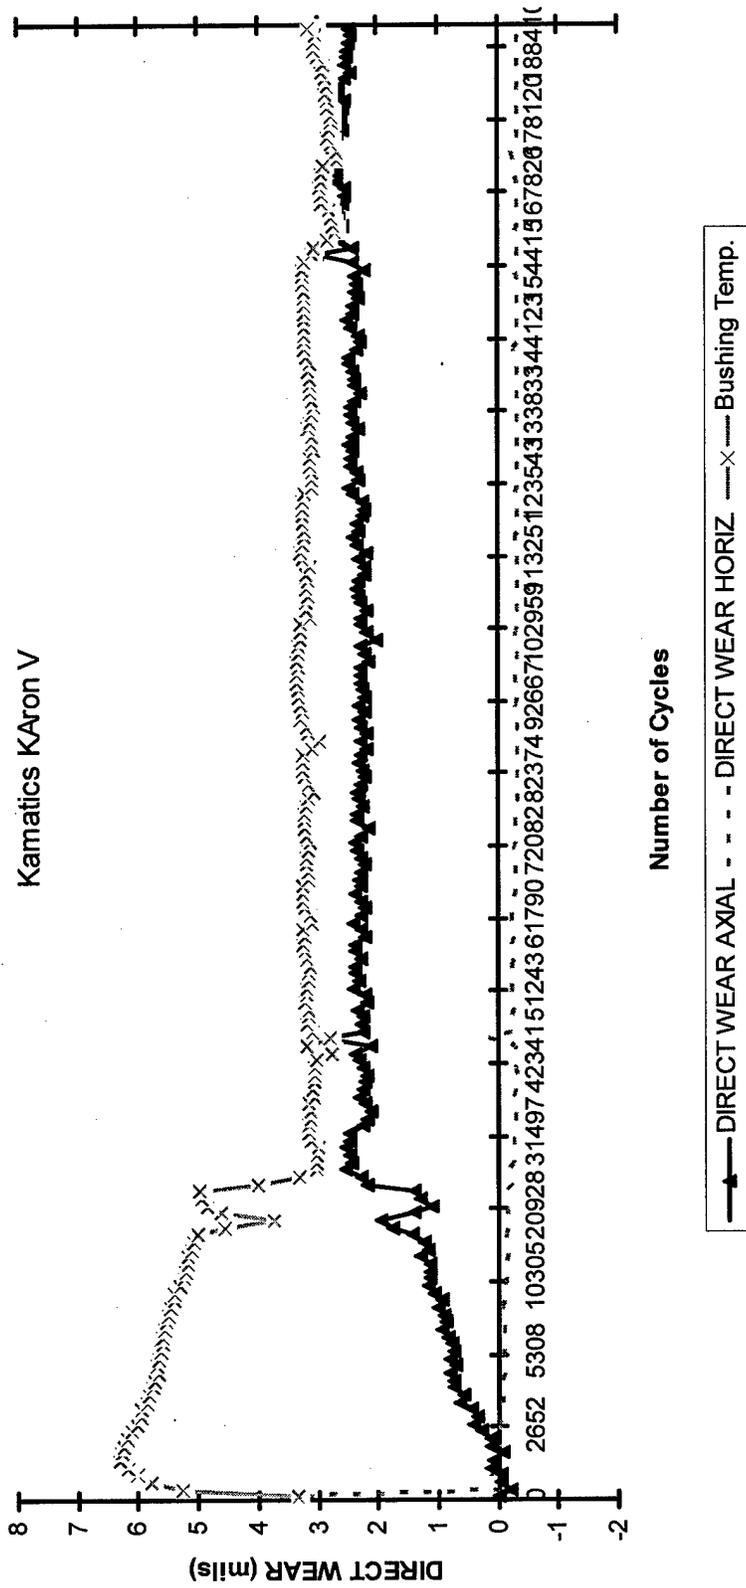


Figure C6.

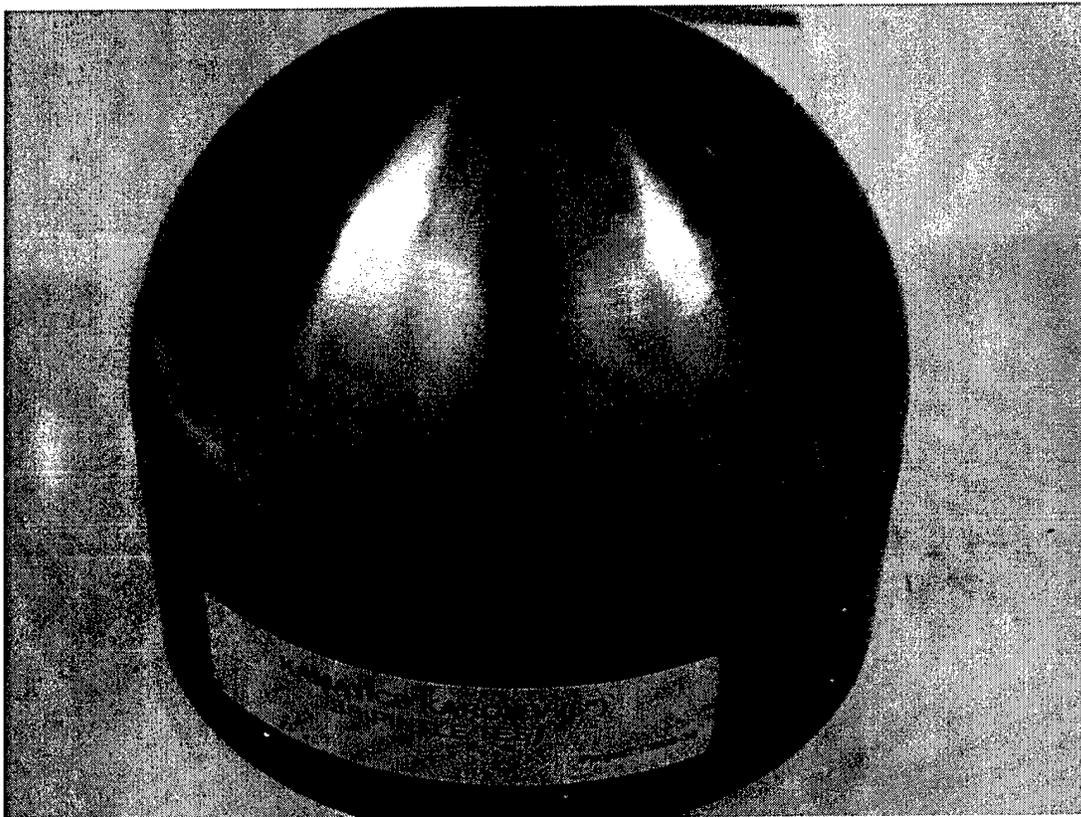


Figure C7. View of 6" Kamatics Karon V pintle.

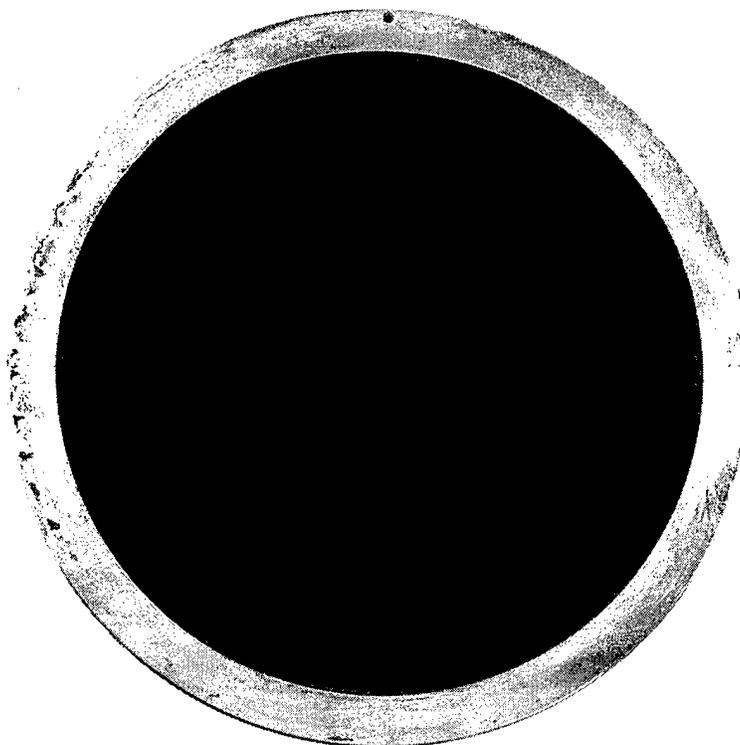


Figure C8. View of Kamatics Karon V bushing. Note dark band, which is next to top edge. This is the pintle contact area.



Figure C9. Close-up view of above image on loaded side. Note polished contact area. There does not appear to be any stress to this area.

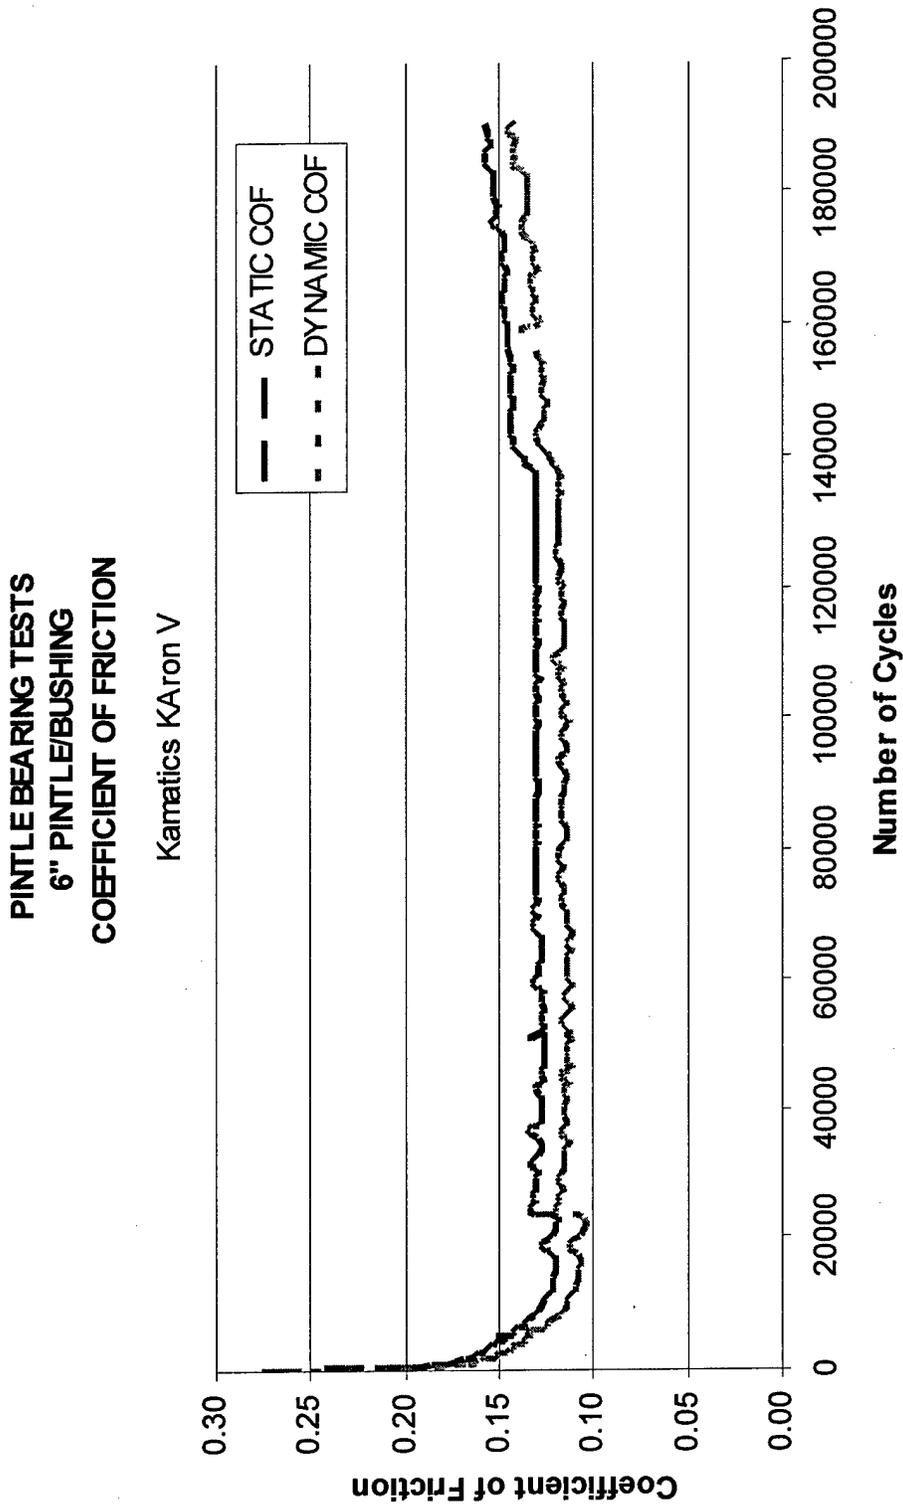


Figure C10.

**PINTLE BEARING TESTS
6" PINTLE/BUSHING
WEAR**

Kamatics KAron V

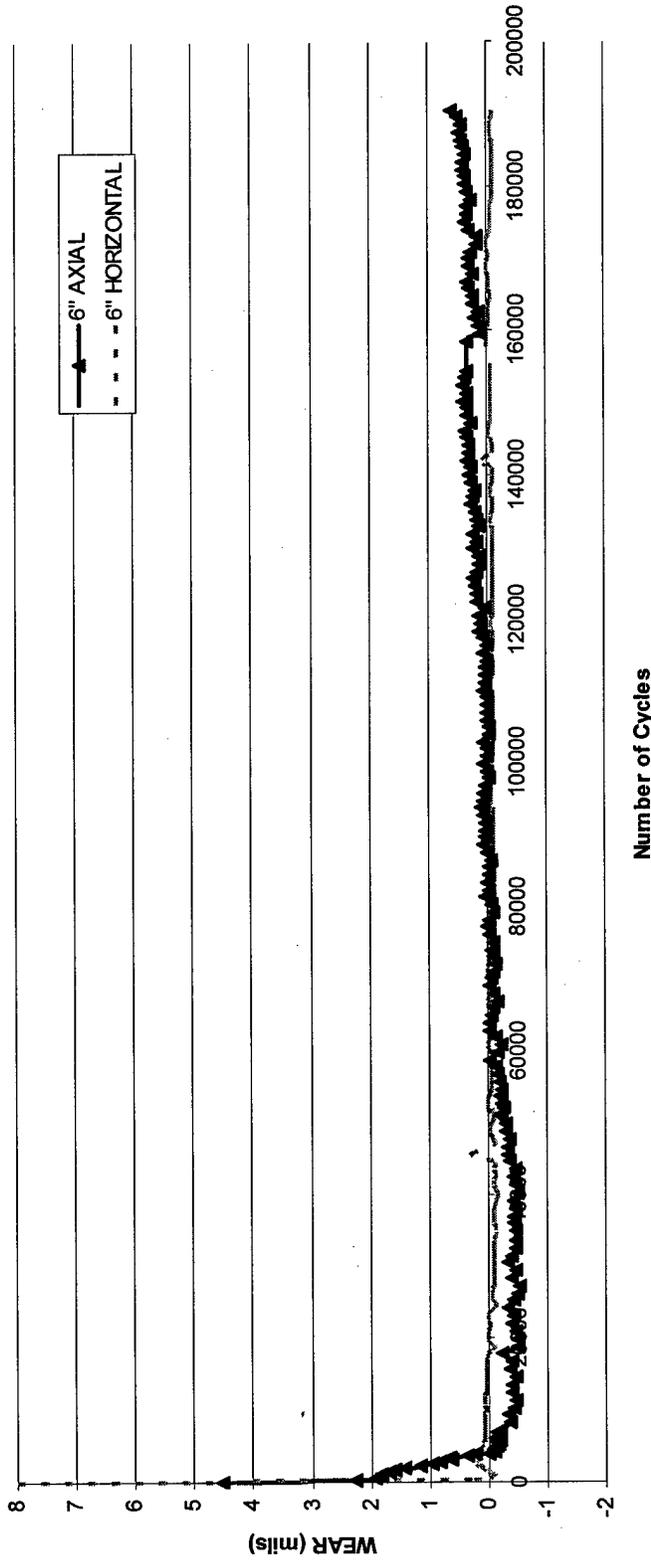


Figure C11.

PINTLE BEARING TESTS 6" PINTLE/BUSHING WEAR AND TEMPERATURE

Kamatics KAron V

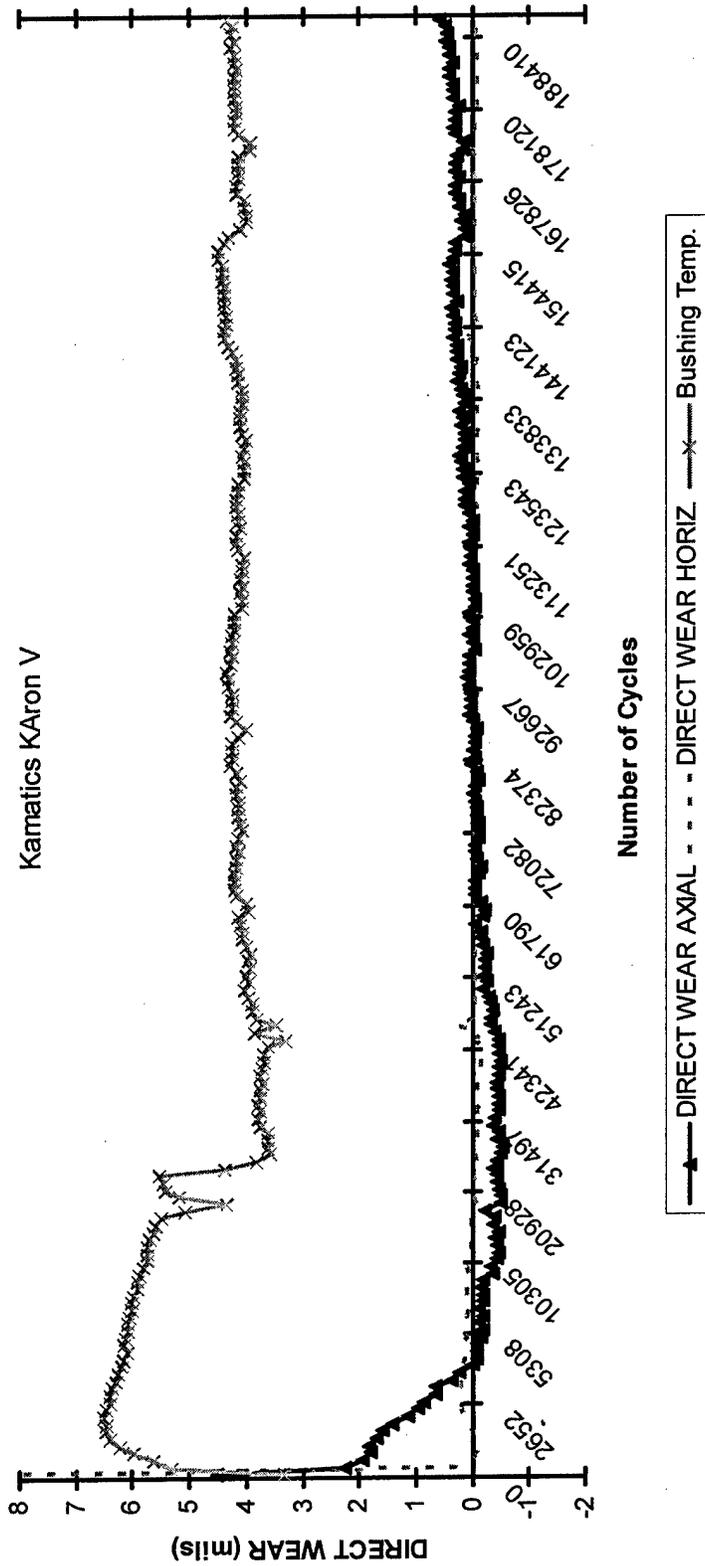


Figure C12.

APPENDIX D

TENMAT SELF-LUBRICATING BUSHING (RETAINING COLLAR) TEST RESULTS

TENMAT T814 (Retaining Collar) PINTLE/BUSHING TEST

The bushings were composed of a lubricant layer 0.1875 inch thick (Tenmat T814) mounted on a bronze backing. The lubricant layer has a light brown colour showing fabric like texture. These particular bushings were held in place with a stainless steel collar compressing the Tenmat T814 into the bronze backing. The test initially started with significant vibration (loud noise). This continued for approximately 100,000 cycles reducing in volume as the pintles seated into the bushings. At approximately the 140,000 cycle point, the water had run out in the reservoir due to spillage. The temperature increased for a short period of time (50 deg C for the 6 inch pintle and 35 deg C for the 5 inch pintle). The water was replaced and the test continued quietly until the end.

Post Test Examination:

Five (5) inch pintle/bushing combination: Pintle contact on the bushing was virtually 100%. The pintle was highly polished with bands of transferred bushing lubricant material. The bands, particularly on the side-loaded area, are an indication of a functioning self-lubricating bushing (Figure D1).

The bushing contact surfaces were polished. There were darker bands towards the bottom of the bushing (Figure D2). There was some build-up of wear debris at the bottom of the bushing. The bushing did not appear to have been stressed by the test, as it was 100% intact.

Six (6) inch pintle/bushing combination: pintle contact was approximately 95%. The pintle was highly polished over most of its contact surface. The edge of the pintle where the main side load was applied had a darkened deposit of transferred bushing material (Figure D7). This was adhering well to the surface and was rough in texture.

The bushing contact surface was polished smooth. The loaded side of the bushings was darker in colour and corresponded to the same area on the pintle (Figure D8). The bottom of the bushing appears to have a build-up of dark wear material. Otherwise, the bushing is similar in appearance to the five (5) inch combination and does not appear to be stressed by the test regime.



Figure D1. Overview of 5" Tenmat T814 pintle. Due to the thickness of the bushing-retaining ring, the first row of pintle anchoring holes had to be machined away.

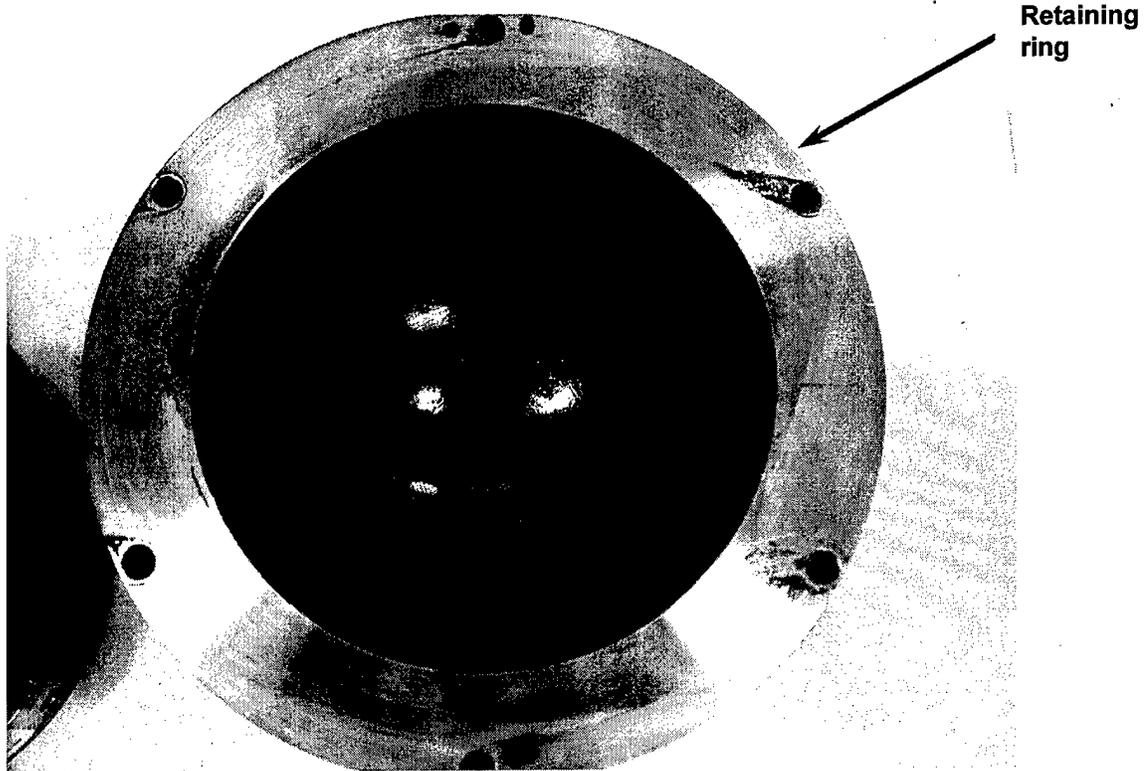


Figure D2. Close-up view of 5" Tenmat T814 bushing.



Figure D3. Close-up view of Tenmat T814 5" bushing. Note darker contact areas.

**PINTLE BEARING TESTS
5" PINTLE/BUSHING
COEFFICIENT OF FRICTION
Tenmat T814 in River Water**

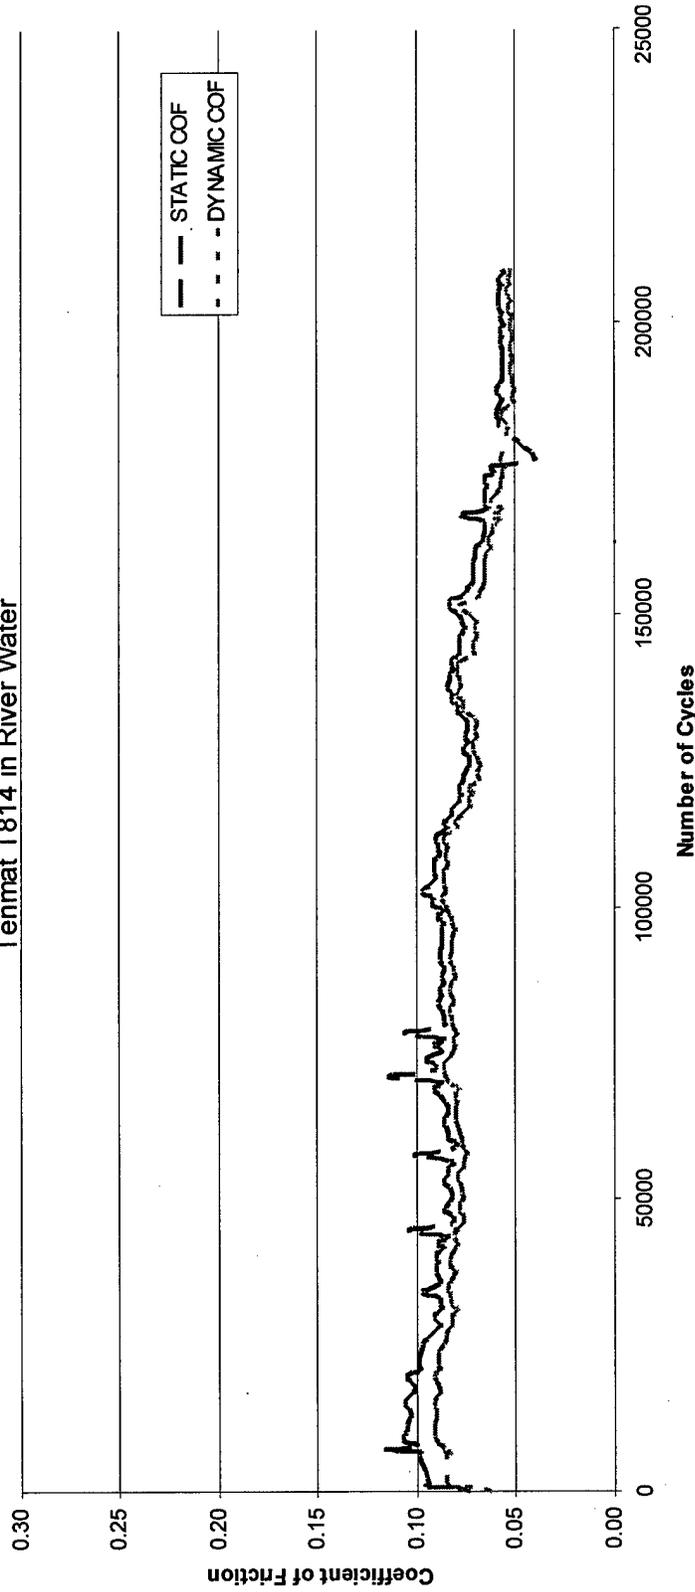


Figure D4.

**PINTLE BEARING TESTS
5" PINTLE/BUSHING
WEAR**

Tenmat T814 in River Water

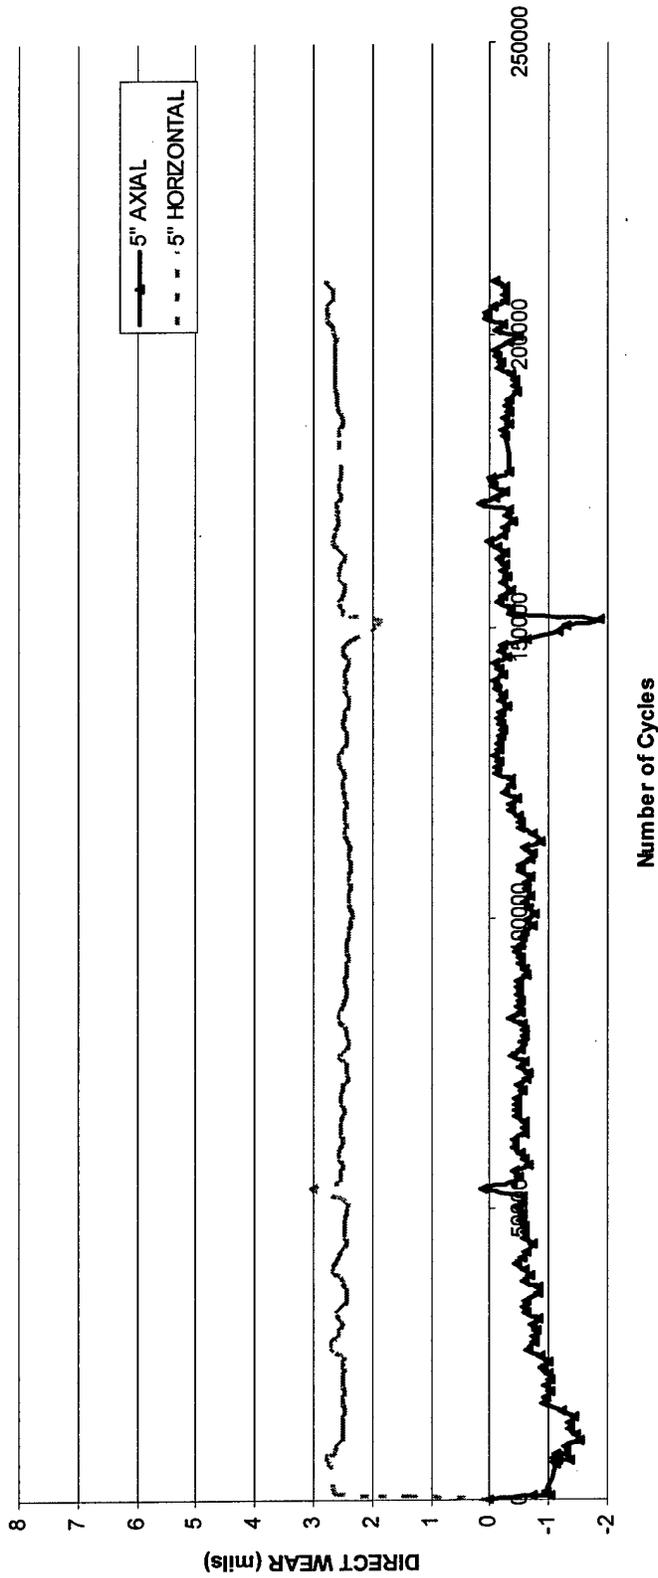


Figure D5.

**PINTLE BEARING TESTS
 5" PINTLE/BUSHING
 WEAR AND TEMPERATURE**

Tenmat T814 in River Water

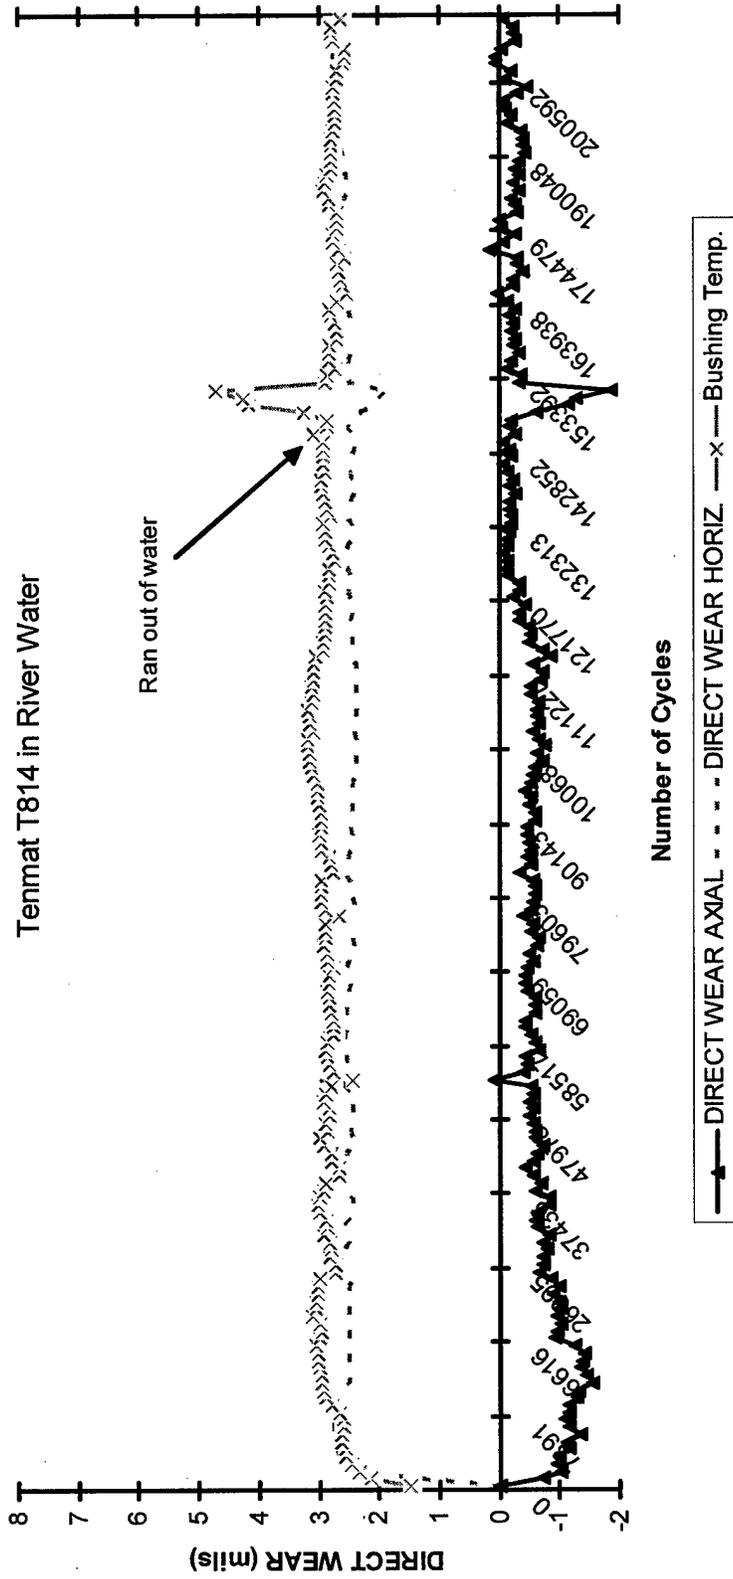


Figure D6.



Figure D7. Overview of 6" Tenmat T814 pintle. Note transferred lubricant material on side of pintle contact surface.



Figure D8. Close-up view of 6" bushing. There is no indication damage to the bushing. Contact is over 95% of the bushing surface.

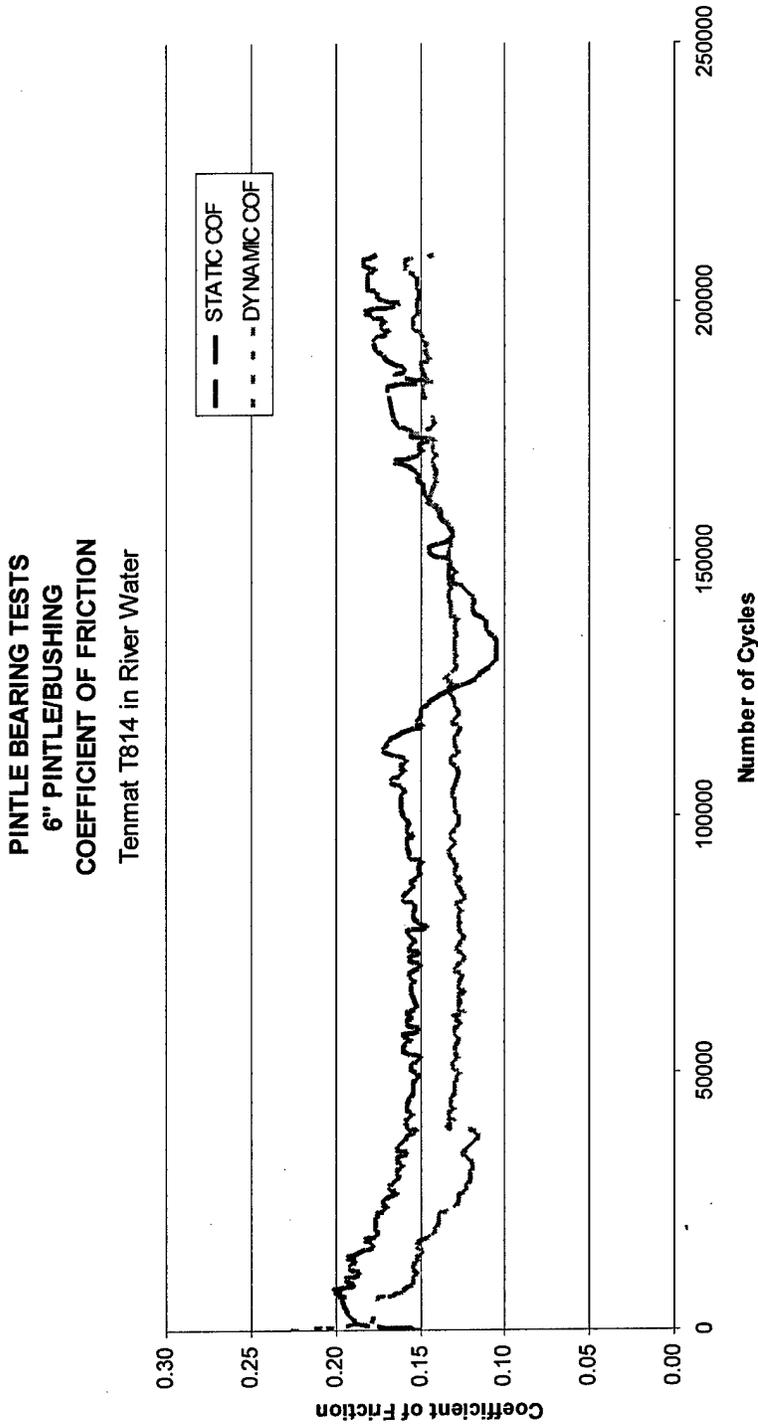


Figure D9.

**PINTLE BEARING TESTS
6" PINTLE/BUSHING
WEAR**

Tenmat T814 in River Water

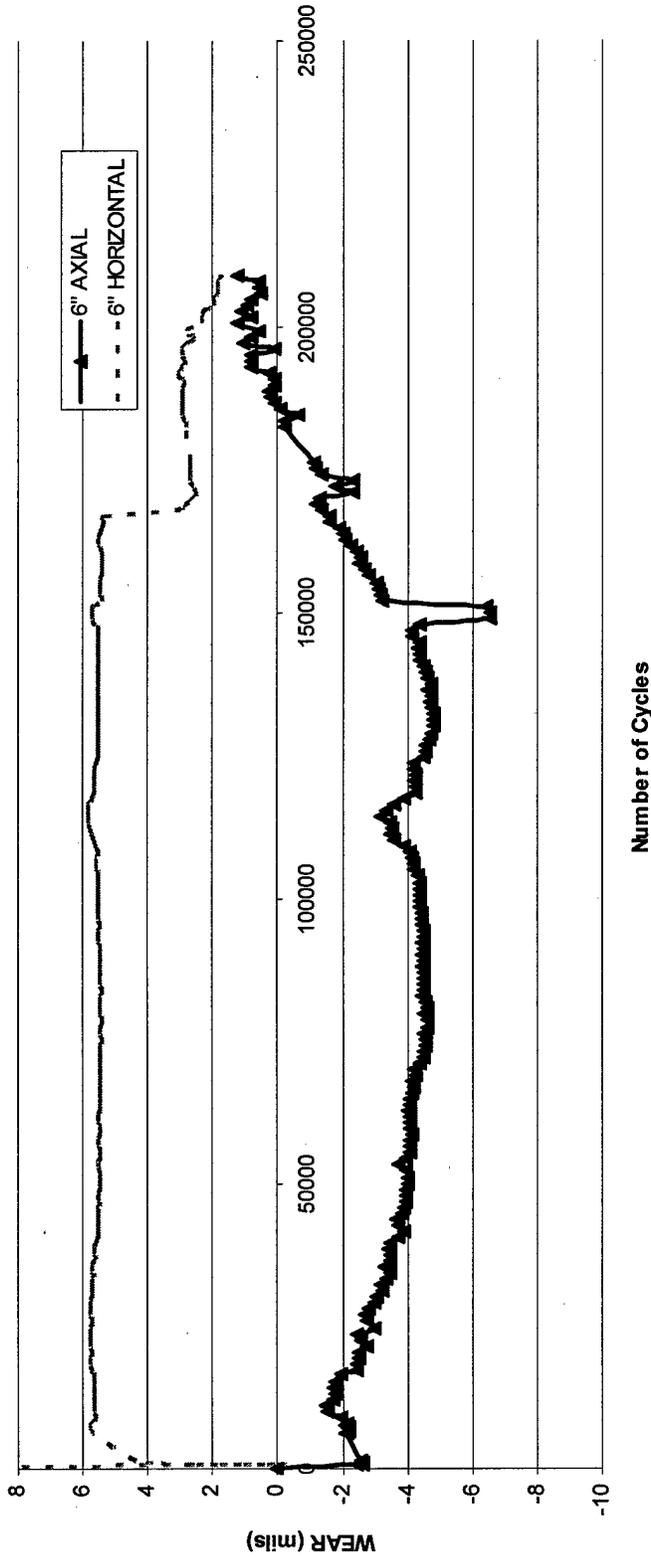


Figure D10.

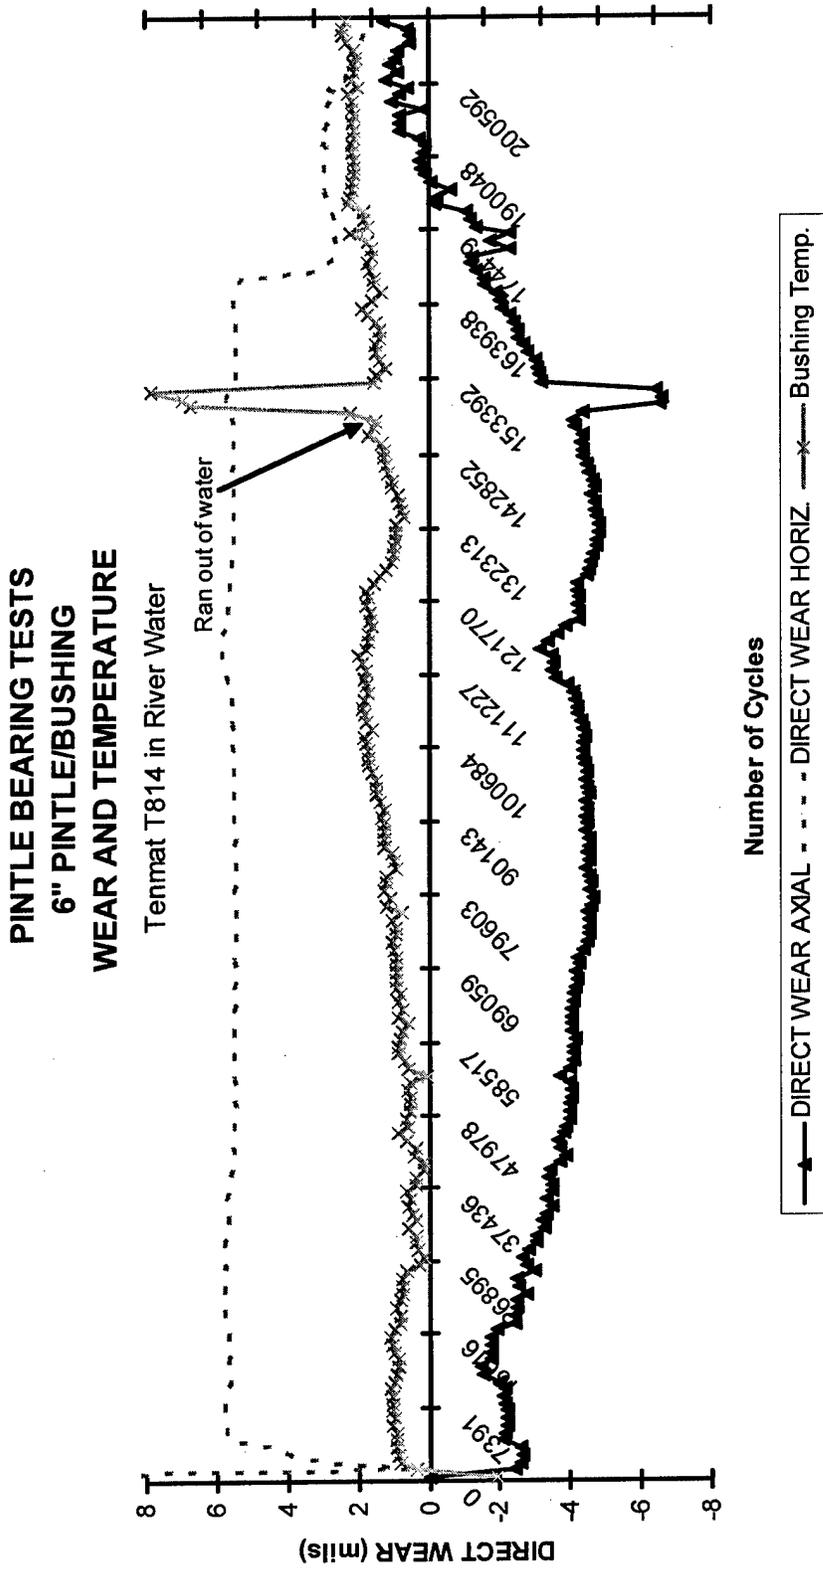


Figure D11.

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing this collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.

1. REPORT DATE (DD-MM-YYYY) 06-2004		2. REPORT TYPE Final		3. DATES COVERED (From - To)	
4. TITLE AND SUBTITLE Field Evaluation of Self-Lubricated Mechanical Components for Civil Works Navigation Structures				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S) Timothy D. Race, Ashok Kumar, and L.D. Stephenson				5d. PROJECT NUMBER CW	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER 33238	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) U.S. Army Engineer Research and Development Center (ERDC) Construction Engineering Research Laboratory (CERL) PO Box 9005 Champaign, IL 61826-9005				8. PERFORMING ORGANIZATION REPORT NUMBER ERDC/CERL SR-04-8	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) U.S. Army Corps of Engineers 441 G Street, NW. Washington, DC 20314-1000				10. SPONSOR/MONITOR'S ACRONYM(S) HQ02	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION / AVAILABILITY STATEMENT Approved for public release; distribution is unlimited.					
13. SUPPLEMENTARY NOTES Copies are available from the National Technical Information Service, 5285 Port Royal Road, Springfield, VA 22161.					
14. ABSTRACT It is operationally and environmentally desirable to replace greased bronze bushings used in navigation lock machinery with self-lubricating bushings. Bronze bushings must be greased manually or with automatic lubricating machines. Grease lines are subject to damage from ice and debris. If the grease line breaks, the lubricating system fails, which may lead to component failure and delays in navigation. Introduction of grease into the riverine environment is also a concern. The Corps of Engineers has been using self-lubricating bushings in navigation locks for the past 20 years. The purpose of this study was to evaluate mechanical properties and durability of emerging advanced self-lubricating bushing/bearing materials in the laboratory and under field conditions, and to provide additional knowledge, needed guidelines, and standard specifications for the proper selection and use of self-lubricating bushing materials for locks based on local environmental conditions and applications. The results of accelerated testing of quarter-scale model self-lubricating pintle bushings in simulated river are also reported.					
15. SUBJECT TERMS evaluation, civil works, navigation structures, mechanical systems, self-lubricating					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT SAR	18. NUMBER OF PAGES 172	19a. NAME OF RESPONSIBLE PERSON Ashok Kumar
a. REPORT Unclassified	b. ABSTRACT Unclassified	c. THIS PAGE Unclassified			19b. TELEPHONE NUMBER (include area code) (217) 373-7235