

# REPORT DOCUMENTATION PAGE

*Form Approved*  
*OMB No. 0704-0188*

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing this collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. **PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.**


|  |                    |  |                                   |   |  |
|--|--------------------|--|-----------------------------------|---|--|
| <b>1. REPORT DATE (DD-MM-YYYY)</b><br>13-07-2006   |                    | <b>2. REPORT TYPE</b><br>Journal Article |                                   | <b>3. DATES COVERED (From - To)</b>   |  |
| <b>4. TITLE AND SUBTITLE</b><br><br><b>Polyazidopyrimidines: High Energy Compounds and Precursors to Carbon Nanotubes (Postprint)</b>  |                    |  |                                   | <b>5a. CONTRACT NUMBER</b>  |  |
|  |                    |  |                                   | <b>5b. GRANT NUMBER</b>   |  |
|  |                    |  |                                   | <b>5c. PROGRAM ELEMENT NUMBER</b>   |  |
| <b>6. AUTHOR(S)</b><br>Chengfeng Ye, Haoxiang Gao, Brendan Twamley, & Jean'ne M. Shreeve (Univ. of Idaho); Jerry A. Boatz (AFRL/PRSP); Gregory W. Drake (Marshall Space Flight Center)   |                    |  |                                   | <b>5d. PROJECT NUMBER</b>   |  |
|  |                    |  |                                   | <b>5e. TASK NUMBER</b><br>23030423  |  |
|  |                    |  |                                   | <b>5f. WORK UNIT NUMBER</b>   |  |
| <b>7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)</b><br><br>Air Force Research Laboratory (AFMC)<br>AFRL/PRSP<br>10 E. Saturn Blvd.<br>Edwards AFB CA 93524-7680  |                    |  |                                   | <b>8. PERFORMING ORGANIZATION REPORT NUMBER</b><br><br>AFRL-PR-ED-JA-2006-238 |  |
| <b>9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES)</b><br><br>Air Force Research Laboratory (AFMC)<br>AFRL/PRS<br>5 Pollux Drive<br>Edwards AFB CA 93524-7048  |                    |  |                                   | <b>10. SPONSOR/MONITOR'S ACRONYM(S)</b>                                       |  |
|  |                    |  |                                   | <b>11. SPONSOR/MONITOR'S NUMBER(S)</b><br>AFRL-PR-ED-JA-2006-238              |  |
| <b>12. DISTRIBUTION / AVAILABILITY STATEMENT</b><br><br>Approved for public release; distribution unlimited (AFRL-ERS-PAS-2006-184)  |                    |  |                                   |   |  |
| <b>13. SUPPLEMENTARY NOTES</b><br>©2006 Wiley-VCH Verlag BmbH & Co. KgaA, Weinheim. Published in Angewandte Chemie 2006, 118, 7420-7423.   |                    |  |                                   |   |  |
| <b>14. ABSTRACT</b><br><br>Organic polyazido substituted compounds are at the forefront of high energy research. Polyazido organic compounds have high relative heats of formation as one azido group adds about 87 kcal/mol of endothermicity to a hydrocarbon compound. <sup>1</sup> In this family of compounds, 3,6-di(azido)-tetrazine ( <b>1</b> ), has the highest reported heat of formation ~ 1101 kJ mol <sup>-1</sup> (6709 kJ kg <sup>-1</sup> ). <sup>2</sup> The compound 4,4',6,6'-tetra(azido)azo-1,3,5-triazine ( <b>2</b> ), has a heat of formation of 2171 (6164 kJ kg <sup>-1</sup> ) (Fig. 1). <sup>3</sup> Recently it was demonstrated that <b>1</b> and <b>4</b> were good precursors to nano carbon nitride materials. <sup>4,5</sup> Thermal decomposition of <b>1</b> <sup>4</sup> and <b>4</b> <sup>5</sup> yields nitrogen-rich nanolayered, nanoclustered and nanodendritic carbon nitrides depending on the different heating processes. |                    |  |                                   |   |  |
| <b>15. SUBJECT TERMS</b>   |                    |  |                                   |   |  |
| <b>16. SECURITY CLASSIFICATION OF:</b>   |                    |  | <b>17. LIMITATION OF ABSTRACT</b> | <b>18. NUMBER OF PAGES</b>  | <b>19a. NAME OF RESPONSIBLE PERSON</b>                     |
| <b>a. REPORT</b>   | <b>b. ABSTRACT</b> | <b>c. THIS PAGE</b>                      |                                   |   | Dr. Scott A. Shackelford                                   |
| Unclassified   | Unclassified       | Unclassified                             | A                                 | 5   | <b>19b. TELEPHONE NUMBER</b><br>(include area code)<br>N/A |

DOI: 10.1002/ange.200602778

**Polyazidopyrimidines: High-Energy Compounds and Precursors to Carbon Nanotubes\*\***

Chengfeng Ye, Haixiang Gao, Jerry A. Boatz, Gregory W. Drake, Brendan Twamley, and Jean'ne M. Shreeve\*

Organic polyazido-substituted compounds are at the forefront of high-energy research. Polyazido organic compounds have high relative heats of formation as one azido group adds about  $87 \text{ kcal mol}^{-1}$  of endothermicity to a hydrocarbon compound.<sup>[1]</sup> In this family of compounds, 3,6-diazido-1,2,4,5-tetrazine (**1**) has the highest reported heat of formation, about  $1101 \text{ kJ mol}^{-1}$  ( $6709 \text{ kJ kg}^{-1}$ ).<sup>[2]</sup> The compound 4,4',6,6'-tetraazido-2,2'-azo-1,3,5-triazine (**2**) has a heat of formation of  $2171 \text{ kJ mol}^{-1}$  ( $6164 \text{ kJ kg}^{-1}$ ; Scheme 1).<sup>[3]</sup> Recently it was demonstrated that **1** and **2** are good precursors to carbon nitride nanomaterials. Thermal decomposition of **1**<sup>[4]</sup> and **2**<sup>[5]</sup> yields nitrogen-rich nanolayered,

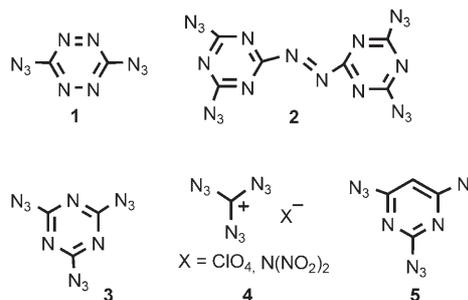**Scheme 1.** Examples of reported polyazido compounds.

[\*] Dr. C. Ye, Dr. H. Gao, Dr. B. Twamley, Prof. J. M. Shreeve  
Department of Chemistry  
University of Idaho  
Moscow, ID 83844-2343 (USA)  
Fax: (+1) 208-885-9146  
E-mail: jshreeve@uidaho.edu

Dr. J. A. Boatz  
Space and Missile Propulsion Division  
Air Force Research Laboratory  
10 East Saturn Blvd.  
Edwards AFB, CA 93524 (USA)

Dr. G. W. Drake  
NASA Solid Propellants Branch ER22  
Marshall Space Flight Center  
Huntsville, AL 34812 (USA)

[\*\*] J.M.S., H.G., and C.Y. gratefully acknowledge the financial support of the AFOSR (Grant F49620-03-1-0209), NSF (Grant CHE0315275), and ONR (Grant N00014-02-1-0600). The Bruker (Siemens) SMART APEX diffraction facility was established at the University of Idaho with the assistance of the NSF-EPSCoR program and the M. J. Murdock Charitable Trust, Vancouver, WA (USA).




Supporting information for this article is available on the WWW under <http://www.angewandte.org> or from the author.

nanoclustered, and nanodendritic carbon nitrides, depending on the different heating processes.

To date, many of the reported polyazido compounds are based on C/N heteroaromatic cycles, including tetrazine (as in **1**),<sup>[4]</sup> triazine (as in **3**),<sup>[6]</sup> heptazine,<sup>[7]</sup> triazole,<sup>[8]</sup> and tetrazole<sup>[9]</sup>, and inorganic anions, including  $[\text{P}(\text{N}_3)_6]^-$ ,<sup>[10]</sup>  $[\text{B}(\text{N}_3)_4]^-$ ,<sup>[11]</sup>  $[\text{Si}(\text{N}_3)_6]^{2-}$ ,<sup>[12]</sup>  $[\text{Te}(\text{N}_3)_5]^-$ ,<sup>[13]</sup>  $[\text{Ti}(\text{N}_3)_5]^-$ ,<sup>[14]</sup>  $[\text{Sb}(\text{N}_3)_6]^-$ ,<sup>[15]</sup> and  $[\text{U}(\text{N}_3)_7]^{3-}$ ,<sup>[16]</sup> as well as triazidocarbenium perchlorate and dinitramide (**4**; Scheme 1).<sup>[1]</sup> Few reports focus on pyrimidine as a basic building block. Although 2,4,6-triazidopyrimidine (**5**) has been known since 1979,<sup>[17]</sup> it has mainly been used for photochemical reactions. Few physical properties of this compound are known.

Preliminary calculations show that **5** has a positive heat of formation comparable to that of 2,4,6-triazido-1,3,5-triazine (**3**). Herein, we report the synthesis of a series of polyazidopyrimidine compounds, their calculated heats of formation, and their role as a source of carbon nanotubes by detonation generation.


Currently, except for the triazidocarbenium cation in **4**,<sup>[1]</sup> molecules with three or four azido groups on the same carbon atom have not been available because of their instability, high sensitivity, and difficulty in synthesis. Only a few geminal diazido compounds have been prepared from the  $\text{SnCl}_2$ - or  $\text{ZnCl}_2$ -catalyzed reaction of substituted benzaldehyde or acetophenone with  $\text{TMSN}_3$ .<sup>[18]</sup> However, heterocycles based on geminal diazido compounds have not been reported. We have prepared pentaazidopyrimidine **7** starting from 5-carboxyaldehyde-2,4,6-triazidopyrimidine (**6**; Scheme 2). The best yield of 35% could be achieved by first substituting the three chlorine atoms on the pyrimidine ring with azido groups and subsequently transforming the aldehyde group into a geminal diazido functionality by using  $\text{TMSN}_3/\text{SnCl}_2$ . Remarkably, this pentaazido compound is a liquid at room temperature with a melting point at about  $-48^\circ\text{C}$  and has good thermal stability up to about  $179^\circ\text{C}$ . It is noteworthy that **7** can be purified by column chromatography and routine handling while avoiding external heating. This suggests that **7**

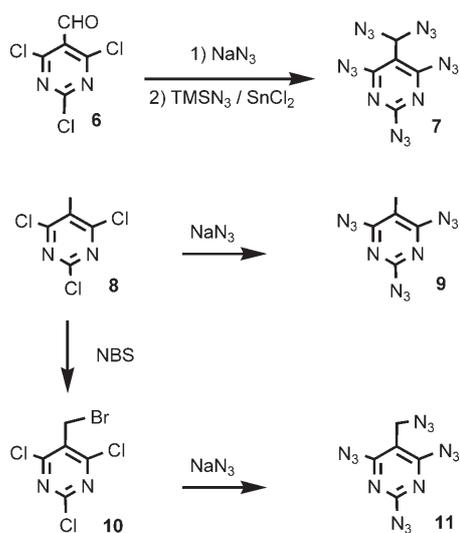

**Scheme 2.** Synthesis of polyazidopyrimidines; TMS =  $\text{SiMe}_3$ .

is not as detonation-sensitive as **1**. However, extreme care is absolutely necessary!

For purposes of comparison, triazido- and tetraazidopyrimidine derivatives **9** and **11** were prepared as outlined in Scheme 2. The solid-state structures of these two compounds were established by single-crystal X-ray analysis (Figure 1).<sup>[19]</sup>

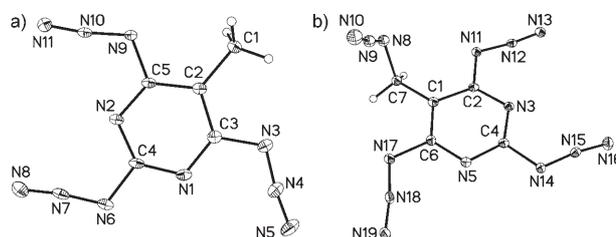

**Figure 1.** Thermal ellipsoid plot (ellipsoids at 30% probability) of **9** (a) and **11** (b). Hydrogen atoms have been included but not labelled.

Compound **9** is planar and packs in layers, in a fashion similar to the packing of **3**.<sup>[6a]</sup> However, in **9** the molecules have significant overlap with the adjacent layer. The layers are also farther apart ( $3.19 \text{ \AA}$ ) as the steric bulk of the methyl group prevents closer association. There are no significant intermolecular interactions in either **3** or **9**. The structure of **11** is quite different. The packing no longer displays flat, planar sheets, but stacks along the  $a$  axis. These stacks are composed of two alternating molecules. The gap between the molecules in these stacks is about  $3.26 \text{ \AA}$  at the maximum separation with  $10^\circ$  angles between the heterocycles. There are also weak nonclassical hydrogen bonds between the methylene group and terminal azido nitrogen atoms, both within the stacks (C7–N13, ca.  $3.31 \text{ \AA}$ ) and between the stacks (C7–N19, ca.  $3.41 \text{ \AA}$ ). This compound was difficult to crystallize and exhibits disorder in the azidomethyl group as well as rotational twinning.<sup>[19]</sup>

The melting point of the triazido analogue **9** is  $103^\circ\text{C}$ , while the addition of one extra azido group reduces the melting point drastically by about  $80^\circ\text{C}$  to  $22.5^\circ\text{C}$  in **11** (Table 1). The introduction of this fourth azido group does not result in any obvious decrease in thermal stability. The presence of a fifth azido group in **7** led to a decrease in the melting point by an additional  $70^\circ\text{C}$  with just a slight decrease in thermal stability (Table 1).

A possible rationale for the lower melting point observed for the (azidomethyl)pyrimidine compound is the inefficient packing caused by the azidomethyl group. The azido group in **11** is disordered (see above) and exhibits free rotation around


**Table 1:** Physical properties of polyazido compounds.

| Compd.    | Density [ $\text{g cm}^{-3}$ ] | M.p. [ $^\circ\text{C}$ ] | $T_d$ (DSC) [ $^\circ\text{C}$ ] | $\Delta_f H_{298}^\circ$ [ $\text{kJ mol}^{-1}$ ] |
|-----------|--------------------------------|---------------------------|----------------------------------|---|
| <b>1</b>  | 1.72                           | 130                       | 130                              | 1121.7 <sup>[b]</sup>                             |
| <b>3</b>  | 1.72                           | 94                        | 180                              | 1136.0 <sup>[c]</sup>                             |
| <b>7</b>  | 1.71                           | $-48$                     | 179                              | 1807.1  |
| <b>9</b>  | 1.55                           | 103                       | 195                              | 1087.4  |
| <b>11</b> | 1.65                           | 22.5                      | 193                              | 1452.7  |
| <b>12</b> |                                |                           |                                  | 2192.0  |

[a] Calculated value in the gas phase. [b]  $\Delta_f H_{298}^\circ$  (solid) =  $1101 \text{ kJ mol}^{-1}$ , reference [2]. [c]  $\Delta_f H_{298}^\circ$  (solid) =  $1050 \text{ kJ mol}^{-1}$ , reference [6b].

the methylene carbon atom C7. This phenomenon has also been confirmed with other examples; for example, 3,5-diazidomethyl-4-amino-triazole (m.p. 92 °C) and its perchlorate salt (m.p. 75 °C) have much lower melting points than 3,5-dimethyl-4-amino-triazole (m.p. 196 °C)<sup>[20]</sup> and its perchlorate salt (m.p. 94 °C; see the Supporting Information). Thus, introducing azidoalkyl groups could be an efficient way to reduce the melting point and increase the heat of formation, both of which are essential for the preparation of energetic ionic liquids.<sup>[21]</sup>

The heats of formation of **7**, **9**, **11**, and 5-triazidomethyl-2,4,6-triazidopyrimidine (**12**) were predicted using quantum chemical calculations (see the Supporting Information for computation details). The optimized geometries of pentaazidopyrimidine **7** and hexaazidopyrimidine **12** are shown in Figure 2; both geometries are proven to be at local minima in

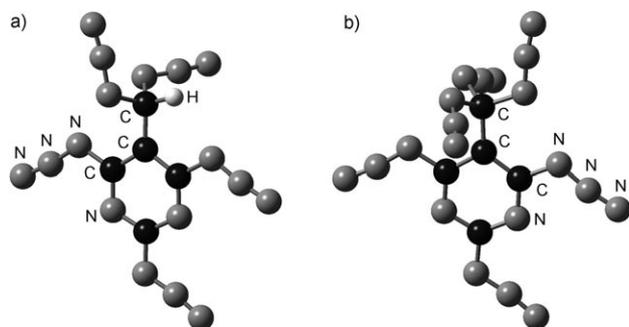


**Figure 2.** Optimized geometries at the B3LYP/6-311G(d,p) level of **7** (a) and **12** (b).

the potential-energy surface. The incremental contribution of each additional azido ligand to the heat of formation in the sequence **9**→**11**, **11**→**7**, and **7**→**12** is +365, +354, and +385 kJ mol<sup>-1</sup>, respectively (Table 1). Similar behavior is observed in the corresponding sequence ofisodesmic reference compounds CH<sub>3</sub>CH<sub>3-n</sub>(N<sub>3</sub>)<sub>n</sub> (*n* = 0–3), in which the incremental changes in heats of formation as a function of *n* are +351, +337, and +323 kJ mol<sup>-1</sup>, respectively. For **7**, using 20 kcal as its heat of sublimation, the heat of formation for the solid state was estimated to be 1723.2 kJ mol<sup>-1</sup> (5764 kJ kg<sup>-1</sup>), which would be the third-highest heat of formation reported for energetic materials, just lower than those of **2** (6164 kJ kg<sup>-1</sup>) and **1** (6709 kJ kg<sup>-1</sup>).

The formation of carbon nanotubes (CNTs) was investigated by catalytic detonation of the polyazidopyrimidines above. Since their discovery in 1990, CNTs have been shown to be extremely promising for applications in materials science and medicinal chemistry owing to interesting electronic, mechanical, and structural properties. Synthesis of nanomaterials on a large scale by detonation of explosive precursors is a new promising method owing to its low cost. Polyazido compounds with little or no hydrogen content are regarded as such ideal precursors for nanomaterials. Kroke first reported the preparation of CNTs using **3** by this detonation method in 1999,<sup>[22]</sup> but the yield was only about 2%. Optimization of the detonation conditions in the presence of transition metals, for example, Fe, Ni, Cu, and Ti, improved the yields to greater than 60%.<sup>[23]</sup>

Compound **3** is very detonation-sensitive, and its explosive nature increases with higher purity and crystal size.<sup>[6a]</sup> We found **5** to be much less sensitive to detonation than **3**. Therefore, **5** was examined as the carbon source and self-heating producer for CNTs. Among the catalysts explored, for example, Cu powder, Cu(OAc)<sub>2</sub>,<sup>[24]</sup> AgNO<sub>3</sub>, and Ni(ClO<sub>4</sub>)<sub>2</sub>, we found that Ni(ClO<sub>4</sub>)<sub>2</sub> was the best catalyst for the production of CNTs. The synthetic method is straightforward. Compound **5** (0.3 g 1.47 mmol) and Ni(ClO<sub>4</sub>)<sub>2</sub> (0.02 g, 0.07 mmol) were placed in a 75-mL stainless-steel vessel, which was then closed with a valve and heated to 250 °C over the course of about 20 minutes. The vessel was then allowed to cool to room temperature. The product was observed as a fleecy, puffy, fiber-like black residue, which could easily be removed from the vessel with forceps. On touching with a glass vial, the black residue agglomerated. This material floats and disperses well in ethanol. SEM and TEM pictures of as-prepared samples clearly show the presence of characteristic hollow-channel CNT structures (lengths ca. 3–20 μm, diameters ca. 60–80 nm and up to 100 nm; Figure 3). The yield of CNTs is estimated to be greater than 90%. They have a bamboo-like morphology (Figure 3c), and these “compartmentalized nanotubes” are segmented with a relatively uniform segment length of about 90 nm.

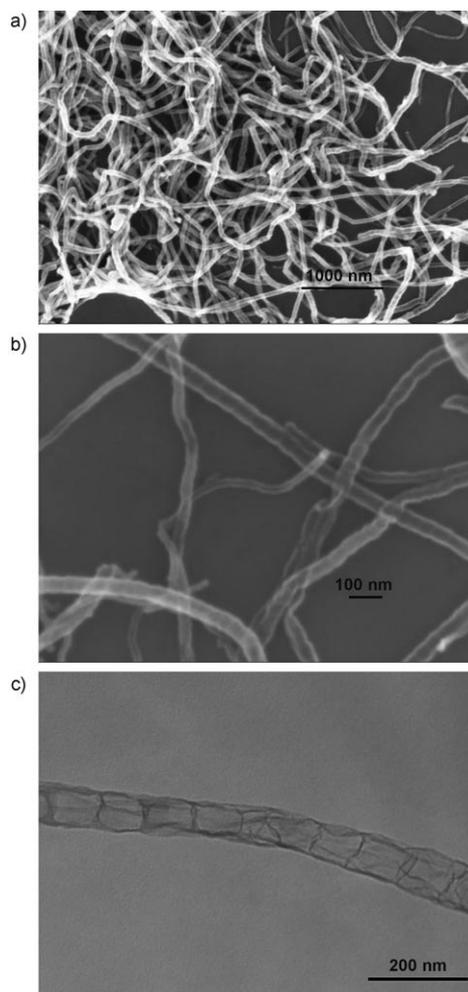

**Figure 3.** SEM (a, b) and TEM (c) images of CNTs generated by catalytic detonation of **5**.

In conclusion, we have successfully synthesized a series of polyazidopyrimidine compounds, in which the azidomethyl group dramatically decreases the melting points. Theoretical calculations show that these compounds exhibit highly promising energetic properties. 2,4,6-Triazidopyrimidine was found to be a novel and less sensitive precursor for the formation of carbon nanotubes in high yields.

**Caution!** All polyazides must be handled with extreme care and with appropriate safety precautions.

Received: July 13, 2006

Published online: September 13, 2006

**Keywords:** azides · explosives · heats of formation · nanotubes · nitrogen

- [1] M. A. Petrie, J. A. Sheehy, J. A. Boatz, G. Rasul, G. K. S. Prakash, G. A. Olah, K. O. Christe, *J. Am. Chem. Soc.* **1997**, *119*, 8802–8808.
- [2] M. H. V. Huynh, M. A. Hiskey, D. E. Chavez, D. L. Naud, R. D. Gilardi, *J. Am. Chem. Soc.* **2005**, *127*, 12537–12543.
- [3] M. H. V. Huynh, M. A. Hiskey, E. L. Hartline, D. P. Montoya, R. Gilardi, *Angew. Chem.* **2004**, *116*, 5032–5036; *Angew. Chem. Int. Ed.* **2004**, *43*, 4924–4928.
- [4] M. H. V. Huynh, M. A. Hiskey, J. G. Archuleta, E. L. Roemer, R. Gilardi, *Angew. Chem.* **2004**, *116*, 5776–5779; *Angew. Chem. Int. Ed.* **2004**, *43*, 5658–5661.
- [5] M. H. V. Huynh, M. A. Hiskey, J. G. Archuleta, E. L. Roemer, *Angew. Chem.* **2005**, *117*, 747–749; *Angew. Chem. Int. Ed.* **2005**, *44*, 737–739.
- [6] a) E. Kebech, T. M. Klapötke, J. Knizek, H. Noth, A. Schulz, *Eur. J. Inorg. Chem.* **1998**, 2013–2016; b) E. G. Gillan, *Chem. Mater.* **2000**, *12*, 3906–3912.
- [7] D. R. Miller, D. C. Swenson, E. G. Gillan, *J. Am. Chem. Soc.* **2004**, *126*, 5372–5373.
- [8] H. Xue, Y. Gao, B. Twamley, J. M. Shreeve, *Chem. Mater.* **2005**, *17*, 191–198.
- [9] A. Hammerl, T. M. Klapötke, *Inorg. Chem.* **2002**, *41*, 906–912.
- [10] R. Haiges, S. Schneider, T. Schroer, K. O. Christe, *Angew. Chem.* **2004**, *116*, 5027–5032; *Angew. Chem. Int. Ed.* **2004**, *43*, 4919–4924.
- [11] W. Frank, T. Habereeder, A. Hammerl, T. M. Klapötke, B. Krumm, P. Mayer, H. Noth, M. Warchhold, *Inorg. Chem.* **2001**, *40*, 1334–1340.
- [12] A. C. Filippou, P. Portius, G. Schnakenburg, *J. Am. Chem. Soc.* **2002**, *124*, 12396–12397.
- [13] T. M. Klapötke, B. Krumm, P. Mayer, I. Schwab, *Angew. Chem.* **2003**, *115*, 6024–6026; *Angew. Chem. Int. Ed.* **2003**, *42*, 5843–5846.
- [14] R. Haiges, J. A. Boatz, S. Schneider, T. Schroer, M. Yousufuddin, K. O. Christe, *Angew. Chem.* **2004**, *116*, 3210–3214; *Angew. Chem. Int. Ed.* **2004**, *43*, 3148–3152.
- [15] R. Haiges, J. A. Boatz, A. Vij, V. Vij, M. Gerken, S. Schneider, T. Schroer, M. Yousufuddin, K. O. Christe, *Angew. Chem.* **2004**, *116*, 6844–6848; *Angew. Chem. Int. Ed.* **2004**, *43*, 6676–6680.
- [16] M.-J. Crawford, A. Ellern, P. Mayer, *Angew. Chem.* **2005**, *117*, 8086–8090; *Angew. Chem. Int. Ed.* **2005**, *44*, 7874–7878.
- [17] V. Y. Pochinok, L. F. Avramenko, A. V. Pochinok, P. A. Kondratenko, V. I. Nagornyi, T. P. Naidenova, N. P. Chibisova, *Ukr. Khim. Zh.* **1979**, *45*, 1074–1077.
- [18] a) K. Nishiyama, T. Yamaguchi, *Synthesis* **1988**, 106–108; b) K. Nishiyama, M. Oba, A. Watanabe, *Tetrahedron* **1987**, *43*, 693–700.
- [19] Crystal data for **9**: C<sub>5</sub>H<sub>3</sub>N<sub>11</sub>, M<sub>r</sub> = 217.18., T = 89(2) K, monoclinic, space group P21/c, a = 9.838(3), b = 15.295(4), c = 6.3070(16) Å, β = 100.683(4)°, V = 932.5(4) Å<sup>3</sup>, Z = 4, ρ<sub>calcd</sub> = 1.547 g cm<sup>-3</sup>, μ = 0.118 mm<sup>-1</sup>, reflections collected/unique 13 723/1690, R1 = 0.0337, wR2 = 0.0932 (I > 2σI), GOF = 1.032. Crystal data for **11**: C<sub>5</sub>H<sub>3</sub>N<sub>14</sub>, M<sub>r</sub> = 258.21, T = 89(2) K, monoclinic, space group P21/a, a = 6.5156(14), b = 22.149(5), c = 7.2649(16) Å, β = 97.540(4)°, V = 1039.3(4) Å<sup>3</sup>, Z = 4, ρ<sub>calcd</sub> = 1.650 g cm<sup>-3</sup>, μ = 0.128 mm<sup>-1</sup>, reflections collected/unique 27 871/2123, R1 = 0.0370, wR2 = 0.0936 (I > 2σI), GOF = 1.055, sample was rotationally twinned (179.8° about reciprocal (0,0,1) with a refined BASF of 0.252(3)), and the azidomethyl group was disordered 50%. CCDC-612107 and CCDC-612108 contain the supplementary crystallographic data for this paper. These data can be obtained free of charge from The Cambridge Crystallographic Data Centre via www.ccdc.cam.ac.uk/data\_request/cif.
- [20] P. C. Wade, B. R. Vogt, T. P. Kissick, L. M. Simpkins, D. M. Palmer, R. C. Millonig, *J. Med. Chem.* **1982**, *25*, 331–333.
- [21] R. P. Singh, R. D. Verma, D. T. Meshri, J. M. Shreeve, *Angew. Chem.* **2006**, *118*, 3664–3682; *Angew. Chem. Int. Ed.* **2006**, *45*, 3584–3601.
- [22] E. Kroke, M. Schwarz, *Adv. Mater.* **1999**, *11*, 158–161.
- [23] T. Utschig, M. Schwarz, G. Miehe, E. Kroke, *Carbon* **2004**, *42*, 823–828.
- [24] a) Y. Lu, Z. P. Zhu, W. Wu, Z. Y. Liu, *Chem. Commun.* **2002**, 2740–2741; b) Y. Lu, Z. P. Zhu, Z. Y. Liu, *Carbon* **2004**, *42*, 361–370.