

REPORT DOCUMENTATION PAGE

Form Approved OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.

PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.

1. REPORT DATE (DD-MM-YYYY) 29-05-2009	2. REPORT TYPE Final Report	3. DATES COVERED (From – To) 2 July 2008 - 22-Jul-10
--	---------------------------------------	--

4. TITLE AND SUBTITLE Erbium-doped Photonic Crystal Fiber	5a. CONTRACT NUMBER FA8655-08-M-4007
	5b. GRANT NUMBER
	5c. PROGRAM ELEMENT NUMBER

6. AUTHOR(S) Dr. Kim P Hansen	5d. PROJECT NUMBER
	5d. TASK NUMBER
	5e. WORK UNIT NUMBER

7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Crystal Fibre A/S Blokken 84 Birkerød 3460 Denmark	8. PERFORMING ORGANIZATION REPORT NUMBER N/A
--	--

9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) EOARD Unit 4515 BOX 14 APO AE 09421	10. SPONSOR/MONITOR'S ACRONYM(S)
	11. SPONSOR/MONITOR'S REPORT NUMBER(S) SPC 08-4007

12. DISTRIBUTION/AVAILABILITY STATEMENT
Approved for public release; distribution is unlimited.

13. SUPPLEMENTARY NOTES

14. ABSTRACT
This report results from a contract tasking Crystal Fibre A/S as follows: ' TASK 1: Crystal Fibre will conduct research and development of large mode area, dual clad Er-doped photonic crystal fiber with the design and specifications to be provided by the HQ USAFA/DFP. The intention is to do one fiber type in both a passive and active (Er-doped) version – totally 2 (two) fibers, with up to three samples for each. The fiber is intended to be a tuned cladding design where smaller cores in the cladding region are designed to resonantly couple to higher order modes in the central active core, thereby improving beam quality. The fiber is designed to be polarization maintaining (PM). Nominal fiber designs will include a 19 cell core with nominal specifications of 300 micron 0.6 NA pump core, and signal core diameter to be defined. Crystal Fibre shall fabricate one preform and draw fiber for both the active and passive fiber. Samples may be sent to HQ USAFA/DFP for further testing and characterization. TASK 2: Crystal Fibre shall provide characteristics of the fiber fabricated to include core and cladding diameters, core and cladding numerical apertures, erbium doping concentration, and pump absorption at 1535nm. TASK 3: Crystal Fibre A/S will pay customs and duties associated with shipment of any samples or reports delivered to the HQ USAFA/DFP up to an amount of 500 USD for each of up to six shipments.

15. SUBJECT TERMS
EOARD, Lasers, optical materials, Optical fiber systems

16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT UL	18. NUMBER OF PAGES 7	19a. NAME OF RESPONSIBLE PERSON A. GAVRIELIDES
a. REPORT UNCLAS	b. ABSTRACT UNCLAS	c. THIS PAGE UNCLAS			19b. TELEPHONE NUMBER (Include area code) +44 (0)1895 616205

FINAL REPORT - FA8655-08-M-4007 - ITEM 0002

Date:	27 May 2009
Customer organization:	United States Air Force Academy (USA-FA/DFP)
Customer contact:	Maj. Benjamin G Ward
Contract No.	FA8655-08-M-4007
Item	0002
Project title:	Erbium-doped Photonic Crystal Fiber
Project Manager:	Kim P. Hansen (kph@crystal-fibre.com)
Measurements by:	Stig Nissen Knudsen and Laurent J. G. Fillon
Fiber IDs:	080809-01-CF1265, length: 25m 080809-02-CF1265, length: 20m 080809-04-CF1265, length: 20m 090507-04-CF1470, length: 70m

Approved for public release; distribution is unlimited.

The project comprises two sets of fiber with similar design. The first fiber batch is passive (i.e. with pure silica cores without rare earth dopants). These passive fibers act as pilot fibers to test the design and their performance is used to lock the design of the second and final fiber set where the core is doped with Erbium.

Passive pilot fibers

PHYSICAL PROPERTIES:

FIBER

TARGET

MATERIAL

Core material:	Pure silica
Cladding material:	Pure silica and B-doped silica
Coating material:	High temperature acrylate (single layer)

DIMENSIONS

Inner cladding (pump core) diameter ¹ :	311 μm	300 μm
Cladding diameter:	695 μm	650 μm
Coating diameter:	750 μm	750 μm
Pitch:	14 μm	14 μm
Relative hole size:	080809-01-CF1265: 0,125	~0,13
	080809-02-CF1265: 0,14	~0,14
	080809-04-CF1265: 0,15	~0,15

OPTICAL PROPERTIES:

SIGNAL CORE:

Attenuation @ 1550 nm

FIBER

25 dB/km

TARGET

-

MULTIMODE PUMP CORE:

Numerical aperture @ 975 nm²:

0.5



>0.45

¹: Measured as diameter of the largest inscribed circle within the inner cladding layer.

²: Measured as the angle corresponding to FWHM of the maximum intensity.


FIBER STRUCTURE

The fiber is a passive pure silica pilot fiber, the purpose of which is to determine structural uniformity and possible fabrication issues of the final Erbium doped fiber. The fiber design is successfully reproduced in the pilot fiber and we have observed no structural nonuniformities or fabrication issues. We were, therefore, confident that the final Erbium doped fiber design could be produced with a high degree of precision.

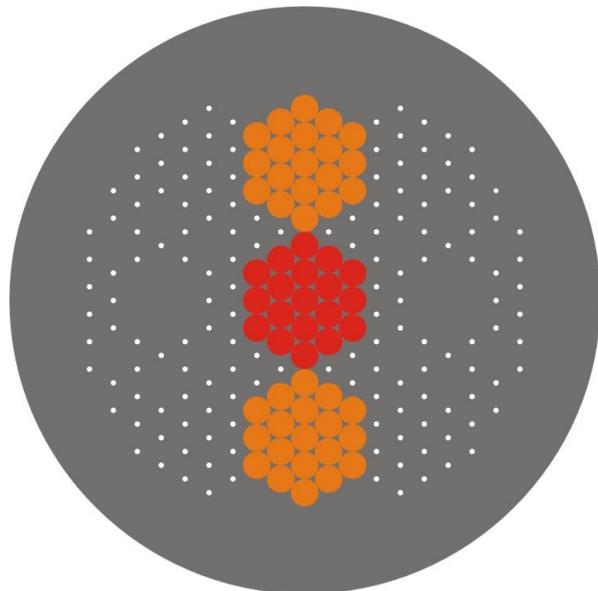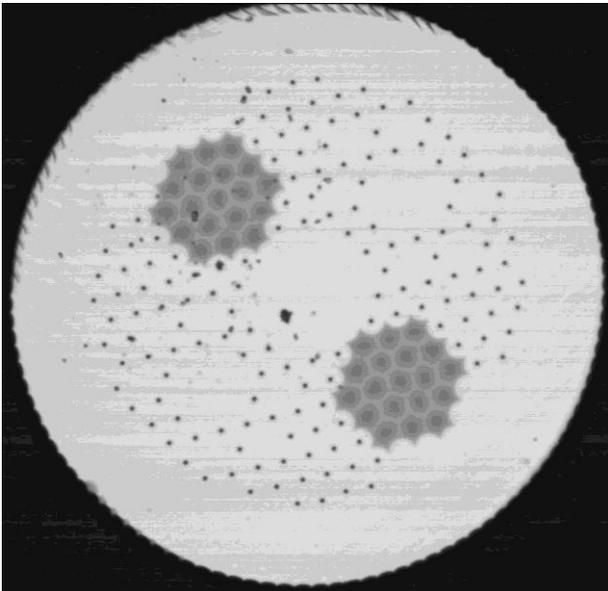


Left: Optical microscope picture of the fiber cross section inside the airclad. Right: Sketch of the design target as specified by USAFA.

NEAR FIELD

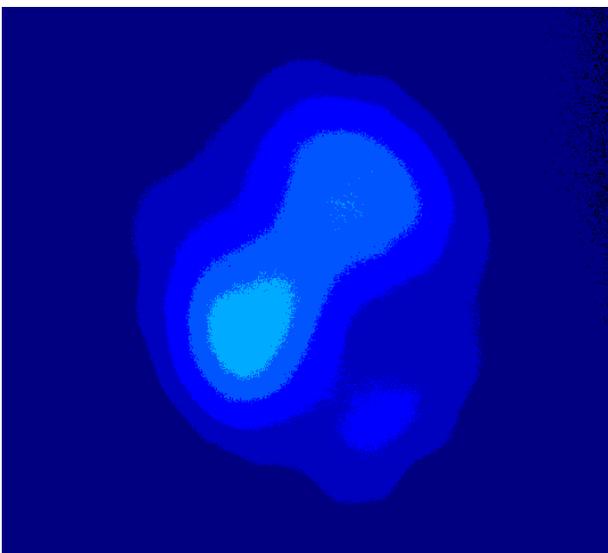

Near field of o8o8o9-04-CF1265 recorded at 1550 nm. 1550 nm light launched into core by 10x aspheric lens. Central core appears highly multi-moded. We have not controlled axis of polarized light coupled to fiber with respect to stress rods – it is "random". Bending the fiber was "random" with respect to the stress rod axis. Above picture is for 2 m of almost straight fiber. Transmitted 1550 nm light is loss very quickly when bending the 2 m sample.

SPECTRAL ATTENUATION

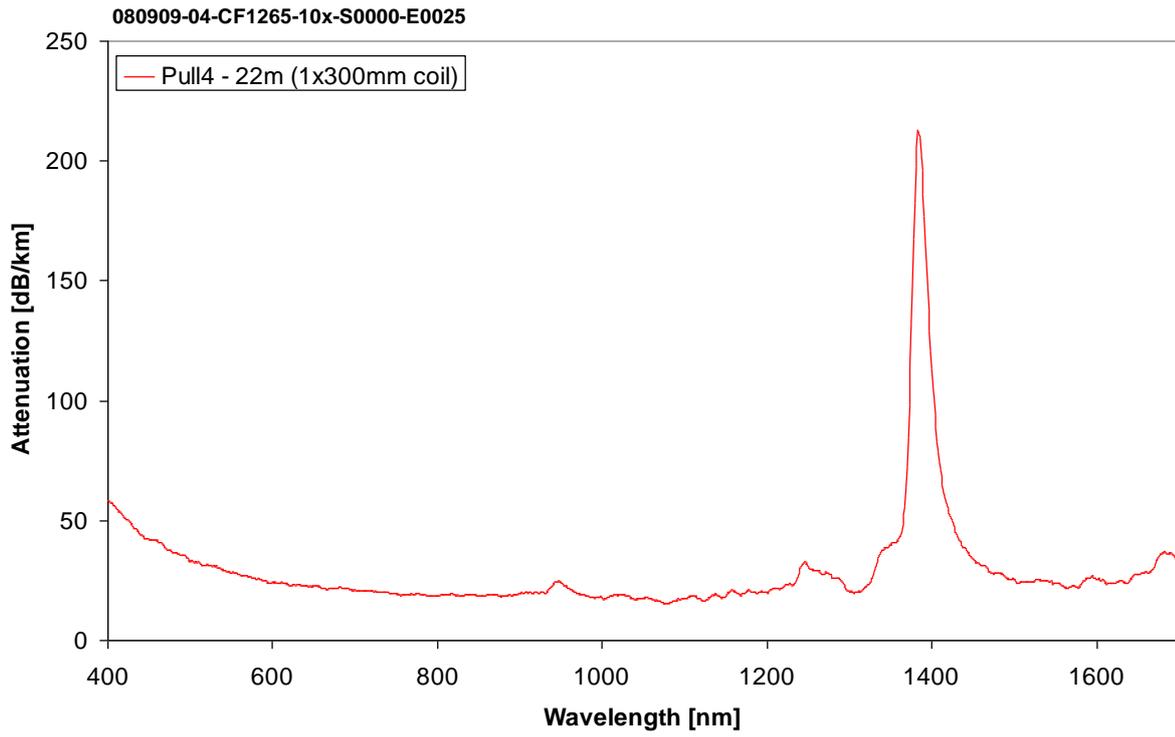

Active fibers


The active fiber batch was produced with targets identical to the passive pilot fibers, which had shown good performance and single-mode operation in the tests at USAFA. The relative hole-size sweep used in the pilot fiber drawing was replaced with a fixed target of 0.14.

PHYSICAL PROPERTIES:	FIBER	TARGET
MATERIAL		
Core material:	Er/Al doped silica	
Cladding material:	Pure silica and B-doped silica	
Coating material:	High temperature acrylate (single layer)	
DIMENSIONS		
Inner cladding (pump core) diameter ¹ :	310 μm	300 μm
Cladding diameter:	705 μm	650 μm
Coating diameter:	760 μm	750 μm
Pitch:	13,6 μm	14 μm
Relative hole size:	0,14-0.15	0.14
OPTICAL PROPERTIES:		
MULTIMODE PUMP CORE:		
Numerical aperture @ 975 nm ² :	0.54	>0.45
Pump absorption @ 1530 nm:	1.2 dB/m	>0.5 dB/m


¹: Measured as diameter of the largest inscribed circle within the inner cladding layer.

²: Measured as the angle corresponding to FWHM of the maximum intensity.


FIBER STRUCTURE

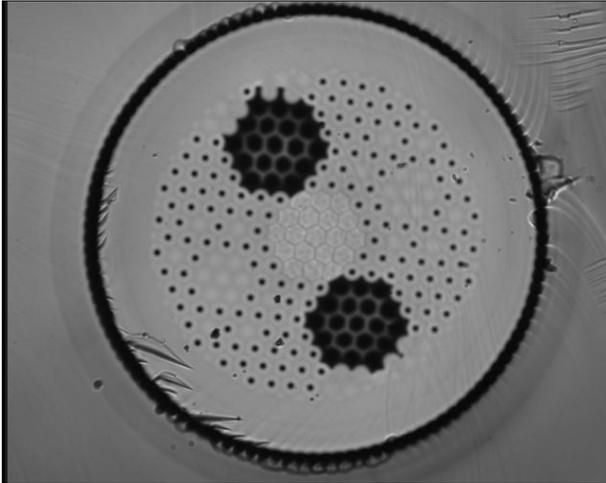


090507-2-CF1470 start x 20 bk ill.tif

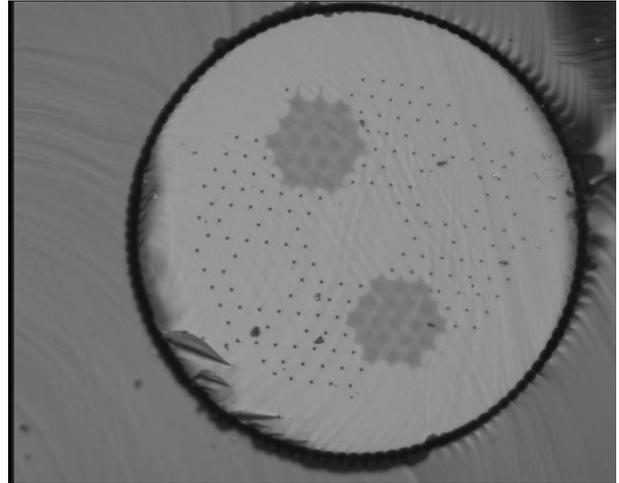

090507-2-CF1470 start x 20 tp ill.tif

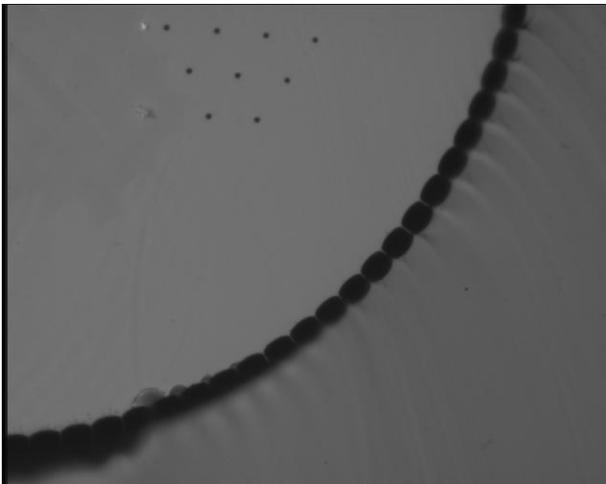

090507-2-CF1470 start x 50 tp bro ill.tif

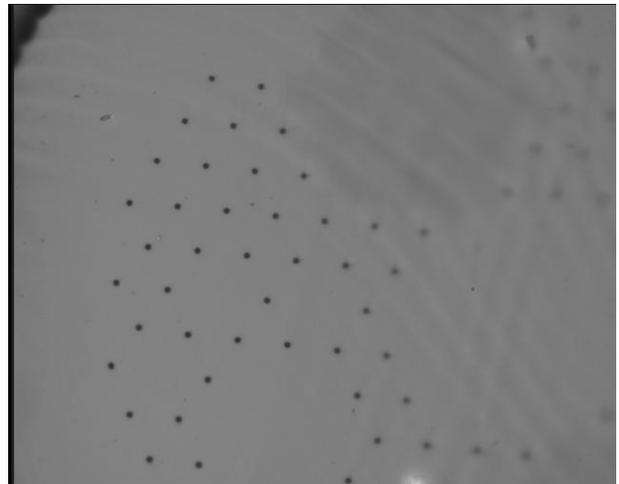

090507-2-CF1470 start x 50 tp ill.tif

Top left: Optical microscope picture of the fiber cross section using illumination from the back to reveal index differences.


Top right: As top left but with front illumination

Bottom left: Optical microscope picture of part of the airclad with front illumination


Bottom right: Zoom on the structure inside the airclad.

PUMP ABSORPTION

The pump absorption of the fiber is measured by cut-back using a broadband light source (see spectral attenuation plots below).

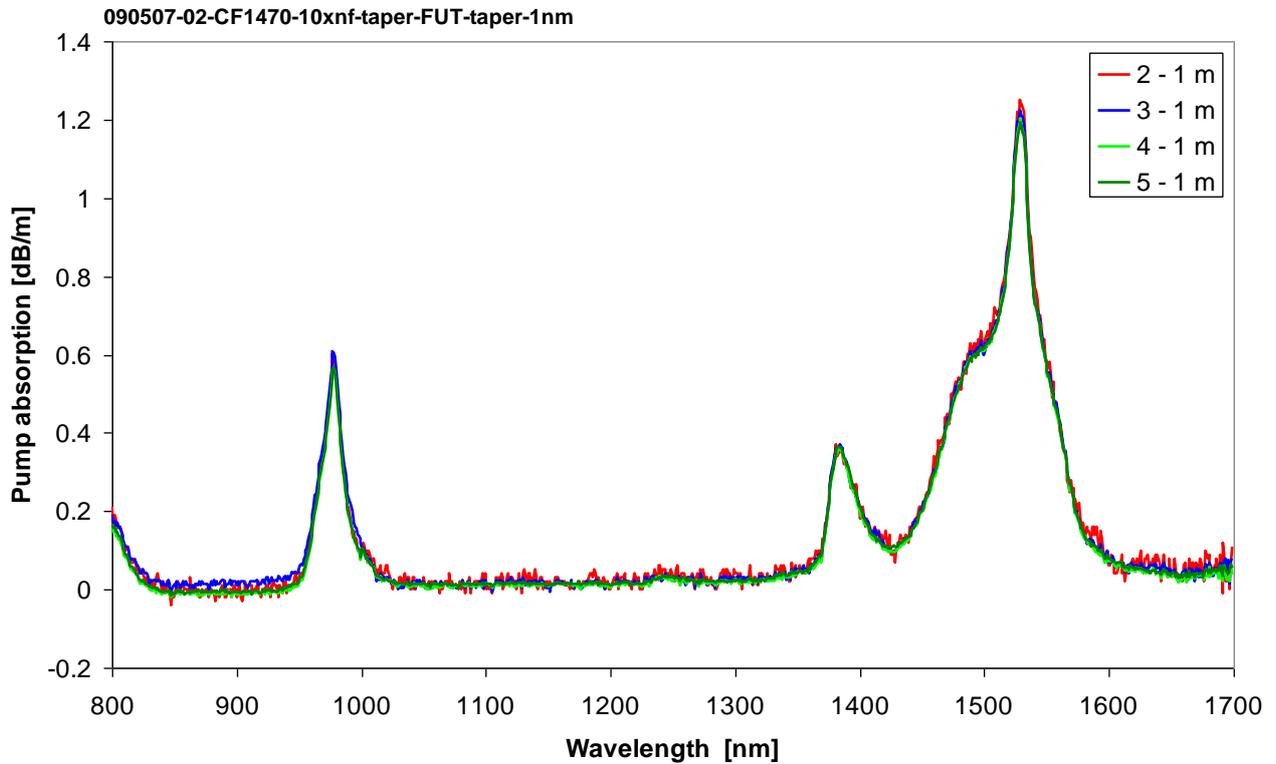

The transmission as function of length is plotted in the figure below for the wavelengths 978 nm, 1480 nm and 1530 nm. The success criterion was to reach a minimum of 0.5 dB/m pump absorption at 1530nm and 1.18 dB/m was measured.

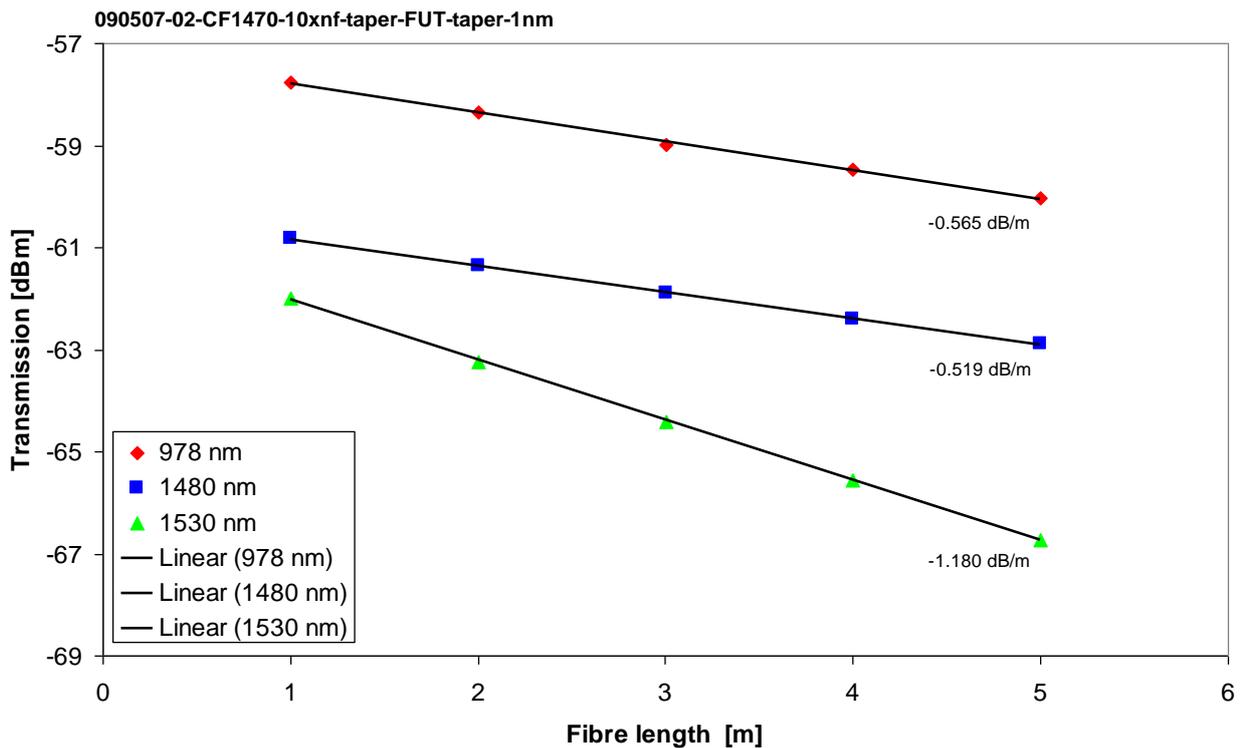

Measurements completed 20.05.2008. All target parameters are concluded to be within specifications.

A handwritten signature in blue ink, appearing to read 'KPH', with a long horizontal flourish extending to the right.

Kim P. Hansen