

*ARMY RESEARCH LABORATORY*

**ARL**

## **Characterization of Pressureless Sintered Boron Carbide**

**by Joshua Pomerantz and Tomoko Sano**

**ARL-TR-6391**

**March 2013**

## **NOTICES**

### **Disclaimers**

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

Citation of manufacturer's or trade names does not constitute an official endorsement or approval of the use thereof.

Destroy this report when it is no longer needed. Do not return it to the originator.

# **Army Research Laboratory**

Aberdeen Proving Ground, MD 21005-5069

---

---

**ARL-TR-6391**

**March 2013**

---

---

## **Characterization of Pressureless Sintered Boron Carbide**

**Joshua Pomerantz**  
George Washington University

**Tomoko Sano**  
Weapons and Materials Research Directorate, ARL

<b>REPORT DOCUMENTATION PAGE</b>			<i>Form Approved</i> <b>OMB No. 0704-0188</b>		
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. <b>PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.</b>					
<b>1. REPORT DATE (DD-MM-YYYY)</b> March 2013		<b>2. REPORT TYPE</b> Final		<b>3. DATES COVERED (From - To)</b> June 2012–August 2012	
<b>4. TITLE AND SUBTITLE</b> Characterization of Pressureless Sintered Boron Carbide			<b>5a. CONTRACT NUMBER</b>		
			<b>5b. GRANT NUMBER</b>		
			<b>5c. PROGRAM ELEMENT NUMBER</b>		
<b>6. AUTHOR(S)</b> Joshua Pomerantz * and Tomoko Sano			<b>5d. PROJECT NUMBER</b>		
			<b>5e. TASK NUMBER</b>		
			<b>5f. WORK UNIT NUMBER</b>		
<b>7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)</b> U.S. Army Research Laboratory ATTN: RDRL-WMM-B Aberdeen Proving Ground, MD 21005-5069			<b>8. PERFORMING ORGANIZATION REPORT NUMBER</b> ARL-TR-6391		
<b>9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)</b>			<b>10. SPONSOR/MONITOR'S ACRONYM(S)</b>		
			<b>11. SPONSOR/MONITOR'S REPORT NUMBER(S)</b>		
<b>12. DISTRIBUTION/AVAILABILITY STATEMENT</b> Approved for public release; distribution is unlimited.					
<b>13. SUPPLEMENTARY NOTES</b> *George Washington University, 2100 M Street, #310, Washington, DC 20052					
<b>14. ABSTRACT</b> This report outlines the characterization study of pressureless sintered boron carbide with graphite additive used as a sintering and densification aid on hexagonally shaped and plate-shaped samples of boron carbide. We conducted this investigation to determine whether pressureless sintered boron carbide could be used as a substitute for the baseline hot-pressed boron carbide. The surfaces were characterized with a scanning electron microscope. The samples were tested for strength, hardness, density, and composition using four-point flexure testing, Knoop microindentation, Archimede's method, and x-ray spectroscopy, respectively. These values were then compared with literature values for pressureless sintered boron carbide and hot-pressed boron carbide. We concluded that the substitution was not feasible because of the high-porosity and low-strength values.					
<b>15. SUBJECT TERMS</b> boron carbide, ceramic, characterization, material					
<b>16. SECURITY CLASSIFICATION OF:</b>			<b>17. LIMITATION OF ABSTRACT</b>	<b>18. NUMBER OF PAGES</b>	<b>19a. NAME OF RESPONSIBLE PERSON</b> Joshua Pomerantz
<b>a. REPORT</b> Unclassified	<b>b. ABSTRACT</b> Unclassified	<b>c. THIS PAGE</b> Unclassified			<b>19b. TELEPHONE NUMBER (Include area code)</b> 410-306-2741

---

## Contents

---

<b>List of Figures</b>	<b>iv</b>
<b>List of Tables</b>	<b>v</b>
<b>Acknowledgments</b>	<b>vi</b>
<b>1. Introduction</b>	<b>1</b>
<b>2. Experimental/Calculations</b>	<b>1</b>
<b>3. Results</b>	<b>3</b>
<b>4. Discussion</b>	<b>6</b>
<b>5. Summary and Conclusions</b>	<b>7</b>
<b>6. References</b>	<b>8</b>
<b>Distribution List</b>	<b>10</b>

---

## List of Figures

---

Figure 1. SEM image of a plate surface (polished 0.25 $\mu\text{m}$ ).....	3
Figure 2. XRD results. ....	4
Figure 3. Strength scatter plot.....	5
Figure 4. SEM of pore in the weakest sample. ....	5
Figure 5. Load-HK curve.....	6

---

## List of Tables

---

Table 1. EDS characterization of the samples. ....	4
Table 2. Summary of the mechanical properties evaluated in this study.....	7

---

## **Acknowledgments**

---

The authors thank Dennis Miller, Paul Moy, Jared Wright, Costas Fountzoulas, and Corydon Hilton for their help on this project.

---

## 1. Introduction

---

The ceramic boron carbide ( $B_4C$ ) has a rhombohedral crystal structure, with icosahedra of either  $B_{11}C$  or  $B_{12}$  located at each corner, connected to each other through C-B-C- intericosahedral chains. While  $B_{11}C$  is more common, the replacement of the  $B_{11}C$  icosahedra with the  $B_{12}$  icosahedra causes uncertainty in the stoichiometry of  $B_4C$ . It is possible for  $B_4C$  to exist as  $B_4C$  or  $B_{13}C_3$ , i.e., to have a carbon content ranging from ~9 atomic percent (at%) to 20 at% (1). With a Knoop hardness (HK) of  $2800 \text{ kg/mm}^2$  at a load of 0.1 kgf (0.98 N),  $B_4C$  is the third hardest material in the world, softer than only cubic boron nitride and diamond (2, 3). This and its low theoretical density of  $2.52 \text{ g/cm}^3$  make it a suitable ceramic for armor (4).

The  $B_4C$  used for body armor is normally consolidated by hot-pressing (HP). HP  $B_4C$  has a density near to the theoretical density; however, HP is slow, and products can be molded into only simple shapes. HP  $B_4C$  is normally machined into its proper shape, a costly and inefficient process. Recently,  $B_4C$  has been pressurelessly sintered without pressure using several different additives to increase densification. These additives, however, have a detrimental effect on the mechanical properties of  $B_4C$  (1). Even with the additives, pressureless sintered  $B_4C$  can still have a high porosity—another factor inhibiting its mechanical performance. For example, the most common additive, free carbon (graphite), increases densification up to 98% of the theoretical density (5) ( $2.47 \text{ g/cm}^3$ ). However, its softness and inhomogeneous distributions lower the hardness of the  $B_4C$  in areas with a high concentration of graphite.

The purpose of this research is to determine the feasibility of substituting pressureless sintered  $B_4C$  with graphite additives for HP of the same material for use in armor. If the pressureless sintered  $B_4C$  demonstrates comparable performance, then the reduced cost of sintering, machining, and processing, as well as the time spent on each step, may justify such a substitution. This study characterizes pressureless sintered  $B_4C$  with graphite additives and compares the results to the literature values for HP  $B_4C$ .

---

## 2. Experimental/Calculations

---

This study evaluated pressureless sintered  $B_4C$  samples with graphite additions, which have been manufactured in Spain into two shapes: hexagonal and plate. Both shapes are characterized in this study to be compared with the literature values.

Specimen densities of both hexagonal and plate samples were determined using the Archimedes method. The dry mass, wet mass, and suspended wet mass were measured using a Mettler Toledo Deller Range AX250 scale. Specimens were placed into a vacuum chamber for 45 min

then submerged in water for 1 h before the wet and suspended wet mass measurements were taken. The apparent density was calculated according to the equation

$$\rho_a = \frac{DM}{DM-SWM}, \quad (1)$$

where  $\rho_a$  is the apparent density,  $DM$  is the dry mass, and  $SWM$  is the suspended wet mass.

The surfaces of the B<sub>4</sub>C samples were characterized under a scanning electron microscope (SEM) (FEI Nova NanoSEM 600). Elemental maps of the locations of elements present were determined by energy-dispersive spectroscopy (EDS). Elemental spectra and qualitative values of elemental content were also obtained. X-ray diffraction (XRD; Siemens 05005) was used to determine the phases present.

Grain boundary size was measured using the Heyn method (lineal intercept procedure) as outlined in section 11 of the ASTM E 112 (6) standard. The ASTM grain size number  $n$  was calculated according to ASTM E 112, equation 2a.

The flexural strength of the plate sample was tested at a room temperature of 25 °C using four-point flexure testing on 52 samples machined (Bomas Machine Specialties, Inc., Somerville, MA) to dimensions of 3 × 4 × 48 mm. The specimens were loaded into a load frame (Instron 5500R Model) with a lower support span of  $L = 40$  mm and an upper support span of  $U = 20$  mm. Specimens were loaded at a rate of 0.5 mm/min, and the break force  $P$  was recorded to six significant figures, as reported by the software (Bluehill). To ensure the greatest accuracy, the width  $B$  and thickness  $D$  of each specimen were measured at three points along the length of the sample and averaged. The average width and thickness of each specimen were used in the calculation of the respective specimen's strength. The strength of each individual sample was calculated according to the equation

$$S = \frac{3PL}{4BD^2}, \quad (2)$$

where  $S$  is the strength of the material,  $P$  is the break force in N,  $L$  is the outer support span in millimeters,  $B$  is the specimen width in millimeters, and  $D$  is the specimen thickness in millimeters (7). The values for the strength of each sample were then averaged to approximate the strength of the material. All tests were completed according to ASTM C 1161 (7). The flexural strength of the hexagonal specimen was not measured because of sample size limitations.

Samples were cold-mounted (Buehler EpoEase Epoxy Mounting System) in 0.25-in (0.64-cm) silicone molds and left to harden for 8 h. They were then polished (Struers RotoPo-31 with RotoForce 4 attachment) using water-based diamond suspensions (Metadi Diamond suspensions) of decreasing size: 45, 15, 9, 6, 3, 1, and 0.25 μm. Subsequent to polishing, the samples were subjected to Knoop microindentation (Instron Wilson Tukon 2100 Version 95.42). The loads of

the indents were applied for increments of 13 s and steadily increased in the order 0.1, 0.3, 0.5, 1.0, 2.5 kg. The software (Minuteman) reported HK in terms of  $\text{kg}/\text{mm}^2$ , so no calculations were necessary. Ten indents which meet the criteria for “acceptable” in the ASTM were taken. The HK of each indent was recorded and averaged to approximate the HK of the material at each load. The data was plotted in a load-HK curve.

---

### 3. Results

---

The dry mass, wet mass, and suspended wet mass of the plate and hexagonal samples were 10.902, 11.088, and 6.355 g and 17.325, 17.427, and 10.052 g, respectively. Using these values in equation 1, we calculated the density of the plate sample to be  $2.40 \text{ g}/\text{cm}^3$  and the hexagonal sample to be  $2.38 \text{ g}/\text{cm}^3$ .

SEM revealed both high porosity and graphite content in both samples. In figure 1, the imperfections on the surface were analyzed by EDS to be almost pure carbon. Further EDS analysis showed this graphite to account for a significant amount of the carbon content. Table 1 summarizes the qualitative characterization of the surface of the  $\text{B}_4\text{C}$  samples.

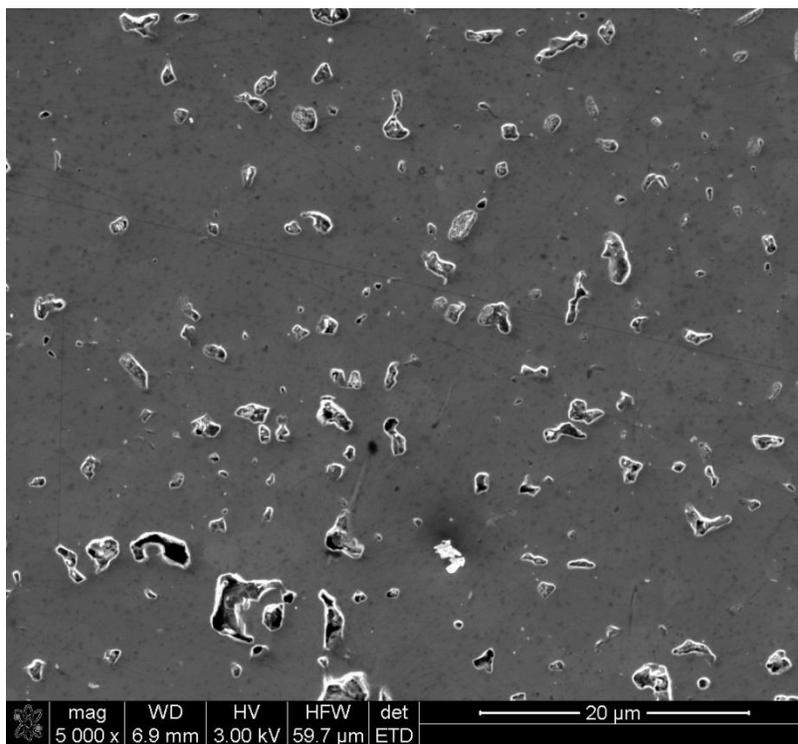


Figure 1. SEM image of a plate surface (polished  $0.25 \mu\text{m}$ ).



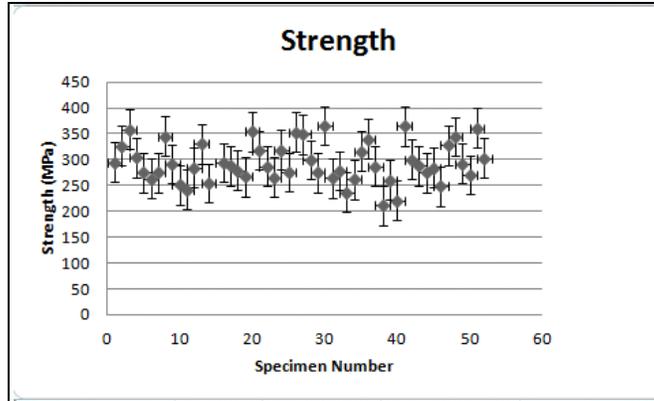


Figure 3. Strength scatter plot.

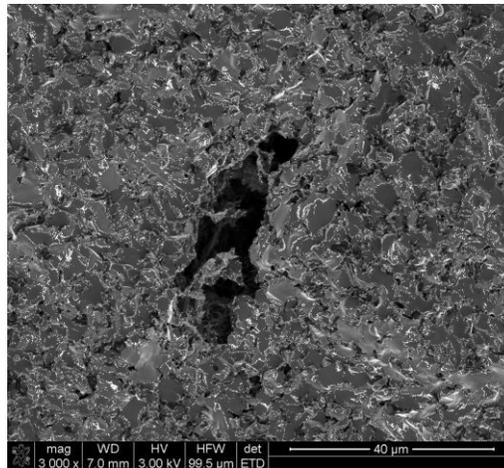


Figure 4. SEM of pore in the weakest sample.

Both samples had approximately the same HK values within experimental error. The load-HK plot is shown in figure 4. The HK of the plate sample at a 1-kgf (9.8 N) load was  $2051 \pm 182.2$  kg/mm<sup>2</sup>. The HK of the hexagonal at the same load was  $2187 \pm 78.25$  kg/mm<sup>2</sup>. As seen in figure 5, HK decreases as the load increases. The error bars in this figure represent the standard deviation. Above loads of 2.5 kgf, several indentations would strike a pore and cause laceration and cracking.

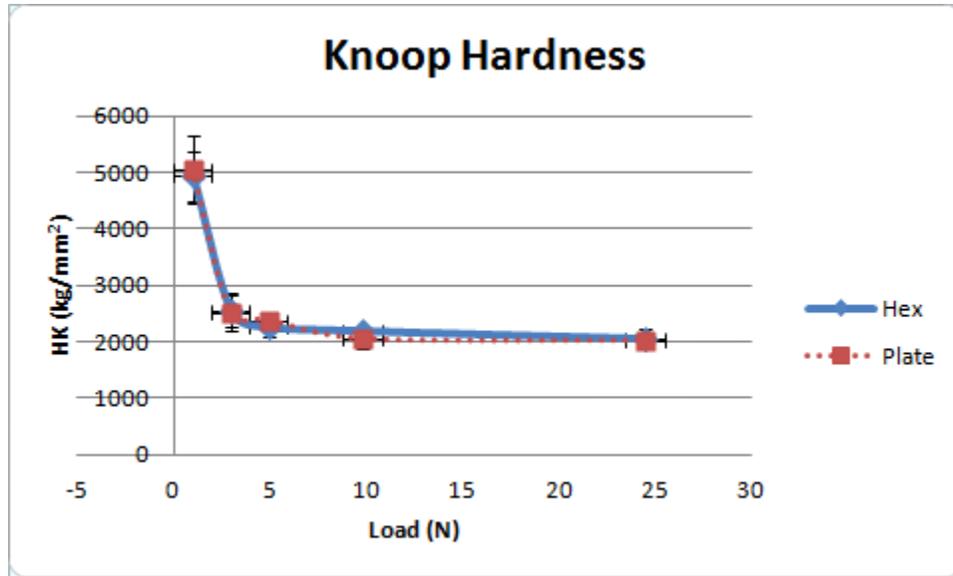


Figure 5. Load-HK curve.

## 4. Discussion

As mentioned in the introduction, the theoretical density of  $B_4C$  is  $2.52 \text{ g/cm}^3$ . The measured densities of the  $B_4C$  hexagonal and plate samples were 95.2% and 94.4% of the theoretical density, respectively. These values indicate a high densification; HP is normally required for densities above 95% of the theoretical density (1). Despite this high densification, however, porosity is still observed under the SEM, and because the porosity had a detrimental effect on the mechanical properties of the samples, it is questionable as to whether this material can be used as an armor material.

SEM imaging revealed large chunks of graphite distributed throughout the material. An effect of this graphite is seen in the high standard deviation in the HK test. Since the graphite is inhomogeneously distributed, certain areas will have more graphite than others. As graphite is softer than  $B_4C$ , the HK measured in these areas is smaller. Areas with moderate amounts of graphite have a higher HK, and areas with little graphite have the highest HK values. This difference makes the HK of an area of the material unpredictable. EDS results are normal within experimental error; variations in carbon could be due to graphite or surface contamination, and the negligible amounts of oxygen detected are most likely due to oxidation.

The average flexural strength of HP  $B_4C$  is  $480 \pm 40 \text{ MPa}$  (8). The significant difference between this value and the strength of the plate sample is most likely caused by the high porosity; pores were determined to be the nucleation site of the fracture of two flexure samples, the sample that fractured at the highest load and the one at the lowest load.

Despite the high standard deviation in the HK test, the average HK values of the samples were high. The values of the plate and hexagonal samples compared to the value of HP B<sub>4</sub>C at 100% theoretical density, which is  $2019.9 \pm 60.2 \text{ kg/mm}^2$  at 1 kgf (9.8 N) (8).

---

## 5. Summary and Conclusions

---

Whether pressureless sintered B<sub>4</sub>C can be a substitute for HP B<sub>4</sub>C for armor applications remains undetermined. This study's specimens' low density and high hardness certainly show potential; however, their high porosity and graphite content have too detrimental an effect on the mechanical properties (such as strength) for the lowered cost and time of manufacturing to be justified. If the densification can be increased, then substitution is plausible. Ballistic testing of the pressureless sintered samples is necessary to conclusively determine the feasibility of the substitution. Table 2 summarizes the mechanical properties evaluated in this study.

Table 2. Summary of the mechanical properties evaluated in this study.

Sample	$\rho$ (g/cm <sup>3</sup> )	Strength (MPa)	HK (9.8 N; kg/mm <sup>2</sup> )
Hex	2.38	—	$2187 \pm 78.25$
Plate	2.40	$295 \pm 38$	$2051 \pm 182.2$
HP Lit.	2.52	$480 \pm 40$	$2019.9 \pm 60.2$

---

## 6. References

---

1. Thévenot, F. Boron Carbide—A Comprehensive Review. *Journal of the European Ceramic Society* **1990**, *6*, 205–225.
2. Cho, N. Processing of Boron Carbide. Ph.D. dissertation, Georgia Institute of Technology, Atlanta, GA, 2006.
3. Bever, M. B., Ed. *Encyclopedia of Materials Science and Engineering*; MIT Press: Cambridge, MA, 1986; Vol. 1.
4. Roy, T. K.; Subramanian, C.; Suri, A. K. Pressureless Sintering of Boron Carbide. *Ceramics International* **2006**, *32*, 227–233.
5. Schwetz, K.; Vogt, G. Process for the Production of Dense Sintered Articles of Boron Carbide. U.S. Patent 4,195,066, March 25, 1980.
6. ASTM E 112. Standard Test Methods for Determining Average Grain Size. *Annu. Book ASTM Stand.* **2007**.
7. ASTM C 1161. Standard Test Method for Flexural Strength of Advanced Ceramics at Ambient Temperature. *Annu. Book ASTM Stand.* **2007**.
8. Gonzalez, L. V.; Speyer, R. F.; Campbell, J. Flexural Strength, Fracture Toughness, and Hardness of Silicon Carbide and Boron Carbide Armor Ceramics. *International Journal of Applied Ceramic Technology* **2010**, *7* (5) 643–651.

NO. OF  
COPIES ORGANIZATION

1 DEFENSE TECHNICAL  
(PDF) INFORMATION CTR  
DTIC OCA  
8725 JOHN J KINGMAN RD  
STE 0944  
FORT BELVOIR VA 22060-6218

1 DIRECTOR  
(HC) US ARMY RESEARCH LAB  
IMAL HRA  
2800 POWDER MILL RD  
ADELPHI MD 20783-1197

1 DIRECTOR  
(PDF) US ARMY RESEARCH LAB  
RDRL CIO LL  
2800 POWDER MILL RD  
ADELPHI MD 20783-1197

1 GOVT PRINTG OFC  
(PDF) A MALHOTRA  
732 N CAPITOL ST NW  
WASHINGTON DC 20401

ABERDEEN PROVING GROUND

3 DIR USARL  
(PDF) RDRL WMM B  
C RANDOW  
RDRL WMM E  
J LASALVIA  
J SWAB

INTENTIONALLY LEFT BLANK.