





NASA CR-165434

National Aeronautics and  
Space Administration

# INTERLAMINAR CRACK GROWTH IN FIBER REINFORCED COMPOSITES DURING FATIGUE

Final Report - Part III

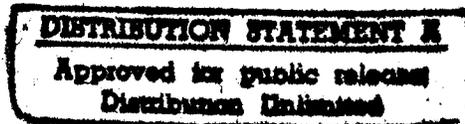


by

S.S. Wang and H.T. Wang

Department of Theoretical and Applied Mechanics  
UNIVERSITY OF ILLINOIS  
at Urbana-Champaign

prepared for  
NATIONAL AERONAUTICS AND SPACE ADMINISTRATION



NASA Lewis Research Center  
Grant NSG 3044

19951226 074

DTIC QUALITY INSPECTED 1

UNCLASSIFIED

1. Report No. NASA CR-165434		2. Government Accession No.		3. Recipient's Catalog No.	
4. Title and Subtitle Interlaminar Crack Growth in Fiber Reinforced Composites During Fatigue				5. Report Date February 1981	
				6. Performing Organization Code	
7. Author(s) S. S. Wang and H. T. Wang				8. Performing Organization Report No.	
9. Performing Organization Name and Address University of Illinois Urbana, IL 61801				10. Work Unit No.	
				11. Contract or Grant No. NSG 3044	
12. Sponsoring Agency Name and Address National Aeronautics and Space Administration Washington DC 20546				13. Type of Report and Period Covered Final Report - Part III	
				14. Sponsoring Agency Code	
15. Supplementary Notes Project Manager: C. C. Chamis NASA Lewis Research Center, Structures & Mechanical Technologies Division 21000 Brookpark Road, Mail Stop 49-6 Cleveland, OH 44135					
16. Abstract Interlaminar crack growth behavior in fiber-reinforced composites subjected to fatigue loading was investigated experimentally and theoretically. In the experimental phase of the study, interlaminar crack propagation rates and mechanisms were determined for the cases of various geometries, laminate parameters and cyclic stress levels. An advanced singular hybrid-stress finite element method was used in conjunction with the experimental results to examine the local crack-tip behavior and to characterize the crack propagation during fatigue. Results elucidate the basic nature of the cyclic delamination damage, and relate the interlaminar crack growth rate to the range of mixed-mode crack-tip stress intensity factors. The results show that crack growth rates to be related directly to the range of the mixed-mode cyclic stress intensity factors by a power law relationship.					
17. Key Words (Suggested by Author(s)) fiber composites, stress intensity, mix-mode, crack growth, hybrid element, stress analysis, finite element, experiments				18. Distribution Statement Unclassified, Unlimited	
19. Security Classif. (of this report) Unclassified		20. Security Classif. (of this page) Unclassified		21. No. of Pages	22. Price*

## TABLE OF CONTENTS

	Page
TABLE OF CONTENTS . . . . .	ii
FOREWORD . . . . .	iii
ABSTRACT . . . . .	1
INTRODUCTION . . . . .	2
EXPERIMENTAL PROGRAM . . . . .	4
Materials and Specimen Preparation . . . . .	4
Experimental Procedure . . . . .	4
Advantages of Present Test Method . . . . .	5
ANALYTICAL PROGRAM . . . . .	6
Mechanical Model and Assumptions . . . . .	6
Method of Analysis . . . . .	7
RESULTS AND DISCUSSION . . . . .	10
Interlaminar Crack Growth During Fatigue . . . . .	11
Interlaminar Crack-Tip Response . . . . .	12
Fatigue Crack Growth Rate Characterization . . . . .	13
Limitations of Current Study . . . . .	15
SUMMARY AND CONCLUSION . . . . .	16
ACKNOWLEDGMENTS . . . . .	17
REFERENCES . . . . .	18
LIST OF FIGURE CAPTIONS . . . . .	21
FIGURES . . . . .	22

## FOREWORD

This report describes a portion of the results obtained on NASA Grant NSG 3044. This work was done under subcontract to the University of Illinois, Urbana, with Prof. S.S. Wang as the Principal Investigator. The prime grantee was the Massachusetts Institute of Technology, with Prof. F.J. McGarry as the Principal Investigator and Dr. J.F. Mandell as a major participant. The NASA - LeRC Project Manager was Dr. C.C. Chamis.

Efforts in this project are primarily directed towards the development of finite element analyses for the study of flaw growth and fracture of fiber composites. This report presents analytical and experimental results for delamination crack growth in fatigue. The work is a follow-up to an earlier interim report NASA CR-135248. H.T. Wang was a research assistant at M.I.T. when the experimental work was performed.

Accession For	
NTIS CRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification .....	
By .....	
Distribution /	
Availability Codes	
Dist	Avail and/or Special
A-1	

Abstract

This paper presents an investigation of interlaminar crack growth behavior in fiber-reinforced composites subjected to fatigue loading. In the experimental phase of the study, interlaminar crack propagation rates and mechanisms were determined for the cases of various geometries, laminate parameters and cyclic stress levels. An advanced singular hybrid-stress finite element method was used in conjunction with the experimental results to examine the local crack-tip behavior and to characterize the crack propagation during fatigue. Results elucidate the basic nature of the cyclic delamination damage, and relate the interlaminar crack growth rate to the range of mixed-mode crack-tip stress intensity factors. The study provides fundamental insight into the problem, reveals several important features of the interlaminar fatigue failure, and should be of practical importance in selection, testing and design of composite materials.

## INTRODUCTION

Damage tolerance has been of great concern for the structural reliability and integrity of fiber-reinforced composites in their advanced engineering applications. Interlaminar cracking, sometimes also called delamination, is considered one of the most frequently encountered types of damage occurring in the material subjected to fatigue loading. It is commonly initiated at geometric discontinuities, processing and manufacturing defects, machining and service flaws, and takes the form of separation of plies under mechanical, thermal and/or environmental loading. The presence and growth of an interlaminar crack may result in (1) significant reduction of stiffness, (2) exposure of the interior to adverse environmental attack, and the degradation of the composite, which may lead to the final failure of the structure. Thus, understanding the interlaminar crack growth behavior under cyclic stresses is of fundamental importance in the application of composite materials.

Laminated composites generally consist of a number of plies with different fiber orientations separated by resin-rich interlaminar regions as shown in Fig. 1. The interlaminar region usually has a dimension of one twentieth to one tenth of the individual ply thickness, depending on manufacturing and processing methods. Since the strength is usually low and stresses are high in the interlaminar region, almost all kinds of defects such as voids, inclusions, broken plies, etc., unavoidably tend to grow in an interlaminar mode at very low nominal stress levels and to propagate along preferential paths. This phenomenon is unique to composites and is particularly significant when the materials are subjected to cyclic loading. The development of a through-the-thickness crack from a defect or flaw in a

real composite may be difficult in many cases. This is in contrast to the flaw growth behavior in monolithic metals in which defects usually develop into a through-the-thickness crack during fatigue.

The importance of the fatigue delamination has long been recognized, but research progress has been slow, since this kind of real-life defect is characteristically difficult to study due to the inherent complexities of the crack geometry, the material anisotropy and discontinuity, and the crack-tip singularity. Because of the matrix-dominated and localized fracture behavior of the delamination, it would be unwise to make any simplification which fails to consider the important resin-rich interlaminar region. Numerous studies have been conducted to investigate the initiation of an interlaminar crack in composites caused by geometric discontinuities [1-3]\*, processing and manufacturing defects [4, 5]. Relatively little work concerning the interlaminar crack growth behavior has been reported [6, 7], especially that associated with in-service and manufacturing defects under repeated stresses. This paper presents an experimental and analytical investigation of the crack growth behavior of an interlaminar crack initiated from a service-induced surface notch in a composite laminate subjected to cyclic loading. Unidirectional composites, which have the simplest laminate configuration, are examined first to explore the fundamental nature of the interlaminar crack. Interlaminar fatigue failure behavior of more complicated angle-ply composites is then studied and compared with the results obtained from the basic unidirectional fiber configuration.

---

\*Numbers in brackets designate References at end of paper.

## EXPERIMENTAL PROGRAM

One of the central concepts in this experimental program is to develop a suitable test technique in which stable interlaminar crack growth can be obtained under cyclic fatigue without being affected by the complex three-dimensional edge effect [8]. Experiments were conducted to identify the influential geometric and laminate parameters, to examine the interlaminar failure mechanisms, and to characterize rationally the fatigue damage behavior in the composites. They also helped to establish a realistic mechanical model for later analytical study and provided experimental data to validate the results.

*Materials and Specimen Preparation*

Scotchply Type 1003 E-glass/epoxy (manufactured by 3M Company, Minneapolis, Minn.) was used in the fabrication of all test specimens. The material was received in a unidirectional prepreg form. Test composites were made by a compressive molding process following manufacturer's instructions. Specimens used in the study were eight-ply composite laminates of various fiber orientations and stacking sequences. An interlaminar crack initiator was introduced in the form of a surface notch penetrating one or more plies as desired by cutting individual plies with a razor blade, prior to the laminate assembly. The specimen had a gauge length of six inches and a width of one inch, and the surface notch extended completely across the specimen width as shown in Fig. 2.

*Experimental Procedures*

All interlaminar crack growth tests were conducted at room temperature in a laboratory environment. Fatigue experiments were run on an Instron

Model 1211 dynamic cyler. Specimens were cycled under a controlled sinusoidal load-time condition with a minimum tensile stress of 1.0 ksi and some maximum tension at a frequency of approximately 5 cycles per second (Fig. 3). No significant heating of the specimen was observed at this frequency during the test. A traveling optical microscope mounted on the testing facilities was used periodically to monitor the interlaminar crack extension in the specimen under transmitted light and to measure accurately the delamination crack length after a given number of cycles. Fatigue crack growth data were obtained for several cases in which interlaminar cracks were initiated at different depths under the surface. Experimental results, expressed by delamination length versus number of loading cycles, are reported in the next section.

#### *Advantages of Present Test Method*

The present experimental method has several advantages particularly suitable for studying the cyclic interlaminar crack growth behavior in composites. As mentioned previously, the initiation of delamination from geometric discontinuities is complicated by the three-dimensional edge effect. Thus, the growth of the interlaminar crack may be expected to be influenced also by the edges of the laminate. Better appreciation of the nature of the problem can be obtained by investigating the delamination growth by itself without being affected by geometric boundaries. This purpose may be achieved in the current experiments by using specimens wide enough to minimize the localized edge effect on the propagating interlaminar crack front. The experiment can also provide a controlled, stable delamination growth at a desired depth and enables the crack length

to be measured accurately and conveniently. Moreover, the specimen geometry is considered relatively easy to model in the analytic study, which will be discussed in the next section.

#### ANALYTICAL APPROACH

The current analytical approach, using an advanced singular finite-element method of the hybrid-stress model, has a capability to overcome the aforementioned difficulties and can provide a numerically exact solution for the problem. The method, pioneered by Pian et al. [9], gives a rapid rate of solution convergence and enables an accurate description of the crack-tip response by introducing a crack-tip superelement including singular and higher order terms based on the complex variable formulation of Muskhelishvili stress functions. It is particularly suitable for studying crack problems in composites, since the complex crack geometry, laminate properties and traction boundary conditions of crack surfaces can be exactly modeled. Additional features of the method include the flexibility of formulation, the selection of element characteristics, and the expedient achievement of interelement compatibility.

#### *Mechanical Model and Assumptions*

Microscopic observation in the experimental study indicated that interlaminar crack growth is clearly a matrix-dominated progressive failure mechanism occurring in a resin-rich interlaminar region. Thus, the composite laminate is modeled as an assembly of anisotropic plies bonded together by thin resin interlayers subjected to an in-plane cyclic stress. Each fiber

reinforced lamina of thickness  $t_0$  has its material axis oriented from the loading direction by an angle  $\theta_1$ . The resin-rich interlayer is assumed to have a uniform thickness,  $t_1$ , and perfectly bonded with the plies everywhere except the region where a crack is initiated from the surface notch tip. The crack geometry and laminate configuration are conveniently expressed by  $(\underline{\theta_1/\theta_2} // \theta_3/\theta_4/\theta_5/\dots\dots\dots)$ , where the double slash and the underline represent the location of the interlaminar crack and the penetration depth of the surface notch, respectively. The interlaminar crack is modeled, for simplicity without losing generality, as a flaw completely embedded in a resin-rich interlayer as shown in Fig. 4. Studies on other extreme cases such as the crack located at a vanishing interlayer or at a ply/interlayer interface, giving a more complicated oscillating three-dimensional singular stresses, are reported elsewhere [10].

#### *Method of Analysis*

General procedure of formulating the plane crack problem in the composite is described in this section. Details of the formulation for the crack-tip superelement and surrounding non-singular elements have been given elsewhere [11, 12] and are not repeated here. Briefly, the formulation of the analysis is based on the variational principle of modified complementary energy. Following Muskhelishvili's formulation [13], the stress and displacement fields may be expressed in terms of two stress functions,  $\phi(z)$  and  $\psi(z)$ , of a complex variable  $z$ . A mapping function  $w(\xi)$  is then introduced to transfer the singular crack domain to a  $\xi$ -plane by  $z = w(\xi) = \xi^2$  where  $-\pi/2 \leq \arg \xi \leq \pi/2$ . The functions  $\phi(\xi)$  and  $\psi(\xi)$  are analytical and interrelated by the traction boundary condition along crack surfaces.

In the crack-tip superelement formulation,  $\phi(\xi)$  is assumed to have the form

$$\phi(\xi) = \sum_{j=1}^n b_j \xi^j \quad (1)$$

and function  $\psi(\xi)$  may be obtained as

$$\psi(\xi) = - \sum_{j=1}^n [\bar{b}_j (-1)^j + \frac{1}{2} j b_j] \xi^j \quad (2)$$

where  $b_j = \beta_j + i \beta_{n+j}$  (non-symmetric case) (3)

or  $b_j = \beta_j$  (symmetric case) (4)

and  $\beta$ s are real constants to be determined. Using Eqs. 1 and 2, the stress and displacement fields may be expressed in terms of the stress coefficients  $\beta$ s. The boundary traction  $\underline{T}$  can be calculated by

$$\underline{T}_i = \sigma_{ij} v_j \quad (5)$$

Interpolating boundary displacements  $\tilde{u}$  in terms of nodal displacements  $\tilde{q}$  and inserting  $\underline{\sigma}$  and  $\underline{T}$  into the variational principle, the crack-tip super-element stiffness matrix may be obtained.

Surrounding non-singular element stiffness matrices are formulated by a conventional hybrid-stress finite element method through a minimum complementary energy principle [14]. The anisotropic elastic properties of each glass/epoxy lamina are considered in the analysis by introducing an appropriate compliance matrix in the element stiffness formulation. Since boundary displacement functions are independently assumed for the crack element and non-singular elements, interelement compatibility can be ensured by a suitable choice of interpolation functions.

The assembled governing equations for the whole system may be written as

$$\underline{\underline{K}} \underline{\underline{q}} = \underline{\underline{Q}} \quad (6)$$

where  $\tilde{K}$  is the global stiffness matrix, and  $Q$ , the consistent loading vector. After solving  $q$  from Eq. 6 by an appropriate solution scheme, the stress and strain fields can be determined. Stress intensity factors  $K_I$  and  $K_{II}$  corresponding to an applied stress level and an interlaminar crack length may be found from the relation

$$K_I = \sqrt{2\pi} \beta_1 \quad (7)$$

and

$$K_{II} = \sqrt{2\pi} \beta_{n+1} \quad (8)$$

The associated elastic energy release rates  $G_I$  and  $G_{II}$  can be obtained by a standard procedure.

The accuracy and convergence assessments of the solutions are complicated by several unusual features of the problem and of the method of analysis due to the inherently singular nature of the interlaminar crack. A study of the accuracy and convergence of the analysis, and solution stability has been conducted by testing cases for which independent solutions are available. Excellent agreements with existing closed-form solutions were obtained. The results indicated that accuracy within approximately one percent of the converged solutions of  $K_I$  and  $K_{II}$  can be achieved by the optimum mesh arrangements used in the current study. Details of the study were reported in [12].

For the cases of cyclic loading, the ranges of interlaminar crack-tip stress intensity factors,  $\Delta K_I$  and  $\Delta K_{II}$ , may be determined by

$$\Delta K_I = (K_I)_{\max} - (K_I)_{\min} \quad (9)$$

and

$$\Delta K_{II} = (K_{II})_{\max} - (K_{II})_{\min} \quad (10)$$

where  $(K_I)_{\max}$  and  $(K_{II})_{\max}$  are opening and shearing mode stress intensity

factors corresponding to a maximum cyclic stress level  $\sigma_{\max}$  for the delamination crack of length  $l_d$ , and  $(K_I)_{\min}$  and  $(K_{II})_{\min}$  are the values associated with a minimum cyclic stress level  $\sigma_{\min}$ . Numerical results of  $(K_I)_{\max}$ ,  $(K_{II})_{\max}$ ,  $(K_I)_{\min}$  and  $(K_{II})_{\min}$  were accurately computed for the delamination test specimens by the computer-aided numerical method.

## RESULTS AND DISCUSSION

Typical results of the crack growth study of the eight-ply fiberglass composites subjected to nominal cyclic stresses are presented in this section. In the experimental phase, interlaminar crack growth rates were determined by the constant load-amplitude fatigue tests. In the analytical phase of the study, the crack-tip stress field and the ranges of the cyclic stress intensity factors were obtained for the laminates with various geometric and ply configurations. Interlaminar crack growth rates during fatigue were then characterized by the ranges of the mixed-mode cyclic stress intensity factors. The individual glass/epoxy lamina used in the analytical modeling had a thickness dimension of 0.01 inch, and the interlaminar layer was taken as one-twentieth of the ply thickness as observed in the microscope. Elastic constants for each lamina were given by

$$\begin{aligned} E_{LL} &= 5.0 \times 10^6 \text{ psi} & G_{Lz} &= 0.75 \times 10^6 \text{ psi} \\ E_{zz} &= 1.5 \times 10^6 \text{ psi} & \nu_{Lz} &= 0.25 \end{aligned}$$

The interlaminar epoxy resin phase has the properties:

$$\begin{aligned} E_m &= 0.5 \times 10^6 \text{ psi} & \nu_m &= 0.35 \\ G_m &= 0.185 \times 10^6 \text{ psi} \end{aligned}$$

*Interlaminar Crack Growth During Fatigue*

Microscopic observation in the fatigue experiments revealed that delamination was initiated after a few load cycles. It propagated in a stable manner and was clearly a matrix-dominated, progressive failure mechanism occurring in a resin-rich region between plies. This suggested an appropriate mechanical model used later in the analytical study. Measurements were made on the change of the subcritical crack length during cyclic loading. Typical fatigue crack growth data in unidirectional and  $(\pm 45^\circ)_{4S}$  glass/epoxy composites are presented in Figs. 5 and 6. Test results shown in the figures for several maximum cyclic stress levels indicate that crack lengths change drastically with the number of load cycles and that crack growth rates are very distinct between the unidirectional and angle-ply laminates. The growth rates of the delamination  $d\ell_d/dN$  were determined by a computational procedure based on the first derivatives of crack growth curves fitted by experimental data. The crack extension rates were found to increase continuously during the course of fatigue, and rapid crack propagation occurred when the ultimate delamination resistance of the composite was approached. Intralaminar failure, which may lead to a complete fracture of the composites, were often observed in  $(45^\circ/-45^\circ//45^\circ/-45^\circ/-45^\circ/45^\circ/-45^\circ/45^\circ)$  and quasi-isotropic  $(45^\circ/-45^\circ//0^\circ/90^\circ/90^\circ/0^\circ/-45^\circ/45^\circ)$  glass/epoxy prior to large-scale delamination. The number of loading cycles to fracture versus applied cyclic stress for the two composite systems is shown in Fig. 7. The ultimate static strengths ( $\sigma_{UTS}$ ) of these laminates were 14.7 and 44.55 Ksi, respectively.

*Interlaminar Crack-Tip Response*

The driving force of the interlaminar crack growth depends primarily on local crack-tip stresses. Thus, it is necessary to have accurate information on the crack-tip behavior. Since the geometry and material properties are very complex in the problem, the response of the composite to the damage may be best illustrated by isostress contours. These contours were plotted from the analytical solutions obtained by the aforementioned hybrid finite element analysis. Figure 8 gives the distribution of the in-plane stress  $\sigma_{xx}/\sigma_{\infty}$  around the crack with  $l_d = 0.8$  inch in a  $(0^\circ/0^\circ//0^\circ/0^\circ/0^\circ/0^\circ/0^\circ/0^\circ)$  glass/epoxy. The computer plot provides a graphic description of the solutions and an overall view of the damage behavior. It reveals several salient features of the problem: (i) the intensified stress field caused by interlaminar damage is very localized within the matrix-rich interlaminar region ahead of the crack tip, (ii) a large stress gradient exists through the laminate thickness with high concentration in adjacent plies, and (iii) a local compressive in-plane stress component is developed along the lower crack flank. Figures 9 and 10 show the contour plots of interlaminar shear and transverse normal stress distributions in the near field. Both stress components reach extremely high levels within the thin interlaminar region when the crack tip is approached. The interlaminar stresses extend continuously through the interface into the adjacent plies.

A more accurate description of the near field stresses may be expressed by a  $\log \sigma_{ij}$  versus  $\log r$  representation, where  $r$  is the distance ahead of the crack tip. The numerical results near the crack tip give straight lines with a slope of  $-\frac{1}{2}$ , indicating a classical fracture mechanics solution, i.e., a  $1/\sqrt{r}$  singularity; details of the results may be found in [15]. The opening

and shearing mode stress components are observed to have the same order of magnitude at the interlaminar crack tip when a uniaxial nominal stress is applied. The singular stress domain is rather small and is embedded in the resin-rich interlayer region.

The redistribution of laminate stresses due to the propagating interlaminar crack will have a significant effect on the deformation and fracture of the composite. For example, the compressive stress in the lower crack flank may introduce severe local buckling of the delaminated plies in the vicinity of the surface notch. This phenomenon was experimentally observed in [16,17]. The highly nonuniform stress distributions in the transverse direction shown in the isostress contour plots suggest that the classical laminate theory may not be applicable to a delaminated composite. The stress concentration may also introduce a transition from interlaminar to intralaminar fracture mode when different ply orientations are used [18]. Furthermore, the presence of the interlaminar crack may become detrimental to the serviceability of the material when used in an adverse environment such as moisture and corrosive chemicals, because not only does the crack expose the interior of the composite to environmental attack, but also the stress concentration in the near field may enhance the rate-dependent degradation process, which is evident by the results in [19].

#### *Fatigue Crack Growth Rate Characterization*

The stable extension of an interlaminar crack in glass/epoxy composites reveal several features of the progressive interlaminar fatigue damage, which can be used to probe the nature of the delamination growth behavior. Since the interlaminar crack growth is observed as a matrix-dominated failure process and since it is strongly affected by the local crack-tip response, it may be appropriate to postulate, as in the cases of metals and polymers [20,21],

that  $\Delta K_I$  and  $\Delta K_{II}$  are critical controlling factors in the fatigue damage. The ranges of the cyclic stress intensity factors are, in turn, related to the crack length, the cyclic stress, the geometry and laminate properties. In the current fatigue test, stress intensity factors change continuously as the load and the interlaminar crack length increase, and the corresponding crack growth rate varies accordingly. For a given crack length and laminate configuration, exact stress intensity factors may be computed by using the present analytical method. Therefore,  $\Delta K_I$  and  $\Delta K_{II}$  can be precisely determined from Eqs. 9 and 10. It may be reasonable, at this point, to postulate further that  $\Delta K_I$  and  $\Delta K_{II}$  independently affect the interlaminar crack growth rate. Thus,  $d\ell_d/dN$ , obtained from the experiments, may be related to both the  $\Delta K_I$  and the  $\Delta K_{II}$  simultaneously as shown in Figs. 11 and 12 for the glass/epoxy composites with two distinct ply orientations. Strong correlation between  $d\ell_d/dN$  and  $\Delta K$ s is observed from the results, and a power law relationship of the following form may be established,

$$\frac{\log\left(\frac{d\ell_d}{dN}\right)}{\alpha_1} = \frac{\log(\Delta K_I) + C_1}{\alpha_2} = \frac{\log(\Delta K_{II}) + C_2}{\alpha_3} \quad (11)$$

where  $\alpha_i$ s are the directional cosines of the lines determined by a least-square curve-fitting method, and  $C_1$  and  $C_2$  are constants associated with the threshold values of the mixed-mode stress intensity factor ranges.

This functional relationship in Eq. 11 suggests that

$$\frac{d\ell_d}{dN} \sim (\Delta K_I)^{\lambda_1} \quad (12a)$$

or

$$\frac{d\ell_d}{dN} \sim (\Delta K_{II})^{\lambda_2} \quad (12b)$$

where the exponents  $\lambda_1$  and  $\lambda_2$  are related to the laminate configuration, the crack geometry and the material properties of composites. The results in

Figs. 11 and 12 give respective  $\lambda_1$  and  $\lambda_2$  the values of 7.32 and 7.42, for  $0^\circ$  and 7.52 and 7.74 for  $\pm 45^\circ$ . The strong correlation between the interlaminar crack propagation rate and the ranges of cyclic stress intensity factors are very informative. Further study is needed to identify the nature of the interlaminar crack under more complex fatigue loading and to construct the crack growth rate surface of mixed-mode failure so as to characterize fully the interlaminar fatigue behavior, and the relative dominance of each individual fracture mode.

#### *Limitations of Current Study*

It should be noted here that several geometric and material complications in composites have not been included in the current analytical modeling, such as the nonuniformity of the resin-rich interlaminar region thickness, the heterogeneity of the fiber and matrix phases, and other types of commonly encountered defects (e.g. voids, inclusions, broken plies, etc.). These complications are statistical in nature and almost always exist in the material. Their presence may have significant effects on the interlaminar crack growth behavior, but has not been fully explored yet. The anti-plane mode deformation and fracture (mode III), which may have an important contribution to the progressive fatigue failure of the materials, especially in the angle-ply composite laminates, have not been considered in the present study. A recent study on edge delamination [10] reveals that the mode III component of the crack-tip field has a very high value, which may be primarily responsible for the interlaminar crack growth and failure of the composites, including the  $\pm 45^\circ$  case. Furthermore, residual stresses due to ply differential thermal contraction during the curing process may strongly affect the crack growth behavior. This effect has not been included in the present investigation.

## SUMMARY AND CONCLUSION

A combined experimental and analytical investigation of interlaminar crack growth in fiber-reinforced composites under cyclic loading has been presented. The unidirectional ply configuration was studied first to elucidate the fundamental failure behavior and, later, served as a reference for studying more complex angle-ply composite laminates. In the experimental phase, microscopic observation of failure mechanisms revealed that delamination is clearly a matrix-dominated, progressive failure occurring in the resin-rich interlaminar region. Interlaminar crack growth rates under tension-tension fatigue were obtained, and test results were further used in conjunction with analytical characterization. The analytical study of the problem was based on an advanced hybrid-stress finite element method, formulated by using Muskhelishvili's complex stress functions through a modified complementary energy principle. Numerical solutions clarify the basic nature of the cyclic interlaminar failure. Implications of the results in the applicability of classical laminate theory to the delamination problem due to the localized interlaminar crack-tip singularity and the stress concentration in the adjacent plies were discussed. Fatigue crack growth rates were found to be related directly to the ranges of the mixed-mode cyclic stress intensity factors by a power law relationship. The study elucidates many important features of the delamination problem, provides insight into the interlaminar fatigue behavior, and should be of practical importance in the testing and design of composites materials.

Acknowledgments

The work described in this paper was supported in part by NASA-Lewis Research Center, Cleveland, Ohio under Grant NSG 3044. The authors are grateful to Dr. C. C. Chamis for his encouragement and cooperation. Fruitful discussion with Dr. J. F. Mandell of the Massachusetts Institute of Technology is deeply acknowledged.

## REFERENCES

- 1 Pipes, R. B., Kaminski, B. E. and Pagano, N. J., "Influence of the Free Edge upon the Strength of Angle-Ply Laminates," *Analysis of the Test Methods for High Modulus Fibers and Composites*, ASTM STP 521, American Society for Testing and Materials, 1973, pp. 218-228.
- 2 Wang, S. S., Mandell, J. F. and McGarry, F. J., "Three Dimensional Solution for a Through-Thickness Crack with Crack Tip Damage in a Cross-Plied Laminate," *Fracture Mechanics of Composites*, ASTM STP 593, American Society for Testing and Materials, 1975, pp. 61-85.
- 3 Reifsnider, K. L., Henneke, E. G., II and Stinchcomb, W. W., "Delamination in Quasi-isotropic Graphite-Epoxy Laminates," *Composite Materials: Testing and Design (Fourth Conference)*, ASTM STP 617, American Society for Testing and Materials, 1977, pp. 93-105.
- 4 Verett, R. M. and Demuts, E., "Effects of Manufacturing and In-Service Defects on Composite Materials," *Proceedings of the Army Symposium on Solid Mechanics, 1976-Composite Materials: The Influence of Mechanics of Failure on Design*, AMMRC MS 76-72, Army Mechanics and Materials Research Center, Watertown, Mass., 1976, pp. 123-137.
- 5 Wang, S. S., "Delamination Fracture from Surface Notch in  $(\pm 45^\circ/0^\circ/90^\circ)_s$  Graphite/Epoxy Composites," *Proceedings of the Second International Conference on Composite Materials (ICCM-II)*, TMS-AIME, 1978.
- 6 Erdogan, F. and Arin, K., "A Sandwich Plate with a Part-Through and Debonding Crack," *Engineering Fracture Mechanics*, Vol. 4, 1972, pp. 449-458.
- 7 Kulkarni, S. V. and Frederick, D., "Propagation of Delamination in a Layered Cylindrical Shell," *International Journal of Fracture*, Vol. 9, 1973, pp. 113-115.

- 8 Pipes, R. B. and Pagano, N. J., "Interlaminar Stresses in Composite Laminates under Uniform Axial Extension," *Journal of Composite Materials*, Vol. 4, 1970, pp. 538-548.
- 9 Pian, T. H. H., Tong, P. and Luk, C. H., "Elastic Crack Analysis by a Finite Element Method," *Proceedings of the Third Conference on Matrix Methods in Structural Mechanics*, 1971, pp. 661-682.
- 10 Wang, S. S., "An Analysis of Edge Delamination Crack in Composite Laminate under Uniform Axial Extension," NASA CR-165439, National Aeronautics and Space Administration, Washington, D.C., 1981.
- 11 Tong, P., Pian, T. H. H. and Lasry, S., "A Hybrid-Element Approach to Crack Problems in Plane Elasticity," *International Journal for Numerical Methods in Engineering*, Vol. 7, 1973, pp. 297-308.
- 12 Wang, S. S., Mandell, J. F. and McGarry, F. J., "An Analysis of the Crack Tip Stress Field in DCB Adhesive Fracture Specimens," *International Journal of Fracture*, Vol. 14, No. 1, Feb., 1978, pp. 39-58.
- 13 Muskhelishvili, N. I., *Some Basic Problems of Mathematical Theory of Elasticity*, P. Noordhoff, Groningen, The Netherlands, 1953.
- 14 Pian, T. H. H., "Derivation of Element Stiffness Matrix by Assumed Stress Distribution," *American Institute of Aeronautics and Astronautics Journal*, Vol. 2, 1964, pp. 1333-1336.
- 15 Wang, S. S. and Mandell, J. F., "Analysis of Delamination in Unidirectional and Crossplied Fiber Reinforced Composites Containing Surface Cracks," NASA Technical Report NASA-CR-135248, May, 1977.

- 16 Sendekyj, G. P., Stalnaker, H. D., Kleismit, R. A., "Effect of Temperature on Frequency Response of Surface-Notched  $[(0^{\circ}, \pm 45^{\circ}, 0^{\circ})_s]_3$  Graphite-Epoxy Laminate", *Fatigue of Filamentary Composite Materials*, ASTM STP 636, K. L. Reifsnider and K. N. Lauraitis, Eds., American Society for Testing and Materials, 1977, pp. 123-140.
- 17 Sendekyj, G. P., "Surface Notches in Composites", submitted for publication, Air Force Flight Dynamics Laboratory, Wright-Patterson AFB, Ohio, 1978.
- 18 Wang, S. S., "Failure Modes of Interlaminar Crack in Quasi-isotropic Fiber-Reinforced Composites Containing a Surface Notch," in *Failure Modes and Processing of Composites IV*, TMS-AIME, Oct., 1977.
- 19 Mandell, J. F., "Origin of Moisture Effects on Crack Propagation in Composites," Research Report R77-4, Department of Materials Science and Engineering, M.I.T., Dec., 1977.
- 20 Hertzberg, R. W., in *Deformation and Fracture Mechanics of Engineering Materials*, Chap. 13, John Wiley and Sons, Inc., New York, 1976, pp. 465-520.
- 21 Manson, J. A. and Hertzberg, R. W., "Fatigue Failure in Polymers," *Critical Reviews in Macromolecular Science*, Vol. 1, No. 4, 1973, pp. 433-500.

## LIST OF CAPTIONS FOR FIGURES

- Fig. 1 Micrograph of Graphite Fiber Reinforced Composite Showing Individual Plies and Resin-Rich Interlayers Between Plies
- Fig. 2 Fatigue Test Specimen for Interlaminar Crack Growth Study
- Fig. 3 Stress vs. Time During Fatigue Test
- Fig. 4 Interlaminar Crack Geometry, Coordinate System, and Hybrid-Stress F.E.M. Mesh Configuration in Composites
- Fig. 5 Interlaminar Crack Growth During Fatigue in (0°/0°// 0°/0°/0°/0°/0°/0°) Glass/Epoxy
- Fig. 6 Interlaminar Crack Growth During Fatigue in (45°/-45°// 45°/-45°/-45°/45°/-45°/45°) Glass/Epoxy
- Fig. 7 Fatigue Stress vs. Number of Cycles to Failure for Glass/Epoxy Composites with Different Laminate Configurations
- Fig. 8 In-plane Longitudinal Stress Contours  $\sigma_{xx}/\sigma_{\infty}$  Near Interlaminar Crack Tip in (0°/0°// 0°/0°/0°/0°/0°/0°) Glass/Epoxy
- Fig. 9 Transverse Normal Stress Contours  $\sigma_{zz}/\sigma_{\infty}$  Near Interlaminar Crack Tip in (0°/0°// 0°/0°/0°/0°/0°/0°) Glass/Epoxy
- Fig. 10 Interlaminar Shear Stress Contours  $\sigma_{xz}/\sigma_{\infty}$  Near Interlaminar Crack Tip in (0°/0°// 0°/0°/0°/0°/0°/0°) Glass/Epoxy
- Fig. 11 Interlaminar Crack Growth Rate  $d\ell_d/dN$  as a Function of the Ranges of Mixed-Mode Stress Intensity Factors,  $\Delta K_I$  and  $\Delta K_{II}$  for (0°/0°// 0°/0°/0°/0°/0°/0°) Glass/Epoxy
- Fig. 12 Interlaminar Crack Growth Rate  $d\ell_d/dN$  as a Function of the Ranges of Mixed-Mode Stress Intensity Factors  $\Delta K_I$  and  $\Delta K_{II}$  for (45°/-45°// 45°/-45°/-45°/45°/-45°/45°) Glass/Epoxy



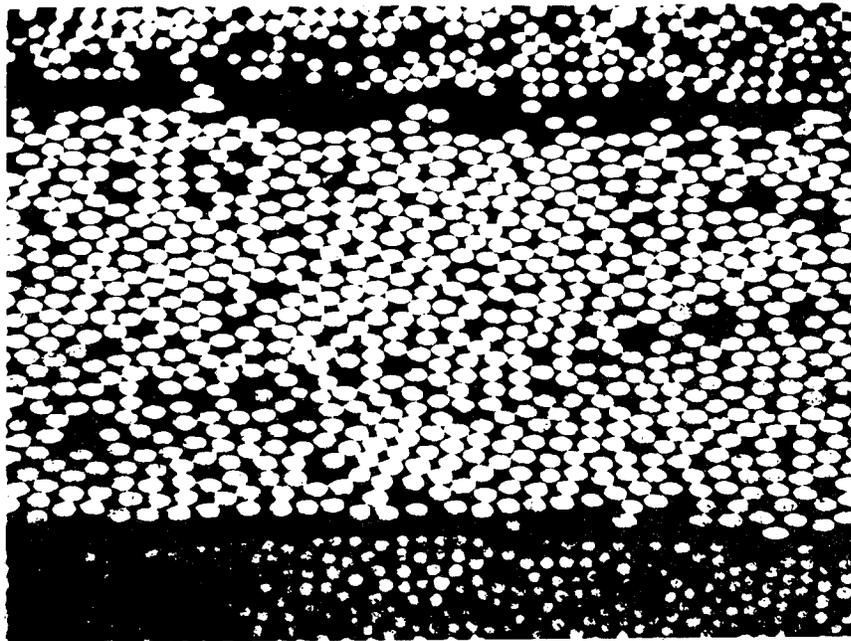


FIG. 1 MICROGRAPH OF GRAPHITE FIBER REINFORCED COMPOSITE SHOWING INDIVIDUAL PLYS AND RESIN-RICH INTERLAYERS BETWEEN PLYS.

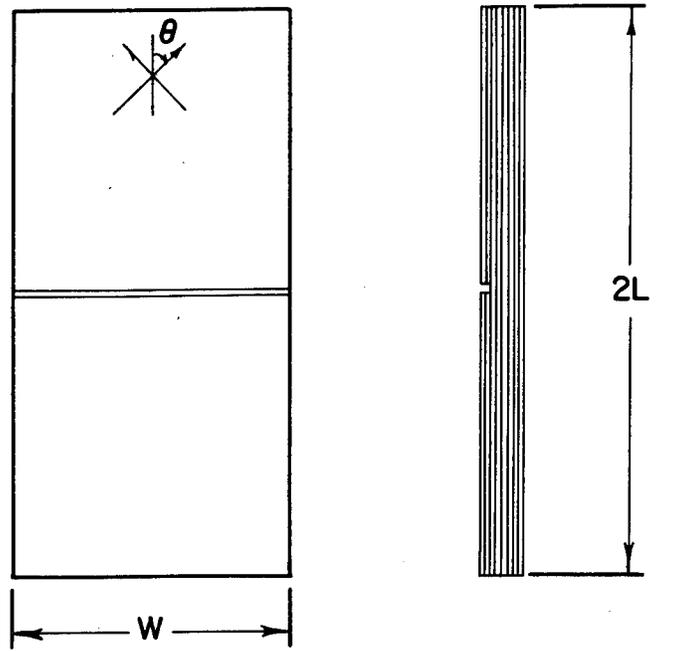

a.) BEFORE LOADING

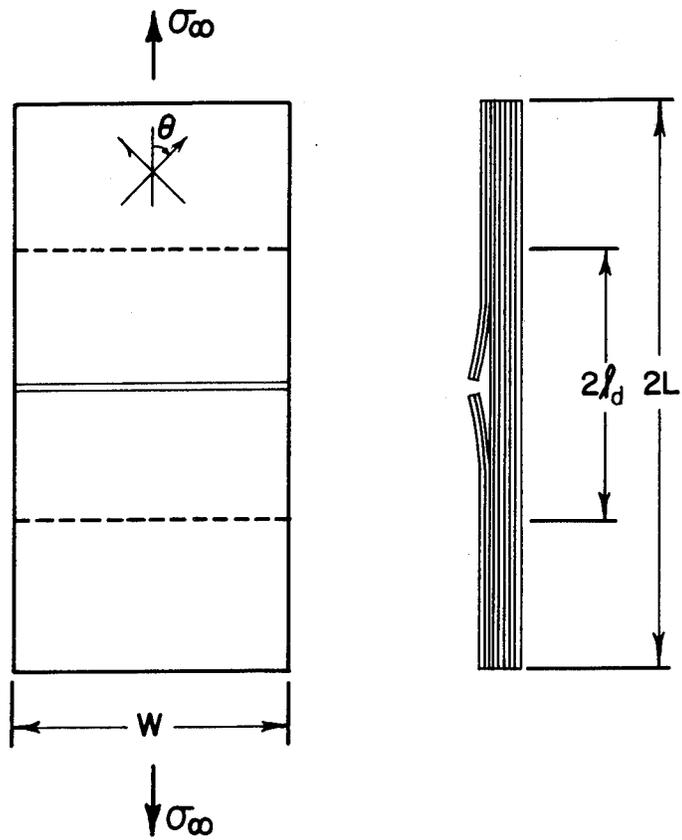

b.) DURING LOADING

FIG. 2 FATIGUE TEST SPECIMEN FOR INTERLAMINAR CRACK GROWTH STUDY ( $2L = 6.0$  in.;  $W = 1.0$  in. )

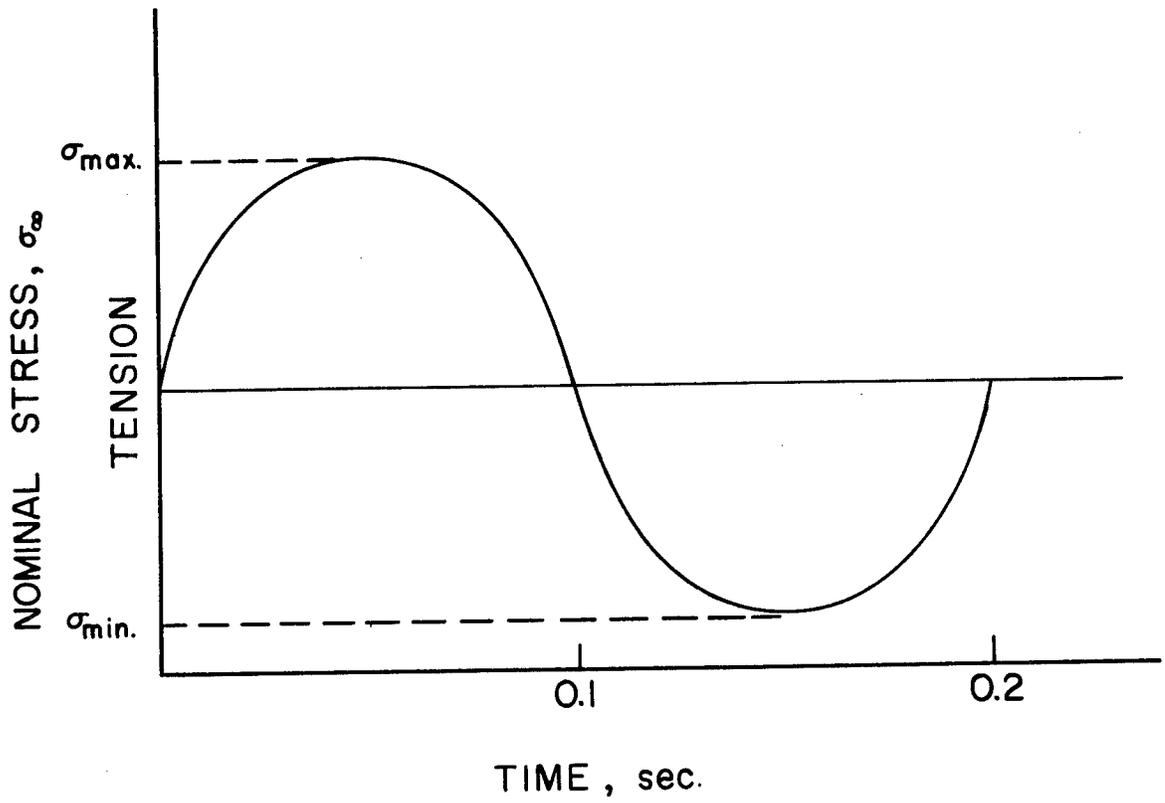


FIG. 3 STRESS vs. TIME FOR FATIGUE TEST

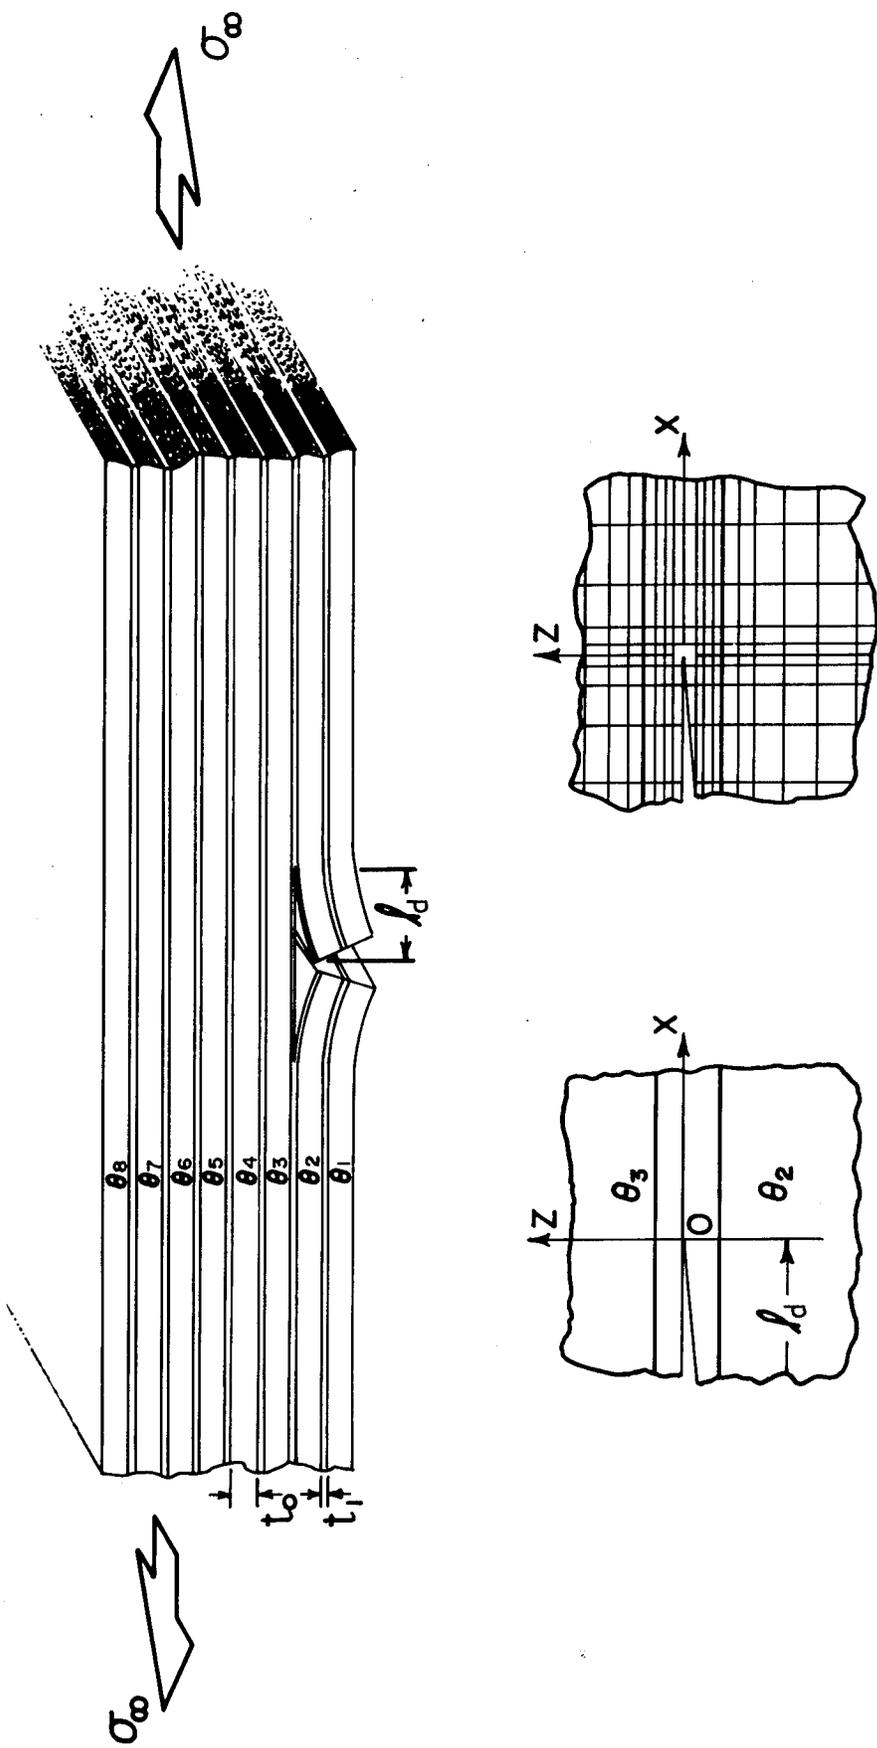


FIG. 4 INTERLAMINAR CRACK GEOMETRY, COORDINATE SYSTEM AND HYBRID-STRESS F.E.M. MESH CONFIGURATION IN COMPOSITES

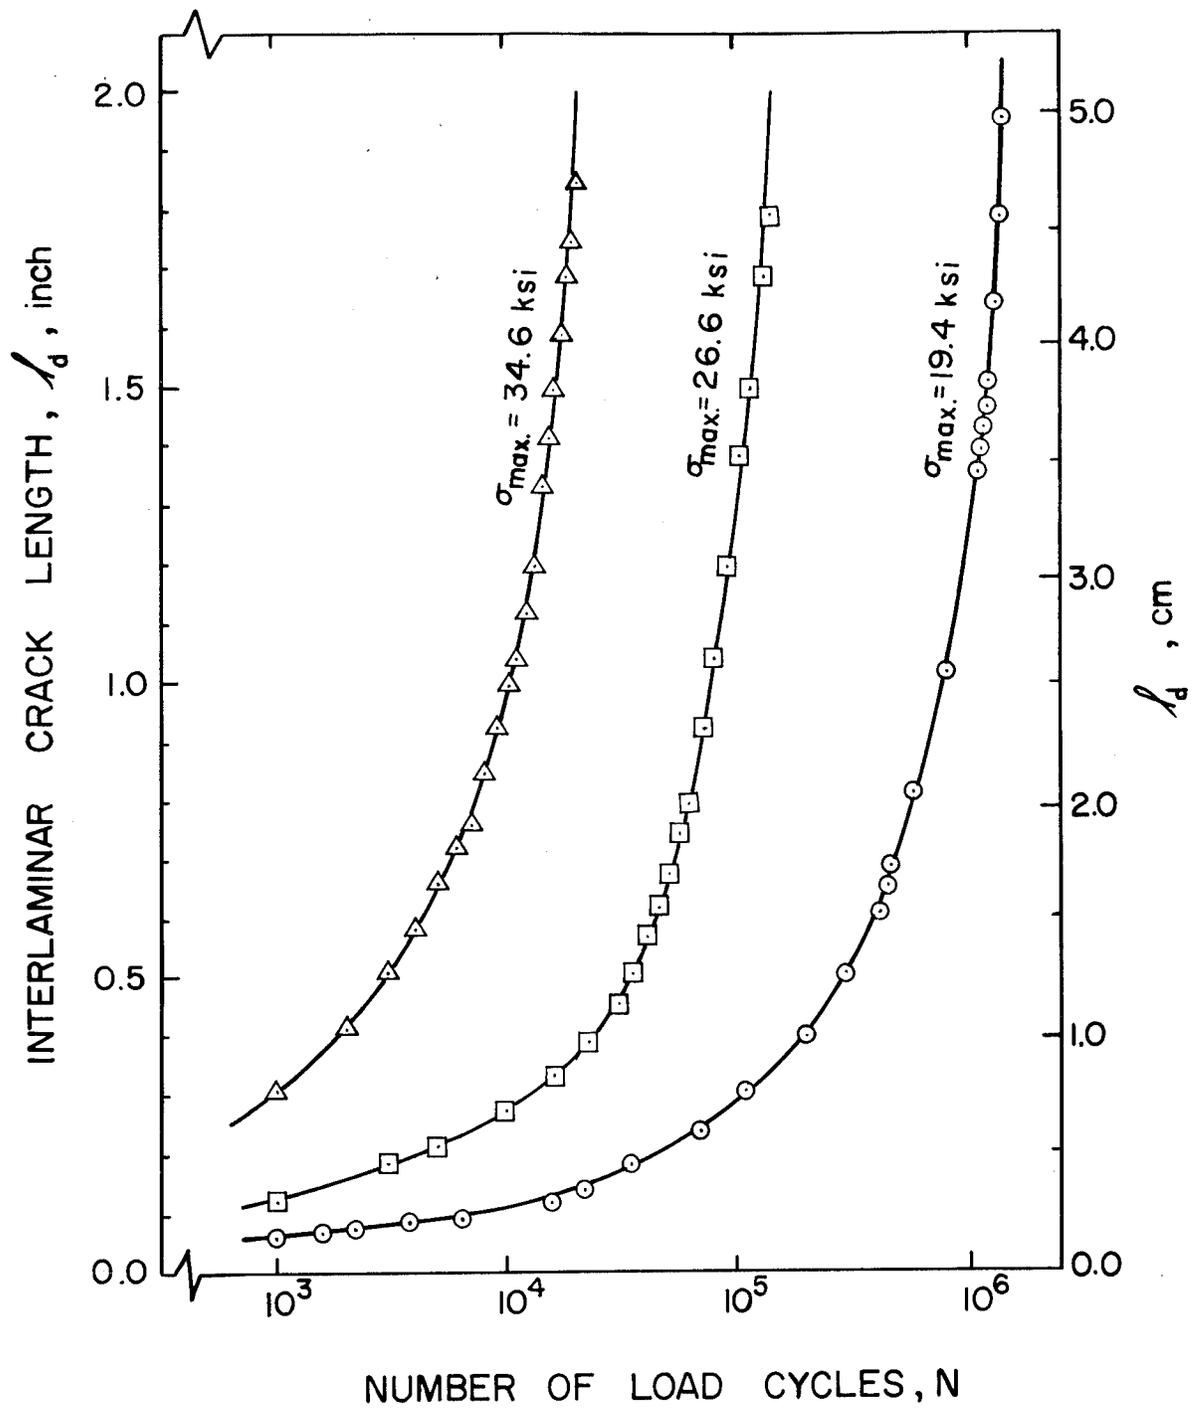


FIG. 5 INTERLAMINAR CRACK GROWTH DURING FATIGUE IN (0%0%0%0%0%0%) GLASS/EPOXY

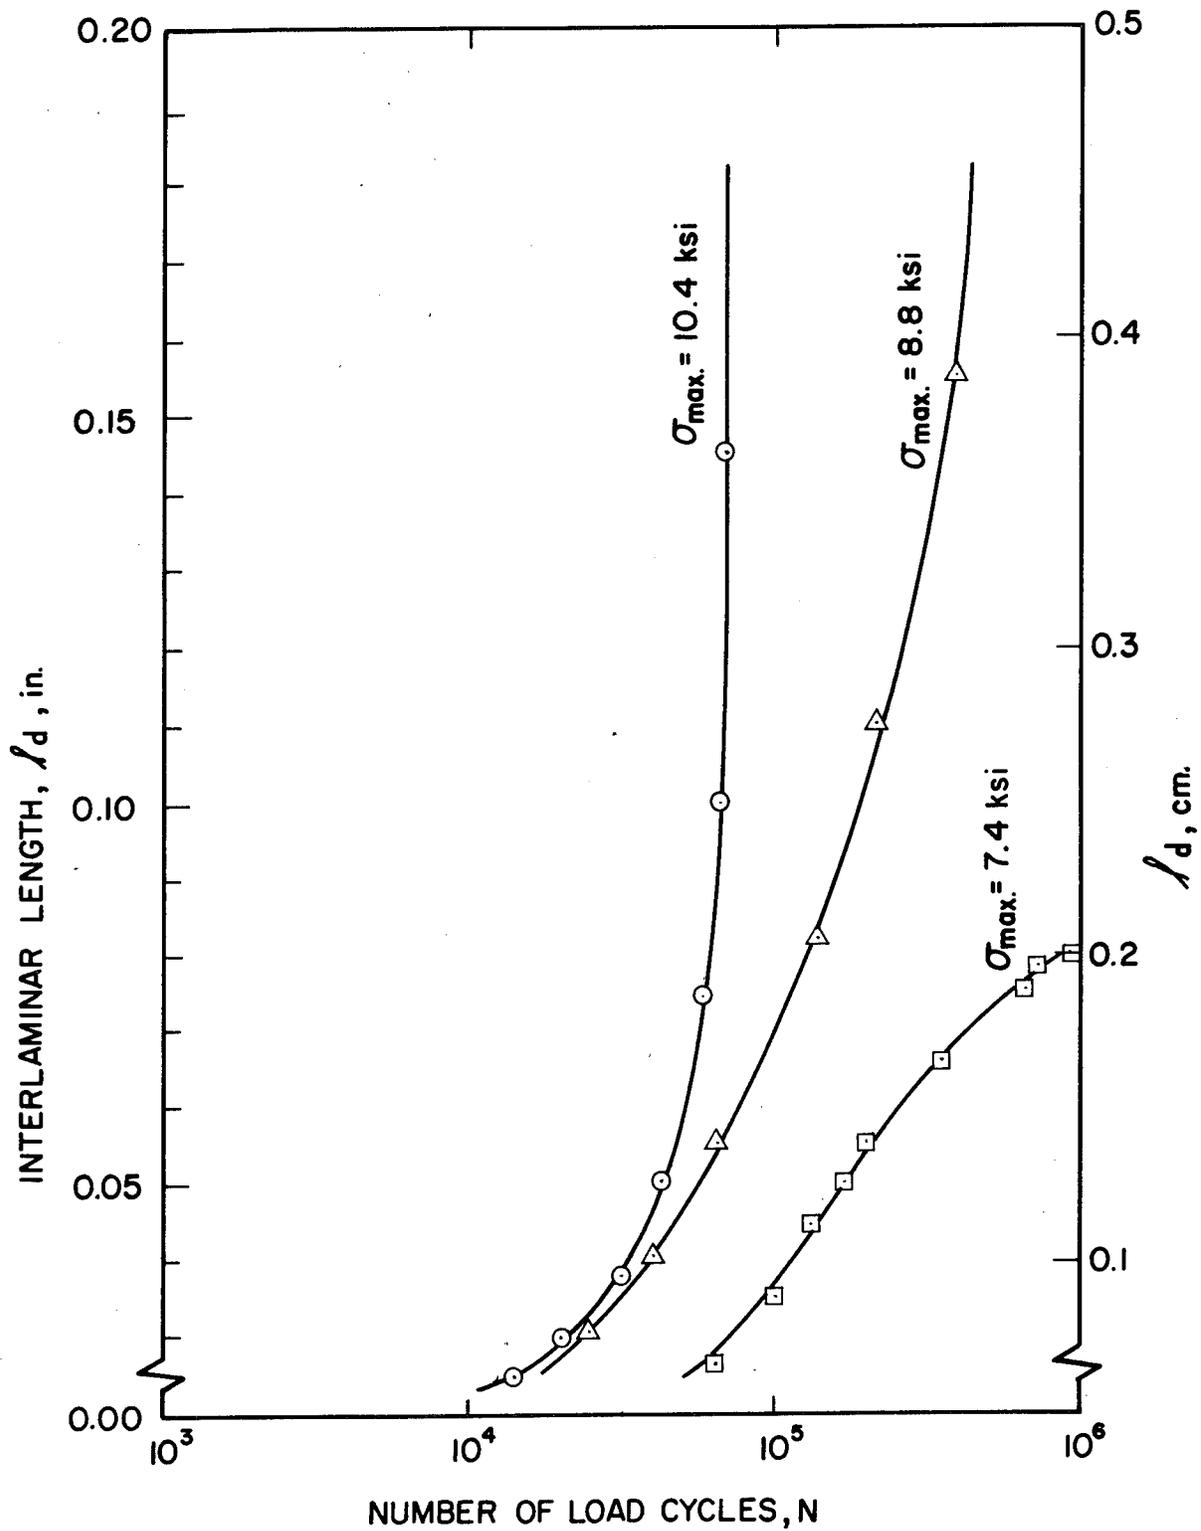


FIG. 6 INTERLAMINAR CRACK GROWTH DURING FATIGUE IN (45°-45°//45°-45°-45°/45°-45°/45°) GLASS/EPOXY

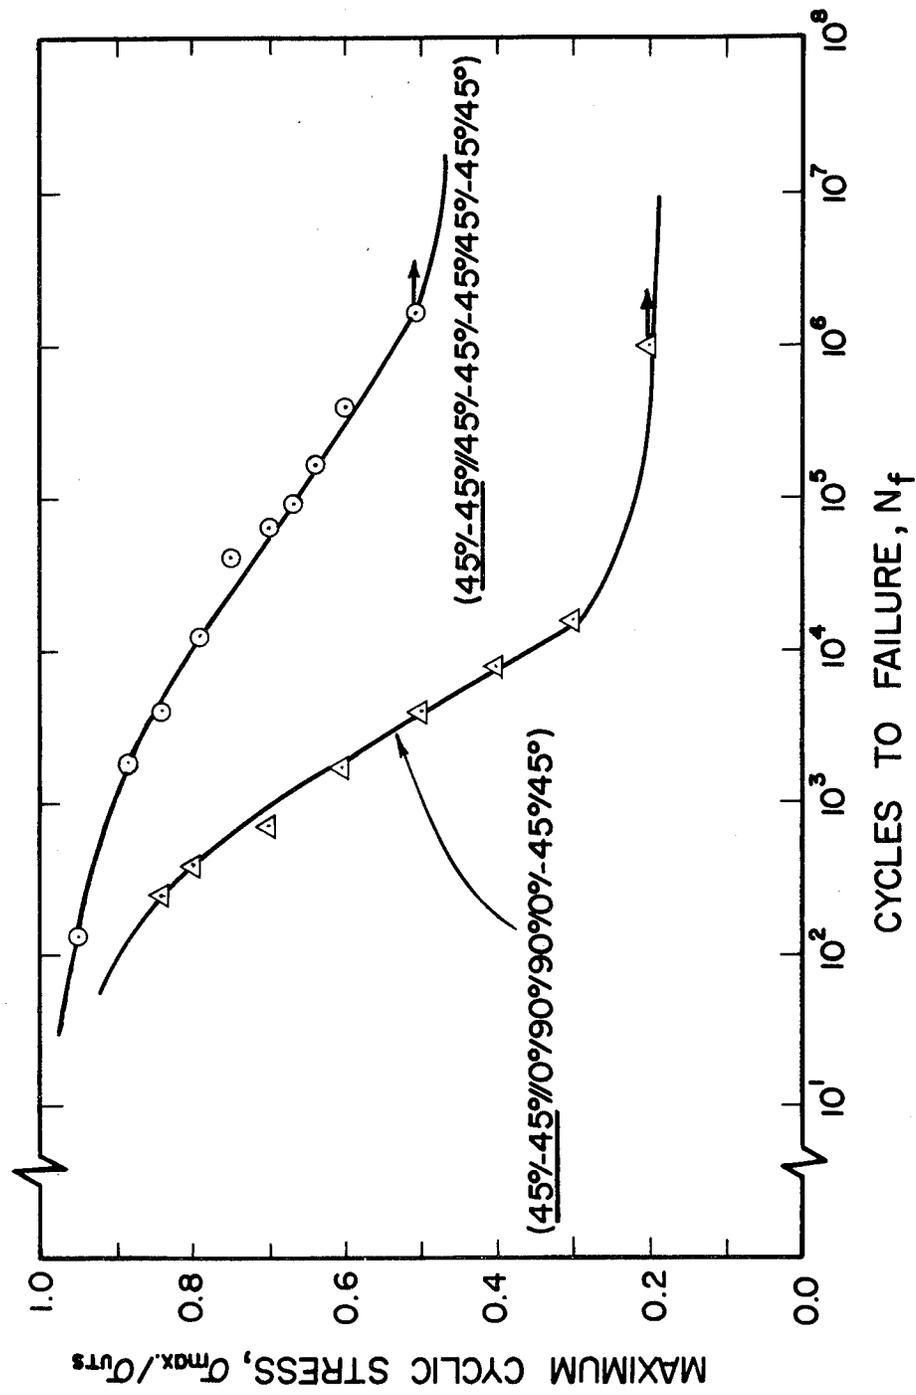


FIG. 7 FATIGUE STRESS vs NUMBER OF CYCLES TO FAILURE FOR GLASS/EPOXY COMPOSITES WITH DIFFERENT LAMINATE CONFIGURATIONS

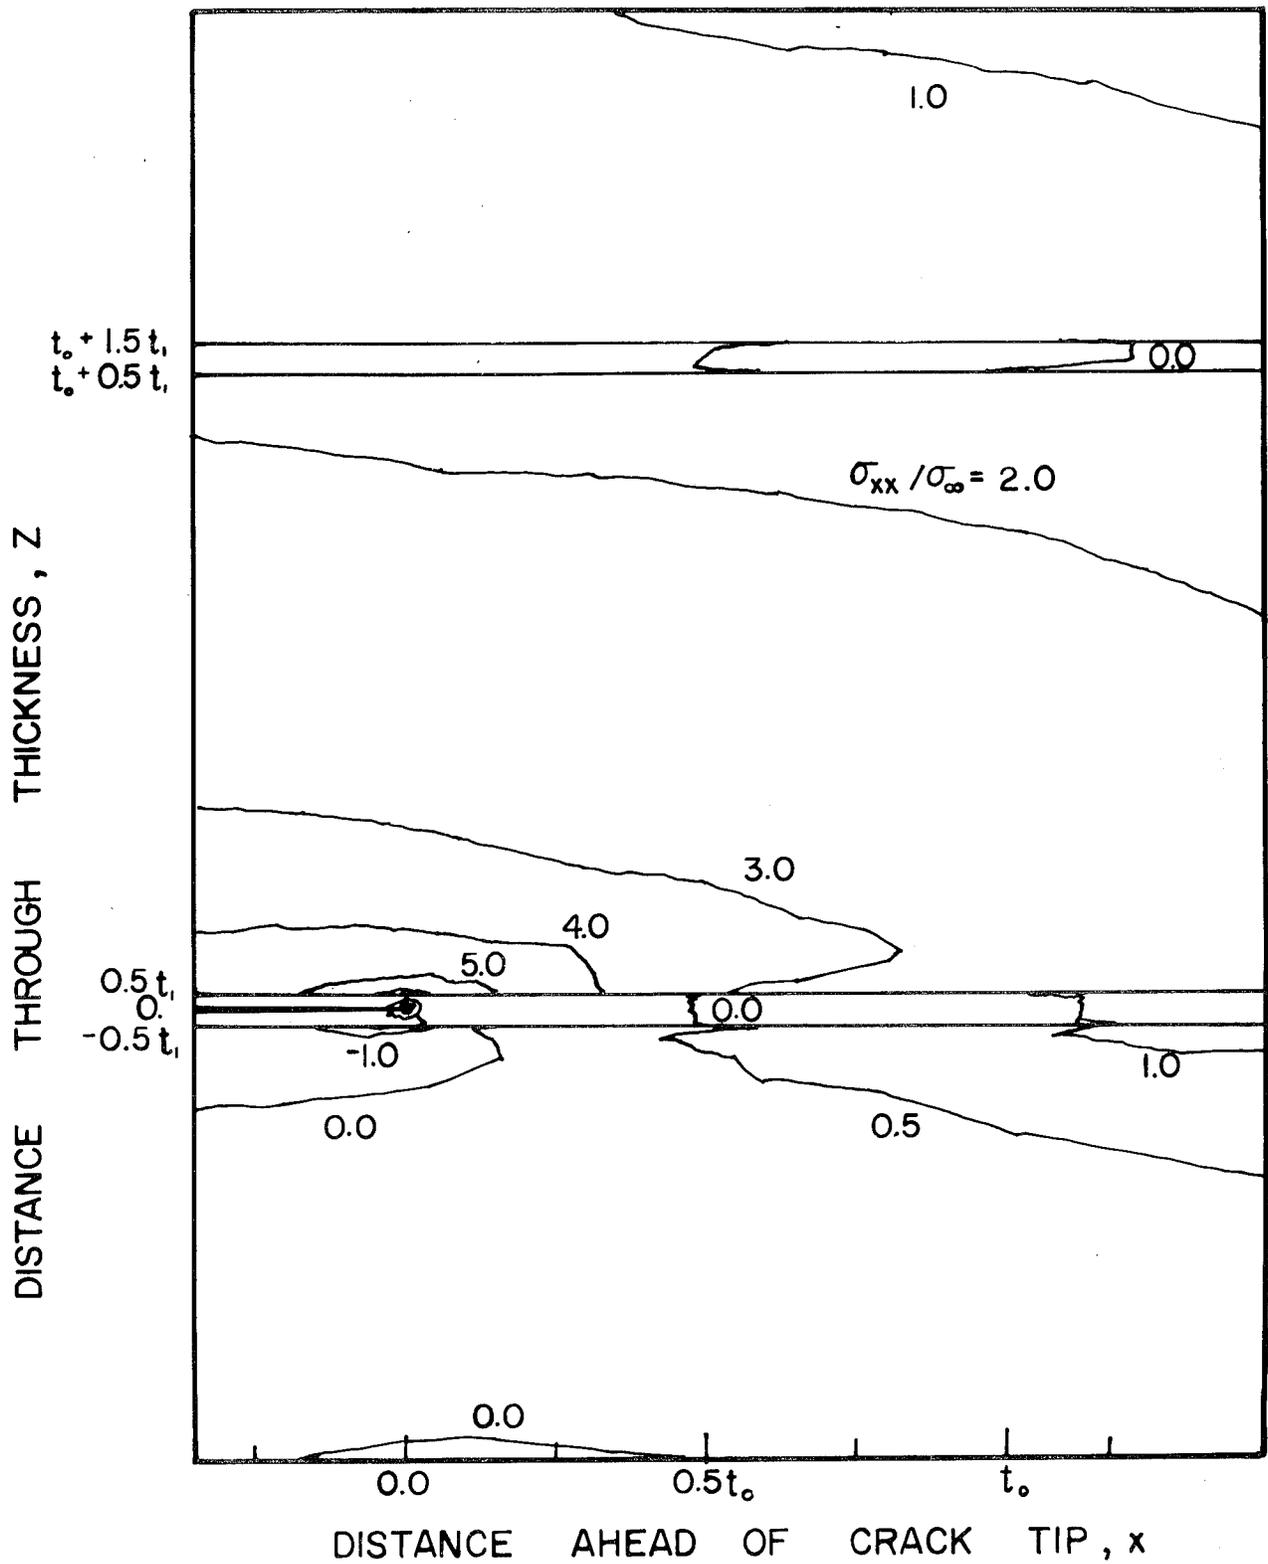


FIG.8 IN-PLANE LONGITUDINAL STRESS CONTOUR  $\sigma_{xx}/\sigma_{\infty}$  NEAR INTERLAMINAR CRACK TIP IN (0°/0°//0°/0°/0°/0°/0°) GLASS/EPOXY

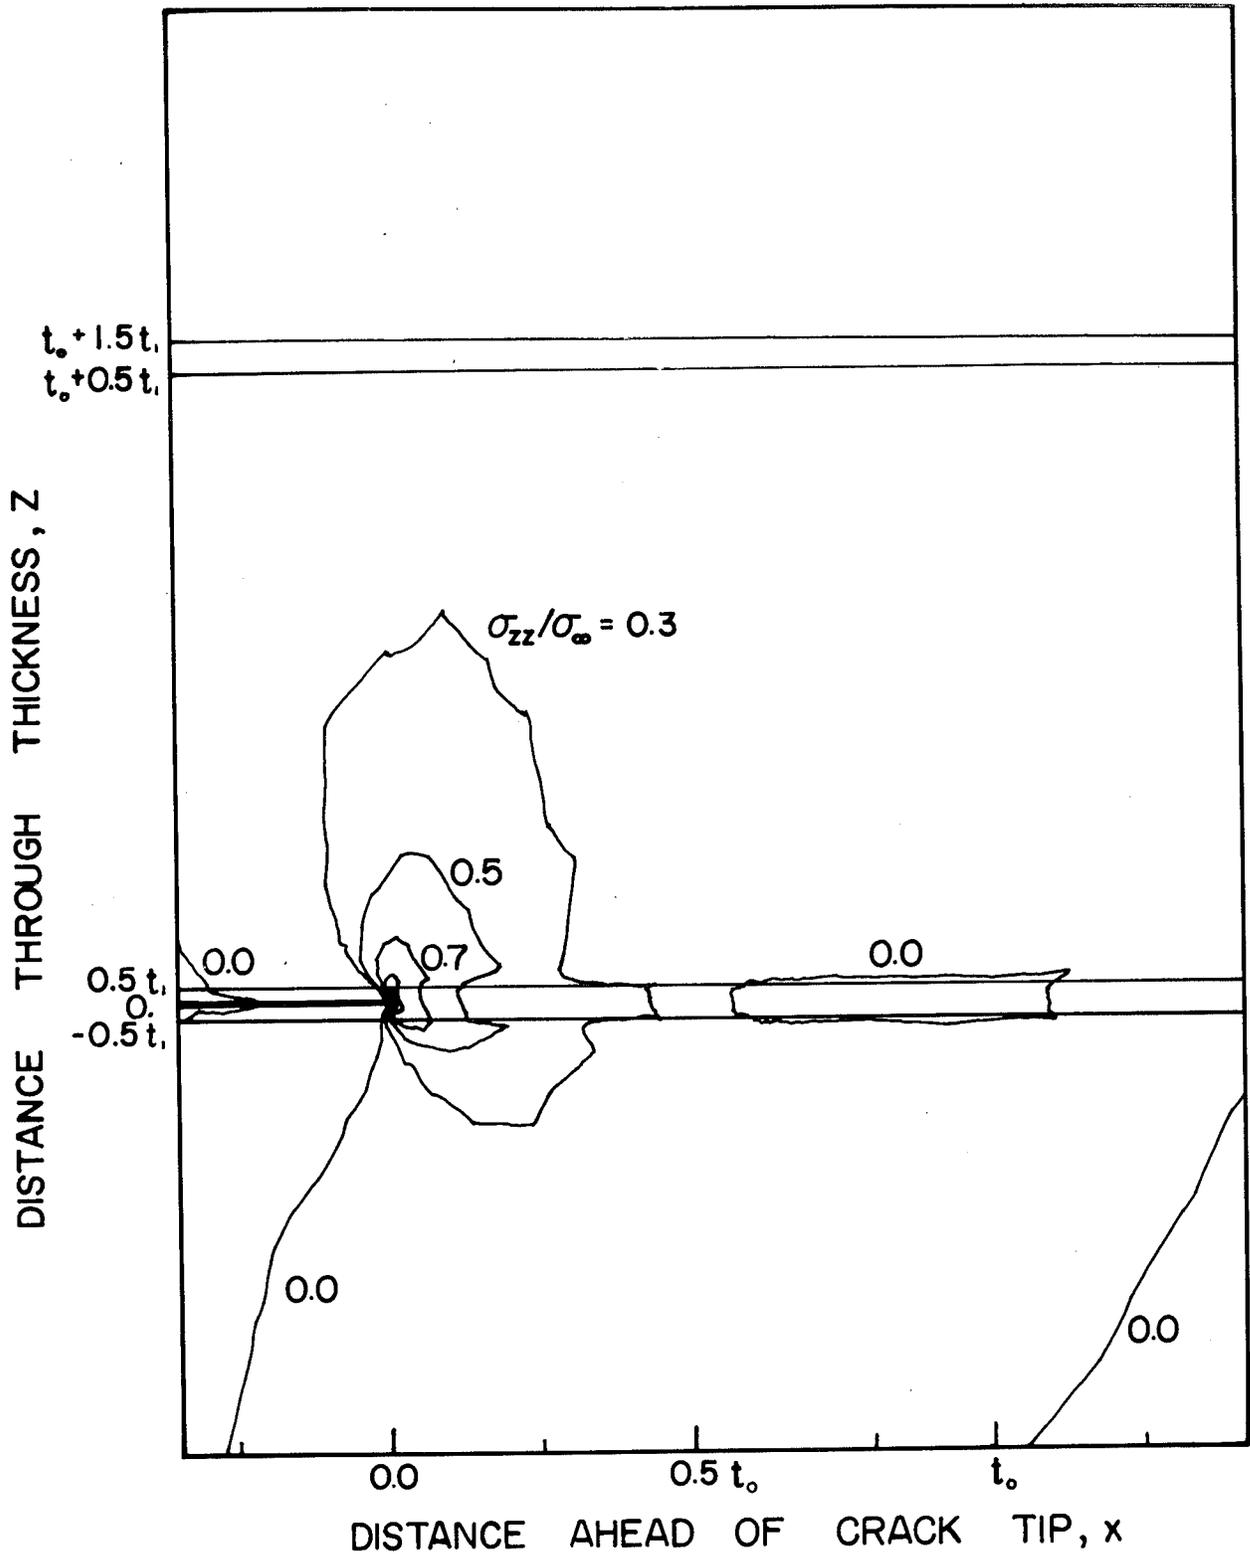


FIG.9 TRANSVERSE NORMAL STRESS CONTOURS  $\sigma_{zz}/\sigma_{\infty}$  NEAR INTERLAMINAR CRACK TIP IN (0°/0°/0°/0°/0°/0°/0°) GLASS/EPOXY

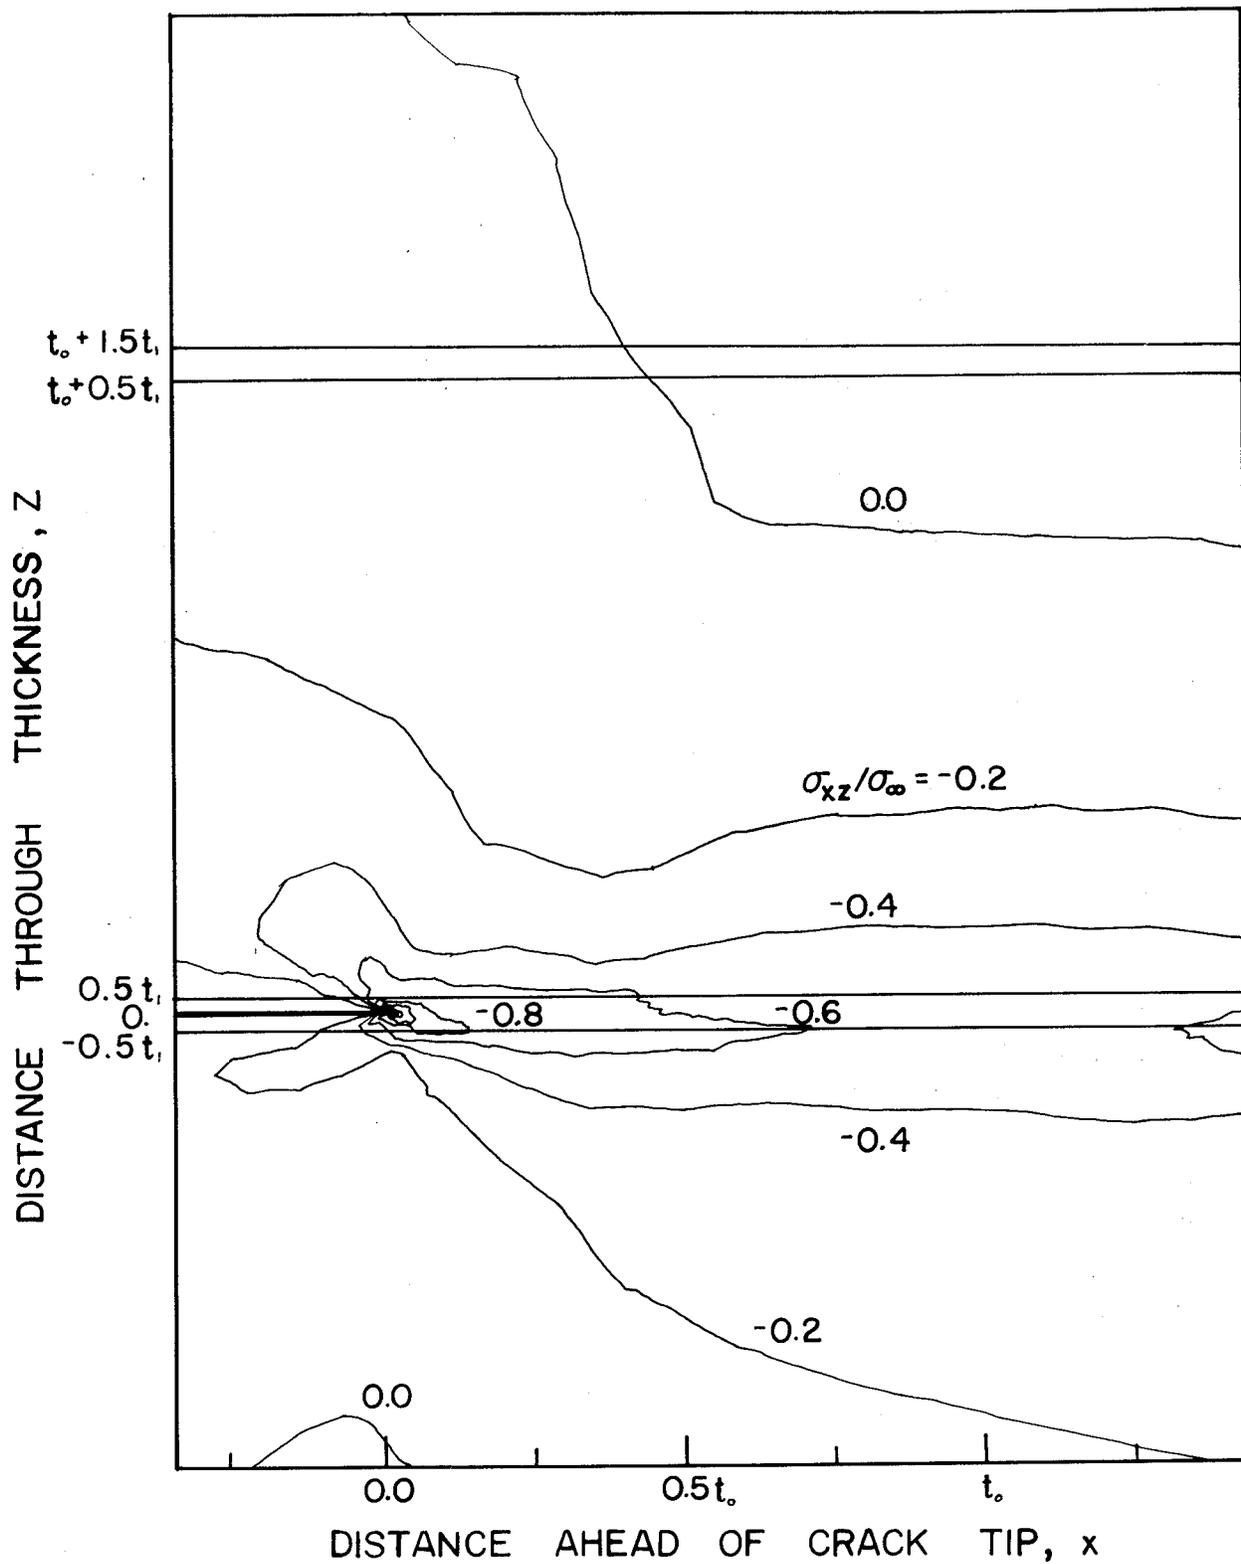


FIG.10 INTERLAMINAR SHEAR STRESS CONTOURS  $\sigma_{xz}/\sigma_{\infty}$  NEAR INTERLAMINAR CRACK TIP IN (0°/0°/0°/0°/0°/0°/0°) GLASS/EPOXY

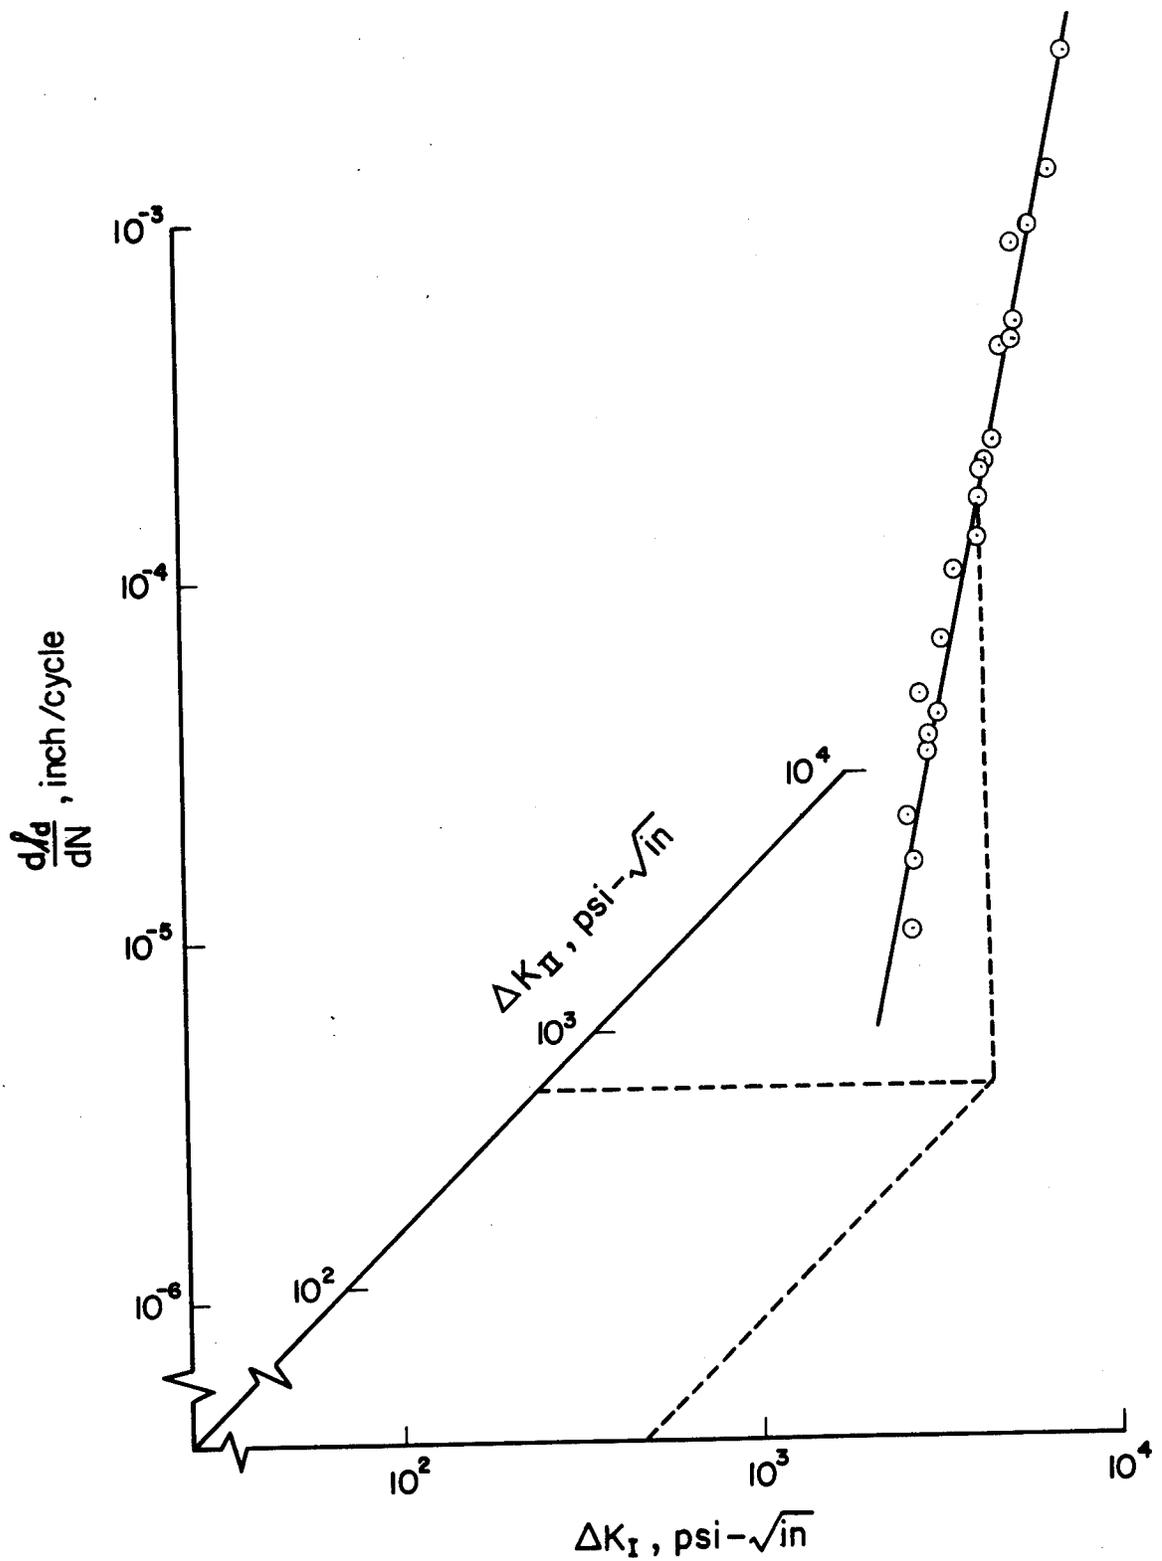


FIG. II INTERLAMINAR CRACK GROWTH RATE  $d/d/dN$  AS A FUNCTION OF MIXED-MODE STRESS FACTOR RANGES  $\Delta K_I$  &  $\Delta K_{II}$  FOR (0°/0°/0°/0°/0°/0°/0°) GLASS/EPOXY

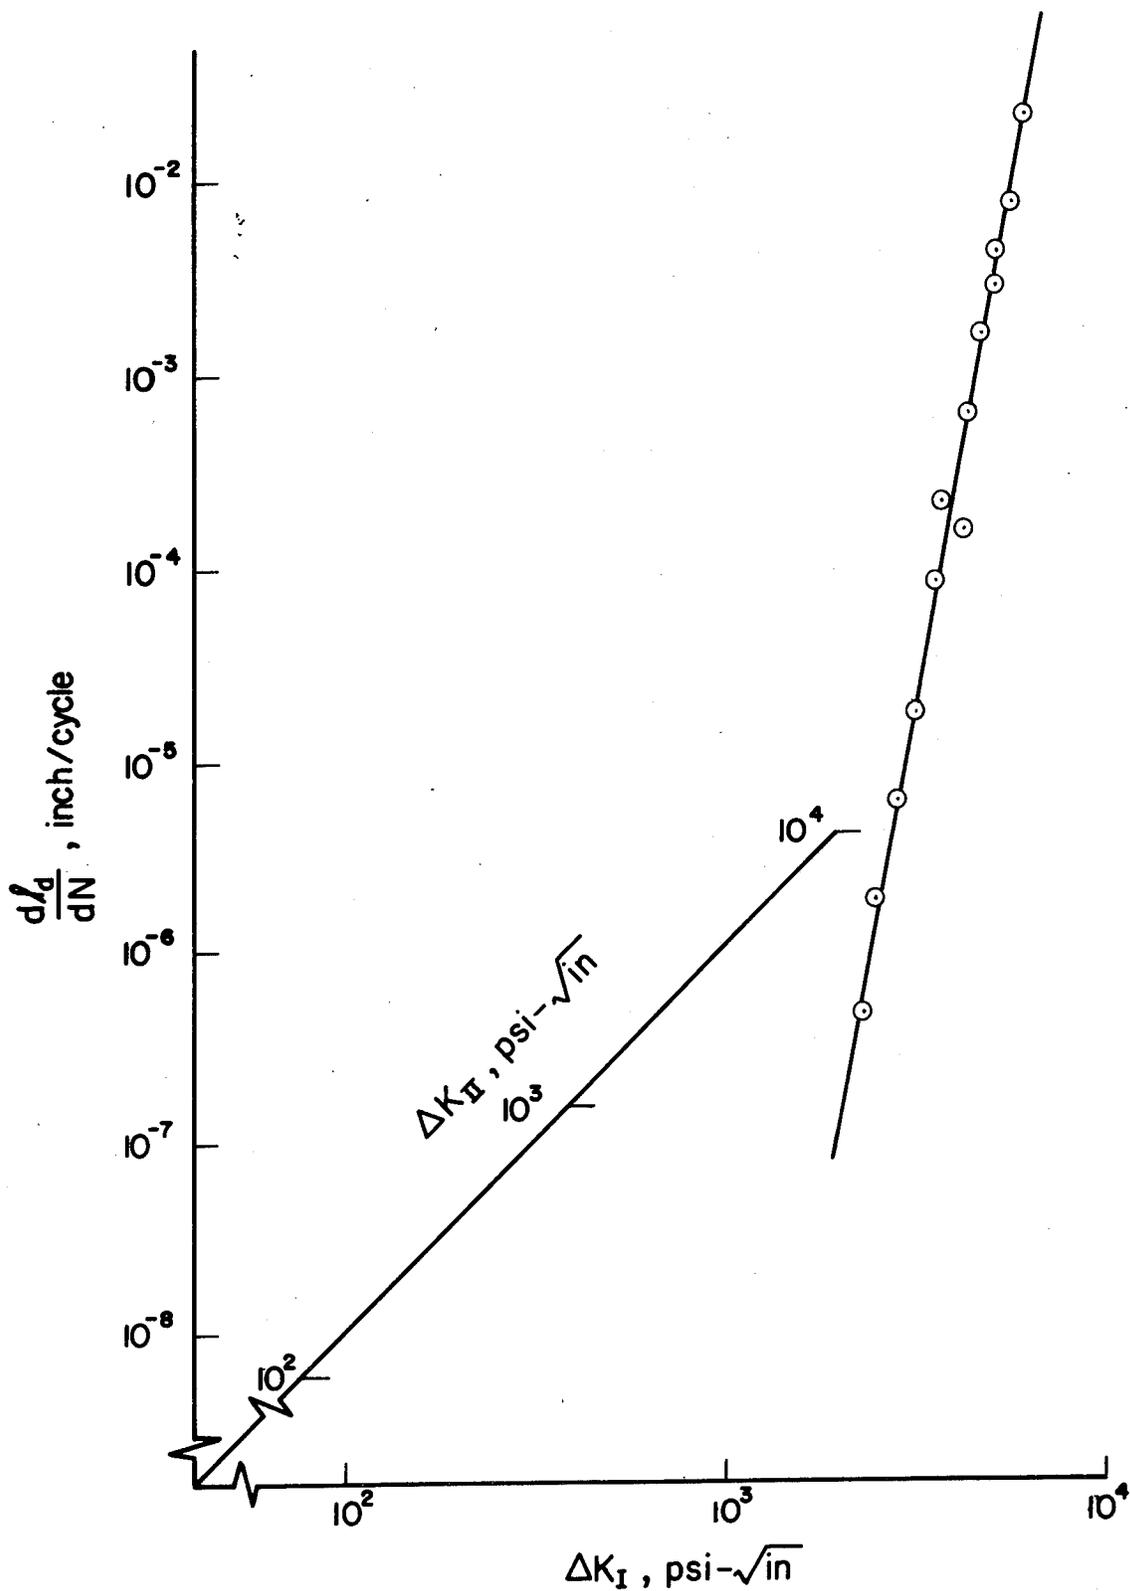


FIG.12 INTERLAMINAR CRACK GROWTH RATE  $d l_d / d N$  AS A FUNCTION OF RANGES OF MIXED-MODE STRESS INTENSITY FACTORS,  $\Delta K_I$  &  $\Delta K_{II}$  FOR (45°-45°//45°-45°-45°/45°-45°/45°) GLASS/EPOXY

FINAL REPORT PART III - DISTRIBUTION LIST

NSG3044

INTERLAMINAR CRACK GROWTH IN  
FIBER REINFORCED COMPOSITES DURING FATIGUE  
NASA CR-165434

Advanced Research Projects Agency  
Washington DC 20525  
Attn: Library

Advanced Technology Center, Inc.  
LTV Aerospace Corporation  
P.O. Box 6144  
Dallas, TX 75222  
Attn: D. H. Petersen  
W. J. Renton

Air Force Flight Dynamics Laboratory  
Wright-Patterson Air Force Base, OH 45433  
Attn: E. E. Baily  
G. P. Sendeckyj (FBC)  
R. S. Sandhu

Air Force Materials Laboratory  
Wright-Patterson Air Force Base, OH 45433  
Attn: H. S. Schwartz (LN)  
T. J. Reinhart (MBC)  
G. P. Peterson (LC)  
E. J. Morrisey (LAE)  
S. W. Tsai (MBM)  
N. J. Pagano  
J. M. Whitney (MBM)

Air Force Office of Scientific Research  
Washington DC 20333  
Attn: J. F. Masi (SREP)

Air Force Office of Scientific Research  
1400 Wilson Blvd.  
Arlington, VA 22209

AFOSR/NA  
Bolling AFB, DC 20332  
Attn: A. K. Amos

Air Force Rocket Propulsion Laboratory  
Edwards, CA 93523  
Attn: Library

Babcock & Wilcox Company  
Advanced Composites Department  
P.O. Box 419  
Alliance, Ohio 44601  
Attn: P. M. Leopold

Bell Helicopter Company  
P.O. Box 482  
Ft. Worth, TX 76101  
Attn: H. Zinberg

The Boeing Company  
P. O. Box 3999  
Seattle, WA 98124  
Attn: J. T. Hoggatt, MS. 88-33  
T. R. Porter

The Boeing Company  
Vertol Division  
Morton, PA 19070  
Attn: E. C. Durchlaub

Battelle Memorial Institute  
Columbus Laboratories  
505 King Avenue  
Columbus, OH 43201  
Attn: L. E. Hulbert

Bendix Advanced Technology Center  
9140 Old Annapolis Rd/Md. 108  
Columbia, MD 21045  
Attn: O. Hayden Griffin

Brunswick Corporation  
Defense Products Division  
P. O. Box 4594  
43000 Industrial Avenue  
Lincoln, NE 68504  
Attn: R. Morse

Celanese Research Company  
86 Morris Ave.  
Summit, NJ 07901  
Attn: H. S. Kliger

Commander  
Natick Laboratories  
U. S. Army  
Natick, MA 01762  
Attn: Library

Commander  
Naval Air Systems Command  
U. S. Navy Department  
Washington DC 20360  
Attn: M. Stander, AIR-43032D

Commander  
Naval Ordnance Systems Command  
U.S. Navy Department  
Washington DC 20360  
Attn: B. Drimmer, ORD-033  
M. Kinna, ORD-033A

Cornell University  
Dept. Theoretical & Applied Mech.  
Thurston Hall  
Ithaca, NY 14853  
Attn: S. L. Phoenix

Defense Metals Information Center  
Battelle Memorial Institute  
Columbus Laboratories  
505 King Avenue  
Columbus, OH 43201

Department of the Army  
U.S. Army Aviation Materials Laboratory  
Ft. Eustis, VA 23604  
Attn: I. E. Figge, Sr.  
Library

Department of the Army  
U.S. Army Aviation Systems Command  
P.O. Box 209  
St. Louis, MO 63166  
Attn: R. Vollmer, AMSAV-A-UE

Department of the Army  
Plastics Technical Evaluation Center  
Picatinny Arsenal  
Dover, NJ 07801  
Attn: H. E. Pebly, Jr.

Department of the Army  
Watervliet Arsenal  
Watervliet, NY 12189  
Attn: G. D'Andrea

Department of the Army  
Watertown Arsenal  
Watertown, MA 02172  
Attn: A. Thomas

Department of the Army  
Redstone Arsenal  
Huntsville, AL 35809  
Attn: R. J. Thompson, AMSMI-RSS

Department of the Navy  
Naval Ordnance Laboratory  
White Oak  
Silver Spring, MD 20910  
Attn: R. Simon

Department of the Navy  
U.S. Naval Ship R&D Laboratory  
Annapolis, MD 21402  
Attn: C. Hersner, Code 2724

Director  
Deep Submergence Systems Project  
6900 Wisconsin Avenue  
Washington DC 20015  
Attn: H. Bernstein, DSSP-221

Director  
Naval Research Laboratory  
Washington DC 20390  
Attn: Code 8430  
I. Wolock, Code 8433

Drexel University  
32nd and Chestnut Streets  
Philadelphia, PA 19104  
Attn: P. C. Chou

E. I. DuPont DeNemours & Co.  
DuPont Experimental Station  
Wilmington, DE 19898  
Attn: D. L. G. Sturgeon

Fiber Science, Inc.  
245 East 157 Street  
Gardena, CA 90248  
Attn: E. Dunahoo

General Dynamics  
P.O. Box 748  
Ft. Worth, TX 76100  
Attn: D. J. Wilkins  
Library

General Dynamics/Convair  
P.O. Box 1128  
San Diego, CA 92112  
Attn: J. L. Christian  
R. Adsit

General Electric Co.  
Evendale, OH 45215  
Attn: C. Stotler  
R. Ravenhall

General Motors Corporation  
Detroit Diesel-Allison Division  
Indianapolis, IN 46244  
Attn: M. Herman

Georgia Institute of Technology  
School of Aerospace Engineering  
Atlanta, GA 30332  
Attn: L. W. Rehfield

Grumman Aerospace Corporation  
Bethpage, Long Island, NY 11714  
Attn: S. Dastin  
J. B. Whiteside

Hamilton Standard Division  
United Aircraft Corporation  
Windsor Locks, CT 06096  
Attn: W. A. Percival

Hercules, Inc.  
Allegheny Ballistics Laboratory  
P. O. Box 210  
Cumberland, MD 21053  
Attn: A. A. Vicario

Hughes Aircraft Company  
Culver City, CA 90230  
Attn: A. Knoell

Illinois Institute of Technology  
10 West 32 Street  
Chicago, IL 60616  
Attn: L. J. Broutman

IIT Research Institute  
10 West 35 Street  
Chicago, IL 60616  
Attn: I. M. Daniel

Jet Propulsion Laboratory  
4800 Oak Grove Drive  
Pasadena, CA 91103  
Attn: Library

Lawrence Livermore Laboratory  
P.O. Box 808, L-421  
Livermore, CA 94550  
Attn: T. T. Chiao  
E. M. Wu

Lehigh University  
Institute of Fracture &  
Solid Mechanics  
Bethlehem, PA 18015  
Attn: G. C. Sih

Lockheed-Georgia Co.  
Advanced Composites Information Center  
Dept. 72-14, Zone 402  
Marietta, GA 30060  
Attn: T. M. Hsu

Lockheed Missiles and Space Co.  
P.O. Box 504  
Sunnyvale, CA 94087  
Attn: R. W. Fenn

Lockheed-California  
Burbank, CA 91503  
Attn: J. T. Ryder  
K. N. Lauraitis  
J. C. Ekvall

McDonnell Douglas Aircraft Corporation  
P.O. Box 516  
Lambert Field, MS 63166  
Attn: J. C. Watson

McDonnell Douglas Aircraft Corporation  
3855 Lakewood Blvd.  
Long Beach, CA 90810  
Attn: L. B. Greszczuk

Material Sciences Corporation  
1777 Walton Road  
Blue Bell, PA 19422  
Attn: B. W. Rosen

Massachusetts Institute of Technology  
Cambridge, MA 02139  
Attn: F. J. McGarry  
J. F. Mandell  
J. W. Mar

NASA-Ames Research Center  
Moffett Field, CA 94035  
Attn: Dr. J. Parker  
Library

NASA-Flight Research Center  
P.O. Box 273  
Edwards, CA 93523  
Attn: Library

NASA-George C. Marshall Space Flight Center  
Huntsville, AL 35812  
Attn: C. E. Cataldo, S&E-ASTN-MX  
Library

NASA-Goddard Space Flight Center  
Greenbelt, MD 20771  
Attn: Library

NASA-Langley Research Center  
Hampton, VA 23365  
Attn: J. H. Starnes

J. G. Davis, Jr.  
M. C. Card  
J. R. Davidson

NASA-Lewis Research Center  
21000 Brookpark Road, Cleveland, OH 44135

Attn: Contracting Officer, MS 501-11  
Tech. Report Control, MS 5-5  
Tech. Utilization, MS 3-16  
AFSC Liaison, MS 501-3  
S&MTD Contract Files, MS 49-6  
L. Berke, MS 49-6  
N. T. Saunders, MS 49-1  
R. F. Lark, MS 49-6  
J. A. Ziemianski, MS 49-6  
R. H. Johns, MS 49-6  
C. C. Chamis, MS 49-6 (8 copies)  
R. L. Thompson, MS 49-6  
T. T. Serafini, MS 49-1  
Library, MS 60-3 (2 copies)

NASA-Lyndon B. Johnson Space Center  
Houston, TX 77001  
Attn: S. Glorioso, SMD-ES52  
Library

NASA Scientific and Tech. Information Facility  
P.O. Box 8757  
Balt/Wash International Airport, MD 21240  
Attn: Acquisitions Branch (15 copies)

National Aeronautics & Space Administration  
Office of Advanced Research & Technology  
Washington DC 20546

Attn: L. Harris, Code RTM-6  
M. Greenfield, Code RTM-6  
D. J. Weidman, Code RTM-6

National Aeronautics & Space Administration  
Office of Technology Utilization  
Washington DC 20546

National Bureau of Standards  
Eng. Mech. Section  
Washington DC 20234  
Attn: R. Mitchell

National Science Foundation  
Engineering Division  
1800 G. Street, NW  
Washington DC 20540  
Attn: Library

Northrop Corporation Aircraft Group  
3901 West Broadway  
Hawthorne, CA 90250  
Attn: R. M. Verette  
G. C. Grimes

Pratt & Whitney Aircraft  
East Hartford, CT 06108  
Attn: J. M. Woodward

Raytheon Co., Missile System Division  
Mechanical Systems Laboratory  
Bedford, MA  
Attn: P. R. Digiovanni

Rensselaer Polytechnic Institute  
Troy, NY 12181  
Attn: R. Loewy

Rockwell International  
Los Angeles Division  
International Airport  
Los Angeles, CA 90009  
Attn: L. M. Lackman  
D. Y. Konishi

Sikorsky Aircraft Division  
United Aircraft Corporation  
Stratford, CT 06602  
Attn: Library

Southern Methodist University  
Dallas, TX 75275  
Attn: R. M. Jones

Space & Missile Systems Organization  
Air Force Unit Post Office  
Los Angeles, CA 90045  
Attn: Technical Data Center

Structural Composites Industries, Inc.  
6344 N. Irwindale Avenue  
Azusa, CA 91702  
Attn: R. Gordon

Texas A&M  
Mechanics & Materials Research Center  
College Station, TX 77843  
Attn: R. A. Schapery  
Y. Weitsman  
TRW, Inc.

23555 Euclid Avenue  
Cleveland, OH 44117  
Attn: I. J. Toth

Union Carbide Corporation  
P. O. Box 6116  
Cleveland, OH 44101  
Attn: J. C. Bowman

United Technologies Research Center  
East Hartford, CT 06108  
Attn: R. C. Novak  
Dr. A. Dennis

University of Dayton Research Institute  
Dayton, OH 45409  
Attn: R. W. Kim

University of Delaware  
Mechanical & Aerospace Engineering  
Newark, DE 19711  
Attn: B. R. Pipes

University of Illinois  
Department of Theoretical & Applied Mechanics  
Urbana, IL 61801  
Attn: S. S. Wang

University of Oklahoma  
School of Aerospace Mechanical & Nuclear Engineering  
Norman, OK 73069  
Attn: C. W. Bert

University of Wyoming  
College of Engineering  
University Station Box 3295  
Laramie, WY 82071  
Attn: D. F. Adams

U. S. Army Materials & Mechanics Research Center  
Watertown Arsenal  
Watertown, MA 02172  
Attn: E. M. Leno  
D. W. Oplinger

V.P. I. and S. U.  
Dept. of Eng. Mech.  
Blacksburg, VA 24061

Attn: R. H. Heller  
H. J. Brinson  
C. T. Herakovich  
K. L. Reifsnider